

Electrocatalytic Production of a Liquid Organic Hydrogen Carrier with Anodic Valorization of the Process

Review and Outlook

Wang, Jiaqi; Li, Yongdan; Hummel, Christin; Huang, Guo; Ji, Xiaoyan; Demiröz, Ezgi; Urakawa, Atsushi; Huang, Siyuan; Zhao, Ruixue; Lercher, Johannes

DOI

[10.1021/acs.energyfuels.4c04644](https://doi.org/10.1021/acs.energyfuels.4c04644)

Publication date

2025

Document Version

Final published version

Published in

Energy and Fuels

Citation (APA)

Wang, J., Li, Y., Hummel, C., Huang, G., Ji, X., Demiröz, E., Urakawa, A., Huang, S., Zhao, R., Lercher, J., Lanzafame, P., Papanikolaou, G., & Centi, G. (2025). Electrocatalytic Production of a Liquid Organic Hydrogen Carrier with Anodic Valorization of the Process: Review and Outlook. *Energy and Fuels*, 39(1), 132-165. <https://doi.org/10.1021/acs.energyfuels.4c04644>

Important note

To cite this publication, please use the final published version (if applicable). Please check the document version above.

Copyright

Other than for strictly personal use, it is not permitted to download, forward or distribute the text or part of it, without the consent of the author(s) and/or copyright holder(s), unless the work is under an open content license such as Creative Commons.

Takedown policy

Please contact us and provide details if you believe this document breaches copyrights. We will remove access to the work immediately and investigate your claim.

Electrocatalytic Production of a Liquid Organic Hydrogen Carrier with Anodic Valorization of the Process: Review and Outlook

Published as part of *Energy & Fuels special issue* “Novel Routes to Green Hydrogen Production in Europe”.

Jiaqi Wang, Yongdan Li, Christin Hummel, Guo Huang, Xiaoyan Ji,* Ezgi Demiröz, Atsushi Urakawa, Siyuan Huang, Ruixue Zhao, Johannes Lercher, Paola Lanzafame, Georgia Papanikolaou, and Gabriele Centi*



Cite This: *Energy Fuels* 2025, 39, 132–165




Read Online

ACCESS |

 Metrics & More

 Article Recommendations

ABSTRACT: Green hydrogen plays a crucial role in decarbonization and the future of low-carbon society. Still, its transport/distribution and cost of production, mainly realized by electrolysis, are major hurdles. Liquid H₂ carriers reduce transport/distribution costs but add further expenses for their production. To address this challenge, we proposed a novel strategy for electrocatalytic production of a liquid organic hydrogen carrier with anodic valorization of the process. This review summarizes the state of the art and outlooks in this new concept. The electrocatalytic process is briefly introduced, and the main components are discussed. Subsequently, the electrocatalytic production of liquid organic hydrogen carriers and anodic oxidation from components to processes, together with the paired processes and reactors, are analyzed, highlighting challenges and prospects.

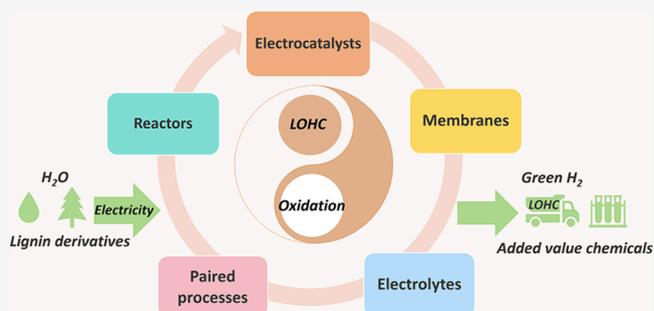

1. INTRODUCTION

Hydrogen (H₂) is a key component in the global strategy for decarbonization,¹ especially in the energy sector, where it serves as an energy carrier to facilitate the penetration of a higher share of intermittent renewable energy and the decarbonization of hard-to-abate industrial sectors. Meanwhile, H₂ is an important feedstock with already a worldwide production of nearly 100 Mtons, although made from fossil fuels (so-called gray H₂).^{2,3} Green H₂, produced mainly by electrolysis, covers only about 1% of the world's production, even with increasing interest.

Being important in cross-sectorial coupling, linking power, gas, and other energy vectors or energy-intensive commodities and replacing them in their respective usages,⁴ substituting gray with green H₂ and expanding the use of H₂ are current major worldwide objectives. However, the substitution is contrasted by two key issues: (i) the very intensive electrical energy demand (>50 kWh/kg of H₂) to produce green H₂⁵ and (ii) the cost/energy for transporting/distributing as well as storing gaseous H₂.^{6–8} Liquid H₂ carriers can greatly improve the latter aspects, with an impact also on the former, because these H₂ carriers allow the production of H₂ in remote areas where renewable electrical energy is available at low costs. Liquid organic hydrogen carriers (LOHCs)^{9–11} are among the most intensively developed H₂ carriers. The hydrogenation-

dehydrogenation of LOHC, typically organics containing multiple aromatic groups, is commonly realized by heterogeneous catalysis, with H₂ produced by electrolysis using renewable electrical energy. There is a rising interest in electrocatalytic processes to produce LOHC¹² to further decrease the carbon footprint. However, the typical anodic reaction is the oxygen evolution reaction (OER), which has main drawbacks: (i) a sluggish kinetic requiring high overpotentials and thus decreasing energy efficiency and increasing costs and (ii) the production of O₂, which in most of the applications does not find onsite utilization.

Substituting OER with a reaction of oxidation leading to added-value chemicals could improve energy efficiency⁴ and rate while at the same time lowering costs by selling the product.¹³ In other words, realizing the electrocatalytic regeneration of LOHC in a device with the coupled valorization of the anodic reaction can (i) intensify the process and energy efficiency and (ii) reduce the costs, making the use

Received: September 23, 2024

Revised: December 11, 2024

Accepted: December 11, 2024

Published: December 25, 2024



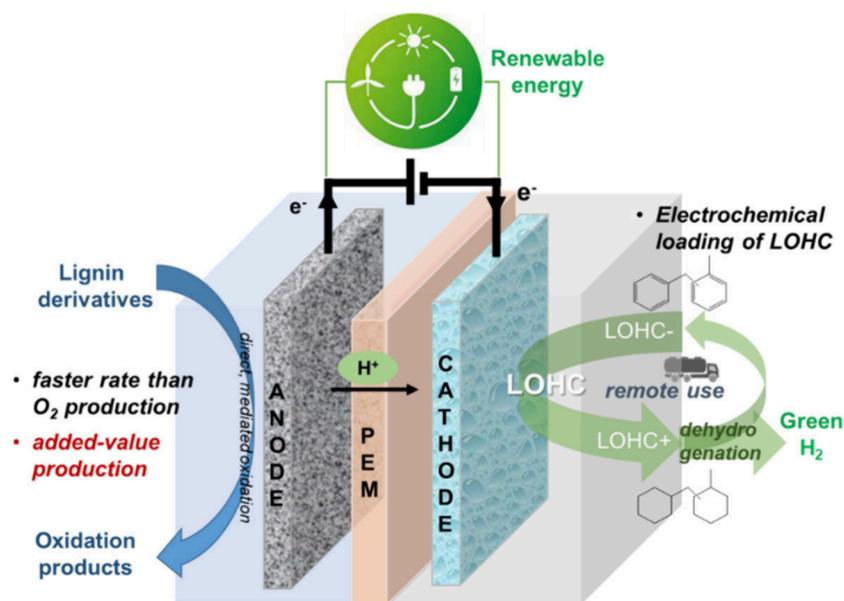


Figure 1. Framework on the electrocatalytic production of LOHC with anodic valorization.

of LOHC more competitive. In addition, it offers benefits of linking sections, such as biorefinery and H₂ economy, that lead to further synergies and potential benefits. The ongoing EU project EPOCH (grant 101070976) is exploring these aspects. The schematic illustration of the electrocatalytic device at the core of this project is presented in Figure 1.¹⁴

Figure 1 shows that the objectives of this project are to (i) integrate the step of electrocatalytic production of H₂ at the cathode side with the regeneration by hydrogenation of the LOHC carrier and (ii) valorize the anodic reaction by producing added-value chemicals. The benefits are the reduction in the cost and energy needs (by process intensification and reducing losses associated with OER), creating a value link between biorefineries and the green H₂ world that offers further potential synergies.

The performance of the proposed concept depends greatly upon the catalysts, membranes, and electrolytes. Even though the concept was newly proposed, its core of electrocatalytic conversion, together with the related components (catalysts, membranes, and electrolytes), has been widely studied.^{15–17} Meanwhile, the proposed concept shows similarities with other processes, including electrocatalytic production of LOHC, anodic oxidation, and the combined processes (H₂ production with anodic valorization and anodic oxidation with H₂ co-production). Therefore, analyzing these aspects and providing insight into the similarities and differences as well as information for further performance comparison are essential. A brief introduction to state of the art based on the previously published reviews, listed in Table 1, is described below.

In summary, briefly, (a) LOHC is an active topic of discussion. Since 2020, 6 reviews have been published from the aspects of innovative LOHCs,¹⁸ mechanism,¹⁹ research progress,²⁰ and scientific limits and challenges.²¹ To the best of our knowledge, only one review summarized the research on the electrocatalytic conversion of aromatic-based LOHCs.¹² (b) Electrocatalysis is a topic of large interest as a key technology toward low-carbon production,^{24–26} while fewer studies deal with aspects more closely related to those presented in the scheme reported in Figure 1, such as advanced catalysts,¹⁶ alloy-derived electrocatalysts,²⁷ earth-

abundant amorphous-metal-based catalysts,²⁸ those based transition metal nitrides,²⁹ iron oxyhydroxide,³⁰ graphdiyne³¹ as well as catalysts specifically for LOHCs.^{22,23} In contrast, no specific reviews on electrocatalysts have been published that are linked directly to the process presented in Figure 1. (c) Membranes and electrolytes, in addition to electrocatalysts/electrode and device aspects mentioned above, are also important elements of electrocatalytic devices. For the membranes, the research work has been reviewed for proton-exchange membranes in electrolysis technology¹⁷ and water electrolysis.³² In contrast, the membrane research aspects directly related to coupling electrocatalytic regeneration of LOHC with anode valorization are not present in the literature, and, to the best of our knowledge, only one review is available, focusing specifically on electrolytes but in relation to aluminum electrolysis.¹⁵ (d) In terms of the general concept associated with Figure 1, four reviews analyze (i) the combining of H₂ production and organic oxidation,³⁶ (ii) the coupling between the production of valuable chemicals at both anode and cathode,³³ (iii) paired electrolysis of biomass-derived compounds toward co-generation of value-added chemicals and fuels,³⁴ and (iv) the coupling of value-added anodic reactions with electrocatalytic CO₂ reduction.³⁵ In summary, very limited reviews are available to discuss the coupling process and related technology aspects of the process outlined in Figure 1.

Thus, the state-of-the-art field in terms of reviews is not exhaustive, and the brief analysis above remarks the need to review the research progress related to the electrocatalytic production of liquid organic hydrogen carriers with anodic valorization of the process, especially considering the importance of green hydrogen production and the novelty of the proposed concept and strategy. To discuss this field, we first briefly introduce the technology and the main components. Then, the electrocatalytic production of LOHC and the anodic oxidation are discussed, along with the paired processes and reactor type. The challenges and prospects in the various sections are discussed.

Table 1. Related Reviews in Recent Years

article	topic	year
D'Ambra et al. ¹⁸	reviewed LOHC and discussed the potential reactivities to design innovative LOHCs	2023
Valentini et al. ¹⁹	summarized the mechanism of the hydrogen-transfer process of different LOHCs	2022
Rao et al. ²⁰	discussed the ideal LOHCs and reviewed the progress in developing LOHCs together with the catalytic approach	2020
Clematis et al. ²¹	provided scientific limits and challenges from a system-level perspective for LOHC	2023
Katarina et al. ²²	summarized the novel catalysts for dibenzyltoluene as a potential LOHC	2021
Yang et al. ²³	summarized N-heterocycles as LOHC and their hydrogenation/dehydrogenation catalysts	2024
Gabriele et al. ²⁴	summarized the catalysis for an electrified chemical production	2023
Georgia et al. ²⁵	discussed the catalysis for e-chemistry: need and gaps for a future defossilized chemical production	2022
Siglinda et al. ²⁶	discussed the role of electrocatalysis in solar-driven chemistry	2019
Lebedeva et al. ¹²	summarized the research on the electrocatalytic conversion of aromatic-based LOHCs	2023
Zeng et al. ¹⁶	summarized the advanced catalysts for electrocatalytic hydrogenation of organics in aqueous conditions	2023
Guo et al. ²⁷	reviewed alloy-derived electrocatalysts for 5-hydroxymethylfurfural toward 2,5-furandicarboxylic acid	2022
Chen et al. ²⁸	summarized the earth-abundant amorphous metal-based catalysts for the electrooxidation of small molecules	2023
Meng et al. ²⁹	reviewed the electrocatalytic applications of electrocatalysts based on transition metal nitrides	2022
Guo et al. ³⁰	reviewed the electrocatalytic applications of electrocatalysts based on iron oxyhydroxide	2023
Cui et al. ³¹	reviewed the electrocatalytic applications of electrocatalysts based on graphdiyne	2020
Ayers et al. ¹⁷	reviewed the proton-exchange membranes in electrolysis technology	2019
Feng et al. ³²	reviewed the proton-exchange membranes in water electrolysis	2017
Li et al. ³³	analyzed the coupling between the production of valuable chemicals at both anode and cathode	2021
Liu et al. ³⁴	reviewed the paired electrolysis of biomass-derived compounds toward co-generation of value-added chemicals and fuels	2021
Xu et al. ³⁵	reviewed the coupling value-added anodic reactions with electrocatalytic CO ₂ reduction	2023
Chen et al. ³⁶	review of coupled electrochemical hydrogen production and organic oxidation for low energy consumption	2023

2. CONCISE INTRODUCTION TO THE ELECTROCATALYTIC TECHNOLOGY

Electrocatalytic processes represent complex multiphase chemical reactions that involve electron transfer steps at the electrode–solution interface. These reactions are influenced by a wide range of factors, including the temperature, pressure, solution medium, condition of the solid surface, and mass transfer conditions. Additionally, the influence of the double-layer structure at the electrode–solution interface, which affects the distribution of ions and potential near the electrodes, is a crucial factor in electrocatalytic processes. A defining characteristic of electrocatalysis is its involvement of multiple consecutive steps that produce chemically adsorbed intermediates on the electrode surface. These steps are essential for a variety of important electrode reactions, which include both the generation and degradation of molecules.

Electrocatalysis can be broadly categorized into two main functional areas: (i) formation of chemically adsorbed intermediates and (ii) chemical adsorption and transformation. In the formation of chemically adsorbed intermediates, ions or

molecules engage in electron transfer steps on the electrode surface to form chemically adsorbed intermediates. These intermediates then convert into stable molecules through heterogeneous chemical reactions or chemical desorption processes, exemplified by the hydrogen evolution reaction (HER) and OER. For the chemical adsorption and transformation, reactants initially undergo chemical adsorption on the electrode surface via either dissociative or associative pathways. These adsorbed reactants then participate in subsequent electron transfers or engage in surface chemical reactions, such as formate electrooxidation.³⁷

The main advantage of electrocatalysis is the ability to effectively modify the energy dynamics of the reaction system by adjusting the electronic field that forms between the electrode surface and the electrolyte solution at the interface. By controlling this field, electrocatalysts can lower activation energy barriers, stabilize reaction intermediates, and direct reaction pathways, thereby enhancing the efficiency and selectivity of electrochemical reactions. This modification is crucial for controlling the direction and rate of chemical reactions under the ambient conditions of temperature and pressure. Moreover, electrocatalysis can alter reaction pathways through interactions between the reactants and electrocatalysts, with changes in activation energy playing a key role in either accelerating or decelerating the reaction rates.³⁷

As shown in Figure 1, the process of interest involves the electrocatalytic treatments of organic molecules, i.e., those for the electrocatalytic hydrogenation of LOHCs and the electrochemical oxidation of organics. The electrocatalytic developments in these reactions are briefly introduced below, together with the main components needed in the processes.

2.1. Reactions. **2.1.1. Electrocatalytic Hydrogenation (ECH).** Electrochemical hydrogenation is carried out using two distinct mechanisms, each defined by specific pathways for electron and proton transfer.³⁸ The initial pathway involves direct electro-reduction (DER), where electrons are first transferred from the organic substrate to the working electrode surface, succeeded by a protonation phase in an aqueous solution, with water serving as the source of protons.³⁹ Another method is ECH, where protons are first adsorbed on the surface of the working electrode, followed by the adsorption of the organic material, and accompanied by electron transformation through the Volmer reaction process.⁴⁰ For the hydrogenation electrolysis in aqueous solutions, DER, HER, and ECH compete with each other, affecting the overall faradaic efficiency. Therefore, precise control of the reaction process is crucial to maximize the target reactions and enhance the efficiency and effectiveness of the electrolysis process.⁴⁰

2.1.2. Electrocatalytic Oxidation. In the electrochemical oxidation processes, there are two main types: direct and indirect oxidations.⁴¹ During direct anodic oxidation, the process primarily involves electron transfer, with molecules being directly oxidized by electrons after their adsorption onto the anode surface. Therefore, this process is largely governed by the transport of molecules and the electron transfer rate at the electrode/solution interface. Generally, the oxidation of molecules is theoretically possible at a potential that is less positive than that required for OER. However, this process frequently leads to electrode fouling due to the formation of polymer layers on the electrode surface, resulting in poor chemical decontamination efficiency and reducing the service life of the anode materials.⁴² Indirect electrochemical oxidation

occurs with the additional generation of intermediate oxidizing species during the reaction, known as physisorbed “active oxygen” (adsorbed hydroxyl radicals) or chemisorbed “active oxygen” (oxygen within the lattice of metal oxide anodes). These oxidizing species exhibit very high oxidative activity, which is particularly effective against organic compounds.⁴³ In fact, both direct and indirect oxidations typically coexist in practical electrochemical oxidation systems, and consequently, optimizing and controlling these two processes is especially crucial for effective utilization.

2.2. Main Device Components. To accomplish the electrocatalytic hydrogenation and oxidation reactions, electrodes/catalysts (anodes and cathodes), membranes, and electrolyte solutions are needed as the main components (Figure 1). They are briefly introduced below. Currently, the understanding of both electrochemical hydrogenation and oxidation processes is still unsatisfactory. The reaction kinetics for these types of reactions are still very slow. In the future, gaining a deeper understanding of these reactions, increasing the reaction rate, the efficiency of electrolytic cells, and the activity of catalysts, together with electrolytes and membranes, will be crucial.

2.2.1. Electrocatalysts for Cathode. Electrochemical catalysts play a critical role in determining the effectiveness of ECH.^{16,44–46} The catalysts can generally be categorized into noble and non-noble metal types.^{47,48} Noble metal catalysts, such as platinum,^{49,50} palladium,^{51,52} rhodium, and ruthenium,^{53,54} are recognized for their remarkable catalytic properties and stability under various reaction conditions. Conversely, non-noble metal catalysts like nickel,^{52,55} copper,^{56,57} cobalt,⁵⁸ and iron⁵⁹ present a viable alternative due to their abundance, lower cost, and satisfactory catalytic performance. However, their amount is typically up to 2 orders of magnitude higher in weight compared to noble-metal-based catalysts to have comparable performances.

Nickel- and copper-based catalysts have remarkable hydrogenation activity,^{60,61} especially when enhanced through alloy formation or nanostructuring, leading to improved performance in electrocatalytic applications. Cobalt catalysts are also promising,⁶² particularly when used in alloyed forms, to enhance stability and activity. Iron-based catalysts,⁶³ noted for their environmentally favorable characteristics, contribute to the growing interest in sustainable catalytic systems. In addition to metal catalysts, metal oxides and hydroxides have gained increasing attention for their unique electronic and structural properties that facilitate efficient electrochemical reactions. These materials often demonstrate excellent catalytic activity and can be tailored through doping or composting with other materials to improve their performance in the ECH processes.

Carbon-based materials, such as graphene, carbon nanotubes (CNTs), and doped carbon, have shown promise as metal-free catalysts^{64,65} in ECH due to their excellent conductivity, abundant active sites, and cost-effectiveness. Doping graphene with nitrogen or phosphorus enhances its hydrogen adsorption capacity and catalytic activity. CNTs, known for their mechanical strength, can be optimized by controlling their physical properties and combining them with functional materials. Additionally, emerging metal-free catalysts like boron–nitrogen co-doped carbon (BCN)⁶⁶ and phosphides⁶⁷ exhibit unique electronic structures that enhance their efficiency in hydrogenation reactions, making them viable for industrial applications.

2.2.2. Electrocatalysts for Anode. The development and design of electrocatalysts for the electrocatalytic oxidation of lignin-derived molecules primarily focus on the complete oxidation of these compounds, especially in wastewater treatment applications. Extensive research has explored various transition metals (such as platinum, nickel, and cobalt) as well as commonly used electrodes like PbO₂,^{68,69} demonstrating significant advancements in this field. However, for the catalysts such as RuO₂–IrO₂⁷⁰ and SnO₂⁷¹ showing excellent performance in electrooxidation, issues like catalyst deactivation and the formation of complex product mixtures that are difficult to separate are still prevalent. Moreover, there is a notable lack of systematic studies and established design criteria for tailoring catalysts to specific target molecules. In addition, a general concern is their cost of manufacture.

To develop new anode catalysts for effective electrochemical activity while achieving selective catalysis, thereby enhancing the efficiency of organic oxidation processes with cost-effective solutions, hydroxide-related catalysts, particularly layered double hydroxides (LDHs),⁷² have demonstrated considerable potential in improving reaction selectivity, yield, and stability. To realize efficient electrooxidation catalysts, various optimization strategies targeting active sites have been investigated,^{28,73} such as enhancing the electronic structure of active sites through heterojunction construction, vacancy engineering, and defect engineering. On the other hand, TiO₂^{74,75} and boron-doped diamond (BDD)^{76,77} have also exhibited good activity in phenol electrooxidation, with various modified materials continually emerging, including studies on the support materials used for TiO₂.

2.2.3. Membranes. In an electrolysis process, the role of the membrane is to isolate the anode and cathode as well as enable ions to travel through it. Because of the second function, they are named polymer electrolyte membranes.⁷⁸ They typically consist of hydrophobic long-chain backbone and hydrophilic ion exchange groups on the main or side chains. Cation-exchange membranes contain negatively charged species such as sulfonic acid groups (–SO₃[–]), whereas anion-exchange membranes have positively charged species like ammonium (–NH₃⁺) groups to enable selective transportation of the charged species.⁷⁹ Bipolar membranes, on the other hand, are made of cation and anion exchange layers that enable the electro-dissociation of water into protons (H⁺) and hydroxide ions (OH[–]) at the interface.⁸⁰ These relatively new membranes create an acidic and alkaline environment on the cathode and anode sides of the electrolyzer.⁸¹

2.2.4. Electrolyte Solutions. In the process of electrocatalytic production of LOHC and anodic oxidation valorization, the electrolyte plays a promoting role in effective ion transport and reactant solubilization. Therefore, selecting an appropriate electrolyte is crucial for enhancing the reaction efficiency, product selectivity, and yield.⁸² First, the electrolyte needs to have a high solubility for the organic substrate to encounter the electrolyte and then undergo electrocatalytic conversion. An ideal electrolyte should also have high electrical conductivity to effectively shuttle charges between the electrodes, thereby facilitating the electrocatalytic reactions. In addition, the electrolyte needs to remain stable during the electrocatalytic process and not react with the reactants or products. It is also necessary to consider environmental friendliness and the recyclable use of electrolytes, as well as avoid the use of toxic substances.⁸³ In general, the electrolytes can be classified as inorganic electrolytes (such as H₂SO₄, HCl,

Table 2. Comparison of LOHC Compounds, Including Toluene/Methylcyclohexane, Benzyltoluene (H0-BT/H12-BT), and Dibenzyltoluene (H0-DBT/H18-DBT)^a

	MCH/TOL		H12-BT/H0-BT		H18-DBT/H0-DBT	
molecular formula	C ₇ H ₁₄	C ₇ H ₈	C ₁₄ H ₂₆	C ₁₄ H ₁₄	C ₂₁ H ₃₈	C ₂₁ H ₂₀
H ₂ storage density at 20 °C (kg of H ₂ m ⁻³)	47.4	0	54.5	0	57.2	0
molecular weight (g mol ⁻¹)	98.189	92.141	194.357	182.261	290.54	272.384
isomeric peaks in GC	1	1	6	3	>20	>12
GHS labels	2, 7, 8, and 9	2, 7, and 8	7 and 8	7, 8, and 9	na	8 and 9
maximum diameter of the molecules (nm)	0.60	<0.60	1.15	<1.15	1.5	<1.5
phase at 290 °C and 3 bar _{abs}	vapor	vapor	liquid	liquid	liquid	liquid
dynamic viscosity at 20 °C (mPa s)	0.5	0.6	7	4	49	424
melting point at atm (°C)	-126	-95	from -80 to 70	-30	< -50	-34
boiling point at atm (°C)	101	111	264–272	277–290	≈371	≈392
density at 20 °C (kg m ⁻³)	770	870	876	996	913	1044
Δ _r H ⁰ at 25 °C per mole of H ₂ (kJ mol ⁻¹)	+68.3	-68.3	+63.5	-63.5	+65.4	-65.4

^aThis table was reproduced with permission from ref 88. Copyright 2022 Royal Society of Chemistry.

NaOH, and KOH), organic electrolytes (acetonitrile and dimethylformamide), and novel electrolytes, including ionic liquids.⁸³

3. ELECTROCATALYTIC REGENERATION OF LOHC BY HYDROGENATION

3.1. LOHC. Hydrogen is considered a green energy and fuel carrier, while in general, it is challenging to store and transport hydrogen itself. The LOHC concept ensures safe transport and long-term storage of these secondary energy sources. LOHC, mostly hydrocarbons, chemically stores hydrogen to be transported and stored safely at room temperature. It is mostly fuel-like and can be integrated into the existing fuel infrastructure with slight modifications without building a completely new one. In addition, LOHC does not pose a higher risk potential than known fuels.¹¹ Compared to other storage media, such as *n*-ethyl-carbazole, toluene, dibenzyltoluene, ammonia, and methanol, LOHCs can be used multiple times like aromatics (closed systems), instead of only once (MeOH, NH₃, etc.).⁸⁴

In the past, aromatic systems had proven to be particularly promising, with the simplest representative being benzene/cyclohexane, followed by toluene/methylcyclohexane, benzyltoluene/perhydro-benzyltoluene and dibenzyltoluene/perhydro-dibenzyltoluene. Other multi-ring systems include decalin/naphthalene, biphenyl/bicyclohexyl, etc. A detailed overview of all possible LOHCs can be found in the review by Gébel et al.⁸⁴ The aromatic toluene, benzyltoluene, and dibenzyltoluene are the most studied, and their properties are listed in Table 2. In general, the hydrogen storage capacities of these LOHCs are 6–8 wt %, and the storage can be achieved at ambient temperature and pressure in highly stable forms. These LOHCs also possess high volumetric hydrogen storage density (>50 g_{H₂}/L) compared to the compressed hydrogen gas (20–30 g_{H₂}/L).^{85,86}

For a desirable LOHC that can be used in a hydrogen circular economy, besides the high storage density, there are other important requirements, which are summarized below:⁸⁷

- High volumetric storage density and excellent reversibility.
- High productivity (H₂ release capacity or H₂ storage capacity) with high selectivity in the hydrogenation and/or dehydrogenation of LOHC under technically reasonable conditions.

- High thermal and chemical stability as well as low loss during storage and transport.
- Good handling in LOHC logistics (a wide liquid range) and low viscosity of the hydrogen-rich and -poor LOHC forms (even at winter temperatures in the global north).
- High safety of LOHC logistics (low or non-flammability) and low to moderate toxicity.
- Commercial availability on a large scale and at low costs.
- Low effort for integrating the LOHC into the existing infrastructure.

The first three criteria mentioned above are often considered for the suitability of hydrocarbon-containing substances as LOHCs. In contrast, good manageability in logistics and commercial availability can be crucial for the successful market entry of the selected LOHCs.^{87,89}

Three LOHCs meet all critical criteria. The first one is toluene, which can be produced in large quantities by petroleum refineries and is cost-effective. The Japanese company Chiyoda Corporation has rewarded this LOHC concept, and, in collaboration with other partners, it has demonstrated the feasibility of the first transport route via Brunei to Japan.⁹⁰ Dibenzyltoluene and benzyltoluene are the other two, which are also commercially available. Both are known as a typical thermal oil (MARLOTHERM), and their production could be ramped up for LOHC uses. In addition, industrial development by the German company Hydrogenious LOHC Technologies pushes the commercialization of benzyltoluene as the hydrogen carrier, and several projects have been implemented to demonstrate the feasibility of this LOHC technology.^{87,90}

However, these three LOHCs possess some drawbacks. One concern is related to the stability of LOHCs after several cycles of hydrogenation/dehydrogenation due to unwanted side reactions.⁹¹ Developing more selective catalysts and improving process implementation are currently being investigated, and attempts to reduce the use of expensive and rare catalysts containing precious metals are also being made.⁹² Another concern is that LOHC is currently produced from the petroleum refining processes. It is worth mentioning that it is possible to produce the LOHCs mentioned above from renewable raw materials like (hemi)cellulose and lignin. Bio-based toluene is already commercially available (e.g., BioBTX B.V.), although still in small quantities, and it can be gradually introduced into the fossil-based LOHC system.^{93–95}

3.2. Introduction to the Electrocatalytic Hydrogenation. Electrocatalytic hydrogenation (ECH) is an innovative process that uses electrical energy to drive the reduction of organic molecules (e.g., LOHCs), including biomolecules, in the presence of a catalyst. This method offers a promising alternative to traditional thermal catalytic hydrogenation by operating under milder conditions and enabling the utilization of “green hydrogen” generated by electrolysis.⁹⁶ This process is also valuable in converting biomass-derived compounds into fuels and chemicals, thereby contributing to sustainable energy solutions. By leveraging renewable electricity, ECH can potentially lower carbon emissions and improve energy efficiency, making it a critical technology in transitioning to a green economy.

Biomass-based molecules are a rich source of complex organic compounds that can be converted into high-value products through reactions such as hydrogenation or used as LOHC substrates. Traditionally, catalytic hydrogenation of such molecules requires high hydrogen pressures (80–200 bar) and elevated temperatures (250–450 °C),⁹⁷ and such harsh reaction conditions are energy-intensive and costly. ECH offers a promising alternative by utilizing electrical energy and green hydrogen under mild conditions, significantly reducing the severity of reaction parameters (Table 3, taking furfural

Table 3. Comparison of Electrocatalytic Hydrogenation and Thermocatalytic Hydrogenation of Furfural to Furfural Alcohol

factor	electrocatalytic hydrogenation ^{61,98,99}	thermocatalytic hydrogenation ^{100–103}
temperature	20–60 °C	120–180 °C
pressure	ambient	10–50 bar
energy source	electricity (potentially renewable)	high heat, usually fossil fuel based
hydrogen requirement	none (uses protons from electrolyte)	pure H ₂ gas (at high pressure)
environmental impact	lower CO ₂ emissions (if renewable powered)	higher CO ₂ emissions (fossil fuel heat)
catalyst durability	high durability (Cu and Ni catalysts at mild conditions)	moderate (Pd and Pt can degrade at high temperatures)
safety	lower risks (ambient pressure, no H ₂ gas)	higher risks (high pressure, H ₂ gas handling)

hydrogenation as an example). ECH not only enhances the efficiency and selectivity of biomolecule conversion but also aligns with sustainable energy practices. By lowering the operational pressures and temperatures, ECH can potentially make the production of LOHCs more economically viable and environmentally friendly.

3.3. Catalysts for ECH of Biomolecules. As mentioned in section 3.1, bio-based LOHCs are valuable directions. Here, we thus comment on recent results in the ECH of biomolecules beyond their use as LOHCs to provide a wider view of the topic.

3.3.1. Supported Nanoparticles Based on Noble Metals.

3.3.1.1. Platinum-Based Catalysts. Platinum-based catalysts are widely used in ECH due to their exceptional catalytic activity and stability. Platinum has excellent hydrogen adsorption and desorption capabilities, making it an efficient catalyst. In the ECH process, platinum catalysts can effectively facilitate the generation and transfer of hydrogen atoms, enabling the hydrogenation of organic molecules.

Although Pt electrodes exhibit excellent activity for producing H_{ad} (adsorbed hydrogen species) from water decomposition, their high selectivity for H₂ formation at low potentials limits their application in the ECH of aldehydes. Optimizing the binding energy between the metal catalyst and the reactants is necessary to enhance ECH efficiency. Lopez-Ruiz and colleagues,¹⁰⁴ based on the Sabatier principle, discovered that the reduction rate of the carbonyl group in aldehydes is related to the binding energy between the aldehyde and metal. Specifically, weak binding hinders the adsorption of reactants, while strong binding inhibits the desorption of products.¹⁰⁵

ECH exhibits significant sensitivity to the structure of Pt. Bondue and colleagues¹⁰⁶ reported that the crystalline surface of the Pt catalyst influences the ECH reaction pathway of acetone. As shown in Figure 2, the hydrogenation of *CH₃COCH₃ to form *CH₃HCOHCH₃ is more favorable on Pt(110) and Pt(553) surfaces, leading to the production of 2-propanol. However, on the Pt(510) surface, the C–O bond cleavage to form *CH₃CCH₃ and OH is preferential to the hydrogenation of *CH₃COCH₃, resulting in the formation of propane. Additionally, acetone does not adsorb on the Pt(111) surface, leading to low ECH activity.

The surface reaction rate is proportional to the coverage of the reactants on the catalyst surface, which necessitates strong substrate adsorption by the catalyst. The application of platinum-group metals with high hydrogenation activity in phenol ECH has been studied. Song et al.¹⁰⁷ investigated the phenol ECH on Pt/C, Rh/C, and Pd/C, finding that Rh/C exhibited the highest hydrogenation rate, followed by Pt/C.

Currently, the high cost and limited supply of platinum restrict its large-scale application. Therefore, researchers are not only focused on developing efficient platinum-based catalysts but also exploring strategies to reduce platinum usage through alloying or nanostructuring.¹⁰⁸

3.3.1.2. Palladium-Based Catalysts. Palladium-based catalysts exhibit excellent catalytic activity in ECH, particularly in selective hydrogenation reactions. The d-electron structure of palladium favors the adsorption of hydrogen molecules and promotes their dissociation, generating active hydrogen atoms. Palladium catalysts demonstrate high selectivity and activity in the hydrogenation of aromatic compounds and unsaturated organic molecules.

Lopez-Ruiz et al.¹⁰⁴ investigated the Pd catalysts that exhibit the highest turnover frequency (TOF) for the reduction of benzaldehyde and furfural, as they have the optimal interaction strength with these compounds (Figure 3).

Chen et al.¹⁰⁹ used Pd supported on carbon felt as an effective catalyst for the ECH of cinnamaldehyde (CAL), achieving a total faradaic efficiency (FE) of 87.54%. Villalba et al.¹¹⁰ revealed that acetophenone and benzophenone could be converted into 1-phenylethanol, ethylbenzene, diphenylmethanol, and diphenylmethane through ECH on the Pd electrode.

Similar to platinum-based catalysts, the cost and resource scarcity of palladium-based catalysts also limit their application. However, it is possible to reduce costs while maintaining catalytic activity by alloying palladium with other metals, such as silver or copper. Peng et al.¹¹¹ synthesized bimetallic Ag₃₂Pd₆₈ nanoparticles, achieving a removal rate of approximately 88% for 2,4-DCP. The optimal incorporation of Ag not only enhanced the adsorption of H* atoms on the catalyst surface but also facilitated the desorption of the formed phenol. Similarly, Chen et al.¹¹² designed bimetallic Pd–Au

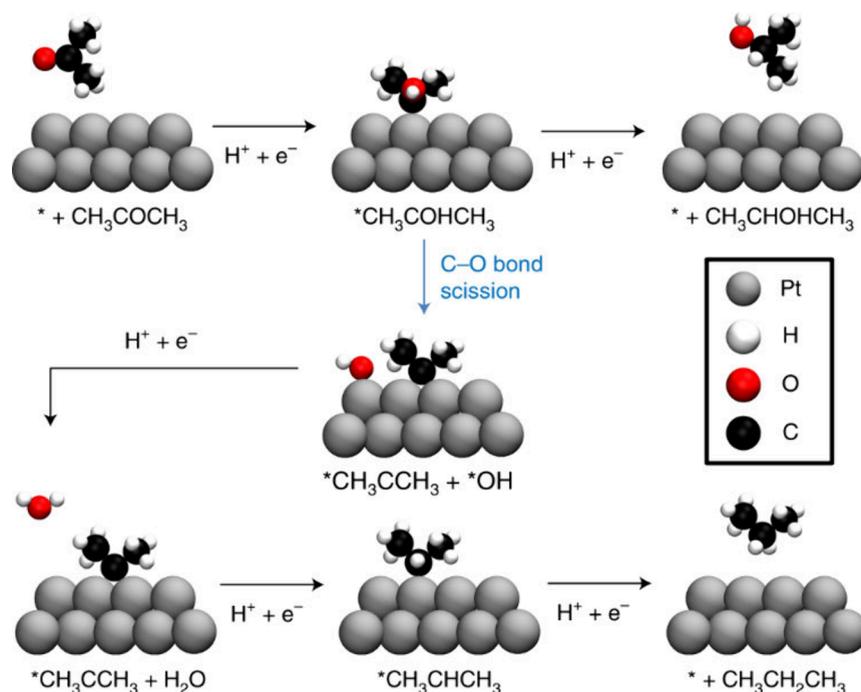


Figure 2. Reaction pathway of acetone. This figure was reproduced with permission from ref 106. Copyright 2019 Springer Nature.

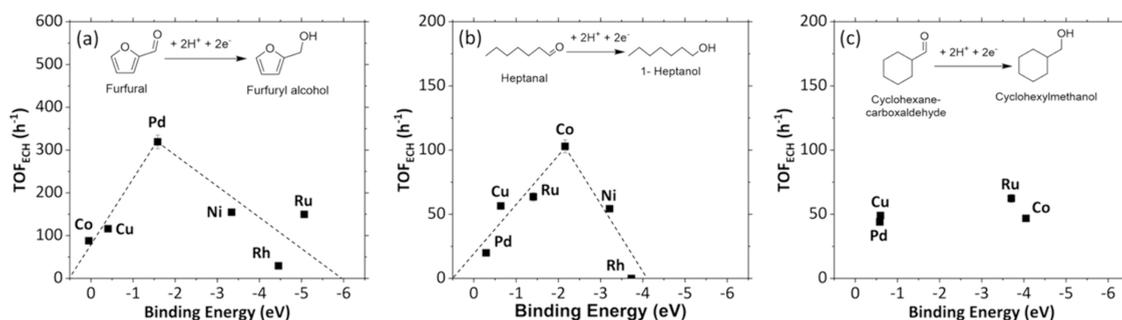


Figure 3. ECH of aldehydes. This figure was reproduced with permission from ref 104. Copyright 2019 American Chemical Society.

alloy nanoparticles as electrocatalysts for the electrochemical hydrodechlorination (EHDC) of 4-chlorophenol, achieving an EHDC efficiency of up to 98.35%. Zhou et al.¹¹³ fabricated CuPd_{0.021} bimetallic electrocatalysts for ECH of furfural to 2-methylfuran with a high FE of 75%.

3.3.1.3. Other Noble Metals (e.g., Rh and Ru). In addition to platinum and palladium, noble metals such as ruthenium (Ru) and rhodium (Rh) have also been applied in ECH. Ruthenium-based catalysts have attracted attention for their high catalytic activity under mild conditions, particularly demonstrating good selectivity in hydrogenation reactions in aqueous solutions.

Abdel-Mageed et al.¹¹⁴ found that the Ru catalysts exhibit poor selectivity for CO methanation in CO₂-rich reformat gas with low CO content. However, when a high amount of H₂O is present in the gas feed, the selectivity of Ru catalysts significantly increases, reaching up to 100%.¹¹⁴ Ruthenium also has good sulfur tolerance, which gives it a significant advantage in hydrogenation reactions involving sulfur-containing compounds. Wang et al.¹¹⁵ found that sulfur vacancies on the surface of Ru clusters bind with thiophene and, in a quasi-equilibrium step, activate H₂ and H₂S, forming intermediates that participate in kinetically relevant hydrogenation and H-

assisted C–S bond cleavage reactions. The turnover rates for desulfurization and hydrogenation increase with larger cluster sizes because sulfur atoms bind more weakly to larger Ru metal clusters, resulting in a greater number of sulfur vacancies during steady-state catalysis.

Rhodium catalysts are renowned for their high selectivity in the hydrogenation of nitrogen-containing heterocycles and alkenes in ECH reactions, making them valuable for applications in fine chemicals and pharmaceutical synthesis.

Overall, despite the excellent performance and selectivity of noble metal catalysts in ECH, their high cost and scarcity have driven researchers to continuously explore new materials and technologies to reduce reliance on these precious metals and enable broader applications.

3.3.2. Supported Nanoparticles Based on Non-noble Metals.
3.3.2.1. Nickel-Based Catalysts. Nickel-based catalysts have garnered significant attention in ECH due to their cost-effectiveness, abundance, and excellent catalytic activity, especially in hydrogen evolution reactions (HER). Nickel's ability to efficiently adsorb hydrogen atoms and facilitate electron transfer makes it a promising alternative to noble metal catalysts. The d-electron configuration of nickel allows

for effective hydrogen adsorption and activation, which is crucial in the ECH processes.

Recent research has focused on enhancing the performance of nickel catalysts through alloying and nanostructuring. Nickel alloys, such as Ni–Mo, Ni–Fe, and Ni–Co, have demonstrated superior catalytic activities due to synergistic effects between nickel and the alloying metals.^{116,117} For instance, Ni–Mo alloys show enhanced hydrogen evolution activity due to the modification of the electronic structure and the creation of additional active sites. Similarly, Ni–Fe and Ni–Co alloys improve the catalytic efficiency by altering the binding energy of hydrogen on the catalyst surface, thereby optimizing the reaction kinetics.

Nanostructuring nickel-based catalysts, including the creation of nanoparticles, nanowires, and nanosheets, significantly increases the surface area and the density of active sites. This morphological control not only enhances the catalyst's intrinsic activity but also improves its stability under operational conditions. Chen et al.¹¹⁸ designed Ni nanosheets exhibiting excellent catalytic performance due to their high surface area and favorable electronic properties. Additionally, core–shell structures, where nickel is coated with another material (e.g., carbon or metal oxides), have been developed to improve both the activity and durability of the catalyst.¹¹⁹

Despite these advancements, nickel-based catalysts face challenges such as surface oxidation, which can lead to decreased catalytic activity over time. Strategies to mitigate this include surface passivation, the use of protective layers, and the development of nickel-based composites that maintain high activity while preventing oxidation. Furthermore, the selectivity of nickel catalysts in complex organic transformations remains a critical area of research, with ongoing efforts to tailor the electronic and geometric properties of these catalysts to achieve high selectivity.

3.3.2.2. Cobalt-Based Catalysts. Cobalt-based catalysts are another class of non-noble metal catalysts that have shown promise in ECH due to their robust catalytic activity and relatively low cost. Cobalt's ability to interact strongly with hydrogen allows it to effectively catalyze the hydrogenation reactions, making it a suitable candidate for replacing noble metals in various applications.

Cobalt catalysts are often employed in the form of alloys (e.g., Co–P, Co–S, and Co–Ni) or as part of composite materials to enhance their catalytic properties.^{120,121} Co–P catalysts have been widely studied for their ability to efficiently catalyze hydrogen evolution, with phosphorus playing a crucial role in modifying the electronic structure of cobalt to improve its activity. Han et al.¹²² prepared Co–S catalysts with excellent conductivity and catalytic activity, particularly in the acidic and neutral media. These materials not only exhibit high catalytic efficiency but also show good stability under operating conditions, making them viable for long-term use in ECH.

Nanostructured cobalt catalysts, including nanoparticles, nanowires, and nanosheets, have been developed to maximize surface area and active site density, thereby enhancing catalytic performance. Nanoparticles have demonstrated significant promise in ECH due to their high surface area and the presence of multiple oxidation states that facilitate various catalytic pathways.¹²³

One of the significant advantages of cobalt-based catalysts is their versatility in catalyzing a broad range of hydrogenation reactions, including those involving complex organic mole-

cules. However, cobalt catalysts are not without challenges. Issues such as catalyst poisoning, deactivation over time, and the formation of inactive phases under specific reaction conditions need to be addressed. Ongoing research focuses on developing more stable cobalt-based catalysts through surface modification, alloying, and the use of stabilizing agents that can prevent catalyst deactivation.

3.3.2.3. Iron-Based Catalysts. Iron-based catalysts have emerged as an attractive alternative in ECH due to their abundance, low cost, and environmentally benign nature. As one of the most abundant transition metals, iron presents a sustainable option for large-scale catalytic processes. Iron-based catalysts such as Fe–N–C, Fe₃O₄, and FeS₂ have shown notable activity and selectivity in hydrogenation reactions.^{124–126}

The catalytic performance of iron-based materials is often enhanced through doping or surface modification. Li et al.¹²⁶ revealed that nitrogen-doped iron catalysts (Fe–N–C) have demonstrated exceptional HER activity, attributed to the introduction of active sites that facilitate hydrogen adsorption and activation. These catalysts have shown stability across a range of pH conditions, making them versatile for various ECH applications.

Moreover, the combination of iron with other metals, such as cobalt or nickel, has been explored to create bimetallic catalysts with improved performance. Fe–Ni catalysts exhibit enhanced catalytic activity due to synergistic effects that optimize electronic properties and promote efficient hydrogenation pathways. Additionally, iron-based catalysts have been incorporated into composite materials with carbon or metal oxides^{127,128} to enhance their stability and activity further.

3.3.3. Metal Oxides and Hydroxides. Metal oxides and hydroxides have gained significant attention as electrocatalysts for hydrogenation reactions due to their unique structural and electronic properties. These materials are characterized by their ability to undergo reversible redox reactions, making them highly effective in catalyzing electrochemical processes. Metal oxides such as titanium dioxide (TiO₂), nickel oxide (NiO), and cobalt oxide (Co₃O₄) are commonly used in ECH due to their stability, abundance, and ability to promote HER.^{129–131} Nevertheless, a general aspect often underestimated is that these materials are poorly conductive, while this is a requirement for electrocatalysis. Thus, improving conductivity by either introducing elements facilitating electron transport (for example, carbon nanofibers) or modifying the material to improve electron conductivity (by doping, for example) is critical. In addition, measuring the electrocatalytically active surface area is fundamental, but it is often not made.

TiO₂ is a widely studied metal oxide catalyst due to its excellent chemical stability. It is often used in conjunction with other metals or dopants to enhance its catalytic activity. Zhang and co-workers¹³² synthesized TiO₂ doped with nitrogen or carbon to improve conductivity and HER activity. Similarly, NiO and Co₃O₄ are known for their high catalytic efficiency in HER, particularly when combined with conductive materials like graphene or carbon nanotubes, which enhance their electron transfer capabilities and overall performance.^{132,133}

Metal hydroxides, such as nickel hydroxide [Ni(OH)₂] and cobalt hydroxide [Co(OH)₂], also play a critical role in ECH.¹³⁴ These hydroxides exhibit layered structures that facilitate the intercalation and deintercalation of protons, a key process in HER. The structural flexibility of metal hydroxides

allows for the incorporation of various dopants, which can tailor the catalytic activity and stability. Hunter¹³⁵ reported the addition of iron to nickel hydroxide to form NiFe-LDH (layered double hydroxide), resulting in a significantly enhanced catalytic performance. The iron addition improves the electron transfer kinetics.

Metal oxides and hydroxides possess multiple features relevant to the ECH mechanism and catalytic behavior, such as the presence of active sites (i) for hydrogen adsorption, (ii) to promote proton-coupled electron transfer (PCET), and (iii) to stabilize the reaction intermediates or adsorb the organic reactants preferentially. The surface chemistry of these materials is crucial for their catalytic performance, as it determines the binding energy of hydrogen and the reaction pathways for hydrogenation.

In metal oxides, the catalytic activity is often associated with the presence of oxygen vacancies or defects that act as active sites for hydrogen adsorption.^{136,137} These defects can enhance the binding of hydrogen molecules, making them more reactive and promoting their conversion into atomic hydrogen, which can then participate in the hydrogenation of organic molecules. Additionally, the electronic structure of metal oxides can be tuned through doping or the creation of heterojunctions with other materials, further optimizing their catalytic performance in ECH.

Metal hydroxides, on the other hand, are known for their ability to undergo redox transitions between different oxidation states (e.g., Ni²⁺/Ni³⁺ and Co²⁺/Co³⁺).^{133,134} This redox flexibility enables them to mediate electron transfer processes during hydrogenation reactions effectively. Moreover, the layered structure of hydroxides allows for efficient proton diffusion, which is essential for maintaining high reaction rates in ECH. The ability to control the oxidation state of metal centers in hydroxides provides an additional level for tuning catalytic activity and selectivity. Overall, metal oxides and hydroxides offer a versatile platform for the design of efficient and stable electrocatalysts for hydrogenation reactions. Their ability to undergo reversible redox transitions, coupled with their structural tunability, makes them attractive candidates for further development in sustainable energy applications.

3.3.4. Metal-Free Catalysts. **3.3.4.1. Carbon-Based Materials.** Carbon-based materials have shown great potential as metal-free catalysts in ECH.^{138–140} Materials such as graphene, carbon nanotubes (CNTs), and doped carbon materials (e.g., nitrogen-doped carbon) are of particular interest due to their excellent conductivity, abundant surface active sites, and tunable structures. In comparison to traditional metal catalysts, a significant advantage of carbon-based catalysts is their cost-effectiveness and the abundant availability of raw materials, making them more economically viable for large-scale industrial applications.

Graphene, with its unique two-dimensional structure and excellent conductivity, has been extensively studied as a foundational material for electrocatalysts. The catalytic performance of graphene can be significantly enhanced by doping with elements such as nitrogen, sulfur, or phosphorus. These dopants modify the electronic structure of the carbon material, enhancing its hydrogen adsorption capacity and, in turn, improving its activity in hydrogenation reactions.^{141,142} CNTs, known for their unique structure, mechanical strength, and conductivity, are also widely used in electrocatalysis. The catalytic performance of CNTs can be further optimized by controlling their diameter, wall thickness, and surface

defects.¹⁴² Additionally, the catalytic activity and stability of CNTs can be effectively enhanced by combining them with other functional materials, such as metal oxides or other inorganic nanoparticles.

3.3.4.2. Emerging Metal-Free Catalysts. In addition to carbon-based materials, several emerging metal-free catalysts have garnered attention recently.^{143,144} These include carbides, boron–nitrogen co-doped carbon (BCN) materials, and phosphides. These novel materials exhibit unique electronic structures and surface chemistry, making them promising candidates for application in ECH.

BCN materials create novel active sites by incorporating boron and nitrogen atoms into the carbon matrix. These active sites have high hydrogen adsorption capacity and low reaction barriers, allowing BCN materials to exhibit high catalytic efficiency in hydrogenation reactions.^{145,146} Additionally, the preparation process of these materials is relatively simple and environmentally friendly, further enhancing their feasibility for industrial applications.

Phosphides are another promising category of metal-free catalysts, particularly in electrocatalytic water splitting and hydrogenation reactions. Zhang et al. reported carbon phosphorus (PC) materials, and with their unique layered structure and electronic properties, they can effectively catalyze hydrogenation reactions at lower potentials.¹⁴⁷ Phosphide materials also offer good chemical stability and durability, maintaining high catalytic activity over extended times.

3.4. Membrane. The specific paired electrolysis of interest (Figure 1) requires proton transfer from the anodic to the cathodic part. We thus limit the discussion here to proton-exchange membranes (PEMs).

3.4.1. Classes of PEM. **3.4.1.1. Perfluorosulfonic Acid (PFSA) Membranes.** PFSA membranes contain a PTFE backbone for enhanced thermal and chemical stability and hydrophilic perfluoro vinyl ether side chains that contain $-\text{SO}_3^-$ groups. These membranes are known for their ability to conduct protons very effectively. However, when operating under low humidity or at elevated temperatures, the proton conductivity and stability can be significantly compromised. Nafion, which is considered the most recognized PEM material, is highly affected under these conditions.¹⁴⁸ Aquivion, with a shorter side chain, provides better stability under relatively higher temperatures.¹⁴⁹

3.4.1.2. Sulfonated Aromatic Polymer (SAP)-Based Membranes. These membranes are typically made from hydrocarbon polymers, such as polyether ether ketone (PEEK), polyether sulfone (PES), polysulfone (PSU), polyphenyl sulfone (PPSU), and poly(2,6-dimethyl-1,4-phenylene oxide) (PPO).⁷⁸ Sulfonic acid groups can be introduced by treating them with a sulfonating agent (H_2SO_4). Due to better chemical and thermal stability and easy preparation, they appear as a good alternative to Nafion. However, they generally exhibit lower proton conductivity due to less developed interconnected hydrophilic channels.¹⁵⁰ SAPs are often available as raw polymers and can be sulfonated after purchase.

3.4.1.3. Polybenzimidazole (PBI)-Based Membranes. Partially or fully aromatic PBI polymers are utilized for PEM due to their high mechanical and thermal stability. The proton conductivity of these membranes is provided by the incorporation of phosphoric acid groups into the polymer structure.¹⁵¹ Unlike Nafion, PBI-based membranes can operate at higher temperatures and conduct protons without the existence of water.

3.4.1.4. Composite Membranes. Hydrocarbon-based membranes require a high amount of $-\text{SO}_3^{2-}$ groups to achieve higher proton conductivities than Nafion. Given that the sulfonation procedure results in excess swelling of the membranes, the stability of the membrane will decay. Because of these reasons, organic–inorganic composite materials are studied, aiming to combine organic properties (processability and electrical characteristics) with inorganic properties (thermal and chemical stability) (Table 4).¹⁵²

Table 4. Commercially Available Proton-Exchange Membranes

membrane	manufacturer	type
Nafion	Chemours	PFSA-based
Aquivion	Syngso	PFSA-based
Celtec ¹⁵³	BASF	sulfonated PBI
Pemion ¹⁵⁴	Ionomr Innovations	sulfonated hydrocarbon
Gore PEM ¹⁵⁵	W.L. Gore & Associates	na

3.4.2. Recent Research. Aquivion membrane with a short side chain (SSC) was compared with Nafion in the work of Nagasawa et al.¹⁵⁶ It was concluded that the structure and equivalent weight (EW) of the PEM significantly impact toluene permeability. Aquivion with a short side chain has an increased concentration of sulfonic acid groups. These ionic groups attract and bind water molecules, forming hydration shells around these ionic sites. This fact reduces the availability of water molecules to solvate nonpolar molecules such as toluene. As a result, toluene becomes less soluble in the water-rich regions of the membrane, and its permeation is suppressed. However, Nafion, with a long side chain (LSC) structure and high EW, shows higher electrochemical performance. This fact was attributed to the better transport to the reaction sites (three-phase boundary), enhancing the reaction kinetics. LSC membranes are likely better in the short term operations, whereas SSC membranes would perform better in the long term.

3.5. Electrolytes. The choice of electrolyte for electrocatalytic hydrogenation is closely related to the specific organic substrate, reaction conditions, and target product properties.¹⁵⁷ The common organic substrates used for electrocatalytic production of LOHC mainly include unsaturated aromatic hydrocarbons, heterocyclic compounds, ketones or aldehydes, alcohol compounds, etc.¹⁵⁸ Lignin model compounds (such as phenol, benzene, and guaiacol, etc.) are the desirable candidates for hydrogen storage due to their unique structure. They can be converted and upgraded to hydrogen-rich and stable products after ECH, such as cyclohexanol, cyclohexane, and cyclohexanone.

3.5.1. Aqueous Electrolyte. In the electrocatalytic hydrogenation reaction, the protons are transferred to the cathode and reduced to adsorbed hydrogen (H_{ad}). The H_{ad} subsequently migrates to the reaction interface to hydrogenate the unsaturated substrate. Electrocatalytic hydrogenation is mainly carried out in acidic solutions, such as H_2SO_4 ,^{44,159–162} HCl ,⁵⁴ HClO_4 ,^{163,164} etc. Song et al.¹⁰⁷ conducted a series of studies on the ECH of phenol in a H-cell using three different electrolytes, among which CH_3COOH had the highest activity, followed by H_3PO_4 . Instead, H_2SO_4 showed the lowest phenol conversion rate.

The pH affects the selectivity and yield of products. In the study of Xin et al.¹⁶⁵ levulinic acid (LA) was reduced to valeric

acid (VA) or γ -valerolactone (GVL) by ECH in a flow cell. They observed a 95% selectivity for VA in an acidic electrolyte (0.5 M H_2SO_4 solution, pH 0), and a 100% selectivity for GVL in a neutral electrolyte ($\text{KH}_2\text{PO}_4/\text{K}_2\text{HPO}_4$ buffer solution, pH 7.5). Nilges et al.¹⁶⁶ investigated 5-hydroxymethylfurfural (HMF), which was completely reduced to 2,5-dimethylfuran (DMF) in a mixture of 0.5 M H_2SO_4 with ethanol (1:1, v/v). HMF preferentially generated furfuryl alcohol (FA) in the phosphate buffer solution (pH 7). Tao et al.¹⁶⁷ observed that the pH value regulated the selectivity. Specifically, when using Pt/C as the catalyst, the highest conversion of phenol in CH_3COOH was observed at pH 5 compared to pH 3 and 10. In contrast, when using Rh/C as the catalyst, the conversion of phenol increased with increasing pH.

In addition, a variety of buffer solutions are used in ECH, and they usually have good electrical conductivity, such as acetate buffer solution,^{48,168,169} sulfate buffer solution,¹⁷⁰ phosphate buffer solution,¹⁶⁵ and borate buffer solution.^{171,172} The buffer solution can maintain the pH stability and provide a relatively stable chemical environment for the electrocatalytic reaction, which in turn improves the product selectivity. Roylance et al.¹⁷³ converted HMF to 2,5-hexanedione (HD) by ECR in the 0.2 M sulfate buffer solution (pH 2). They found that the local pH at the working electrode increases rapidly due to the proton consumption during the HMF reduction in an unbuffered, weakly acidic solution. The pH change alters the yield, selectivity, and product type.

The kind of anode electrolyte (anolyte) to combine with cathode electrolyte (catholyte) is also critical and has a significant impact on the reaction results. Wijaya et al.¹⁷⁴ investigated the different combinations of “catholyte–anolyte” on the efficiency of ECH. The result showed that the conversion rate of guaiacol decreased in the following order: acid–acid (38%) > neutral–acid (36%) > acid–alkaline (16%) > alkaline–acid (0%), i.e., acid–acid pair is the most efficient combinations for the reaction. It was also found that the neutral–acid pair produced the highest FE, suggesting that most of the protons required for ECH come from the anode side.

3.5.2. Organic Solvents as Co-solvents. Some organic substrates are difficult to dissolve in acidic aqueous solutions. Therefore, organic solvents can be added to the electrolyte solution as co-solvents to increase the solubility of substrates. Organic solvents are classified into three categories:

- Polar protonic solvents, such as methanol, ethanol, and isopropanol, act as either hydrogen bond donors or acceptors.¹⁶⁷
- Polar non-protonic solvents: acetonitrile (MeCN), dimethylformamide (DMF),¹⁷⁵ dimethyl sulfoxide (DMSO), ethyl acetate, tetrahydrofuran (THF), 2-methyltetrahydrofuran (2-Me-THF), and ketone.
- Nonpolar solvents, such as hexane, benzene, and toluene.

For ECH involving aromatic compounds, the protonated organic solvents are a preferable option. Mulero et al.¹⁷⁶ studied the ECH of benzophenone in ethanol/water (90:10, v/v) plus 0.1 M H_2SO_4 solution in a polymer electrolyte membrane electrochemical reactor (PEMER). At low current densities, the conversion of benzophenone was up to 30%, with a selectivity of dibenzyl alcohol >90%.

Although organic solvents can increase the solubility of reactants, their presence also decreases the conductivity. The

use of alcohols as co-solvents may lead to a decrease in the ECH rate and FE. Lopez-Ruiz et al.¹⁷⁷ added methanol, ethanol, or isopropanol to the electrolyte to explore the effects of alcohol on the rates of benzaldehyde ECH. The FE and reaction rate decreased with increasing alcohol concentration. The influence of alcohol type became gradually significant as the length of the alcohol chain increased.

In addition, some organic solvents tend to adsorb competitively onto the active sites of electrodes (catalysts), thereby weakening their overall activity. Alternative solvents were thus proposed and developed. Wijaya et al.¹⁷⁸ identified methanesulfonic acid (MSA) as a promising green alternative to conventional organic solvents, which possess ionic conductivity comparable to that of inorganic acids, as well as low toxicity and corrosivity. They used this solvent to perform the ECH of guaiacol using Pt/C catalyst powder in a stirred slurry electrocatalytic reactor. They obtained products, including cyclohexanol (45–53%) and 2-methoxycyclohexanol (20–26%), thus confirming the feasibility of MSA.

3.5.3. Ionic Liquids. Recently, ionic liquids (ILs) have emerged as a promising class of green organic solvents that have the potential to replace conventional electrolytes due to their unique properties. ILs are salts with a melting point below 100 °C. Typically, ILs consist of organic cations (e.g., imidazolium, pyridinium, pyrrolidinium, phosphonium, and ammonium) and inorganic or organic anions (e.g., halogens, BF₄⁻, Tf₂N⁻, PF₆⁻, etc.). ILs typically not only exhibit high conductivity but also high solubility for unsaturated compounds, such as polycyclic aromatic hydrocarbons and aromatic compounds. ILs have a wide electrochemical stabilization window, which enables them to operate stably over a wide range of potentials.¹⁷⁹ In addition, ILs have modifiable anionic and cationic structures. Using ILs as the electrolyte in the electrocatalytic production of LOHC offers a promising way to achieve a sustainable and efficient energy conversion process.¹⁸⁰ However, generally, the viscosity of ILs is relatively high, and water or organic solvents are added as co-solvents.

Andrey et al.¹⁸¹ used 1-butyl-3-methylimidazolium hexafluorophosphate ([BMIM][PF₆]) ILs/water (80:20, v/v) as the electrolyte solution in a flow-cell to study the ECH of aromatic compounds (naphthalene, quinoline, and carbazole). Their study successfully obtained the desired products under mild conditions, validating the potential of ILs as effective electrolytes. Chu et al.¹⁸² reported the ECH of furfural (FF) in a H-cell, where 1-ethyl-3-methylimidazolium tetrafluoroborate ([EMIM][BF₄]) plus water (H₂O) was used as the cathode electrolyte. The FF was converted to FA with a total conversion efficiency of 61.7%. Wu et al.¹⁸³ investigated the effect of ILs on the ECH of LA to GVL in a typical H-cell. The comparison of the FE and current density indicates that [BMIM][BF₄] had the best performance among the studied ILs ([EMIM][BF₄], [BMIM][BF₄], [HMIM][BF₄], [OMIM][BF₄], [TBA][BF₄] and [TBP][BF₄]). Consequently, they used [BMIM][BF₄]-MeCN-H₂O as the electrolyte solution to perform the ECH of LA, GVL was found as the only product, and [BMIM][BF₄] (1.8 wt %)-MeCN-H₂O (1.8 wt %) was identified as the optimal electrolyte solution.

ILs with specific structures and functions can be further designed and synthesized by changing the combination of anions and cations as well as their functionalization to improve the efficiency of ECH of LOHC. According to the survey, proton ionic liquids (PILs) are preferred, and hydrophilic ILs

would be better, while more work needs to be conducted further.¹²

4. ANODIC OXIDATION

Biomass and biomass-derived mainly consist of cellulose, hemicellulose, and lignin, which are abundant resources for synthesizing high-value chemicals by electrocatalytic oxidation. The value-added processing biomass consists of two key stages: the initial depolymerization into its constituent monomers and the upgrading of the monomers by electrocatalytic reduction or oxidation into a variety of value-added fuels and chemicals.^{184–186}

In recent years, research on the electrocatalytic oxidation of biomass-derived key platform chemicals, such as HMF, FF,^{187,188} and glycerol^{189–192} has attracted widespread attention and made significant progress. As lignin is the richest source of aromatic compounds on Earth and is a key feedstock for the production of high-value-added products, recently, the electrocatalytic oxidation of lignin and its model compounds has also been greatly developed.^{192–198}

4.1. Substrates and Products. Coupling the electrocatalytic cathodic regeneration of LOHCs with an anodic oxidation process to valorize lignin derivatives producing high-value chemicals is a promising strategy to (i) improve process economics, (ii) link H₂ and biorefinery economies, and (iii) improve environmental sustainability. The oxidation reaction at the anode serves as a pivotal component of the entire electrocatalytic system, facilitating the provision of electrons and protons necessary for the ECH of precursors into LOHCs. Conventionally, OER is coupled with the cathodic reaction.^{25,199} However, this approach demands a substantial overpotential to drive the reaction, has slow kinetics, and the oxygen produced may often need to find application. Hence, the substitution of OER with thermodynamically favorable organic oxidation reactions has generated significant interest. While often the total oxidation of waste is explored,^{41,200,201} the selective oxidation path has undoubtedly greater interest, although more challenging.


Most of the literature data is focused on the electrocatalytic oxidation of small alcohols and cellulose-derived products, such as furans. Many organic molecules, such as methanol, ethanol, formic acid, and urea, have been widely used in electrocatalytic oxidation to replace OER. In contrast, the research concerning the electrocatalytic oxidation of lignin-derived molecules has predominantly centered on the complete oxidation (or degradation) of these compounds, driven by wastewater treatment application,^{202,203} and the discussions on the electro-oxidation of lignin-derived molecules to value-added chemicals are still very limited. Also, depolymerization of lignin molecules generally generates various monomers, dimers, and macromolecules, with monomers and dimers being predominant, and the chemical properties of these molecules also depend upon the method used for lignin depolymerization.^{204,205}

Assessing whether lignin-derived molecules are suitable for electrochemical oxidation involves evaluating their thermodynamic feasibility, solubility in aqueous solutions, and the value of the products generated. For aromatic molecules such as guaiacol, vanillin, toluene, *p*-xylene, *m*-xylene, *o*-xylene, and anisole, their standard electrode potentials are mostly below 1 V versus reversible hydrogen electrode (RHE), which is lower than 1.23 V versus RHE required for OER.^{206,207} Therefore, from an energy standpoint, these molecules are not suitable

due to their high energy demand. In terms of solubility, lignin-derived aromatic molecules such as catechol, resorcinol, and *p*-cresol demonstrate better solubility.^{208–211} The solubility of all lignin-derived molecules depends upon the salt or buffer used for dissolution and increases with temperature, varying depending upon the specific pH level. The major oxidation products of these aromatic molecules have also been identified, along with their potential industrial applications, depending upon the selectivity of the method used. This indication offers insights into the potential commercial value of the products derived from the electrochemical oxidation of lignin. Below, these aspects are evidenced by taking four molecules as examples:


4.1.1. Catechol.²⁰⁹ This process is a $2\text{H}^+/2\text{e}^-$ oxidation with an oxidation potential of 0.2 V, producing a substance that is used as a fungicide, a reagent in photography, and the production of dyes, with a solubility of 430 g/L (Scheme 1).

Scheme 1. Oxidation of Catechol to 1,2-Benzoquinone

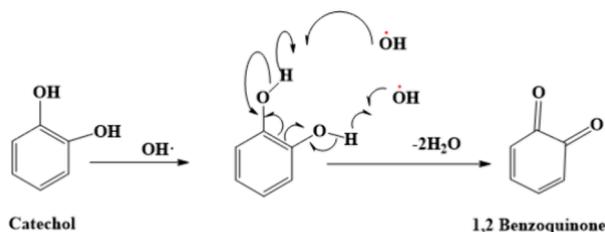

4.1.2. Resorcinol.²¹⁰ 2,4-Benzoquinone, with a solubility of 1100 g/L and an oxidation potential of 0.6 V, is used as a chemical intermediate, a polymerization inhibitor, an oxidizing agent, a photographic chemical, a tanning agent, and in the cosmetic industry (Scheme 2).


Scheme 2. Oxidation of Resorcinol to 2,4-Benzoquinone

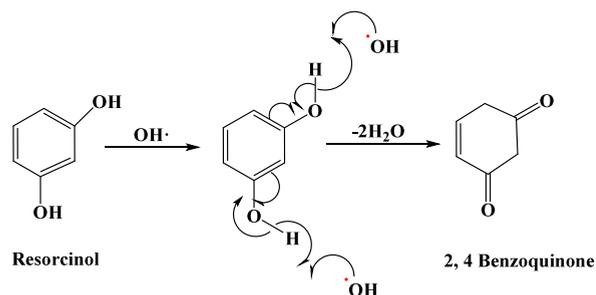


4.1.3. *p*-Cresol.²¹¹ Parabens (*p*-hydroxybenzoic acid), with a solubility of 240 g/L and oxidation potential of 1.038 V, are an important class of preservatives extensively used in the cosmetic and pharmaceutical industries for preparing shampoos, commercial moisturizers, shaving gels, personal lubricants, topical/parenteral pharmaceuticals, spray tanning solutions, and toothpaste (Scheme 3).

4.1.4. Phenol.²⁰⁸ Phenol oxidation produces hydroquinone and *p*-benzoquinone, with product selectivity controlled by the electrooxidation parameters (Scheme 4). Hydroquinone, with a solubility of 83 g/L and an oxidation potential of 0.65 V, is clinically used to treat dyschromia, including melasma, chloasma, solar lentigines, freckles, and post-inflammatory hyperpigmentation. *p*-Benzoquinone is utilized in the dye, textile, chemical, tanning, and cosmetic industries.

Scheme 3. Oxidation of *p*-Cresol to 4-Hydroxybenzyl Alcohol and *p*-Hydroxyl Benzoic Acid

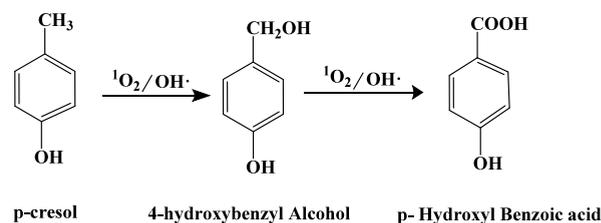



Scheme 4. Oxidation of *p*-Cresol to 4-Hydroxybenzyl Alcohol and *p*-Hydroxyl Benzoic Acid

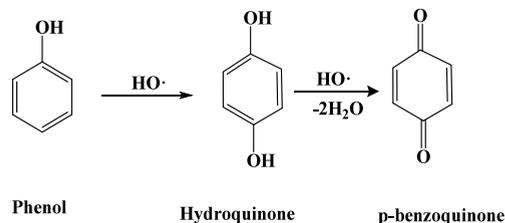




4.2. Brief Introduction of Electrocatalytic Oxidation.

The electrocatalytic oxidation (ECO) of organic compounds can proceed through two primary pathways: (i) direct oxidation at the interface between the electrode and electrolyte or (ii) indirect oxidation involving both heterogeneous electron transfer reactions and homogeneous redox reactions.

Direct oxidation occurs through the electron transfer between the organic substrates and the anode, usually at low anodic potentials. During electrolysis in an acidic or alkaline solution, H_2O (or OH^-) undergoes discharge at the anode, leading to the generation of adsorbed hydroxyl radicals on the surface of the anode, as reported by the following equations (eqs 1 and 2):^{205,212}




The oxidation of organic species adsorbed on an electrocatalytic surface proceeds through interactions with a so-called higher metal oxide and adsorbed hydroxyl radicals (eqs 3–5).



As already mentioned ECO of organic compounds include multiple mechanisms, each with distinctive pathways, intermediates, and reaction conditions, which can be optimized for various applications. Examples of ECO applications illustrate how diverse mechanistic pathways can selectively target specific organic pollutants or achieve higher efficiencies toward different products in specific reaction environments. Direct oxidation is frequently employed for the degradation of organic contaminants in water treatment, primarily due to the high reactivity of hydroxyl radicals ($\cdot\text{OH}$) generated at the anode surface. In this case, the organic pollutants such for example phenols and dyes adsorbed on the anode surface undergo oxidation via electron transfer directly with the anode or through interactions with $\cdot\text{OH}$.²¹³ An example of this type of

mechanism has been found through the use of boron-doped diamond (BDD) electrodes highly effective anodes for generating hydroxyl radicals, which enable the direct oxidation of phenolic compounds in wastewater treatments.²¹⁴ Hydroxyl radicals ($\bullet\text{OH}$) generated at the anode surface break down contaminants effectively. These radicals are produced by the oxidation of water molecules in acidic or neutral conditions, or from hydroxide ions when the pH is 10 or higher.²¹⁵ In fact, for a metal oxide (MO) anode with a high oxygen overvoltage, the initial oxidation of water leads to the formation of a physisorbed hydroxyl radical through eq 1. This intermediate can then undergo further oxidation to form a chemically adsorbed “superoxide” species (eq 3). However, the predominance of reaction 3 to the detriment of reaction 1 on the anode surface means that anodes are classified as active and inactive, respectively. The use of anodes based on RuO_2 , IrO_2 , and Pt lead to a large amount of (MO_{x+1}) , this species then oxidizes aromatic organic compounds, converting them primarily into carboxylic acids, though with relatively low levels of complete mineralization.²¹⁶ Conversely, in non-active metal oxide anodes such as SnO_2 and PbO_2 , $\text{MO}_x(\bullet\text{OH})$ is primarily generated. Once generated this physisorbed radical interacts more efficiently with a wide range of aromatic compounds, resulting in their complete mineralization or breakdown. One of the most effective non-active anode is the boron-doped diamond and its use lead as only reaction 1.²¹⁷ Meanwhile, dioxygen is concurrently generated via water oxidation or OER (eqs 6 and 7).²⁰⁵ This process diverts some of the oxidizing currents away from the desired substrate transformations, affecting the FE of the reaction.



Indirect oxidation reactions commonly use an electrolyte medium, with an electrocatalyst or mediator facilitating electron transfer between the electrode and substrates.²¹⁸ This process involves both heterogeneous electron transfer and homogeneous redox reactions, where a mediator interacts with the substrate and is subsequently regenerated at the electrode surface. Mediators must be stable in both oxidized and reduced forms to prevent decomposition. Two main types of mediator systems, laccase and electrolytic mediator systems, are proposed as environmentally friendly methods for organic electro-oxidation.²¹⁹ The efficiency and selectivity of these systems significantly depend upon the chosen mediator, with studies exploring a variety of mediators like nitrobenzene, transition metal complexes, and iodide ions. However, further research is required to fully understand the optimal selection of mediators and their effect on various substructures of substrates.

In laccase-mediated systems (LMS), the enzyme laccase catalyzes oxidation with the help of mediators, extending the enzyme's capability to oxidize substrates that would otherwise be unreactive.²²⁰ Notable mediators such as 2,2'-azine-bis(3-ethylbenzothiazoline-6-sulfonic acid (ABTS), 1-hydroxybenzotriazole (HBT),²⁰⁵ 2,2,6,6-tetramethyl-1-piperidinyloxy (TEMPO), and *N*-hydroxyphthalimide (NHPI)²²¹ facilitate the oxidation of organic components, improving reaction efficiency and selectivity for potential industrial applications. LMS mediators are classified by mechanism-hydrogen atom transfer, ionic, and electron transfer, influencing the oxidation

pathways and products formed in lignin processing. For example, NHPI has demonstrated high effectiveness for the electrochemical oxidation of lignin, selectively targeting β -O-4 linkages and other structures under mild conditions.²²²

Electrolytic mediator systems (EMS) differ using an anode to facilitate electron transfer, allowing for oxidation under broader pH and temperature conditions.²²³ Similar mediators, like NHPI and HBT, can be employed in EMS, yielding different oxidation outcomes compared to LMS.²⁰⁵ For instance, for lignin electro-oxidation, EMS with HBT produces a mixture of C-carbonyl and $\text{C}\alpha$ - $\text{C}\beta$ cleavage products, whereas LMS yields only C-carbonyl products. While EMS offers greater versatility and broader conditions for lignin valorization, further investigation is needed to refine these systems for consistent selectivity and efficiency.²²⁴

However, another mechanism, although less studied, in which electrocatalysts can also induce the formation of other oxidizing and more selective species on the electrode surface, such as peroxy and hydroperoxy species, superoxy, dioxygen radicals, singlet oxygen, etc., can occur. The generation of these oxidizing species and the design of electrodes for their selective production are still under exploration, unlike hydroxyl radical species, which have been extensively studied in the oxidative degradation of organics in wastewater treatments.^{225–228}

The *in situ* generation of H_2O_2 represents an appealing strategy due to its selective oxidizing properties. H_2O_2 can further interact with isolated Ti ions on the electrode surface or within a solid catalyst (such as Ti silicate-TS-1^{229,230}) at the liquid interface with the electrode, leading to the formation of peroxy species. Additionally, the oxidation of H_2O_2 can facilitate the production of superoxide ions ($\text{O}_2^{\bullet-}$), which readily react in the presence of protic solvents, leading to the formation of O_2 and hydroperoxide anion ($\text{HO}_2^{\bullet-}$).²³¹

Numerous systems for the electrocatalytic oxidation of small organic molecules have been documented in the literature, offering insights into how various organic compounds undergo electrochemical oxidation through distinct reaction mechanisms across different pH environments. This understanding provides insights into catalyst selection and applications in renewable energy and chemical synthesis. Feng et al. reported a review in recent advances in Ni-based catalysts for the electrochemical oxidation of ethanol (EOR). The EOR can in fact, represent a promising alternative to the anodic OER due to a lower overpotential, in comparison to the anodic OER. Ethanol can partially oxidized to acetate in an alkali environment with an equilibrium potential of 0.11 V versus RHE²³² considerably lower than the 1.23 V versus RHE required for the oxygen evolution reaction (OER). The high electrical conductivity of Nickel plays an essential role in boosting the efficiency of EOR, together with the metal's capacity for multiple oxidation states, especially the +3 oxidation state as nickel oxyhydroxide (NiOOH), exhibits significant electroactivity throughout the EOR process, further enhancing the reaction's effectiveness.²³³ The nature of the electrolyte also plays an important role when Ni-based materials are employed for EOR. Usually alkaline conditions are used to avoid corrosion phenomena that instead occur under oxidative potentials in acidic electrolytes.²³⁴ The addition of noble metals helps prevent corrosion and makes it possible to use nickel-based materials for ethanol oxidation reactions (EOR) in acidic environments.²³⁵

Lai et al.²³⁶ have explored the EOR on platinum and gold electrodes, employing both electrochemical and spectroscopic

methods across electrolytes with varying pH and compositions, largely influenced by buffering anions. The study found that reaction activity increases significantly when the electrolyte pH is above 10. Moreover, the results suggest that reaction selectivity is highly influenced by the type of electrolyte used and, to a lesser degree, by the pH value. The observations of this research supported the proposal of a potential overall mechanism for the EOR. Specifically, breaking the carbon–carbon bonds a key step for full oxidation was observed only on platinum when strongly adsorbing anions were not present.

The electrooxidation of methanol (MOR) is another important process thanks to the release of energy. In fact, methanol, known for its high hydrogen content, has gained significant attention as a fuel in energy storage and conversion technologies.²³⁷ This reaction serves as a crucial half-reaction in hydrogen production via methanol reforming and in the operation of direct methanol fuel cells (DMFCs).^{238,239} Moreover, the methanol oxidation reaction (MOR) is also important for converting methanol into valuable products like formate.^{240,241} The nature of the electrolyte plays an important role in MOR, acid environments induce an easier oxidation of methanol but the process depends a lot upon the presence of catalysts based on noble metals, given the low stability of catalysts based on non-noble metals that are easily dissolved. However, the use of alkaline environments favors the polarization at low anodic overpotential and the deprotonation of methanol.^{242,243} Tripković et al.²⁴⁴ report a study regarding the kinetics of MOR using Pt and Pt/Ru catalysts in two different electrolytes (0.5 M H₂SO₄ and 0.1 NaOH) and at two different temperatures (295 and 333 K). The results obtained highlighted that the activity of Pt and Pt/Ru catalysts for methanol oxidation depends significantly upon the electrolyte pH and temperature. Alkaline solutions, favors the reaction kinetics resulting much faster than in acidic conditions. This pH-dependent effect is thought to result from competitive adsorption between oxygenated species and anions from the electrolyte. Furthermore, both Pt and Pt₂Ru₃ catalysts display enhanced activity at elevated temperatures, with an increase of about 5 times in activity at 333 K compared to 295 K. However, only minor differences in activity are observed between pure Pt and Pt alloys with high Ru content. This was attributed, probably to the slower methanol dehydrogenation on Ru-rich surfaces, combined with an insufficient number of Pt active sites necessary for the efficient dissociative chemisorption of methanol.

The electrochemistry aimed at selectively oxidizing bio-based molecules is still in its early stages, although some interesting findings have been yielded.^{245–249}

4.3. Electrocatalysts. **4.3.1. Lignin and Lignin-Derived Molecules.** The research concerning the development and design of electrocatalysts for the ECO of lignin-derived molecules has predominantly centered on the complete oxidation of these compounds in wastewater. Electrochemical degradation of lignin to low molecular phenolic compounds was studied on various transition metals (Pt, Ni, Co, Ni, Co, etc.) in aqueous alkaline media,^{193,250} PbO₂ (a widely used anode),¹⁹⁷ and other electrodes based on Ir which may be too expensive for an effective use.²⁵¹ Parpot et al.²⁵² discussed various examples of direct electro-oxidation of lignin for vanillin production, including (i) PbO₂ anode (giving up to 64% yield of vanillin, the best performances), and (ii) Ni anode and dimensionally stable anodes (DSAs), e.g., electrochemically active metal oxides deposited on an inert but

metallic substrate (typically titanium, Ti). Other authors also studied this reaction using Pb/PbO₂ anodes.^{197,198,253} NiSn20% alloy anodes²⁵⁴ and Ti/RuO₂–IrO₂ anodes²⁵¹ were also investigated. The main common issues are the deactivation and obtaining a complex mixture that is difficult to separate. Electron-transfer mediators of nitroaromatic oxidants improve the reaction rate of the cleavage of β -O-4 linkages. However, selectivity and yields are generally poor.

Significant advancements have been achieved in the direct electro-oxidation of lignin-derived molecules. For instance, the electrooxidation of guaiacol on a PbO₂/Nb electrode at 70 °C resulted in over 90% conversion in less than 1 h, albeit yielding various products, including catechol, methoxyhydroquinone, 3-methoxycatechol, formic acid, oxalic acid, maleic acid, and insoluble polymers.²⁵⁵ Polymerization of these products represents a common drawback in ECO. Interestingly, Zhou et al.²⁵⁶ recently introduced a Mn-doped cobalt oxyhydroxide catalyst that operates via a base-catalyzed mechanism for converting lignin derivatives into carboxylates. Remarkably high yields (80–99%) and operational stability (200 h) were reported. Furthermore, the conversion of guaiacol on Ti/Sb-SnO₂ and Ti/Pb₃O₄ anodes results in the formation of maleic acid as an intermediate, although complete degradation remains the predominant pathway.²⁰¹

In the applications above, the primary objective is to generate hydroxyl radicals on the anode surface efficiently. These radicals serve as potent oxidizing agents, facilitating the complete conversion of organics into CO₂. Conversely, for selective oxidation, the focus shifts toward the generation of specific oxygen species capable of selectively oxidizing organic molecules under conditions of ECO. However, there remains a notable absence of systematic studies and established design criteria for developing catalysts tailored to the specific target molecules.

Even though the active species for heterogeneous selective oxidation catalysts are well understood,²⁵⁷ these catalysts typically operate within distinct temperature ranges and often are not conductive. Consequently, there is a high need for the development of novel anodes tailored specifically for the selective electro-oxidation of organic molecules. Designed anodes must bridge the gap between the requirements for effective electrochemical activity and the demands for selective catalysis, enhancing efficiency and selectivity in organic molecule oxidation processes.

Tang et al.²⁴⁹ recently conducted a comprehensive review of various strategies, including photo-, electro-, and photo-electrocatalytic methods, employed for the selective oxidation of alcohols. While such reactions are significantly promising, several challenges persist, particularly in the field of lignin-derived molecules, often without clear elucidation. The selective oxidation of alcohol leads to the formation of the corresponding aldehyde as a primary byproduct. The presence of aldehyde, even in trace amounts, can trigger autocatalytic or organocatalytic oxidation processes.^{258,259} This behavior is enhanced in the presence of an anode, potentially leading to non-ideal electrocatalytic behavior.²⁶⁰ Consequently, achieving true electrocatalytic behavior becomes elusive, significantly limiting the scalability and reproducibility of results.

Moreover, in these contexts, the formation of polymeric species, such as humins, occurs, which are hard to detect (often not analyzed) and can also deactivate the electrocatalyst by fouling. While studies conducted under highly diluted conditions may mitigate some of these challenges, they become

increasingly pronounced when tests are performed using concentrated solutions for practical applications. Therefore, addressing these intrinsic issues is of crucial importance from a practical point of view. This necessitates a concerted effort toward developing appropriate methodologies and mitigating the negative effects of byproducts and polymeric species on electrocatalytic performance.

Li et al. recently explored anodic oxidation reactions aimed at valorizing the cathodic production of H₂.³³ While they extensively discussed alcohol oxidation reactions, particularly focusing on simple alcohols like methanol, ethanol, and isopropanol, as well as polyalcohols such as glycerol and 1,2-propanediol, they do not mention the issues above, often hidden in the literature. Furthermore, the extension of findings from studies on these simpler alcohols to more complex molecules derived from lignin is not straight. Several notable studies exemplify the conversion of various alcohols to valuable products: the conversion of (i) methanol to formate with very high FE over CoxP@NiCo-LDH/NF electrocatalyst,²⁶¹ (ii) ethanol to acetate on Pd-based electrocatalysts^{262,263} or to ethyl acetate on Co₃O₄ nanosheets,²⁶⁴ (iii) Rh nanosheets for isopropanol to acetone,²⁶⁵ (iv) 1,2-propanediol oxidation to corresponding lactate on Pt/C, or pyruvate on Au/C,²⁶⁶ and (v) Bi-doped Pt electrocatalysts for glycerol oxidation to glyceraldehyde and other products.²⁶⁷

These and other studies show the absence of clear emerging anodic electrocatalysts for the selective conversion of this even-restricted class of organics. In parallel, there are no valid design criteria for selecting anodic electrocatalysts and their mechanistic aspects, including the nature of the active surface oxygen species, to develop selective electro-oxidation catalysts.

4.3.2. Glucose and Furanic Compounds. The electro-oxidation of glucose and furanic compounds stands as another interesting area within the ECO research. Various electrocatalysts have been investigated for glucose oxidation, including Au–Pd- and Ag–Au-based catalysts,^{268,269} as well as Fe₂P-based electrocatalysts as studied by Du et al.²⁷⁰ While the primary target in glucose electro-oxidation is gluconic acid, the formation of secondary compounds such as gluconate, glucaric acid, and gluconolactone is also observed. Notably, bifunctional Co–Ni alloy electrocatalysts have demonstrated efficacy in this domain.²⁷¹ In parallel, furanic compounds, notably derived from biomass, have garnered significant attention, encompassing molecules such as furfural and 5-hydroxymethylfurfural.²⁷² These compounds, integral to the furan platform, have been studied extensively, particularly concerning tandem or paired anodic reactions aimed at valorizing biomass-derived molecules originating from cellulose.^{34,273,274} Various anodes have been explored in these investigations, including bifunctional Ni₂P/Ni/NF,²⁷⁵ Ni₃S₂/NF,²⁷⁶ and Ni₂P nanoparticles on nickel foam.²⁷⁷

4.4. Membranes. This section discusses aspects related to membranes only with reference to those relevant to coupling with the ECO anodic part.

4.4.1. PEM Electrolysis for Value-Added Oxidation Products. PEM electrolyzers are employed for hydrogen production from organic compound oxidation.²⁷⁸ This technology offers various advantages to the principles of green chemistry.²⁷⁹

Caravaca et al.²⁸⁰ first reported the direct lignin electrolysis on the PEM electrolyzer. Alkaline lignin solution with 10 g/L lignin and 1 M NaOH was continuously supplied to the anode, and anion-exchange membrane Fumapem FAA-3-50 was

utilized. Hydrogen was produced at around 0.45 V, lower than the conventional water electrolysis. Khalid et al.²⁸¹ prepared a three-dimensional (3D)-printed electrolysis cell that operates at room temperature. Aemion anion-exchange membrane was sandwiched between the commercial nickel foams (for both anode and cathode). 1.38 mL/min hydrogen production rate was achieved, which was 2.7 times higher than the water electrolysis at the chronoamperometry test.

Du et al.²⁸² used Nafion 115 for lignin depolymerization. Polyoxometalate (POM) or FeCl₃ served as charge transfer and also cleaved the complex lignin structure under mild reaction conditions. In a recent work of Umer et al., glucose, starch, lignin, and glucose were used in the H-type PEM cells equipped with Nafion 117. FeCl₃ (Lewis acid) was used to aid in the depolymerization and oxidation of biomass components during the hydrogen production.

4.5. Electrolytes. This section also discusses aspects only related to ECO from three aspects.

4.5.1. Aqueous Electrolyte. In general, biomass and its derivatives are insoluble in weakly acidic and weakly alkaline solutions, and strong alkaline solutions (such as NaOH and KOH) facilitate their dissolution. For this reason, they are widely used in electrocatalytic oxidation reactions.^{193,195–198} Wang et al.²⁸³ investigated the electrocatalytic oxidation of aspen lignin in 1 M NaOH solution. After 8 h of reaction, lignin was converted into valuable products such as 4-methylbenzyl ether, vanillin, and syringaldehyde. Chakthranon et al.²⁸⁴ pointed out that alkaline electrolytes are the most commonly used medium for the oxidation of furan compounds.

ECO is highly dependent upon the pH of the electrolyte, which is critical for the solubility of the reactants and final products. In the ECO of HMF to 2,5-furandicarboxylic acid (FDCA), one of the top ten value-added chemicals, due to the extremely low solubility of FDCA in water, an alkaline environment (0.1 M KOH solution) is required to convert carboxyl groups into water-soluble carboxylate ions, preventing the product from crystallizing on the electrode and causing permanent deactivation. Chakthranon et al.²⁸⁴ found that 0.33 M KOH is the optimal electrolyte concentration, which can completely dissolve the product and prevent it from crystallizing on the electrode.

The pH value of the electrolyte solutions largely determines the activity and product selectivity of ECO.^{285,286} Hauke et al.²⁸⁷ studied the ECO of HMF. They found that by changing the electrolyte solution from 0.1 M KOH (pH 13) to 1 M KOH (pH 14), the time for completing the electrocatalytic conversion of HMF to FDCA was greatly reduced. Suzuki et al.²⁸⁸ investigated the glycerol oxidation activity in the NaOH solution at different pH values and found that the catalytic activity increased with increasing the pH value. Liu et al.²⁴⁵ studied the effect of pH on the selectivity of glycerol oxidation, and they found that glycerol tended to convert into formate and dihydroxyacetone (DHA) in the electrolytes with low pH (pH 9). In contrast, it tended to form formate and glyceraldehyde (GLAD) at high pH (pH 13). Zhou et al.²⁵⁶ performed selectively upgrading lignin-derived secondary alcohols or ketones to carboxylates in an alkaline electrolyte solution using MnCoOOH/NF as the catalyst. In a nearly neutral electrolyte (pH 8.3), 1-phenylethanol was quantitatively converted to acetophenone. As the pH value increases (pH 13.9), high concentrations of hydroxide ions promote the

cleavage of the C–C bond, leading to a significant increase in the conversion rate and selectivity of benzoate esters.

Although low-cost alkaline solutions are desirable solvents for electrocatalytic oxidation, high concentrations of alkaline solutions may lead to electrode corrosion, and some metal catalysts cannot maintain long-term stability. In the study by Cai et al.,¹⁹⁷ the Pb/PbO₂ electrode showed the highest efficiency in electrocatalytic depolymerization of lignin in the 1 M NaOH solution. When the NaOH concentration exceeds 1 M, the oxide layer on the surface of Pb/PbO₂ will be destroyed. Moreover, the condensation of the produced lignin intermediates will aggravate when the alkali concentration increases to a certain value, which is not conducive to obtaining the target product. The study by Zirbes²⁵⁰ also observed that the maximum yield of vanillin by electrochemical depolymerization of lignin was achieved using 3 M NaOH, and concentrations up to 5 M resulted in a decrease in yield.

Kubota et al.¹⁸⁷ reported for the first time the ECO of HMF to FDCA using MnOx as a catalyst in a strongly acidic solution (H₂SO₄, pH 1). FDCA can spontaneously precipitate without the need to change the pH of the solution components or use other solutions to separate the product, providing references for the production of FDCA in acid media. In the study by Kubota et al.,²⁸⁹ a new electrochemical oxidation method was proposed to convert FF to maleic acid (MA) with a yield of 65.1% using PbO₂ in the same acidic solution, with 2-furanol as the reaction intermediate.

4.5.2. Organic Solvents. Organic solvents can increase the solubility of substrates, and the addition of organic solvents to the electrolyte solution facilitates electrocatalytic oxidation. Hasan et al.²⁹⁰ reported that the treatment of lignin by combining electro-oxidation and electro-reduction using THF–H₂SO₄ as an electrolyte can selectively break the β-O-4 bond of lignin, which can improve the selectivity of the aromatic products. Ma et al.²⁹¹ investigated the electrocatalytic oxidation of lignin model compounds in the *tert*-butylhydroxides solution (*t*-BuOOH in 70% water). The β-O-4 bonds were efficiently cleaved, and the aromatic aldehydes and phenols were obtained with high selectivity yields.

4.5.3. Ionic Liquids. Many studies have shown that ILs, as designable solvents, have good solubility for biomolecules, and electrocatalytic oxidation using ILs as reaction media has been developed.²⁹² Reichert et al.²⁹³ studied triethylamine methanesulfonate ([HNEt₃][MeSO₃]) for the electro-oxidation cleavage of lignin to obtain aromatic products. As a proton ionic liquid (PIL), [HNEt₃][MeSO₃] has good solubility for lignin and dissociable protons to provide proton donor and acceptor sites, as well as high ionic conductivity, leading to relatively low overpotential, superior solubility, and electrochemical stability compared to aqueous-phase electrolytes. Liu et al.²⁹⁴ used the PIL [BSO₃Hmim][OTf] with H₂O as the electrolyte to electrocatalytically oxidize four phenolic lignin model compounds to quinone. They also studied the effect of different ratios of IL to H₂O on the electrolysis reaction, and it showed the highest catalytic activity when the ratio of IL to water was 2:1. In comparison to pure IL, the IL–H₂O system is more conducive to the electrocatalytic degradation of the substrates. Later,²⁹⁵ the IL was mixed with MeCN (2:1, v/v) to perform the electrocatalytic depolymerization of lignin in a H-cell. The substrate was completely converted into monomers, such as phenols (80–99%) and acetophenone (75–96%). They also investigated the performance of 5 ILs ([py₁₃][NTf₂], ([N₁₁₁₃][NTf₂], [py₁₄][OTf], [EMIM][BF₄],

and [EMIM][OTf]), in which [EMIM][BF₄] and [EMIM][OTf] showed the highest conversion and yield rate, while [py₁₄][OTf] had the lowest conversion rate.

Zhu et al.²⁹⁶ reported that methyl-substituted aromatic compounds enable electrooxidation to the corresponding aldehydes in the aqueous imidazole ILs solutions ([BMIM][BF₄], [BMIM][HSO₄], [BMIM][O₃SCF₃], [BMIM][O₃SC₆H₄CH₃], [BMIM][OOCCH₃], and [EMIM][BF₄]). The electrooxidation process was sensitive to the electrolyte pH value, and the selectivity for aldehydes is 87–92% when the pH of the electrolyte is between about 2–6 with [EMIM][BF₄]. The aldehydes were further oxidized to the corresponding carboxylic acids in the most acidic IL ([BMIM][HSO₄], pH 0.6), and the process led preferentially to form *p*-methoxybenzyl alcohol in a slightly alkaline IL ([BMIM][OOCCH₃], pH 8.53). Moreover, ILs showed excellent electrochemical stability and can be recovered at least 35 times.

Recently, deep eutectic solvents (DESs) have also received increasing attention in the field of biomass oxidation to value-added products.²⁹⁷ DES contains both hydrogen bond donors (HBDs) and hydrogen bond acceptors (HBAs), and the excellent solubility of DES is attributed to their ability to form hydrogen bonds that can give and receive protons and electrons.²⁹⁸ DES exhibits similar characteristics to traditional ILs, while the preparation process is simple, and it is cost-effective and biodegradable.²⁹² Davide et al.²⁹⁹ prepared DESs of urea/choline chloride (urea–ChCl) and ethylene glycol/choline chloride (EtGly–ChCl) to dissolve and electrochemically oxidize lignin. In comparison to urea–ChCl and 1 M NaOH, EtGly–ChCl showed the highest solubility for lignin. When lignin was electrocatalytically depolymerized using EtGly–ChCl–H₂O (10% H₂O) as electrolyte, depolymerization products, such as guaiacol, vanillin, acetyl vanillinone, and eugenol, were obtained, and guaiacol and vanillin were the two most abundant compounds, with relative yields of 30–38% for guaiacol and 34–37% for vanillin.

5. PROCESSES AND REACTORS

5.1. Paired/Coupled Processes. Even though the initial studies on paired/coupled electrocatalytic processes focused mainly (for the anodic part) on the removal of organic contaminants in wastewater, recently, attention was given especially to the valorization of organic compounds,^{300–302} being a more valuable area. However, at the same time, it also creates more challenges in the design of the electrochemical reactors capable of increasing mass transfer and energy efficiency while optimizing at the same time the coupled electrocatalytic systems.

Paired electrolysis is a highly effective method for improving the generation of valuable chemicals at both the anode and cathode. In these systems, valuable products are generated at both electrodes using H⁺ and HO[−] as electron carriers, thus avoiding the necessity for additional supporting ions or redox couples. The majority of research on paired electrolysis has concentrated on combining gas production (such as water splitting) with hydrogen production alongside organic oxidation. Studies exploring the simultaneous transformation of two different organic substances within a single electrocatalytic device to yield two valuable products are notably scarce. By doing so, they first enhance the overall energy utilization efficiency. Second, coupled systems hold the potential to convert organic molecules into valuable products

simultaneously, e.g., process intensification. Finally, they can further facilitate the industrialization of electrocatalytic oxidation/reduction of different organic molecules.³⁰³ However, compared to simpler half-reactions, paired electrolysis introduces greater complexity and several significant challenges,³⁰⁴ including (1) ensuring that the reaction conditions are compatible for both the anode and cathode processes, (2) limitations on the types of reactions that can be conducted due to the compatibility of the reactants, products, electrolytes, and solvents involved, and (3) the need to develop methods for separating products that are both efficient and cost-effective.

5.1.1. HER. Noble-metal-based electrocatalysts coupled with HER have been utilized for the full oxidation of small alcohols to CO₂, ensuring total proton utilization. Even though this approach allows for the complete utilization of protons, partial oxidation is preferred to yield valuable products.³⁰⁵ The electrosynthesis of high-value-added 1,1-diethoxyethane (DEE) from ethanol was successfully made with high selectivity and efficiency by coupling it with hydrogen production. This was achieved through the utilization of an effective bifunctional catalyst based on PtIr nanowires.³⁰⁶

The electrocatalytic oxidation of polyhydric alcohols demands a more careful design of the electrocatalyst due to the risk of overoxidation, which can lead to the cleavage of the C–C bond. Additionally, the required cell voltage is significantly lower than that of conventional water splitting, typically below 1 V. By designing a NiMo nitride electrocatalyst, which decreased the cell voltage by approximately 260 mV compared to water splitting, effective glycerol oxidation was achieved, resulting in the anodic production of formate and the H₂ production at the cathode with high FEs, 95 and 99.7%, respectively.³⁰⁷ Analogously, the coupling of HER with HMF oxidation also facilitates the improvement of energy efficiency of the overall electrolysis, leading to a significant reduction of the cell voltage by 200 mV compared to conventional water splitting.

Zhao and his team have reported an interesting coupling by simultaneously performing the oxidation of HMF to 2,5-furandicarboxylic acid at the anode and HER at the cathode by utilizing double-layer hydroxides based on CoFe@NiFe as an electrocatalyst. The overall reaction achieves a current density of 38 mA cm⁻² at 1.40 V, leading to 100% selectivity to 2,5-furandicarboxylic acid and a nearly 100% FE, accompanied by high yields of hydrogen, reaching 901 μmol cm⁻².³⁰⁸ Furthermore, high yields of H₂ at the cathode and value-added products at the anode were reached in the HMF oxidation reaction over co-doped Ni₃S₂ electrocatalysts on the NF substrates. In this study, it was demonstrated how very high current densities can be achieved starting from a very low potential thanks to an optimized electrocatalyst based on Co_{0.4}NiS@NF.³⁰⁹

5.1.2. CO₂RR. Replacing OER at the anode with the electrocatalytic oxidation of biomass-derived molecules and coupling it with the carbon dioxide reduction reaction (CO₂RR) can significantly enhance the overall efficiency. Such integration can also enhance the sustainability and efficiency of chemical transformations, using CO₂ as a feedstock to generate value-added products. For instance, integrating CO₂ electroreduction with the conversion of biomass-derived intermediates can potentially yield a range of valuable chemicals and fuels, offering the dual benefit of mitigating CO₂ emissions while utilizing renewable biomass. This paired approach not only addresses environmental

concerns but also contributes to the circular economy by creating more efficient use of resources.

Nam et al.³¹⁰ reported an example of HMF-CO₂ coupled electrochemical system. In this system, nickel oxide nanoparticle catalysts based on 3D transition metal NPs NiO, Mn₃O₄, and Co₃O₄ were used. Operating at a current density of 2 mA cm⁻² for 3 h and a cell voltage of 2.5 V, the system achieved a 36% conversion of HMF at the anode and produced formic acid at the cathode with an 81% yield. These results highlight the potential for not only generating polymeric materials but also producing liquid fuels.

Instead, through the use of catalysts based on PdOx/ZIF-8 as cathode and PdO as anode, it was possible to obtain the simultaneous production of CO and organic acids from CO₂ and HMF, respectively.³¹¹ The favorable thermodynamics of HMF oxidation have also been utilized for electrocatalytic ammonia production using Ru(III) PEI@MWCNT catalysts. This approach achieved stable electrolysis over 27 h at a current density of 0.50 mA cm⁻², with the cell voltage decreasing from 1.56 to 1.34 V compared to OER.³¹² The examples discussed above illustrate successful attempts to enhance emerging electrocatalytic technologies by coupling them with the electrocatalytic oxidation of small bioderived molecules.

Liu et al.³¹³ pair the cathodic electrochemical CO₂ reduction with the anodic electrochemical 5-hydroxymethylfurfural oxidation to co-produce high-value chemicals efficiently while significantly reducing the energy requirements (Figure 4).

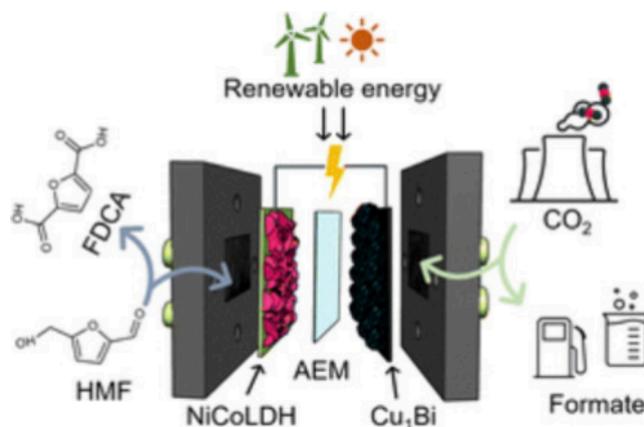


Figure 4. Paired cell: the cathodic electrochemical CO₂ reduction with the anodic electrochemical 5-hydroxymethylfurfural oxidation. This figure was reproduced with permissions from ref 313. Copyright 2023 Royal Society of Chemistry.

Utilizing single-atom Cu-doped Bi as the cathode catalyst and NiCo layer doubled hydroxides (NiCo LDH) as the anode catalyst, this system demonstrates exceptional functionality. Concurrently, the NiCo LDH anode achieves efficient electrooxidation of HMF to 2,5-furandicarboxylic acid with a faradaic efficiency exceeding 95% at low potential. This approach not only underscores the efficiency and cost-effectiveness of utilizing electrocatalytic processes for CO₂ reduction and biomass valorization but also demonstrates significant potential for reducing energy demand in chemical production.

However, utilizing raw biomass, such as lignin or its high molecular weight products, could be a highly attractive option for commercial-scale applications. Significant research efforts

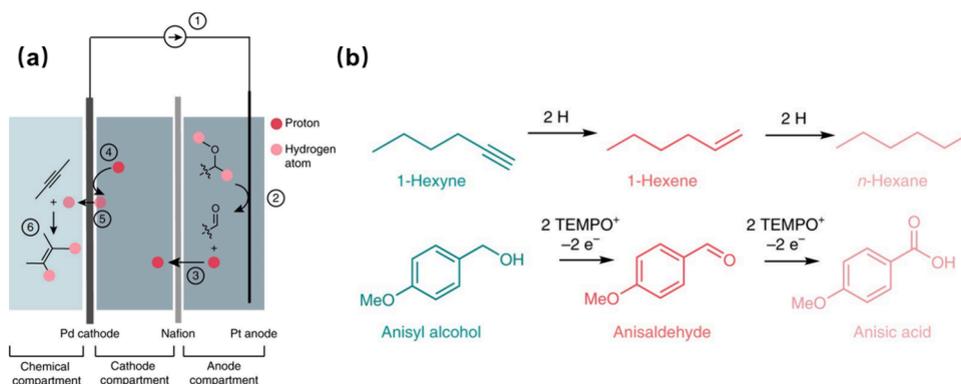


Figure 5. (a) Configuration of a triple-compartment cell for paired electrolysis is outlined as follows: (1) An electric current is directed through the palladium. (2) At the platinum anode, alcohol undergoes oxidation to form an aldehyde, facilitated by an electron-transfer mediator, while releasing protons. (3) These protons then traverse a Nafion proton-exchange membrane. (4) At the palladium foil cathode, the protons are converted into adsorbed hydrogen atoms. (5) These hydrogen atoms migrate through the palladium lattice to reach the other side of the foil. (6) Hydrogen atoms then add across an unsaturated bond, completing the hydrogenation process. (b) Paired reaction mechanisms. This figure was reproduced with permissions from ref 304. Copyright 2018 Springer Nature.

are required to design electrocatalysts capable of reducing the cell voltage compared to OER while also achieving high faradaic efficiency and product selectivity by employing feed streams of varying composition and purity.

5.1.3. Organic Components. The coupling of electrocatalytic oxidation and reduction reactions for lignin derivatives remains an area with limited literature. Liu et al.³¹⁴ demonstrate the possibility of synthesis of adipic acid from lignin-derived phenolic compounds via coupled electrolysis using bimetallic catalysts. They used an electrolyzer capable of controlling separately the pH in both anodic and cathodic compartments. In the cathode, phenol was hydrogenated into various ketone–alcohol compounds using a PtAu alloy catalyst, achieving yields of 92% with a FE of 43%. Simultaneously, in the anode, ketone–alcohols were oxidized to adipic acid using a CuCo_2O_4 -based catalyst, attaining yields of 85% and an FE of 84%. This study demonstrated that the approach of a two-electrode flow-bipolar membrane electrolyzer efficiently promotes the electrosynthesis of adipic acid from phenol. The process achieved a yield of 38.5% and a selectivity of 70.2%, operating at a cell voltage of just 2.1 V and achieving a current of 2.5 A. Moreover, the electrolyzer exhibited stable performance over 200 h at a constant current of 2.5 A, underscoring its potential for practical, long-term applications. This study not only demonstrates the feasibility of coupling oxidation and reduction reactions within a single electrolyzer but also paves the way for future advancements in the sustainable synthesis of valuable chemicals from lignin derivatives.

Wu et al.²⁰⁸ reported for the first time the simultaneous electrocatalytic reduction and oxidation of phenol to produce cyclohexanone and benzoquinone, respectively. Using nitrogen-doped hierarchically porous carbon-supported NiPt bimetallic nanoparticles as the cathode catalyst and FeRu bimetallic nanoparticles as the anode catalyst, they achieved selectivities higher than 99.9% for both cyclohexanone and benzoquinone. This coupled system demonstrated enhanced electrocatalytic performance, with an overall electron efficiency of 87.7%, surpassing conventional single-electrode electrocatalytic reduction or oxidation of phenol. The integrated system operated at a constant current density, optimizing the performance of the two half-cells. At controlled current densities of 7.5 mA/cm^2 , the selectivities for cyclohexanone

and benzoquinone consistently exceeded 99.9%, effectively preventing excessive reduction and oxidation of the desired products along 90 h of reaction. Additionally, conducting the two desired reactions simultaneously on separate electrodes reduced the electrical energy demand to less than half that of the half-cells operating independently. This efficiency is attributed to the electrons and protons needed for the cathodic reaction being supplied by the anodic reaction.

Sherbo et al.³⁰⁴ provide a compelling example with their work on paired electrolysis within an electrochemical cell (Figure 5). This innovative approach facilitates the simultaneous production of valuable chemicals, 4-methoxybenzyl alcohol to 4-methoxybenzaldehyde, with the concomitant formation of 1-hexene from 1-hexyne under ambient conditions using electricity. The reactions are efficiently separated and facilitated by a dense palladium membrane, which allows hydrogen atoms to permeate and hydrogenate 1-hexyne. Over 5 h, the system achieves quantitative conversion and maintains a high selectivity of $\geq 95\%$ for both products, showcasing the potential of electrosynthesis for efficient and waste-free chemical production.

Zhang et al.³¹⁵ present a notable example with their innovative use of paired electrosynthesis in an electrochemical cell (Figure 6). This approach harnesses water as both the source of oxygen and hydrogen to simultaneously produce valuable chemicals, converting 5-hydroxymethylfurfural to 2,5-furandicarboxylic acid and reducing *p*-nitrophenol to *p*-aminophenol under ambient conditions. The process is facilitated by the versatile NiB_x catalyst, which serves both as the anode and cathode, allowing for the efficient separation and conversion of substrates. The system allows hydrogen atoms to permeate through and hydrogenate the organic substrates, employing a dense palladium membrane. In 5 h experiments, the cell demonstrates an exceptional conversion efficiency, maintaining a high selectivity of $\geq 99\%$ for both reactions. This result exemplifies the capabilities of paired electrosynthesis for sustainable and zero-waste chemical production.

Zhang et al.¹⁴⁷ used 1 M KOH + 50 mM FF as both cathode and anode electrolytes to study electrocatalytic oxidation and hydrogenation of FF in a H-cell. The electrocatalytic hydrogenation product was furyl alcohol, and the oxidation

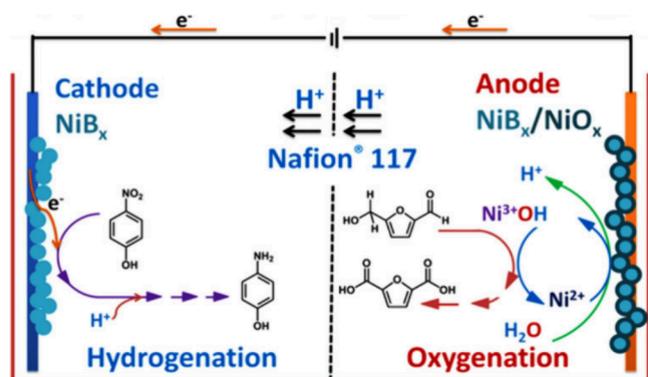


Figure 6. Paired electrolysis setup for converting *p*-nitrophenol to *p*-aminophenol and HMF to FDCA. This figure was reproduced with permissions from ref 315. Available under a CC BY-NC-ND 4.0 license (<https://creativecommons.org/licenses/by-nc-nd/4.0/>). Copyright 2019 Peili Zhang. Published by Wiley-VCH Verlag GmbH & Co. KGaA.

product was furylic acid with almost 100% selectivity, and the FE of FF conversion can reach 97–99%.

5.2. Reactors/Electrolyzers. **5.2.1. Types of Reactors/Electrolyzers.** Due to the different electrolyte conditions required for electrocatalytic hydrogenation and oxidation, they are typically made within a divided cell, which is separated by a membrane to control ion transport. The type of cell goes from more simple configurations, such as H-cells, to more realistic and industrial-relevant configurations, such as flow cells and zero-gap. However, often, the H-cell (the most used) does not provide reliable information for the other types of cells, including in terms of electrocatalyst selection, because the factors controlling the behavior are different.³¹⁶

The most commonly used device in the laboratory is the H-cell, which is conveniently used to explore the effect of various factors on the reaction, but there are limitations in the current densities, resulting in low overall product conversion. Using a flow cell can reduce the distance between the counter electrode and the working electrode, decreasing the reaction resistance and thus improving the mass transfer of the reactants. The zero-gap electrolyzer retains the excellent properties of the flow cell with high mass transfer efficiency and can avoid the use of liquid electrolytes.³¹⁷

In recent years, electrocatalytic palladium membrane reactors (ePMRs) have played an important role in the field of electrocatalytic hydrogenation and oxidation. ePMRs have the outstanding advantage of allowing good control of reaction conditions, such as freeing solvent selection in the hydrogenation chamber from the limitations of proton solvents, thus achieving higher substrate solubility while alleviating problems such as low FE and complex product separations.¹⁵⁷ Han et al.³¹⁸ reported for the first time a four-compartment device hydrogenation strategy using ePMR. This pioneering electrocatalytic double hydrogenation method utilizes water and formaldehyde as the hydrogen source, which allows the simultaneous hydrogenation and oxidation of the same organic substrate on both sides of the electrolytic cell. This approach not only saves voltage input but also achieves a theoretical maximum FE of 200%. In the work of Stankovic et al.,³¹⁹ 0.1 M FF in *tert*-butanol (*t*-BuOH) was used as the hydrogenation chamber electrolyte, 1 M H₂SO₄ solution was the anode electrolyte, and FF was converted to 2-methyltetrahydrofuran (MTHF) by electrocatalytic hydrogenation with high

selectivity of 76% using a Pd membrane reactor. In contrast, the selectivity dropped to below 35% when using a H-cell. In their preceding study,³²⁰ it was found that *t*-BuOH could inhibit byproduct formation and improve product selectivity, but it was inapplicable to the conventional H-cell.

5.2.2. PEM Electrolysis for LOHC Hydrogenation.

5.2.2.1. Benzene. The coupling benzene hydrogenation and water electrolysis in PEM electrolyzers was first studied by Itoh et al.³²¹ They proposed that the positive voltage from the benzene hydrogenation (0.17 V) would decrease the external voltage requirement from 1.23 V of water electrolysis to a lower value.¹³ Nafion 117 was roughened by sandpaper prior to soaking it in a Pt precursor solution. Then, the sample was reduced by treating with NaBH₄. Afterward, Rh coating was applied in the same way to realize a Rh–Pt electrode. Both water and benzene were humidified and fed with carrier gases prior to being fed to a finite-gap cell operating at 25–70 °C.

5.2.2.2. Toluene. Direct toluene hydrogenation toward methylcyclohexane was proposed in 2015 by Mitsushima et al.,³²² where the toluene hydrogenation voltage was 0.15 V. Different from the work of Itoh et al.,³²¹ toluene was fed to the electrolyzer without dilution. Nafion 212 membrane was selected as PEM, and a zero-gap electrolyzer cell was utilized. For this configuration, the performance of PtRu/C was found to be higher than Pt/C, where toluene is hydrogenated without HER up to 450 mA cm⁻² at 2 V cell voltage.

Takano et al.³²³ used a similar electrolysis setup. Given that the PEM cells usually do not include a reference electrode, the Pt/C catalyst on the anode can be implemented as a pseudoreference electrode. Subsequently, the catalysts of Pt/C, Rh/C, Ru/C, and PtRu/C were tested. It was hypothesized that better performance of PtRu/C catalyst could be due to dual functions such as the high catalytic activity of the rich adsorbed hydrogen on Pt and the strong toluene adsorption by Ru. Matsuoka et al.³²² used a high surface active area (25 cm²) membrane electrode assemblies. By recirculating the cathode stream, the toluene concentration was decreased from 100 to 7.6% with PtRu/C catalyst. Other Pt alloy catalysts (Pt₃M, M = Rh, Au, Pd, Ir, Cu, and Ni) were investigated by Imada et al.³²⁴ and Pt₃Rh/C performed better than commercial Pt/C.

Non-platinum catalysts were investigated by Inami et al.³²⁵ in a finite-gap system with Nafion 117 membrane. Within Ru, Rh, Pd, Ir, and Au supported on Ketjenblack (KB), Ru/KB showed superior performance at low loadings. The synergy between Ru and Ir in alloy catalyst was further explained by the same group,³²⁶ as well as the effect of different carbon supports.³²⁷ A spontaneous deposition method was also applied by the same group for the selective deposition of Ir on Ru nanoparticles, allowing for control over the surface structure.³²⁸

5.2.2.3. Mass Transport. Rate-limiting factors of direct toluene hydrogenation were investigated in a PEM system containing a reversible hydrogen electrode. Polarization properties showed that the mass transfer for the cathode and the electron transfer process for the anode were crucial.¹⁵⁹

In the work on optimization of the flow channel of the electrolyzer, superior performance of porous carbon (with no flow field) was reported. In comparison to parallel, interdigit, and serpentine channels, porous carbon performed better due to enhanced toluene transport and minimized charge transfer resistance, leading to higher efficiency and lower voltage requirements.³²⁹

Nagasawa et al.³³⁰ investigated the effect of PtRu/C catalyst loading on mass transfer. Thicker catalyst layers limited the mass transfer, whereas thin layers had an insufficient amount of catalyst. The optimum loading was found to be 1.4–1.6 mg cm⁻².

During direct methylcyclohexane (MCH), water is dragged from the anode to the cathode due to electro-osmosis phenomena. Shigemasa et al.³³¹ visualized this phenomenon with a transparent cell, showing the porous transport layer (PTL) at the cathode. In the following work of Reyna-Pena,³³² hydrogen bubbles inside the PTL were observed using X-ray computed tomography. Rib-channel and flat flow field plates (FFP) were compared. The rib-channel configuration was beneficial for reduced pressure drop and easy bubble removal even though hydrogen bubbles were trapped under the ribs. However, current efficiency was lower considering the higher distance of toluene feed to the catalyst layer. Flat FFPs, on the other hand, lower the distance to active sites, which can improve the toluene conversion.

5.2.2.4. Combining Electro- and Heterogeneous (Thermal) Catalysis. Nagasawa et al.³³³ made use of H₂ bubbles to further increase the conversion by doping PTLs with Pt catalyst. This technology, called “direct MCH”, is implemented by ENEOS, Chiyoda, and QUT.

5.2.2.5. Polycyclic Hydrocarbons. Polycyclic aromatic hydrogenation on PEM flow cells was studied by Tsyganok et al.¹⁸¹ Reactions were performed in an electrochemical reactor configured with a Nafion 324 membrane. Sulfur-resistant tungsten disulfide (WS₂) on glassy carbon electrodes and Raney nickel cathodes were studied. The reactants were dissolved in a solution of ionic liquids butyl-3-methylimidazolium tetrafluoroborate (BMIM·BF₄) and hexafluorophosphate (BMIM·PF₆) and water, which served to provide high solubility, high conductivity, and protons for the electrochemical hydrogenation process. Current efficiency values and conversions were found to be insufficient.

6. CHALLENGES AND PERSPECTIVES

Even though intensive research has been conducted from the components (catalysts, electrolytes, and membranes), to the processes and reactors, there are still challenges to be addressed, and more work needs to be carried out to improve the performance. As the core, catalysts play an essential role in both ECH and ECO, and their challenges and perspectives were primarily discussed in this section.

6.1. Challenges and Perspectives of Electrocatalysts for ECH.

6.1.1. Stability and Durability of Catalysts. One of the major challenges in ECH is the stability and durability of catalysts. Many catalysts, especially those based on transition metals and their compounds, can deactivate due to several factors: poisoning, surface oxidation, and structural degradation under harsh reaction conditions.

The support plays a crucial role in the stability of ECH electrocatalysts. This objective can be achieved by increasing the specific surface area, tuning the electronic structure, and optimizing adsorption behavior through surface functionalization.^{334,335} Another strategy is to introduce stabilizers or dopant elements into the catalyst structure to enhance resistance to degradation, thereby maintaining the catalyst's stable performance over a long period.^{175,336}

6.1.2. Selectivity Issues. Selectivity is another key challenge in ECH, especially when dealing with complex organic molecules. It is essential to attain high selectivity for the

target product while minimizing side reactions to achieve an efficient and economically viable process. The reaction selectivity in ECH largely depends upon the adsorption energies of the reactants, hydrogen atoms, and products. Therefore, the selectivity of ECH reactions is greatly influenced by the surface properties and electronic structure of the catalyst, which can be tuned by modifying the electrocatalyst.

To improve selectivity, researchers have focused on tailoring the electronic and geometric structure of catalysts. This goal can be achieved through alloying, doping, or the design of nanostructured catalysts with specific active sites that favor certain reaction pathways.^{106,116,337} Additionally, modifying reaction conditions, such as temperature, pressure, and solvent choice, can also help to enhance selectivity by influencing the reaction kinetics and the adsorption behavior of reactants on the catalyst surface.¹¹³

6.1.3. Scale-Up Challenges. While significant progress has been made in the development of catalysts for ECH at the laboratory scale, scaling up these processes for industrial applications presents numerous challenges. One of the primary difficulties is maintaining the activity, selectivity, and stability of catalysts when transitioning from small-scale experiments to large-scale production. The performance of a catalyst can be significantly affected by changes in reactor design, feedstock purity, and process conditions.

Moreover, the synthesis and processing of catalysts on a large scale can introduce additional challenges. For instance, the reproducibility of nanostructured catalysts, which often exhibit excellent performance at the lab scale, can be difficult to achieve when produced in bulk quantities. Additionally, the cost and availability of catalyst materials can become limiting factors as the demand increases for large-scale applications.

6.1.4. Recent Advances and Innovations. Despite the challenges, recent advances in catalyst design and fabrication have shown promise in addressing some of the limitations associated with ECH. The development of hybrid and composite catalysts, which combine the advantages of different materials, has led to improvements in both catalytic activity and stability. Furthermore, the exploration of novel catalytic materials, such as metal-organic frameworks (MOFs)^{120,338} and single-atom catalysts,^{339–341} has opened up new avenues for enhancing selectivity and durability in ECH. These materials offer unique structural features and active sites that can be precisely tuned to target specific reactions, making them highly attractive for future development in electrocatalysis.

6.1.5. Advances in In Situ Characterization Techniques. *In situ* characterization allows for real-time observation of changes in catalyst structure and morphology, as well as the formation of reaction intermediates, revealing transient reaction mechanisms. *In situ* X-ray absorption near edge structure (XANES) can identify changes in catalyst sites during the ECH process. Wang et al.³⁴² used an *in situ* XANES electrochemical cell to reveal the promotion of competitive adsorption of acetylene relative to hydrogen on optimized Cu particle catalysts (Figure 7).

In situ Fourier transform infrared spectroscopy (FTIR) can be used to identify adsorbed species and observe the formation of reaction intermediates on the catalyst surface during the ECH process. Zhou et al. successfully tuned the electronic properties of PtNi nanoparticles through B-doping and utilized *in situ* FTIR to track the ECH of guaiacol on the catalyst.³⁴³

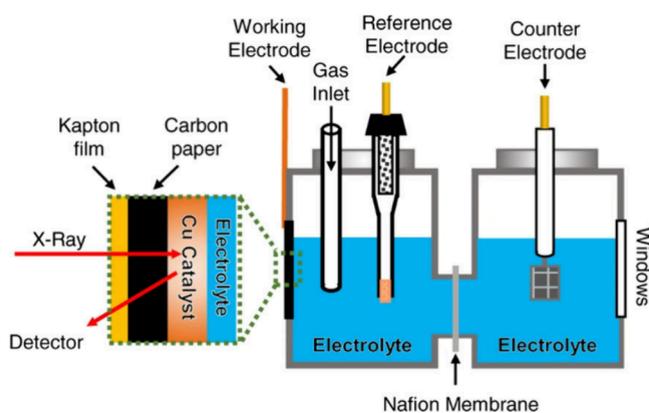


Figure 7. Schematic illustration of an *in situ* XANES electrolytic cell. This figure was reproduced with permission from ref 342. Available under a CC-BY 4.0 license (<http://creativecommons.org/licenses/by/4.0/>). Copyright 2021 Suheng Wang.

6.1.6. Potential Directions for Research. As the field of ECH continues to evolve, several promising research directions are emerging that could significantly enhance the efficiency, selectivity, and sustainability of this technology. One critical area of focus is the design and development of new catalyst materials that are both highly active and durable. The exploration of earth-abundant and non-toxic materials is essential to make ECH more economically viable and environmentally friendly. For example, further studies on transition-metal-based catalysts, such as iron, cobalt, and nickel, could yield catalysts with improved performance while reducing reliance on rare and expensive noble metals.

Another promising direction is the use of advanced computational methods and machine learning to predict and optimize catalyst performance.¹³⁰ By integrating theoretical modeling with experimental data, researchers can accelerate the discovery of novel catalyst compositions and structures with tailored properties for specific reactions. This approach not only shortens the development cycle but also provides deeper insights into the underlying mechanisms of ECH.

6.1.7. Emerging Trends and Technologies. The development of advanced catalysts is at the heart of the evolving field of ECH. Several emerging trends and technologies are focused on creating more efficient, durable, and scalable catalysts that can meet the demands of industrial applications.

6.1.7.1. Single-Atom Catalysts (SACs). One of the most promising trends is the development of SACs. These catalysts consist of individual metal atoms dispersed on a support material, offering maximum atom utilization and unique active sites. SACs are gaining attention due to their ability to catalyze specific reactions precisely and with high efficiency and selectivity. In the ECH processes, SACs have shown the potential to improve reaction rates while minimizing the use of expensive metals, making them an attractive option for both academic research and industrial applications. Their application extends to selectively hydrogenating complex organic molecules, which is a significant challenge in traditional catalysis.

6.1.7.2. Metal–Organic Frameworks (MOFs). MOFs represent another cutting-edge technology in catalyst development. They are highly porous materials composed of metal ions coordinated to organic ligands, creating a flexible and tunable structure. These materials can be designed to feature specific active sites and pore sizes, which can accommodate

reactants and promote selective hydrogenation reactions. The versatility of MOFs makes them ideal candidates for ECH, where their structural properties can be optimized for different reaction environments. Moreover, MOFs (or the materials obtained from their pyrolysis) can support other active catalytic species, enhancing their stability and reusability in continuous processes.

6.1.7.3. Doped and Functionalized Carbon Materials. Doping carbon materials with heteroatoms (such as nitrogen, sulfur, or boron) or functionalizing their surfaces with various groups is another promising strategy. These modifications can significantly alter the electronic properties of carbon catalysts, enhancing their interaction with reactants and improving catalytic performance. For instance, nitrogen-doped graphene has shown enhanced catalytic activity in hydrogenation reactions, attributed to the altered electron distribution and increased active sites. These doped carbon materials are not only cost-effective but also offer a sustainable alternative to traditional metal catalysts, especially in applications requiring large-scale production.

6.1.7.4. In Situ Characterization and Real-Time Monitoring. Advancements in *in situ* characterization techniques, such as *in situ* FTIR and X-ray absorption spectroscopy, are providing deeper insights into catalyst behavior during ECH. These techniques allow for real-time monitoring of reaction intermediates and catalyst surface changes, enabling researchers to fine-tune catalyst design and reaction conditions for optimal performance. The integration of these analytical tools into industrial systems could lead to more efficient and adaptive ECH processes, ensuring consistent quality and performance across large-scale applications.

6.2. Challenges and Perspectives of Electrocatalysts for ECO.

6.2.1. Challenges. Despite these advancements, a leading anode remains elusive in both glucose and furanic compound electro-oxidation. Moreover, the studies are more challenging due to the irreproducibility of some reported results, hindering progress and the development of effective anodes for the ECO applications. Despite extensive research on ECO, there is a notable absence of specific studies dedicated to the electro-oxidation of lignin-derived molecules, and the support of current studies regarding mechanistic insights is minimal. On the basis of the above, the design of the anodes for ECO of lignin-derived molecules requires a great effort from the scientific community. Although, as reported at the beginning of this paragraph, the literature is limited to the total electrocatalytic oxidation of organic molecules even structurally similar to lignin derivatives, such as phenols, studies on the modification of the used electrocatalysts as well as on the modulation of the reaction conditions could represent a starting point for the development of anodes.

6.2.2. Perspectives. To realize efficient electrocatalysts, it is important to improve the intrinsic catalytic activity of active sites and maximize the active site availability. Adjusting the electronic structure of catalyst active sites via heterojunction construction, facilitating electronic transfer between the active site and substrate, introducing heteroatomic doping, and creating vacancies make it possible to improve the catalytic activity. Through these strategies, a better adsorption/desorption process between the reagents and the electrocatalysts could be achieved by improving the overall thermodynamic efficiency of the reaction. Another critical factor is to maximize the number of active sites, which is important for electrooxidation processes including multi-

electronic organic substances. The use of a 3D structure can lead to major exposure of active sites, enhancing catalytic performance.⁷³

6.2.3. Two Special Electrocatalysts. The electrocatalytic behavior of two different classes of electrocatalysts employed in the complete oxidation of phenols, based on TiO₂ nanostructures and boron-doped diamond (BDD) structures, deserves to be analyzed to guide the design of anodes for the selective oxidation of lignin-derived molecules. Different electrochemical systems based on TiO₂ have been used in the last decades for the degradation of phenols due to their high catalytic activity, chemical stability, and durability.^{344–346} The use of such anodes leads to a decrease in the consumption of power for oxygen formation due to the high oxygen evolution potential on TiO₂.³⁴⁷ Anodes based on titanium-supported coating of noble metal oxides induce a pathway of phenol oxidation that leads to the formation of quinone-like species, followed by further oxidation to organic acids favored at low potential and high phenol concentration. However, this last condition can induce the polymerization of these compounds.³⁴⁸ Jin et al. highlight the importance of 3D space in TiO₂/activated carbon fibers (ACF) and TiO₂/ACF–graphite anodes to increase the contact area between phenol and electrode.³⁴⁹ The high capability to adsorb hydroxyl radicals induced by the presence of TiO₂ nanostructures compared to ACF–graphite anodes leads, besides CO₂, also a set of aromatic intermediates, such as hydroquinone, pyrocatechol, and benzoquinone, which can undergo a further hydroxylic radicals attack to form maleic acid and formic acid. The observed behavior suggests that the limitation of the adsorption capacity, for example, on a two-dimensional (2D) TiO₂ structure, which provides only restricted adsorption sites,³⁴⁷ could prevent the complete mineralization of the aromatic intermediates formed, favoring the partial oxidation products. Moreover, the chemical doping of TiO₂ 2D nanostructures could affect the nature of the generated active surface oxygen species.

Boron-doped diamond thin film electrode (BDD), due to the wide potential windows in aqueous and non-aqueous solutions, good stability and corrosion resistivity have also been widely employed for the complete electrochemical oxidation of phenols in acidic media.³⁵⁰ The high local concentration of hydroxyl radicals on the BDD surface leads to the total oxidation of phenol to CO₂ operating at high current density and low phenol concentration. Also, in this case, the partial oxidation of phenol to other aromatics compounds, e.g., benzoquinone, hydroquinone, and catechol, is observed at low current density and high phenol concentration. Thus, the local concentration of oxygen species represents a key parameter, which can be controlled through a chemical modification of the electrocatalyst as well as the operating conditions, e.g., applied potential and the concentration of oxidizable species.³⁴⁹

6.3. Challenges and Perspectives from Other Aspects.
6.3.1. Electrolytes. For an ideal electrolyte, it must first have excellent conductivity to effectively shuttle charges between electrodes, so as to promote the electrocatalytic reaction. In addition, the electrolyte needs to have high solubility to effectively dissolve the organic substrate and improve the high dispersion of reactants, thereby improving the reaction rate and ensuring a more efficient catalytic process. Also, the electrolyte needs to be stable in the electrocatalytic process and cannot react unnecessarily with

reactants or products to avoid product pollution. It is also necessary to consider the environmental friendliness of electrolytes and avoid the use of toxic substances to minimize the impact on the environment. The recycling of electrolytes is another concern to reduce costs. All these requirements make it challenging to develop advanced catholytes. Even though ILs/DESs have been proposed as promising electrolytes, their relatively high cost, the limited studies on their environmental impact, as well as their recycling are essential concerns, which need further investigation. Also, in general, adjusting the electrolytes to improve the performance was always studied together with the specific catalysts, and how to clarify the role and contribution of electrolytes themselves is worthy of study. Also, for anolytes, high concentrations can exacerbate the oxidation process, leading to significant carbon loss and reduced selectivity of the target product. As a result, most studies were conducted with low electrolyte concentrations to achieve high product selectivity. However, industrial production demands high product concentrations, which is beneficial for reducing the cost of product separation. Therefore, it is essential to select a suitable electrolyte to improve the FE and the selectivity of the target product, which is crucial for the industrial application of electrocatalytic oxidation of biomass molecules.

6.3.2. Others. From the aspect of electrocatalytic regeneration of LOHC by hydrogenation, the main challenges are to improve the process performance and achieve a long-term stable operation. Also, producing renewable LOHC is another concern. Concerning the membrane, the long-term durability of ion-exchange membranes under operational conditions is still mostly untested, particularly for applications with organic molecules. Increased crossover of reactants and byproducts over time can diminish overall system efficiency. Finally, for the overall device, similar to its components of catalysts and novel electrolytes, there are challenges in scaling up, such as the optimization of electrolyzer design, energy management, and cost control, calling for long-term research and development.

7. CONCLUSION

This review summarizes the research progress related to this new concept of electrocatalytic production of liquid organic hydrogen carriers with anodic valorization of the process. At the same time, it presents the challenges and opportunities, but also the complexity of the many aspects to be taken into account. The review also offers clues to open new directions in the highly active area of electrocatalytic technologies for the low-carbon production of fuels and chemicals.

Specifically, the electrocatalytic processes, including the reaction processes of hydrogenation and oxidation and the main components of electrocatalysts for cathodes and anodes, membranes, and electrolyte solutions, are briefly introduced. Subsequently, the electrocatalytic hydrogenation of liquid organic hydrogen carriers and electrocatalytic anodic oxidation are analyzed with respect to advances in terms of the single components: catalysts, membranes, and electrolyte solutions. Then, aspects related to the reactor and processes, as well as system integration and intensification, are commented together with the paired processes and reactors. Finally, the challenges and prospects are highlighted to show how this direction represents one of the crucial technologies for the future, even the many issues still to be solved. We hope, however, that this review, which derives from the joint contributions of the

various researchers in the frame of the EU project EPOCH (grant 101070976), provides a firm foundation for developing the framework of electrocatalytic production of liquid organic hydrogen carrier with anodic valorization of the process, promoting the development and application of green hydrogen.

AUTHOR INFORMATION

Corresponding Authors

Xiaoyan Ji – Energy Engineering, Division of Energy Science, Luleå University of Technology, 97187 Luleå, Sweden; orcid.org/0000-0002-0200-9960; Email: xiaoyan.ji@ltu.se

Gabriele Centi – Department of Chemical, Biological, Pharmaceutical and Analytical Sciences (ChiBioFarAm), University of Messina, 98166 Messina, Italy; Email: gabriele.centi@unime.it

Authors

Jiaqi Wang – Department of Chemical and Metallurgical Engineering, School of Chemical Engineering, Aalto University, 00076 Aalto, Finland

Yongdan Li – Department of Chemical and Metallurgical Engineering, School of Chemical Engineering, Aalto University, 00076 Aalto, Finland; orcid.org/0000-0002-0430-9879

Christin Hummel – Hydrogenious LOHC Technologies, 91058 Erlangen, Germany

Guo Huang – Energy Engineering, Division of Energy Science, Luleå University of Technology, 97187 Luleå, Sweden

Ezgi Demiröz – Department of Chemical Engineering, Delft University of Technology, 2629 HZ Delft, Netherlands; orcid.org/0000-0001-6788-2990

Atsushi Urakawa – Department of Chemical Engineering, Delft University of Technology, 2629 HZ Delft, Netherlands; orcid.org/0000-0001-7778-4008

Siyuan Huang – Department of Chemistry and Catalysis Research Center, Technical University of Munich, 85748 Garching, Germany

Ruixue Zhao – Department of Chemistry and Catalysis Research Center, Technical University of Munich, 85748 Garching, Germany

Johannes Lercher – Department of Chemistry and Catalysis Research Center, Technical University of Munich, 85748 Garching, Germany; orcid.org/0000-0002-2495-1404

Paola Lanzafame – Department of Chemical, Biological, Pharmaceutical and Analytical Sciences (ChiBioFarAm), University of Messina, 98166 Messina, Italy

Georgia Papanikolaou – Department of Chemical, Biological, Pharmaceutical and Analytical Sciences (ChiBioFarAm), University of Messina, 98166 Messina, Italy

Complete contact information is available at:

<https://pubs.acs.org/10.1021/acs.energyfuels.4c04644>

Author Contributions

All authors contributed equally, and the order is based on the alphabet of their affiliations.

Notes

The authors declare no competing financial interest.

Biographies

Jiaqi Wang is a doctoral researcher in the School of Chemical Engineering at Aalto University under the supervision of Prof.

Yongdan Li. His research focuses on the electrochemical reaction (oxidation and hydrogenation) of organic molecules and flexible energy storage and conversion devices.

Yongdan Li was awarded his Ph.D. degree from Tianjin University and is currently a tenured professor at Aalto University. He has long worked as an educator and practitioner in industrial catalysis. His research focuses on catalytic reactors and processes for energy conversion, with active projects in photocatalytic water splitting, lignin depolymerization, solid oxide fuel cells with non-hydrogen fuels, direct carbon fuel cells, and selective catalytic reduction of NO_x with ammonia and hydrogen.

Christin Hummel has a strong background in R&D chemistry and catalysis. She works as a technology manager at Hydrogenious LOHC Technologies since 2021. Prior to that, she worked as an R&D chemist for redox flow batteries at CMBlu Energy AG. As Ph.D. researcher at the Leibniz Institute for Catalysis, she developed catalysts for production of lignin-based biofuels and obtained her doctorate in 2018. She completed her diploma (equivalent to M.Sc.) in chemistry at the Friedrich Schiller University Jena, Germany.

Guo Huang is a Ph.D. student at Xiaoyan Ji's Group in Lulea University of Technology. Her research focuses on the lignin derivatives dissolution and electrocatalytic conversion with ionic liquids. She obtained a master's degree in materials science and engineering from Guangxi University in 2023 and obtained a bachelor's degree in functional materials from Henan Normal University in 2020.

Xiaoyan Ji is a professor of energy science at Lulea University of Technology. She created a "ionic liquids for energy applications" research team, where CO₂ capture/separation, CO₂ electrochemical conversion, advanced electrolytes for batteries, and lignin conversion coupling H₂ production via electrochemical process are the focus. She obtained her Ph.D. degree in chemical engineering in 2000. She has over 25 years of research and development experience in the fields of chemical engineering and energy engineering.

Ezgi Demiröz is a Ph.D. student in Urakawa's group. Her research focuses on the development of zero-gap PEM electrolyzers for the hydrogenation of liquid organic hydrogen carriers. She previously obtained her M.Sc. degree in chemical and biological engineering from Koç University. Earlier, she earned her B.Sc. degree in chemical engineering from Gazi University, during which she completed an Erasmus internship at TU Eindhoven.

Atsushi Urakawa is a full professor of catalysis engineering at TU Delft. After completing his Ph.D. degree in 2006 at ETH Zurich, he worked there as a senior scientist and lecturer. He joined ICIQ (Spain) as a group leader in 2010, before returning to TU Delft in 2019. His research focuses on a multidisciplinary approach based on material science, reaction engineering, and *in situ/operando* methodologies to gain solid comprehension of the active sites and the transformation pathways.

Siyuan Huang earned his master's degree in physics from the Southern University of Science and Technology in 2022. Subsequently, he joined the Technical University of Munich as a doctoral candidate, focusing on electrocatalytic hydrogenation of biomass materials.

Ruixue Zhao is a researcher at the Technical University of Munich specializing in catalytic transformations. Her work focuses on multifunctional catalysis for alkane activation, sorption, and transport in porous materials, biomass conversion, and hydrogenation processes for clean energy production.

Johannes Lercher is a professor at the Technical University of Munich, specializing in heterogeneous catalysis. His research focuses on acid–base catalysis, hydrocarbon activation, and the development of catalytic processes for sustainable energy conversion and chemical production.

Paola Lanzafame is an associate professor in industrial chemistry at the University of Messina. Since 2002, she has been involved in various national and international projects, also coordinating the related research activities. She contributed to the EU IDECAT Network of Excellence. Her recent activity is focused on the development of new nanostructured catalytic materials for the photoelectrocatalytic conversion of CO₂ into high-value-added fuels and chemicals. She is the author of 60 publications (*h*-index of 22) and over 90 conference presentations.

Georgia Papanikolaou is a researcher in industrial chemistry at the University of Messina since 2019. She has participated in numerous national and international projects. The main scientific interests concern the fields of the heterogeneous catalysis and the development of novel materials. Her recent scientific activity is centered on the development of novel nanostructured electrodes for the electrocatalytic valorization of CO₂ and biomass derivatives. She is the author of 36 publications (*h*-index of 16).

Gabriele Centi is a full professor of industrial chemistry at the University of Messina, Italy, and president of the European Research Institute of Catalysis and the International Association of Catalysis Societies. He coordinates an ERC Synergy project on plasma catalysis and is a board member of SUNERGY. He has been honored with the Humboldt Research Award and by the Chinese Academy of Sciences. He has over 600 publications, 12 books, an *h*-index of 92, and 35 000 citations.

ACKNOWLEDGMENTS

All authors acknowledge the financial support from Horizon-EIC, Pathfinder Challenges (Grant 101070976).

NOMENCLATURE

BCN = boron–nitrogen co-doped carbon
 BDD = boron-doped diamond
 CAL = cinnamaldehyde
 CNT = carbon nanotube
 CO₂RR = carbon dioxide reduction reaction
 DER = direct electro-reduction
 DES = deep eutectic solvent
 ePMR = electrocatalytic palladium membrane reactor
 ECH = electrocatalytic hydrogenation
 ECO = electrocatalytic oxidation
 EHDC = electrochemical hydrodechlorination
 EPOCH = electrocatalytic production of liquid organic hydrogen carrier and chemicals from lignin (EU project)
 FDCA = 2,5-furandicarboxylic acid
 FE = faradaic efficiency
 FF = furfural
 HER = hydrogen evolution reaction
 HMF = 5-hydroxymethylfurfural
 IL = ionic liquid
 LDH = layered double hydroxide
 LOHC = liquid organic hydrogen carrier
 MCH = methylcyclohexane
 MOF = metal–organic framework
 OER = oxygen evolution reaction
 PBI = polybenzimidazole

PCET = proton-coupled electron transfer
 PFSA = perfluorosulfonic acid
 PIL = proton ionic liquid
 PTL = porous transport layer
 RHE = reference hydrogen electrode
 SAC = single-atom catalyst
 SAP = sulfonated aromatic polymer
 TOF = turnover frequency
 XANES = X-ray absorption near edge structure

REFERENCES

- (1) Centi, G.; Perathoner, S. Status and Gaps toward Fossil-Free Sustainable Chemical Production. *Green Chem.* **2022**, *24* (19), 7305–7331.
- (2) International Energy Agency (IEA). *Global Hydrogen Review 2023*; IEA: Paris, France, 2023; <https://www.iea.org/reports/global-hydrogen-review-2023>.
- (3) Sherif, S. A.; Goswami, D. Y.; Stefanakos, E. K.; Steinfeld, A. *Handbook of Hydrogen Energy*; CRC Press: Boca Raton, FL, 2014.
- (4) European Innovation Council (EIC). *Challenge Guide Novel Routes to Green Hydrogen Production—Part I*; EIC: Brussels, Belgium, 2021; <https://eic.ec.europa.eu/eic-funding-opportunities/calls-proposals/eic-pathfinder-challenge-novel-routes-green-hydrogen-production>.
- (5) Laurikko, J.; Ihonen, J.; Kiviaho, J.; Himanen, O.; Weiss, R.; Saarinen, V.; Kärki, J.; Hurskainen, M. *National Hydrogen Roadmap for Finland*; TEKES: Helsinki, Finland, 2020.
- (6) Martin, A.; Agnoletti, M.-F.; Brangier, E. Users in the Design of Hydrogen Energy Systems: A Systematic Review. *Int. J. Hydrogen Energy* **2020**, *45* (21), 11889–11900.
- (7) Centi, G.; Perathoner, S. Rethinking Chemical Production with “Green” Hydrogen. *Pure Appl. Chem.* **2024**, *96* (4), 471–477.
- (8) Panigrahi, P. K.; Chandu, B.; Motapothula, M. R.; Puvvada, N. Potential Benefits, Challenges and Perspectives of Various Methods and Materials Used for Hydrogen Storage. *Energy Fuels* **2024**, *38* (4), 2630–2653.
- (9) Geiling, J.; Wagner, L.; Auer, F.; Ortner, F.; Nuß, A.; Seyfried, R.; Stammberger, F.; Steinberger, M.; Bösmann, A.; Öchsner, R.; et al. Operational Experience with a Liquid Organic Hydrogen Carrier (LOHC) System for Bidirectional Storage of Electrical Energy over 725 H. *J. Energy Storage* **2023**, *72*, 108478.
- (10) Perreault, P.; Van Hoecke, L.; Pourfallah, H.; Kummamuru, N. B.; Boruntea, C.-R.; Preuster, P. Critical Challenges Towards the Commercial Rollouts of a LOHC-Based H₂ Economy. *Curr. Opin. Electrochem.* **2023**, *41*, 100836.
- (11) Chu, C.; Wu, K.; Luo, B.; Cao, Q.; Zhang, H. Hydrogen Storage by Liquid Organic Hydrogen Carriers: Catalyst, Renewable Carrier, and Technology - a Review. *Carbon Resour. Convers.* **2023**, *6* (4), 334–351.
- (12) Lebedeva, O.; Kultin, D.; Kalenchuk, A.; Kustov, L. Advances and Prospects in Electrocatalytic Hydrogenation of Aromatic Hydrocarbons for Synthesis of “Loaded” Liquid Organic Hydrogen Carriers. *Curr. Opin. Electrochem.* **2023**, *38*, 101207.
- (13) Li, J.; Xie, W.; Zhou, H.; Li, Z.; Shao, M. Techno-Economic Analysis of Electrochemical Hydrogen Production Coupled with Alternative Oxidation. *Chem. Eng. Sci.* **2024**, *298*, 120322.
- (14) EPOCH. *Epoch Project Website*; EPOCH: Luleå, Sweden, 2024; <https://eic-epoch.eu/>.
- (15) Wu, J.; Xie, P.; Hao, W.; Lu, D.; Qi, Y.; Mi, Y. Ionic Liquids as Electrolytes in Aluminum Electrolysis. *Front. Chem.* **2022**, *10*, 1014893.
- (16) Zeng, Y.; Zhao, M.; Zeng, H.; Jiang, Q.; Ming, F.; Xi, K.; Wang, Z.; Liang, H. Recent Progress in Advanced Catalysts for Electrocatalytic Hydrogenation of Organics in Aqueous Conditions. *eScience* **2023**, *3* (5), 100156.
- (17) Ayers, K. The Potential of Proton Exchange Membrane-Based Electrolysis Technology. *Curr. Opin. Electrochem.* **2019**, *18*, 9–15.

- (18) D'Ambra, F.; Gébel, G. Literature Review: State-of-the-Art Hydrogen Storage Technologies and Liquid Organic Hydrogen Carrier (LOHC) Development. *Sci. Technol. Energy Transition* **2023**, *78*, 32.
- (19) Valentini, F.; Marrocchi, A.; Vaccaro, L. Liquid Organic Hydrogen Carriers (LOHCs) as H-Source for Bio-Derived Fuels and Additives Production. *Adv. Energy Mater.* **2022**, *12* (13), 2103362.
- (20) Rao, P. C.; Yoon, M. Potential Liquid-Organic Hydrogen Carrier (LOHC) Systems: A Review on Recent Progress. *Energies* **2020**, *13* (22), 6040.
- (21) Clematis, D.; Bellotti, D.; Rivarolo, M.; Magistri, L.; Barbucci, A. Hydrogen Carriers: Scientific Limits and Challenges for the Supply Chain, and Key Factors for Techno-Economic Analysis. *Energies* **2023**, *16* (16), 6035.
- (22) Sisáková, K.; Podrojková, N.; Oriňáková, R.; Oriňák, A. Novel Catalysts for Dibenzyltoluene as a Potential Liquid Organic Hydrogen Carrier Use—A Mini-review. *Energy Fuels* **2021**, *35* (9), 7608–7623.
- (23) Li, Y.; Guo, X.; Zhang, S.; He, Y. A Perspective Review on N-Heterocycles as Liquid Organic Hydrogen Carriers and Their Hydrogenation/Dehydrogenation Catalysts. *Energy Fuels* **2024**, *38* (14), 12447–12471.
- (24) Centi, G.; Perathoner, S. Catalysis for an Electrified Chemical Production. *Catal. Today* **2023**, *423*, 113935.
- (25) Papanikolaou, G.; Centi, G.; Perathoner, S.; Lanzafame, P. Catalysis for *e*-Chemistry: Need and Gaps for a Future De-Fossilized Chemical Production, with Focus on the Role of Complex (Direct) Syntheses by Electrocatalysis. *ACS Catal.* **2022**, *12* (5), 2861–2876.
- (26) Perathoner, S.; Centi, G. Catalysis for Solar-Driven Chemistry: The Role of Electrocatalysis. *Catal. Today* **2019**, *330*, 157–170.
- (27) Guo, M.; Lu, X.; Xiong, J.; Zhang, R.; Li, X.; Qiao, Y.; Ji, N.; Yu, Z. Alloy-Driven Efficient Electrocatalytic Oxidation of Biomass-Derived 5-Hydroxymethylfurfural towards 2,5-Furandicarboxylic Acid: A Review. *ChemSusChem* **2022**, *15* (17), No. e202201074.
- (28) Chen, Z.; Han, N.; Zheng, R.; Ren, Z.; Wei, W.; Ni, B.-J. Design of Earth-Abundant Amorphous Transition Metal-Based Catalysts for Electrooxidation of Small Molecules: Advances and Perspectives. *SusMat* **2023**, *3* (3), 290–319.
- (29) Meng, Z.; Zheng, S.; Luo, R.; Tang, H.; Wang, R.; Zhang, R.; Tian, T.; Tang, H. Transition Metal Nitrides for Electrocatalytic Application: Progress and Rational Design. *Nanomaterials* **2022**, *12* (15), 2660.
- (30) Guo, B.; Huo, H.; Zhuang, Q.; Ren, X.; Wen, X.; Yang, B.; Huang, X.; Chang, Q.; Li, S. Iron Oxyhydroxide: Structure and Applications in Electrocatalytic Oxygen Evolution Reaction. *Adv. Funct. Mater.* **2023**, *33* (25), 2300557.
- (31) Cui, M.; Hu, T.; Chen, L.; Li, P.; Gong, Y.; Wu, Z.; Wang, S. Recent Progress in Graphdiyne for Electrocatalytic Reactions. *ChemElectroChem* **2020**, *7* (24), 4843–4852.
- (32) Feng, Q.; Yuan, X. Z.; Liu, G.; Wei, B.; Zhang, Z.; Li, H.; Wang, H. A Review of Proton Exchange Membrane Water Electrolysis on Degradation Mechanisms and Mitigation Strategies. *J. Power Sources* **2017**, *366*, 33–55.
- (33) Li, R.; Xiang, K.; Peng, Z.; Zou, Y.; Wang, S. Recent Advances on Electrolysis for Simultaneous Generation of Valuable Chemicals at Both Anode and Cathode. *Adv. Energy Mater.* **2021**, *11* (46), 2102292.
- (34) Liu, H.; Li, W. Recent Advances in Paired Electrolysis of Biomass-Derived Compounds Toward cogeneration of Value-Added Chemicals and Fuels. *Curr. Opin. Electrochem.* **2021**, *30*, 100795.
- (35) Xu, Z.; Peng, C.; Zheng, G. Coupling Value-Added Anodic Reactions with Electrocatalytic CO₂ Reduction. *Chem. - Eur. J.* **2023**, *29* (11), 202203147.
- (36) Chen, Y.; Fu, Y.; Peng, W.; Wang, S. Minireview of Coupled Electrochemical Hydrogen Production and Organic-Oxidation for Low Energy Consumption. *Energy Fuels* **2023**, *37* (23), 17915–17931.
- (37) Bard, A. J.; Faulkner, L. R. *Electrochemical Methods: Fundamentals and Applications*, 2nd ed.; John Wiley: Hoboken, NJ, 2000.
- (38) Lessard, J. Electrocatalytic Hydrogenation. In *Organic Electrochemistry*, 5th ed.; Hammerich, O., Speiser, B. Eds.; CRC Press: Boca Raton, FL, 2015; pp 1658–1664.
- (39) Yang, J.; Qin, H.; Yan, K.; Cheng, X.; Wen, J. Advances in Electrochemical Hydrogenation since 2010. *Adv. Synth. Catal.* **2021**, *363* (24), 5407–5416.
- (40) Villalba, M. A.; Koper, M. T. M. Selective Electrocatalytic Hydrogenation of A,B-Unsaturated Ketone on (111)-Oriented Pd and Pt Electrodes. *Electrochim. Acta* **2022**, *417*, 140264.
- (41) Panizza, M.; Cerisola, G. Direct and Mediated Anodic Oxidation of Organic Pollutants. *Chem. Rev.* **2009**, *109* (12), 6541–6569.
- (42) Sun, J.; Lu, H.; Lin, H.; Du, L.; Huang, W.; Li, H.; Cui, T. Electrochemical Oxidation of Aqueous Phenol at Low Concentration Using Ti/BDD Electrode. *Sep. Purif. Technol.* **2012**, *88*, 116–120.
- (43) Cai, J.; Zhou, M.; Liu, Y.; Savall, A.; Groenen Serrano, K. Indirect Electrochemical Oxidation of 2,4-Dichlorophenoxyacetic Acid Using Electrochemically-Generated Persulfate. *Chemosphere* **2018**, *204*, 163–169.
- (44) May, A. S.; Biddinger, E. J. Strategies to Control Electrochemical Hydrogenation and Hydrogenolysis of Furfural and Minimize Undesired Side Reactions. *ACS Catal.* **2020**, *10* (5), 3212–3221.
- (45) Zheng, M.; Zhang, J.; Wang, P.; Jin, H.; Zheng, Y.; Qiao, S.-Z. Recent Advances in Electrocatalytic Hydrogenation Reactions on Copper-Based Catalysts. *Adv. Mater.* **2024**, *36* (14), 2307913.
- (46) Zhou, X.; Yu, X.; You, B.; Jing, Y. Progress and Perspectives on Electrocatalytic Transmembrane Hydrogenation. *J. Mater. Chem. A* **2024**, *12* (32), 20527–20541.
- (47) Zhang, L. J.; Rao, T. U.; Wang, J. Y.; Ren, D. Z.; Sirisommoonchai, S.; Choi, C.; Machida, H.; Huo, Z. B.; Norinaga, K. A Review of Thermal Catalytic and Electrochemical Hydrogenation Approaches for Converting Biomass-Derived Compounds to High-Value Chemicals and Fuels. *Fuel Process. Technol.* **2022**, *226*, 107097.
- (48) Sanyal, U.; Lopez-Ruiz, J.; Padmaperuma, A. B.; Holladay, J.; Gutiérrez, O. Y. Electrocatalytic Hydrogenation of Oxygenated Compounds in Aqueous Phase. *Org. Process Res. Dev.* **2018**, *22* (12), 1590–1598.
- (49) Lu, X. K.; Wang, J.; Peng, W. C.; Li, N.; Liang, L.; Cheng, Z. J.; Yan, B. B.; Yang, G. X.; Chen, G. Y. Electrocatalytic Hydrogenation of Phenol by Active Sites on Pt-Decorated Shrimp Shell Biochar Catalysts: Performance and Internal Mechanism. *Fuel* **2023**, *331*, 125845.
- (50) Kong, A. Q.; Liu, M. H.; Zhang, H. J.; Cao, Z. F.; Zhang, J. L.; Li, W.; Han, Y.; Fu, Y. Highly Selective Electrocatalytic Hydrogenation of Benzoic Acid over Pt/C Catalyst Supported on Carbon Fiber. *Chem. Eng. J.* **2022**, *445*, 136719.
- (51) Nogami, S.; Shida, N.; Iguchi, S.; Nagasawa, K.; Inoue, H.; Yamanaka, I.; Mitsushima, S.; Atobe, M. Mechanistic Insights into the Electrocatalytic Hydrogenation of Alkynes on Pt-Pd Electrocatalysts in a Proton-Exchange Membrane Reactor. *ACS Catal.* **2022**, *12* (9), 5430–5440.
- (52) Aboukhatir, A.; Abu Haija, M.; Banat, F.; Othman, I.; Sabri, M. A.; Govindan, B. Ni_(1-x)Pd_x Alloyed Nanostructures for Electrocatalytic Conversion of Furfural into Fuels. *Catalysts* **2023**, *13* (2), 260.
- (53) Ji, K. Y.; Xu, M.; Xu, S.-M.; Wang, Y.; Ge, R. X.; Hu, X. Y.; Sun, X. M.; Duan, H. H. Electrocatalytic Hydrogenation of 5-Hydroxymethylfurfural Promoted by a Ru₁Cu Single-Atom Alloy Catalyst. *Angew. Chem., Int. Ed.* **2022**, *61* (37), 202209849.
- (54) Li, Z.; Garedew, M.; Lam, C. H.; Jackson, J. E.; Miller, D. J.; Saffron, C. M. Mild Electrocatalytic Hydrogenation and Hydrodeoxygenation of Bio-Oil Derived Phenolic Compounds Using Ruthenium Supported on Activated Carbon Cloth. *Green Chem.* **2012**, *14* (9), 2540–2549.
- (55) Zhou, P.; Guo, S.-X.; Li, L. B.; Ueda, T.; Nishiwaki, Y.; Huang, L.; Zhang, Z. H.; Zhang, J. Selective Electrochemical Hydrogenation of Phenol with Earth-abundant Ni–MoO₂ Heterostructured Cata-

- lysts: Effect of Oxygen Vacancy on Product Selectivity. *Angew. Chem., Int. Ed.* **2023**, *62* (8), 202214881.
- (56) Zheng, M.; Zhang, J. Y.; Wang, P. T.; Jin, H. Y.; Zheng, Y.; Qiao, S.-Z. Recent Advances in Electrocatalytic Hydrogenation Reactions on Copper-Based Catalysts. *Adv. Mater.* **2024**, *36* (14), 2307913.
- (57) Yang, Z. H.; Chou, X. Y.; Kan, H. Y.; Xiao, Z. H.; Ding, Y. Nanoporous Copper Catalysts for the Fluidized Electrocatalytic Hydrogenation of Furfural to Furfuryl Alcohol. *ACS Sustainable Chem. & Eng.* **2022**, *10* (22), 7418–7425.
- (58) Akinola, J.; Barth, I.; Goldsmith, B. R.; Singh, N. Electrocatalytic Hydrogenation of Phenol on Platinum-Cobalt Alloys. *J. Catal.* **2024**, *430*, 115331.
- (59) Fu, M. C.; Shang, R.; Huang, Z.; Fu, Y. Conversion of Levulinate Ester and Formic Acid into γ -Valerolactone Using a Homogeneous Iron Catalyst. *Synlett* **2014**, *25* (19), 2748–2752.
- (60) Li, L.; Wang, X.; Fu, N. Electrochemical Nickel-Catalyzed Hydrogenation. *Angew. Chem., Int. Ed.* **2024**, *63* (22), 202403475.
- (61) Dixit, R. J.; Bhattacharyya, K.; Ramani, V. K.; Basu, S. Electrocatalytic Hydrogenation of Furfural Using Non-Noble-Metal Electrocatalysts in Alkaline Medium. *Green Chem.* **2021**, *23* (11), 4201–4212.
- (62) Guo, S.; Wu, Y.; Wang, C.; Gao, Y.; Li, M.; Zhang, B.; Liu, C. Electrocatalytic Hydrogenation of Quinolines with Water over a Fluorine-Modified Cobalt Catalyst. *Nat. Commun.* **2022**, *13* (1), 5297.
- (63) Sahoo, B.; Kreyenschulte, C.; Agostini, G.; Lund, H.; Bachmann, S.; Scalone, M.; Junge, K.; Beller, M. A Robust Iron Catalyst for the Selective Hydrogenation of Substituted (Iso)-Quinolones. *Chem. Sci.* **2018**, *9* (42), 8134–8141.
- (64) Jayan, K.; Thadathil, D. A.; Varghese, A. Electrochemical Hydrogenation of Organic Compounds: A Sustainable Approach. *Asian J. Org. Chem.* **2023**, *12* (10), 202300309.
- (65) Qin, Y.; Lu, J.; Zou, Z.; Hong, H.; Li, Y.; Li, Y.; Chen, L.; Hu, J.; Huang, Y. Metal-Free Chemoselective Hydrogenation of Unsaturated Carbon-Carbon Bonds Via Cathodic Reduction. *Org. Chem. Front.* **2020**, *7* (14), 1817–1822.
- (66) Thakur, A. K.; Kurtyka, K.; Majumder, M.; Yang, X.; Ta, H. Q.; Bachmatiuk, A.; Liu, L.; Trzebicka, B.; Rummeli, M. H. Recent Advances in Boron- and Nitrogen-Doped Carbon-Based Materials and Their Various Applications. *Adv. Mater. Interfaces* **2022**, *9* (11), 2101964.
- (67) Bhunia, K.; Chandra, M.; Kumar Sharma, S.; Pradhan, D.; Kim, S.-J. A Critical Review on Transition Metal Phosphide Based Catalyst for Electrochemical Hydrogen Evolution Reaction: Gibbs Free Energy, Composition, Stability, and True Identity of Active Site. *Coord. Chem. Rev.* **2023**, *478*, 214956.
- (68) Cai, P.; Fan, H. X.; Cao, S.; Qi, J.; Zhang, S. M.; Li, G. Electrochemical conversion of corn stover lignin to biomass-based chemicals between Cu/Ni-Mo-Co cathode and Pb/PbO₂ anode in alkali solution. *Electrochim. Acta* **2018**, *264*, 128–139.
- (69) Lan, C. X.; Fan, H. X.; Shang, Y. Y.; Shen, D. Y.; Li, G. Electrochemically catalyzed conversion of cornstalk lignin to aromatic compounds: an integrated process of anodic oxidation of a Pb/PbO₂ electrode and hydrogenation of a nickel cathode in sodium hydroxide solution. *Sustain Energy Fuels* **2020**, *4* (4), 1828–1836.
- (70) Tolba, R.; Tian, M.; Wen, J. L.; Jiang, Z. H.; Chen, A. C. Electrochemical Oxidation of Lignin at IrO₂-Based Oxide Electrodes. *J. Electroanal. Chem.* **2010**, *649* (1–2), 9–15.
- (71) Jia, Y. Q.; Wen, Y. Q.; Han, X.; Qi, J.; Liu, Z. H.; Zhang, S. M.; Li, G. Electrocatalytic degradation of rice straw lignin in alkaline solution through oxidation on a Ti/SnO₂-SbO₃/PbO₂-PbO₂ anode and reduction on an iron or tin doped titanium cathode. *Catal. Sci. Technol.* **2018**, *8* (18), 4665–4677.
- (72) Jiang, S.; Zhang, M. Y.; Xu, C.; Liu, G. Z.; Zhang, K. F.; Zhang, Z. Y.; Peng, H. Q.; Liu, B.; Zhang, W. J. Recent Developments in Nickel-Based Layered Double Hydroxides for Photo(-)/Electrocatalytic Water Oxidation. *ACS Nano* **2024**, *18* (26), 16413–16449.
- (73) Wu, X.; Wang, Y.; Wu, Z.-S. Design Principle of Electrocatalysts for the Electrooxidation of Organics. *Chem.* **2022**, *8* (10), 2594–2629.
- (74) Caglar, A.; Aktas, N.; Kivrak, H. Photocatalytic Glucose Electrooxidation of Titanium Dioxide Doped Cdte Enhanced for a Photocatalytic Fuel Cell. *Fuel* **2022**, *330*, 125653.
- (75) Tanos, F.; Razzouk, A.; Lesage, G.; Cretin, M.; Bechelany, M. A Comprehensive Review on Modification of Titanium Dioxide-Based Catalysts in Advanced Oxidation Processes for Water Treatment. *ChemSusChem* **2024**, *17* (6), 202301139.
- (76) Karim, A. V.; Nidheesh, P. V.; Oturan, M. A. Boron-Doped Diamond Electrodes for the Mineralization of Organic Pollutants in the Real Wastewater. *Curr. Opin. Electrochem.* **2021**, *30*, 100855.
- (77) Mavrikis, S.; Göltz, M.; Rosiwal, S.; Wang, L.; Ponce de León, C. Boron-Doped Diamond Electrocatalyst for Enhanced Anodic H₂O₂ Production. *ACS Appl. Energy Mater.* **2020**, *3* (4), 3169–3173.
- (78) Khomein, P.; Ketelaars, W.; Lap, T.; Liu, G. Sulfonated Aromatic Polymer as a Future Proton Exchange Membrane: A Review of Sulfonation and Crosslinking Methods. *Renewable Sustainable Energy Rev.* **2021**, *137*, 110471.
- (79) Yuzer, B.; Aydın, M. I.; Ozaktac, D.; Demir, M. E.; Bicer, Y. Ion-Exchange Membranes in Electrolysis Process. In *Current Trends and Future Developments on (Bio-)Membranes*; Basile, A., Ghasemzadeh, K., Eds.; Elsevier: Amsterdam, Netherlands, 2024; Chapter 9, pp 265–298.
- (80) Liu, H. Z.; Lee, T. H.; Chen, Y. F.; Cochran, E. W.; Li, W. Z. Paired and Tandem Electrochemical Conversion of 5-(Hydroxymethyl) Furfural Using Membrane-Electrode Assembly-Based Electrolytic Systems. *ChemElectroChem.* **2021**, *8* (15), 2817–2824.
- (81) Pärnamäe, R.; Mareev, S.; Nikonenko, V.; Melnikov, S.; Sheldeshov, N.; Zabolotskii, V.; Hamelers, H. V. M.; Tedesco, M. Bipolar Membranes: A Review on Principles, Latest Developments, and Applications. *J. Membr. Sci.* **2021**, *617*, 118538.
- (82) Lu, X.; Tu, W.; Zhou, Y.; Zou, Z. Effects of Electrolyte Ionic Species on Electrocatalytic Reactions: Advances, Challenges, and Perspectives. *Adv. Energy Mater.* **2023**, *13* (27), 2300628.
- (83) Mukesh, C.; Huang, G.; Qin, H.; Liu, Y.; Ji, X. Insight into Lignin Oxidative Depolymerization in Ionic Liquids and Deep Eutectic Solvents. *Biomass Bioenergy* **2024**, *188*, 107305.
- (84) D'Ambra, F.; Gébel, G. Literature review: State-of-the-art Hydrogen Storage Technologies and Liquid Organic Hydrogen Carrier (LOHC) Development. *Sci. Technol. Energy Transition* **2023**, *78*, 32.
- (85) Kwak, Y.; Kirk, J.; Moon, S.; Ohm, T.; Lee, Y.-J.; Jang, M.; Park, L.-H.; Ahn, C.-i.; Jeong, H.; Sohn, H.; et al. Hydrogen Production from Homocyclic Liquid Organic Hydrogen Carriers (LOHC): Benchmarking Studies and Energy-Economic Analyses. *Energy Convers. Manage.* **2021**, *239*, 114124.
- (86) Dürr, S.; Müller, M.; Jorschick, H.; Helmin, M.; Bösmann, A.; Palkovits, R.; Wasserscheid, P. Carbon Dioxide-Free Hydrogen Production with Integrated Hydrogen Separation and Storage. *ChemSusChem* **2017**, *10* (1), 42–47.
- (87) Jorschick, H.; Preuster, P.; Bösmann, A.; Wasserscheid, P. Hydrogenation of Aromatic and Heteroaromatic Compounds - a Key Process for Future Logistics of Green Hydrogen Using Liquid Organic Hydrogen Carrier Systems. *Sustain Energy Fuels* **2021**, *5* (5), 1311–1346.
- (88) Rüde, T.; Dürr, S.; Preuster, P.; Wolf, M.; Wasserscheid, P. Benzyltoluene/Perhydro Benzyltoluene - Pushing the Performance Limits of Pure Hydrocarbon Liquid Organic Hydrogen Carrier (LOHC) Systems. *Sustain Energy Fuels* **2022**, *6* (6), 1541–1553.
- (89) Wulf, C.; Zapp, P. Assessment of System Variations for Hydrogen Transport by Liquid Organic Hydrogen Carriers. *Int. J. Hydrogen Energy* **2018**, *43* (26), 11884–11895.
- (90) Li, H.; Zhang, X.; Zhang, C.; Ding, Z.; Jin, X. Application and Analysis of Liquid Organic Hydrogen Carrier (LOHC) Technology in Practical Projects. *Energies* **2024**, *17* (8), 1940.

- (91) Modisha, P.; Bessarabov, D. Stress Tolerance Assessment of Dibenzyltoluene-Based Liquid Organic Hydrogen Carriers. *Sustain Energy Fuels* **2020**, *4* (9), 4662–4670.
- (92) Acharya, D.; Ng, D.; Xie, Z. Recent Advances in Catalysts and Membranes for Mch Dehydrogenation: A Mini Review. *Membranes* **2021**, *11* (12), 955.
- (93) Deischter, J.; Schute, K.; Neves, D. S.; Ebert, B. E.; Blank, L. M.; Palkovits, R. Aromatisation of Bio-Derivable Isobutyraldehyde over H₂m-5 Zeolite Catalysts. *Green Chem.* **2019**, *21* (7), 1710–1717.
- (94) Lonchay, W.; Bagnato, G.; Sanna, A. Highly Selective Hydroxypropylation of Lignin Waste to Benzene, Toluene and Xylene in Presence of Zirconia Supported Iron Catalyst. *Bioresour. Technol.* **2022**, *361*, 127727.
- (95) Vispute, T. P.; Zhang, H.; Sanna, A.; Xiao, R.; Huber, G. W. Renewable Chemical Commodity Feedstocks from Integrated Catalytic Processing of Pyrolysis Oils. *Science* **2010**, *330* (6008), 1222–1227.
- (96) Bartlett, J.; Krupnick, A. Investment Tax Credits for Hydrogen Storage. *Resources Magazine*; Resources for the Future: Washington, D.C., 2020.
- (97) Mortensen, P. M.; Grunwaldt, J. D.; Jensen, P. A.; Knudsen, K. G.; Jensen, A. D. A Review of Catalytic Upgrading of Bio-Oil to Engine Fuels. *Appl. Catal., A* **2011**, *407* (1), 1–19.
- (98) Yang, Z.; Chou, X.; Kan, H.; Xiao, Z.; Ding, Y. Nanoporous Copper Catalysts for the Fluidized Electrocatalytic Hydrogenation of Furfural to Furfuryl Alcohol. *ACS Sustainable Chem. Eng.* **2022**, *10* (22), 7418–7425.
- (99) Liu, L.; Liu, H.; Huang, W.; He, Y.; Zhang, W.; Wang, C.; Lin, H. Mechanism and Kinetics of the Electrocatalytic Hydrogenation of Furfural to Furfuryl Alcohol. *J. Electroanal. Chem.* **2017**, *804*, 248–253.
- (100) Puthiaraj, P.; Kim, K.; Ahn, W.-S. Catalytic Transfer Hydrogenation of Bio-based Furfural by Palladium Supported on Nitrogen-Doped Porous Carbon. *Catal. Today* **2019**, *324*, 49–58.
- (101) Alibegovic, K.; Morgan, D. G.; Losovj, Y.; Pink, M.; Stein, B. D.; Kuchkina, N. V.; Serkova, E. S.; Salnikova, K. E.; Shifrina, Z. B.; Matveeva, V. G.; et al. Efficient Furfuryl Alcohol Synthesis from Furfural over Magnetically Recoverable Catalysts: Does the Catalyst Stabilizing Medium Matter? *ChemSelect* **2017**, *2* (20), 5485–5491.
- (102) Scholz, D.; Aellig, C.; Hermans, I. Catalytic Transfer Hydrogenation/Hydrogenolysis for Reductive Upgrading of Furfural and 5-(Hydroxymethyl)furfural. *ChemSusChem* **2014**, *7* (1), 268–275.
- (103) Nguyen-Huy, C.; Kim, J. S.; Yoon, S.; Yang, E.; Kwak, J. H.; Lee, M. S.; An, K. Supported Pd Nanoparticle Catalysts with High Activities and Selectivities in Liquid-Phase Furfural Hydrogenation. *Fuel* **2018**, *226*, 607–617.
- (104) Lopez-Ruiz, J. A.; Andrews, E.; Akhade, S. A.; Lee, M.-S.; Koh, K.; Sanyal, U.; Yuk, S. F.; Karkamkar, A. J.; Derewinski, M. A.; Holladay, J.; et al. Understanding the Role of Metal and Molecular Structure on the Electrocatalytic Hydrogenation of Oxygenated Organic Compounds. *ACS Catal.* **2019**, *9* (11), 9964–9972.
- (105) Kuo, D.-Y.; Paik, H.; Kloppenburg, J.; Faeth, B.; Shen, K. M.; Schlom, D. G.; Hautier, G.; Suntivich, J. Measurements of Oxygen Electroadsorption Energies and Oxygen Evolution Reaction on RuO₂ (110): A Discussion of the Sabatier Principle and Its Role in Electrocatalysis. *J. Am. Chem. Soc.* **2018**, *140* (50), 17597–17605.
- (106) Bondue, C. J.; Calle-Vallejo, F.; Figueiredo, M. C.; Koper, M. T. M. Structural Principles to Steer the Selectivity of the Electrocatalytic Reduction of Aliphatic Ketones on Platinum. *Nat. Catal.* **2019**, *2* (3), 243–250.
- (107) Song, Y.; Gutiérrez, O. Y.; Herranz, J.; Lercher, J. A. Aqueous Phase Electrocatalysis and Thermal Catalysis for the Hydrogenation of Phenol at Mild Conditions. *Appl. Catal. B: Env.* **2016**, *182*, 236–246.
- (108) Nogami, S.; Shida, N.; Iguchi, S.; Nagasawa, K.; Inoue, H.; Yamanaka, I.; Mitsushima, S.; Atobe, M. Mechanistic Insights into the Electrocatalytic Hydrogenation of Alkynes on Pt-Pd Electrocatalysts in a Proton-Exchange Membrane Reactor. *ACS Catal.* **2022**, *12* (9), 5430–5440.
- (109) Chen, H.; Peng, T.; Liang, B.; Zhang, D.; Lian, G.; Yang, C.; Zhang, Y.; Zhao, W. Efficient Electrocatalytic Hydrogenation of Cinnamaldehyde to Value-Added Chemicals. *Green Chem.* **2022**, *24* (9), 3655–3661.
- (110) Villalba, M.; del Pozo, M.; Calvo, E. J. Electrocatalytic Hydrogenation of Acetophenone and Benzophenone Using Palladium Electrodes. *Electrochim. Acta* **2015**, *164*, 125–131.
- (111) Peng, Y.; Cui, M.; Zhang, Z.; Shu, S.; Shi, X.; Brosnahan, J. T.; Liu, C.; Zhang, Y.; Godbold, P.; Zhang, X.; et al. Bimetallic Composition-Promoted Electrocatalytic Hydrodechlorination Reaction on Silver-Palladium Alloy Nanoparticles. *ACS Catal.* **2019**, *9* (12), 10803–10811.
- (112) Chen, Y.; Feng, C.; Wang, W.; Liu, Z.; Li, J.; Liu, C.; Pan, Y.; Liu, Y. Electronic Structure Engineering of Bimetallic Pd-Au Alloy Nanocatalysts for Improving Electrocatalytic Hydrodechlorination Performance. *Sep. Purif. Technol.* **2022**, *289*, 120731.
- (113) Zhou, P.; Li, L.; Mosali, V. S. S.; Chen, Y.; Luan, P.; Gu, Q.; Turner, D. R.; Huang, L.; Zhang, J. Electrochemical Hydrogenation of Furfural in Aqueous Acetic Acid Media with Enhanced 2-Methylfuran Selectivity Using Cupd Bimetallic Catalysts. *Angew. Chem., Int. Ed.* **2022**, *61* (13), 202117809.
- (114) Abdel-Mageed, A. M.; Eckle, S.; Behm, R. J. High Selectivity of Supported Ru Catalysts in the Selective Co Methanation—Water Makes the Difference. *J. Am. Chem. Soc.* **2015**, *137* (27), 8672–8675.
- (115) Wang, H.; Iglesia, E. Thiophene Hydrodesulfurization Catalysis on Supported Ru Clusters: Mechanism and Site Requirements for Hydrogenation and Desulfurization Pathways. *J. Catal.* **2010**, *273* (2), 245–256.
- (116) Zhou, P.; Guo, S.-X.; Li, L.; Ueda, T.; Nishiwaki, Y.; Huang, L.; Zhang, Z.; Zhang, J. Selective Electrochemical Hydrogenation of Phenol with Earth-Abundant Ni–MoO₂ Heterostructured Catalysts: Effect of Oxygen Vacancy on Product Selectivity. *Angew. Chem., Int. Ed.* **2023**, *62* (8), 202214881.
- (117) Han, Q.; Rehman, M. U.; Wang, J.; Rykov, A.; Gutiérrez, O. Y.; Zhao, Y.; Wang, S.; Ma, X.; Lercher, J. A. The Synergistic Effect between Ni Sites and Ni-Fe Alloy Sites on Hydrodeoxygenation of Lignin-Derived Phenols. *Appl. Catal., B* **2019**, *253*, 348–358.
- (118) Carroll, K. J.; Burger, T.; Langenegger, L.; Chavez, S.; Hunt, S. T.; Román-Leshkov, Y.; Brushett, F. R. Electrocatalytic Hydrogenation of Oxygenates Using Earth-Abundant Transition-Metal Nanoparticles under Mild Conditions. *ChemSusChem* **2016**, *9* (15), 1904–1910.
- (119) Zhang, Y.-R.; Wang, B.-X.; Qin, L.; Li, Q.; Fan, Y.-M. A Non-Noble Bimetallic Alloy in the Highly Selective Electrochemical Synthesis of the Biofuel 2,5-Dimethylfuran from 5-Hydroxymethylfurfural. *Green Chem.* **2019**, *21* (5), 1108–1113.
- (120) Wu, Y.; Song, X.; Li, S.; Zhang, J.; Yang, X.; Shen, P.; Gao, L.; Wei, R.; Zhang, J.; Xiao, G. 3D-monoclinic M-BTC MOF (M = Mn, Co, Ni) as highly efficient catalysts for chemical fixation of CO₂ into cyclic carbonates. *J. Ind. Eng. Chem.* **2018**, *58*, 296–303.
- (121) Kurisingal, J. F.; Babu, R.; Kim, S.-H.; Li, Y. X.; Chang, J.-S.; Cho, S. J.; Park, D.-W. Microwave-Induced Synthesis of a Bimetallic Charge-Transfer Metal Organic Framework: A Promising Host for the Chemical Fixation of CO₂. *Catal. Sci. Technol.* **2018**, *8* (2), 591–600.
- (122) Han, S.; Shi, Y.; Wang, C.; Liu, C.; Zhang, B. Hollow Cobalt Sulfide Nanocapsules for Electrocatalytic Selective Transfer Hydrogenation of Cinnamaldehyde with Water. *Cell Rep. Phys. Sci.* **2021**, *2* (2), 100337.
- (123) Tang, F.; Zhang, G.; Wang, L.; Huang, J.; Liu, Y.-N. Unsymmetrically N, S-Coordinated Single-Atom Cobalt with Electron Redistribution for Catalytic Hydrogenation of Quinolines. *J. Catal.* **2022**, *414*, 101–108.
- (124) Xiao, S.; Zhang, C.; Chen, R.; Chen, F. Selective Oxidation of Benzyl Alcohol to Benzaldehyde with H₂O₂ in Water on Epichlorohydrin-Modified Fe₃O₄ Microspheres. *New J. Chem.* **2015**, *39* (6), 4924–4932.

- (125) Merki, D.; Vrabel, H.; Rovelli, L.; Fierro, S.; Hu, X. Fe, Co, and Ni Ions Promote the Catalytic Activity of Amorphous Molybdenum Sulfide Films for Hydrogen Evolution. *Chem. Sci.* **2012**, *3* (8), 2515–2525.
- (126) Zhang, S.; Zhang, Z.; Ge, M.; Liu, B.; Chen, S.; Zhang, D.; Gao, L. Converting Lignin into Long-Chain Fatty Acids with the Electro-Fenton Reaction. *Gcb Bioenergy* **2021**, *13* (8), 1290–1302.
- (127) Calado Galvão de Melo, S.; da Silva, M. E. P.; da Silva, M. E. B.; da Paz, J. A.; de Menezes Barbosa, C. M. B.; de Menezes, F. D.; Loureiro, R. N. A.; Navarro, M.; da Costa, J. A. P.; da Silva, G. F.; et al. Ultrasound as a Tool for Reducing Energy Consumption in Electrocatalytic Hydrogenation of Aromatic Ketones Using Graphite as Catalyst Support. *Int. J. Hydrogen Energy* **2020**, *45* (43), 22855–22872.
- (128) Sauter, W.; Bergmann, O. L.; Schröder, U. Hydroxyacetone: A Glycerol-Based Platform for Electrocatalytic Hydrogenation and Hydrodeoxygenation Processes. *ChemSusChem* **2017**, *10* (15), 3105–3110.
- (129) Wang, Y.; Yan, D.; El Hankari, S.; Zou, Y.; Wang, S. Recent Progress on Layered Double Hydroxides and Their Derivatives for Electrocatalytic Water Splitting. *Adv. Sci.* **2018**, *5* (8), 1800064.
- (130) Seh, Z. W.; Kibsgaard, J.; Dickens, C. F.; Chorkendorff, I.; Nørskov, J. K.; Jaramillo, T. F. Combining Theory and Experiment in Electrocatalysis: Insights into Materials Design. *Science* **2017**, *355* (6321), 4998.
- (131) Abramo, F. P.; De Luca, F.; Chiodoni, A.; Centi, G.; Giorgianni, G.; Italiano, C.; Perathoner, S.; Abate, S. Nanostructure-Performance Relationships in Titania-Only Electrodes for the Selective Electrocatalytic Hydrogenation of Oxalic Acid. *J. Catal.* **2024**, *429*, 115277.
- (132) Zhao, Y.; Jia, X.; Chen, G.; Shang, L.; Waterhouse, G. I. N.; Wu, L.-Z.; Tung, C.-H.; O'Hare, D.; Zhang, T. Ultrafine Ni Nanosheets Stabilized by TiO₂ from Monolayer Niti-Ldh Precursors: An Active Water Oxidation Electrocatalyst. *J. Am. Chem. Soc.* **2016**, *138* (20), 6517–6524.
- (133) Xu, L.; Jiang, Q.; Xiao, Z.; Li, X.; Huo, J.; Wang, S.; Dai, L. Plasma-Engraved Co₃O₄ Nanosheets with Oxygen Vacancies and High Surface Area for the Oxygen Evolution Reaction. *Angew. Chem., Int. Ed.* **2016**, *55* (17), 5277–5281.
- (134) Friebel, D.; Louie, M. W.; Bajdich, M.; Sanwald, K. E.; Cai, Y.; Wise, A. M.; Cheng, M.-J.; Sokaras, D.; Weng, T.-C.; Alonso-Mori, R.; et al. Identification of Highly Active Fe Sites in (Ni,Fe)OOH for Electrocatalytic Water Splitting. *J. Am. Chem. Soc.* **2015**, *137* (3), 1305–1313.
- (135) Hunter, B. M.; Thompson, N. B.; Müller, A. M.; Rossman, G. R.; Hill, M. G.; Winkler, J. R.; Gray, H. B. Trapping an Iron(VI) Water-Splitting Intermediate in Nonaqueous Media. *Joule* **2018**, *2* (4), 747–763.
- (136) Ma, D.; Lu, Z.; Tang, Y.; Li, T.; Tang, Z.; Yang, Z. Effect of Lattice Strain on the Oxygen Vacancy Formation and Hydrogen Adsorption at CeO₂ (111) Surface. *Phys. Lett. A* **2014**, *378* (34), 2570–2575.
- (137) Petchmark, M.; Ruangpornvisuti, V. Hydrogen Adsorption on C-ZrO₂ (111), T-ZrO₂ (101), and M-ZrO₂ (111) Surfaces and Their Oxygen-Vacancy Defect for Hydrogen Sensing and Storage: A First-Principles Investigation. *Mater. Lett.* **2021**, *301*, 130243.
- (138) Centi, G.; Perathoner, S. Carbon Nanotubes for Sustainable Energy Applications. *ChemSusChem* **2011**, *4* (7), 913–925.
- (139) Centi, G.; Perathoner, S. Problems and Perspectives in Nanostructured Carbon-Based Electrodes for Clean and Sustainable Energy. *Catal. Today* **2010**, *150* (1), 151–162.
- (140) Su, D. S.; Perathoner, S.; Centi, G. Nanocarbons for the Development of Advanced Catalysts. *Chem. Rev.* **2013**, *113* (8), 5782–5816.
- (141) Wang, P.; Shi, X.; Fu, C.; Li, X.; Li, J.; Lv, X.; Chu, Y.; Dong, F.; Jiang, G. Strong Pyrrolic-N-Pd Interactions Boost the Electrocatalytic Hydrodechlorination Reaction on Palladium Nanoparticles. *Nanoscale* **2020**, *12* (2), 843–850.
- (142) Zhang, Z.-X.; Liu, Y.; Meng, W.-J.; Wang, J.; Li, W.; Wang, H.; Zhao, D.; Lu, J.-X. One-Pot Synthesis of Ni Nanoparticle/Ordered Mesoporous Carbon Composite Electrode Materials for Electrocatalytic Reduction of Aromatic Ketones. *Nanoscale* **2017**, *9* (45), 17807–17813.
- (143) Li, T.; Hu, T.; Dai, L.; Li, C. M. Metal-Free Photo- and Electro-Catalysts for Hydrogen Evolution Reaction. *J. Mater. Chem. A* **2020**, *8* (45), 23674–23698.
- (144) Wang, T.; Xie, H.; Chen, M.; D'Aloia, A.; Cho, J.; Wu, G.; Li, Q. Precious Metal-Free Approach to Hydrogen Electrocatalysis for Energy Conversion: From Mechanism Understanding to Catalyst Design. *Nano Energy* **2017**, *42*, 69–89.
- (145) Ma, X.; Du, J.; Sun, H.; Ye, F.; Wang, X.; Xu, P.; Hu, C.; Zhang, L.; Liu, D. Boron, Nitrogen Co-Doped Carbon with Abundant Mesopores for Efficient CO₂ Electroreduction. *Appl. Catal., B* **2021**, *298*, 120543.
- (146) Zehtab Yazdi, A.; Fei, H.; Ye, R.; Wang, G.; Tour, J.; Sundararaj, U. Boron/Nitrogen Co-Doped Helically Unzipped Multiwalled Carbon Nanotubes as Efficient Electrocatalyst for Oxygen Reduction. *ACS Appl. Mater. Interfaces* **2015**, *7* (14), 7786–7794.
- (147) Zhang, X.; Han, M.; Liu, G.; Wang, G.; Zhang, Y.; Zhang, H.; Zhao, H. Simultaneously High-Rate Furfural Hydrogenation and Oxidation Upgrading on Nanostructured Transition Metal Phosphides through Electrocatalytic Conversion at Ambient Conditions. *Appl. Catal. B: Env.* **2019**, *244*, 899–908.
- (148) Ying, J.; Liu, T.; Wang, Y.; Guo, M.; Shen, Q.; Lin, Y.; Yu, J.; Yu, Z. Perspectives on Membrane Development for High Temperature Proton Exchange Membrane Fuel Cells. *Energy Fuels* **2024**, *38* (8), 6613–6643.
- (149) Bonanno, M.; Müller, K.; Bensmann, B.; Hanke-Rauschenbach, R.; Aili, D.; Franken, T.; Chromik, A.; Peach, R.; Freiberg, A. T. S.; Thiele, S. Review and Prospects of PEM Water Electrolysis at Elevated Temperature Operation. *Adv. Mater. Technol.* **2024**, *9* (2), 2300281.
- (150) Kim, M.; Ko, H.; Nam, S. Y.; Kim, K. Study on Control of Polymeric Architecture of Sulfonated Hydrocarbon-Based Polymers for High-Performance Polymer Electrolyte Membranes in Fuel Cell Applications. *Polymers* **2021**, *13* (20), 3520.
- (151) Das, A.; Im, K. S.; Kabir, M. M.; Shon, H. K.; Nam, S. Y. Polybenzimidazole (PBI)-Based Membranes for Fuel Cell, Water Electrolysis and Desalination. *Desalination* **2024**, *579*, 117500.
- (152) Kim, D. J.; Jo, M. J.; Nam, S. Y. A Review of Polymer-Nanocomposite Electrolyte Membranes for Fuel Cell Application. *J. Ind. Eng. Chem.* **2015**, *21*, 36–52.
- (153) BASF. *Fuel Cell Materials*; BASF: Ludwigshafen, Germany, 2024; <https://chemicals.basf.com/global/en/Catalysts/fuel-cell-materials>.
- (154) Ionomr Innovations, Inc. *Pemion—Proton-Exchange Materials*; Ionomr Innovations, Inc.: Vancouver, British Columbia, Canada, 2024; <https://ionomr.com/solutions/pemion>.
- (155) W. L. Gore & Associates. *Electronic Components & Electrochemical Materials*; W. L. Gore & Associates: Newark, DE, 2024; <https://www.gore.com/products/categories/electronic-components-electrochemical-materials>.
- (156) Nagasawa, K.; Tanimoto, K.; Koike, J.; Ikegami, K.; Mitsushima, S. Toluene Permeation through Solid Polymer Electrolyte During Toluene Direct Electro-Hydrogenation for Energy Carrier Synthesis. *J. Power Sources* **2019**, *439*, 227070.
- (157) Han, G.; Li, G.; Sun, Y. Electrocatalytic Hydrogenation Using Palladium Membrane Reactors. *JACS Au* **2024**, *4* (2), 328–343.
- (158) Zhang, Y.; Shen, Y. Electrochemical Hydrogenation of Levulinic Acid, Furfural and 5-Hydroxymethylfurfural. *Appl. Catal., B* **2024**, *343*, 123576.
- (159) Nagasawa, K.; Sawaguchi, Y.; Kato, A.; Nishiki, Y.; Mitsushima, S. Rate-Determining Factor of the Performance for Toluene Electrohydrogenation Electrolyzer. *Electrocatal.* **2017**, *8* (2), 164–169.

- (160) Zhao, B.; Chen, M.; Guo, Q.; Fu, Y. Electrocatalytic Hydrogenation of Furfural to Furfuryl Alcohol Using Platinum Supported on Activated Carbon Fibers. *Electrochim. Acta* **2014**, *135*, 139–146.
- (161) Sasaki, K.; Kunai, A.; Harada, J.; Nakabori, S. Electrolytic Hydrogenation of Phenols in Aqueous Acid Solutions. *Electrochim. Acta* **1983**, *28* (5), 671–674.
- (162) Kwon, Y.; Birdja, Y. Y.; Raoufoghaddam, S.; Koper, M. T. M. Electrocatalytic Hydrogenation of 5-Hydroxymethylfurfural in Acidic Solution. *ChemSusChem* **2015**, *8* (10), 1745–1751.
- (163) Rodriguez, J. L.; Pastor, E. A Comparative Study on the Adsorption of Benzyl Alcohol, Toluene and Benzene on Platinum. *Electrochim. Acta* **2000**, *45* (25), 4279–4289.
- (164) Singh, N.; Lee, M.-S.; Akhade, S. A.; Cheng, G.; Camaioni, D. M.; Gutiérrez, O. Y.; Glezakou, V. A.; Rousseau, R.; Lercher, J. A.; Campbell, C. T. Impact of Ph on Aqueous-Phase Phenol Hydrogenation Catalyzed by Carbon-Supported Pt and Rh. *ACS Catal.* **2019**, *9* (2), 1120–1128.
- (165) Xin, L.; Zhang, Z.; Qi, J.; Chadderdon, D. J.; Qiu, Y.; Warsko, K. M.; Li, W. Electricity Storage in Biofuels: Selective Electrocatalytic Reduction of Levulinic Acid to Valeric Acid or Γ -Valerolactone. *ChemSusChem* **2013**, *6* (4), 674–686.
- (166) Nilges, P.; Schröder, U. Electrochemistry for Biofuel Generation: Production of Furans by Electrocatalytic Hydrogenation of Furfurals. *Energy Environ. Sci.* **2013**, *6* (10), 2925–2931.
- (167) Peng, T.; Zhang, W.; Liang, B.; Lian, G.; Zhang, Y.; Zhao, W. Electrocatalytic Valorization of Lignocellulose-Derived Aromatics at Industrial-Scale Current Densities. *Nat. Commun.* **2023**, *14* (1), 7229.
- (168) Sanyal, U.; Koh, K.; Meyer, L. C.; Karkamkar, A.; Gutiérrez, O. Y. Simultaneous Electrocatalytic Hydrogenation of Aldehydes and Phenol over Carbon-Supported Metals. *J. Appl. Electrochem.* **2021**, *51* (1), 27–36.
- (169) Song, Y.; Sanyal, U.; Pangotra, D.; Holladay, J. D.; Camaioni, D. M.; Gutiérrez, O. Y.; Lercher, J. A. Hydrogenation of Benzaldehyde Via Electrocatalysis and Thermal Catalysis on Carbon-Supported Metals. *J. Catal.* **2018**, *359*, 68–75.
- (170) Kwon, Y.; de Jong, E.; Raoufoghaddam, S.; Koper, M. T. M. Electrocatalytic Hydrogenation of 5-Hydroxymethylfurfural in the Absence and Presence of Glucose. *ChemSusChem* **2013**, *6* (9), 1659–1667.
- (171) Roylance, J. J.; Kim, T. W.; Choi, K.-S. Efficient and Selective Electrochemical and Photoelectrochemical Reduction of 5-Hydroxymethylfurfural to 2,5-Bis(Hydroxymethyl)Furan Using Water as the Hydrogen Source. *ACS Catal.* **2016**, *6* (3), 1840–1847.
- (172) Martel, A.; Mahdavi, B.; Lessard, J.; Ménard, H.; Brossard, L. Electrocatalytic Hydrogenation of Phenol on Various Electrode Materials. *Can. J. Chem.* **1997**, *75* (12), 1862–1867.
- (173) Roylance, J. J.; Choi, K.-S. Electrochemical Reductive Biomass Conversion: Direct Conversion of 5-Hydroxymethylfurfural (HMF) to 2,5-Hexanedione (HD) Via Reductive Ring-Opening. *Green Chem.* **2016**, *18* (10), 2956–2960.
- (174) Wijaya, Y. P.; Grossmann-Neuhäusler, T.; Dhewangga Putra, R. D.; Smith, K. J.; Kim, C. S.; Gyenge, E. L. Electrocatalytic Hydrogenation of Guaiacol in Diverse Electrolytes Using a Stirred Slurry Reactor. *ChemSusChem* **2020**, *13* (3), 629–639.
- (175) Wang, F.; Xu, M.; Wei, L.; Wei, Y.; Hu, Y.; Fang, W.; Zhu, C. G. Fabrication of La-doped TiO₂ Film Electrode and Investigation of Its Electrocatalytic Activity for Furfural Reduction. *Electrochim. Acta* **2015**, *153*, 170–174.
- (176) Mozo Muleró, C.; Sáez, A.; Iniesta, J.; Montiel, V. An Alternative to Hydrogenation Processes. Electrocatalytic Hydrogenation of Benzophenone. *Beilstein J. Org. Chem.* **2018**, *14*, 537–546.
- (177) Lopez-Ruiz, J. A.; Sanyal, U.; Egbert, J.; Gutiérrez, O. Y.; Holladay, J. Kinetic Investigation of the Sustainable Electrocatalytic Hydrogenation of Benzaldehyde on Pd/C: Effect of Electrolyte Composition and Half-Cell Potentials. *ACS Sustainable Chem. Eng.* **2018**, *6* (12), 16073–16085.
- (178) Wijaya, Y. P.; Putra, R. D. D.; Smith, K. J.; Kim, C. S.; Gyenge, E. L. Guaiacol Hydrogenation in Methanesulfonic Acid Using a Stirred Slurry Electrocatalytic Reactor: Mass Transport and Reaction Kinetics Aspects. *ACS Sustainable Chem. Eng.* **2021**, *9* (39), 13164–13175.
- (179) de Souza, R. F.; Padilha, J. C.; Gonçalves, R. S.; Rault-Berthelot, J. Dialkylimidazolium Ionic Liquids as Electrolytes for Hydrogen Production from Water Electrolysis. *Electrochem. Commun.* **2006**, *8* (2), 211–216.
- (180) Steinrück, H.-P.; Wasserscheid, P. Ionic Liquids in Catalysis. *Catal. Lett.* **2015**, *145* (1), 380–397.
- (181) Tsyganok, A.; Holt, C. M.; Murphy, S.; Mitlin, D.; Gray, M. R. Electrocatalytic Hydrogenation of Aromatic Compounds in Ionic Liquid Solutions over WS₂-on-Glassy Carbon and Raney Nickel Cathodes. *Fuel* **2012**, *93*, 415–422.
- (182) Chu, D.; Hou, Y.; He, J.; Xu, M.; Wang, Y.; Wang, S.; Wang, J.; Zha, L. Nano TiO₂ Film Electrode for Electrocatalytic Reduction of Furfural in Ionic Liquids. *J. Nanopart. Res.* **2009**, *11* (7), 1805–1809.
- (183) Wu, H.; Song, J.; Xie, C.; Hu, Y.; Zhang, P.; Yang, G.; Han, B. Surface Engineering in Pbs Via Partial Oxidation: Towards an Advanced Electrocatalyst for Reduction of Levulinic Acid to Γ -Valerolactone. *Chem. Sci.* **2019**, *10* (6), 1754–1759.
- (184) Fan, Y.; Zou, Y.; Wang, S. Electrocatalytic Oxidation of Biomass Derived Molecules. *Sci. Bull.* **2023**, *68* (22), 2695–2699.
- (185) Lai, Z. I.; Lee, L. Q.; Li, H. Electroreforming of Biomass for Value-Added Products. *Micromachines* **2021**, *12* (11), 1405.
- (186) Zhu, P.; Shi, M.; Shen, Z.; Liao, X.; Chen, Y. Electrocatalytic Conversion of Biomass-Derived Furan Compounds: Mechanisms, Catalysts and Perspectives. *Chem. Sci.* **2024**, *15* (13), 4723–4756.
- (187) Kubota, S. R.; Choi, K.-S. Electrochemical Oxidation of 5-Hydroxymethylfurfural to 2,5-Furandicarboxylic Acid (Fdca) in Acidic Media Enabling Spontaneous Fdca Separation. *ChemSusChem* **2018**, *11* (13), 2138–2145.
- (188) Cai, M.; Zhang, Y.; Zhao, Y.; Liu, Q.; Li, Y.; Li, G. Two-Dimensional Metal-Organic Framework Nanosheets for Highly Efficient Electrocatalytic Biomass 5-(Hydroxymethyl)Furfural (Hmf) Valorization. *J. Mater. Chem. A* **2020**, *8* (39), 20386–20392.
- (189) Wu, J.; Yang, X.; Gong, M. Recent Advances in Glycerol Valorization Via Electrooxidation: Catalyst, Mechanism and Device. *Chin. J. Catal.* **2022**, *43* (12), 2966–2986.
- (190) Hu, X.; Lu, J.; Liu, Y.; Chen, L.; Zhang, X.; Wang, H. Sustainable Catalytic Oxidation of Glycerol: A Review. *Environ. Chem. Lett.* **2023**, *21* (5), 2825–2861.
- (191) Luo, W.; Tian, H.; Li, Q.; Meng, G.; Chang, Z.; Chen, C.; Shen, R.; Yu, X.; Zhu, L.; Kong, F.; Cui, X.; Shi, J. Controllable Electron Distribution Reconstruction of Spinel NiCo₂O₄ Boosting Glycerol Oxidation at Elevated Current Density. *Adv. Funct. Mater.* **2024**, *34* (3), 2306995.
- (192) Fan, L.; Liu, B.; Liu, X.; Senthilkumar, N.; Wang, G.; Wen, Z. Recent Progress in Electrocatalytic Glycerol Oxidation. *Energy Technol.* **2021**, *9* (2), 2000804.
- (193) Di Fidio, N.; Timmermans, J. W.; Antonetti, C.; Raspollini Galletti, A. M.; Gosselink, R. J. A.; Bisselink, R. J. M.; Slaghek, T. M. Electro-Oxidative Depolymerisation of Technical Lignin in Water Using Platinum, Nickel Oxide Hydroxide and Graphite Electrodes. *New J. Chem.* **2021**, *45* (21), 9647–9657.
- (194) Yu, X.; Wei, Z.; Lu, Z.; Pei, H.; Wang, H. Activation of Lignin by Selective Oxidation: An Emerging Strategy for Boosting Lignin Depolymerization to Aromatics. *Bioresour. Technol.* **2019**, *291*, 121885.
- (195) Li, J.; Zhou, W.; Huang, Y.; Gao, J. Lignin-Assisted Water Electrolysis for Energy-Saving Hydrogen Production with Ti/PbO₂ as the Anode. *Front. Energy Res.* **2021**, *9*, 762346.
- (196) Liu, M.; Wen, Y.; Qi, J.; Zhang, S.; Li, G. Fine Chemicals Prepared by Bamboo Lignin Degradation through Electrocatalytic Redox between Cu Cathode and Pb/PbO₂ Anode in Alkali Solution. *ChemistrySelect* **2017**, *2* (17), 4956–4962.
- (197) Cai, P.; Fan, H.; Cao, S.; Qi, J.; Zhang, S.; Li, G. Electrochemical Conversion of Corn Stover Lignin to Biomass-Based Chemicals between Cu/NiMoCo Cathode and Pb/PbO₂ Anode in Alkali Solution. *Electrochim. Acta* **2018**, *264*, 128–139.

- (198) Jia, Y.; Wen, Y.; Han, X.; Qi, J.; Liu, Z.; Zhang, S.; Li, G. Electrocatalytic Degradation of Rice Straw Lignin in Alkaline Solution through Oxidation on a Ti/SnO₂-Sb₂O₃/A-PbO₂/B-PbO₂ Anode and Reduction on an Iron or Tin Doped Titanium Cathode. *Catal. Sci. Technol.* **2018**, *8* (18), 4665–4677.
- (199) Centi, G.; Perathoner, S.; Genovese, C.; Arrigo, R. Advanced (Photo)Electrocatalytic Approaches to Substitute the Use of Fossil Fuels in Chemical Production. *Chem. Commun.* **2023**, *59* (21), 3005–3023.
- (200) Jiang, Y.; Zhao, H.; Liang, J.; Yue, L.; Li, T.; Luo, Y.; Liu, Q.; Lu, S.; Asiri, A. M.; Gong, Z.; et al. Anodic Oxidation for the Degradation of Organic Pollutants: Anode Materials, Operating Conditions and Mechanisms. A Mini Review. *Electrochem. Commun.* **2021**, *123*, 106912.
- (201) Rai, D.; Sinha, S. Research Trends in the Development of Anodes for Electrochemical Oxidation of Wastewater. *Rev. Chem. Eng.* **2023**, *39* (5), 807–855.
- (202) Banerjee, A.; Calay, R. K.; Mustafa, M. Review on Material and Design of Anode for Microbial Fuel Cell. *Energies* **2022**, *15* (6), 2283.
- (203) Hadi, N. H.; Somalu, M. R.; Samat, A. A.; Muchtar, A.; Baharuddin, N. A.; Anwar, M. A Review on the Preparation of Anode Materials and Anode Films for Solid Oxide Fuel Cell Applications. *Int. J. Energy Res.* **2021**, *45* (10), 14357–14388.
- (204) Galkin, M. From Stabilization Strategies to Tailor-Made Lignin Macromolecules and Oligomers for Materials. *Curr. Opin. Green Sustainable Chem.* **2021**, *28*, 100438.
- (205) Garedew, M.; Lam, C. H.; Petitjean, L.; Huang, S.; Song, B.; Lin, F.; Jackson, J. E.; Saffron, C. M.; Anastas, P. T. Electrochemical Upgrading of Depolymerized Lignin: A Review of Model Compound Studies. *Green Chem.* **2021**, *23* (8), 2868–2899.
- (206) Garedew, M.; Young-Farhat, D.; Jackson, J. E.; Saffron, C. M. Electrocatalytic Upgrading of Phenolic Compounds Observed after Lignin Pyrolysis. *ACS Sustainable Chem. Eng.* **2019**, *7* (9), 8375–8386.
- (207) Groppi, G.; Tronconi, E.; Cortelli, C.; Leanza, R. Conductive Monolithic Catalysts: Development and Industrial Pilot Tests for the Oxidation of *o*-Xylene to Phthalic Anhydride. *Ind. Eng. Chem. Res.* **2012**, *51* (22), 7590–7596.
- (208) Wu, R.; Meng, Q.; Yan, J.; Liu, H.; Zhu, Q.; Zheng, L.; Zhang, J.; Han, B. Electrochemical Strategy for the Simultaneous Production of Cyclohexanone and Benzoquinone by the Reaction of Phenol and Water. *J. Am. Chem. Soc.* **2022**, *144* (4), 1556–1571.
- (209) Nematollahi, D.; Atlasi-Pak, A. R.; Esmaili, R. Electrochemical Oxidation of Catechols (=Benzene-1,2-Diols) in the Presence of Benzoylacetone: Synthesis of New Derivatives of 5,6-Dihydroxybenzofuran. *Helv. Chim. Acta* **2012**, *95* (9), 1605–1612.
- (210) Ngamchuea, K.; Tharat, B.; Hirunsit, P.; Suthirakun, S. Electrochemical Oxidation of Resorcinol: Mechanistic Insights from Experimental and Computational Studies. *RSC Adv.* **2020**, *10* (47), 28454–28463.
- (211) Wang, F.; Yang, G.; Zhang, W.; Wu, W.; Xu, J. Oxidation of *p*-Cresol to *p*-Hydroxybenzaldehyde with Molecular Oxygen in the Presence of Cumn-Oxide Heterogeneous Catalyst. *Adv. Synth. Catal.* **2004**, *346* (6), 633–638.
- (212) Comninellis, C. Electrocatalysis in the Electrochemical Conversion/Combustion of Organic Pollutants for Waste Water Treatment. *Electrochim. Acta* **1994**, *39* (11), 1857–1862.
- (213) Abdessamad, N.; Akrou, H.; Hamdaoui, G.; Elghniji, K.; Ksibi, M.; Bousselmi, L. Evaluation of the Efficiency of Monopolar and Bipolar BDD Electrodes for Electrochemical Oxidation of Anthraquinone Textile Synthetic Effluent for Reuse. *Chemosphere* **2013**, *93* (7), 1309–1316.
- (214) Panizza, M.; Michaud, P. A.; Cerisola, G.; Comninellis, C. Electrochemical Treatment of Wastewaters Containing Organic Pollutants on Boron-Doped Diamond Electrodes: Prediction of Specific Energy Consumption and Required Electrode Area. *Electrochem. Commun.* **2001**, *3* (7), 336–339.
- (215) Martínez-Huitle, C. A.; Brillas, E. Decontamination of Wastewaters Containing Synthetic Organic Dyes by Electrochemical Methods: A General Review. *Appl. Catal., B* **2009**, *87* (3), 105–145.
- (216) Isarain-Chávez, E.; Baró, M. D.; Rossinyol, E.; Morales-Ortiz, U.; Sort, J.; Brillas, E.; Pellicer, E. Comparative Electrochemical Oxidation of Methyl Orange Azo Dye Using Ti/Ir-Pb, Ti/Ir-Sn, Ti/Ru-Pb, Ti/Pt-Pd and Ti/RuO₂ anodes. *Electrochim. Acta* **2017**, *244*, 199–208.
- (217) Marselli, B.; Garcia-Gomez, J.; Michaud, P. A.; Rodrigo, M. A.; Comninellis, C. Electrogenation of Hydroxyl Radicals on Boron-Doped Diamond Electrodes. *J. Electrochem. Soc.* **2003**, *150* (3), D79.
- (218) Lu, X.; Gu, X. A review on Lignin-Based Epoxy Resins: Lignin Effects on Their Synthesis and Properties. *Int. J. Biol. Macromol.* **2023**, *229*, 778–790.
- (219) Luo, J.; Liu, T. L. Electrochemical Valorization of Lignin: Status, Challenges, and Prospects. *J. Bioresour. Bioprod.* **2023**, *8* (1), 1–14.
- (220) Luo, P.; Feinberg, E. C.; Guirado, G.; Farid, S.; Dinnocenzo, J. P. Accurate Oxidation Potentials of 40 Benzene and Biphenyl Derivatives with Heteroatom Substituents. *J. Org. Chem.* **2014**, *79* (19), 9297–9304.
- (221) Long, X.; Wang, Z.; Wu, S.; Wu, S.; Lv, H.; Yuan, W. Production of Isophthalic Acid from *m*-xylene Oxidation Under the Catalysis of the H₃PW₁₂O₄₀/Carbon and Cobalt Catalytic System. *J. Ind. Eng. Chem.* **2014**, *20* (1), 100–107.
- (222) Crestini, C.; Jurasek, L.; Argyropoulos, D. S. On the Mechanism of the Laccase-Mediator System in the Oxidation of Lignin. *Chem. - Eur. J.* **2003**, *9* (21), 5371–5378.
- (223) Luo, X.; Tang, X.; Ni, J.; Wu, B.; Li, C.; Shao, M.; Wei, Z. Electrochemical Oxidation of Styrene to Benzaldehyde by Discrimination of Spin-paired π Electrons. *Chem. Sci.* **2023**, *14* (7), 1679–1686.
- (224) Márquez, O. P.; Fontal, B.; Márquez, J.; Ortiz, R.; Castillo, R.; Choy, M.; Lárez, C. Electrochemical Oxidation of 1,2-Dimethoxybenzene: Characteristics and Morphology of Deposited Product. *J. Electrochem. Soc.* **1995**, *142* (3), 707.
- (225) Swankaert, B.; Geltmeyer, J.; Rabaey, K.; De Buysser, K.; Bonin, L.; De Clerck, K. A Review on Ion-exchange Nanofiber Membranes: Properties, Structure and Application in Electrochemical (Waste)Water Treatment. *Sep. Purif. Technol.* **2022**, *287*, 120529.
- (226) Liu, Y.; Yu, X.; Kamali, M.; Zhang, X.; Feijoo, S.; Al-Salem, S. M.; Dewil, R.; Appels, L. Biochar in hydroxyl radical-based electrochemical advanced oxidation processes (eAOPs) - Mechanisms and prospects. *Chem. Eng. J.* **2023**, *467*, 143291.
- (227) Martínez-Huitle, C. A.; Rodrigo, M. A.; Sirés, I.; Scialdone, O. A Critical Review on Latest Innovations and Future Challenges of Electrochemical Technology for the Abatement of Organics in Water. *Appl. Catal., B* **2023**, *328*, 122430.
- (228) Xie, J.; Zhang, C.; Waite, T. D. Hydroxyl radicals in anodic oxidation systems: generation, identification and quantification. *Water Res.* **2022**, *217*, 118425.
- (229) Bordiga, S.; Damin, A.; Bonino, F.; Ricchiardi, G.; Lamberti, C.; Zecchina, A. The Structure of the Peroxo Species in the TS-1 Catalyst as Investigated by Resonant Raman Spectroscopy. *Angew. Chem. Int. Ed.* **2002**, *41* (24), 4734–4737.
- (230) Přeč, J. Catalytic Performance of Advanced Titanosilicate Selective Oxidation Catalysts - A Review. *Catal. Rev.* **2018**, *60* (1), 71–131.
- (231) Nichols, F.; Ozoemena, K. I.; Chen, S. Electrocatalytic Generation of Reactive Species and Implications in Microbial Inactivation. *Chin. J. Catal.* **2022**, *43* (6), 1399–1416.
- (232) Fu, R.; Zhang, P.-S.; Jiang, Y.-X.; Sun, L.; Sun, X.-H. Wastewater Treatment by Anodic Oxidation in Electrochemical Advanced Oxidation Process: Advance in Mechanism, Direct and Indirect Oxidation Detection Methods. *Chemosphere* **2023**, *311*, 136993.
- (233) Fleischmann, M.; Korinek, K.; Pletcher, D. The oxidation of Organic Compounds at a Nickel Anode in Alkaline Solution. *J. electroanal. chem. interfacial electrochem* **1971**, *31* (1), 39–49.

- (234) Parreira, L. S.; da Silva, J. C. M.; D'Villa -Silva, M.; Simões, F. C.; Garcia, S.; Gaubeur, I.; Cordeiro, M. A. L.; Leite, E. R.; dos Santos, M. C. PtSnNi/C Nanoparticle Electrocatalysts for the Ethanol Oxidation Reaction: Ni Stability Study. *Electrochim. Acta* **2013**, *96*, 243–252.
- (235) Tiainen, T. J.; Schwarz, R. B. Synthesis and Characterization of Mechanically Alloyed Ni-Sn Powders. *J. Less-Common Met.* **1988**, *140*, 99–112.
- (236) Lai, S. C. S.; Kleijn, S. E. F.; Öztürk, F. T. Z.; van Rees Vellinga, V. C.; Koning, J.; Rodriguez, P.; Koper, M. T. M. Effects of Electrolyte pH and Composition on the Ethanol Electro-Oxidation Reaction. *Catal. Today* **2010**, *154* (1), 92–104.
- (237) Liu, C.; Yang, F.; Schechter, A.; Feng, L. Recent Progress of Ni-based Catalysts for Methanol Electrooxidation Reaction in Alkaline Media. *Adv. Sensor Energy Mater.* **2023**, *2* (2), 100055.
- (238) Zhou, Y.; Kuang, Y.; Hu, G.; Wang, X.; Feng, L. An Effective Pt-CoTe/NC Catalyst of Bifunctional Methanol Electrolysis for Hydrogen Generation. *Mater. Today Phys.* **2022**, *27*, 100831.
- (239) Zhan, Y.-L.; Shen, Y.-B.; Li, S.-P.; Yue, B.-H.; Zhou, X.-C. Hydrogen Generation from Methanol Reforming Under Unprecedented Mild Conditions. *Chin. Chem. Lett.* **2017**, *28* (7), 1353–1357.
- (240) Hao, J.; Liu, J.; Wu, D.; Chen, M.; Liang, Y.; Wang, Q.; Wang, L.; Fu, X.-Z.; Luo, J.-L. In Situ Facile Fabrication of Ni(OH)₂ Nanosheet Arrays for Electrocatalytic Co-Production of Formate and Hydrogen From Methanol in Alkaline Solution. *Appl. Catal. B Environ.* **2021**, *281*, 119510.
- (241) Li, S.; Ma, R.; Hu, J.; Li, Z.; Liu, L.; Wang, X.; Lu, Y.; Sterbinsky, G. E.; Liu, S.; Zheng, L.; Liu, J.; Liu, D.; Wang, J. Coordination Environment Tuning of Nickel Sites by Oxyanions to Optimize Methanol Electro-Oxidation Activity. *Nat. Commun.* **2022**, *13* (1), 2916.
- (242) Tong, Y.; Yan, X.; Liang, J.; Dou, S. X. Metal-Based Electrocatalysts for Methanol Electro-Oxidation: Progress, Opportunities, and Challenges. *Small* **2021**, *17* (9), 1904126.
- (243) Varcoe, J. R.; Slade, R. C. T. Prospects for Alkaline Anion-Exchange Membranes in Low Temperature Fuel Cells. *Fuel Cells* **2005**, *5* (2), 187–200.
- (244) Tripković, A. V.; Popović, K. D.; Grgur, B. N.; Bliznac, B.; Ross, P. N.; Marković, N. M. Methanol Electrooxidation on Supported Pt and PtRu Catalysts in Acid and Alkaline Solutions. *Electrochim. Acta* **2002**, *47* (22), 3707–3714.
- (245) Liu, C.; Hirohara, M.; Maekawa, T.; Chang, R.; Hayashi, T.; Chiang, C.-Y. Selective Electro-Oxidation of Glycerol to Dihydroxyacetone by a Non-precious Electrocatalyst - CuO. *Appl. Catal. B: Env.* **2020**, *265*, 118543.
- (246) Kwon, Y.; Birdja, Y.; Spanos, I.; Rodriguez, P.; Koper, M. T. M. Highly Selective Electro-Oxidation of Glycerol to Dihydroxyacetone on Platinum in the Presence of Bismuth. *ACS Catal.* **2012**, *2* (5), 759–764.
- (247) Baravkar, M. D.; Prasad, B. L. V. Selective Electro-Oxidation of Phenol to 1,4-Hydroquinone Employing Carbonaceous Electrodes: Surface Modification is the Key. *New J. Chem.* **2022**, *46* (5), 2518–2525.
- (248) Barone, M. R.; Jones, A. M. Selective C-H Bond Electro-Oxidation of Benzylic Acetates and Alcohols to Benzaldehydes. *Org. Biomol. Chem.* **2017**, *15* (47), 10010–10015.
- (249) Tang, D.; Lu, G.; Shen, Z.; Hu, Y.; Yao, L.; Li, B.; Zhao, G.; Peng, B.; Huang, X. A Review on Photo-, Electro- and Photoelectrocatalytic Strategies for Selective Oxidation of Alcohols. *J. Energy Chem.* **2023**, *77*, 80–118.
- (250) Zirbes, M.; Schmitt, D.; Beiser, N.; Pitton, D.; Hoffmann, T.; Waldvogel, S. R. Anodic Degradation of Lignin at Active Transition Metal-based Alloys and Performance-enhanced Anodes. *ChemElectroChem.* **2019**, *6* (1), 155–161.
- (251) Tolba, R.; Tian, M.; Wen, J.; Jiang, Z.-H.; Chen, A. Electrochemical Oxidation of Lignin at IrO₂-Based Oxide Electrodes. *J. Electroanal. Chem.* **2010**, *649* (1), 9–15.
- (252) Parpot, P.; Bettencourt, A. P.; Carvalho, A. M.; Belgsir, E. M. Biomass Conversion: Attempted Electrooxidation of Lignin for Vanillin Production. *J. Appl. Electrochem.* **2000**, *30* (6), 727–731.
- (253) Lan, C.; Fan, H.; Shang, Y.; Shen, D.; Li, G. Electrochemically Catalyzed Conversion of Cornstalk Lignin to Aromatic Compounds: An Integrated Process of Anodic Oxidation of a Pb/PbO₂ Electrode and Hydrogenation of a Nickel Cathode in Sodium Hydroxide Solution. *Sustain. Energy Fuels* **2020**, *4* (4), 1828–1836.
- (254) Ghahremani, R.; Farales, F.; Bateni, F.; Staser, J. A. Simultaneous Hydrogen Evolution and Lignin Depolymerization using NiSn Electrocatalysts in a Biomass-Depolarized Electrolyzer. *J. Electrochem. Soc.* **2020**, *167* (4), 043502.
- (255) Samet, Y.; Abdelhedi, R.; Savall, A. A Study of the Electrochemical Oxidation of Guaiacol. *Phys. Chem. News* **2002**, *8*, 89–99.
- (256) Zhou, H.; Li, Z.; Xu, S.-M.; Lu, L.; Xu, M.; Ji, K.; Ge, R.; Yan, Y.; Ma, L.; Kong, X.; et al. Selectively Upgrading Lignin Derivatives to Carboxylates through Electrochemical Oxidative C(OH)–C Bond Cleavage by a Mn-Doped Cobalt Oxyhydroxide Catalyst. *Angew. Chem., Int. Ed.* **2021**, *60* (16), 8976–8982.
- (257) Centi, G.; Cavani, F.; Trifirò, F. *Selective Oxidation by Heterogeneous Catalysis*; Springer: New York, 2001; DOI: 10.1007/978-1-4615-4175-2.
- (258) Miedziak, P. J.; Patisson, S.; Edwards, J. K.; Tarbit, B.; Taylor, S. H.; Hutchings, G. J. The over-Riding Role of Autocatalysis in Allylic Oxidation. *Catal. Lett.* **2022**, *152* (4), 1003–1008.
- (259) Pavan, M. J.; Fridman, H.; Segalovich, G.; Shames, A. I.; Lemcoff, N. G.; Mokari, T. Photooxidation of Benzyl Alcohol with Heterogeneous Photocatalysts in the UV Range: The Complex Interplay with the Autoxidative Reaction. *ChemCatChem.* **2018**, *10* (12), 2541–2545.
- (260) Liu, C.; Xiao, Z.; Wu, S.; Shen, Y.; Yuan, K.; Ding, Y. Anodically Triggered Aldehyde Cation Autocatalysis for Alkylation of Heteroarenes. *ChemSusChem* **2020**, *13* (8), 1997–2001.
- (261) Li, M.; Deng, X.; Liang, Y.; Xiang, K.; Wu, D.; Zhao, B.; Yang, H.; Luo, J.-L.; Fu, X.-Z. Co_xP@NiCo-Ldh Heteronanosheet Arrays as Efficient Bifunctional Electrocatalysts for Co-Generation of Value-Added Formate and Hydrogen with Less-Energy Consumption. *J. Energy Chem.* **2020**, *50*, 314–323.
- (262) Chen, Y. X.; Lavacchi, A.; Miller, H. A.; Bevilacqua, M.; Filippi, J.; Innocenti, M.; Marchionni, A.; Oberhauser, W.; Wang, L.; Vizza, F. Nanotechnology Makes Biomass Electrolysis More Energy Efficient Than Water Electrolysis. *Nat. Commun.* **2014**, *5* (1), 4036.
- (263) Zhao, X.; Dai, L.; Qin, Q.; Pei, F.; Hu, C.; Zheng, N. Self-Supported 3D PdCu Alloy Nanosheets as a Bifunctional Catalyst for Electrochemical Reforming of Ethanol. *Small* **2017**, *13* (12), 1602970.
- (264) Dai, L.; Qin, Q.; Zhao, X.; Xu, C.; Hu, C.; Mo, S.; Wang, Y. O.; Lin, S.; Tang, Z.; Zheng, N. Electrochemical Partial Reforming of Ethanol into Ethyl Acetate Using Ultrathin Co₃O₄ Nanosheets as a Highly Selective Anode Catalyst. *ACS Cent. Sci.* **2016**, *2* (8), 538–544.
- (265) Zhao, Y.; Xing, S.; Meng, X.; Zeng, J.; Yin, S.; Li, X.; Chen, Y. Ultrathin Rh Nanosheets as a Highly Efficient Bifunctional Electrocatalyst for Isopropanol-Assisted Overall Water Splitting. *Nanoscale* **2019**, *11* (19), 9319–9326.
- (266) Chadderdon, D. J.; Xin, L.; Qi, J.; Brady, B.; Miller, J. A.; Sun, K.; Janik, M. J.; Li, W. Selective Oxidation of 1,2-Propanediol in Alkaline Anion-Exchange Membrane Electrocatalytic Flow Reactors: Experimental and DFT Investigations. *ACS Catal.* **2015**, *5* (11), 6926–6936.
- (267) González-Cobos, J.; Baranton, S.; Coutanceau, C. Development of Bismuth-Modified Ptpd Nanocatalysts for the Electrochemical Reforming of Polyols into Hydrogen and Value-Added Chemicals. *ChemElectroChem* **2016**, *3* (10), 1694–1704.
- (268) Rafaïdeen, T.; Baranton, S.; Coutanceau, C. Pd-Shaped Nanoparticles Modified by Gold ad-Atoms: Effects on Surface Structure and Activity Toward Glucose Electrooxidation. *Front. Chem.* **2019**, *7*, 453.

- (269) Yu, L.; Akolkar, R. Lead Underpotential Deposition for the Surface Characterization of Silver Ad-Atom Modified Gold Electrocatalysts for Glucose Oxidation. *J. Electroanal. Chem.* **2017**, *792*, 61–65.
- (270) Du, P.; Zhang, J.; Liu, Y.; Huang, M. Hydrogen Generation from Catalytic Glucose Oxidation by Fe-Based Electrocatalysts. *Electrochem. Commun.* **2017**, *83*, 11–15.
- (271) Lin, C.; Zhang, P.; Wang, S.; Zhou, Q.; Na, B.; Li, H.; Tian, J.; Zhang, Y.; Deng, C.; Meng, L.; et al. Engineered Porous Co-Ni Alloy on Carbon Cloth as an Efficient Bifunctional Electrocatalyst for Glucose Electrolysis in Alkaline Environment. *J. Alloys Compd.* **2020**, *823*, 153784.
- (272) Bielski, R.; Gryniewicz, G. Furan Platform Chemicals Beyond Fuels and Plastics. *Green Chem.* **2021**, *23* (19), 7458–7487.
- (273) Liu, H.; Lee, T.-H.; Chen, Y.; Cochran, E. W.; Li, W. Paired and Tandem Electrochemical Conversion of 5-(Hydroxymethyl)-Furfural Using Membrane-Electrode Assembly-Based Electrolytic Systems. *ChemElectroChem.* **2021**, *8* (15), 2817–2824.
- (274) Holade, Y.; Tuleushova, N.; Tingry, S.; Servat, K.; Napporn, T. W.; Guesmi, H.; Cornu, D.; Kokoh, K. B. Recent Advances in the Electrooxidation of Biomass-Based Organic Molecules for Energy, Chemicals and Hydrogen Production. *Catal. Sci. Technol.* **2020**, *10* (10), 3071–3112.
- (275) Jiang, N.; Liu, X.; Dong, J.; You, B.; Liu, X.; Sun, Y. Electrocatalysis of Furfural Oxidation Coupled with H₂ Evolution Via Nickel-Based Electrocatalysts in Water. *ChemNanoMat* **2017**, *3* (7), 491–495.
- (276) You, B.; Liu, X.; Jiang, N.; Sun, Y. A General Strategy for Decoupled Hydrogen Production from Water Splitting by Integrating Oxidative Biomass Valorization. *J. Am. Chem. Soc.* **2016**, *138* (41), 13639–13646.
- (277) You, B.; Jiang, N.; Liu, X.; Sun, Y. Simultaneous H₂ Generation and Biomass Upgrading in Water by an Efficient Noble-Metal-Free Bifunctional Electrocatalyst. *Angew. Chem., Int. Ed.* **2016**, *55* (34), 9913–9917.
- (278) Ferreira, A. P. R. A.; Oliveira, R. C. P.; Mateus, M. M.; Santos, D. M. F. A Review of the Use of Electrolytic Cells for Energy and Environmental Applications. *Energies* **2023**, *16* (4), 1593.
- (279) Garedeew, M.; Lin, F.; Song, B.; DeWinter, T. M.; Jackson, J. E.; Saffron, C. M.; Lam, C. H.; Anastas, P. T. Greener Routes to Biomass Waste Valorization: Lignin Transformation through Electrocatalysis for Renewable Chemicals and Fuels Production. *ChemSusChem* **2020**, *13* (17), 4214–4237.
- (280) Caravaca, A.; Garcia-Lorence, W. E.; Gil, S.; de Lucas-Consuegra, A.; Vernoux, P. Towards a Sustainable Technology for H₂ Production: Direct Lignin Electrolysis in a Continuous-Flow Polymer Electrolyte Membrane Reactor. *Electrochem. Commun.* **2019**, *100*, 43–47.
- (281) Khalid, M.; De, B. S.; Singh, A.; Shahgaldi, S. Lignin Electrolysis at Room Temperature on Nickel Foam for Hydrogen Generation: Performance Evaluation and Effect of Flow Rate. *Catalysts* **2022**, *12* (12), 1646.
- (282) Du, X.; Liu, W.; Zhang, Z.; Mulyadi, A.; Brittain, A.; Gong, J.; Deng, Y. Low-Energy Catalytic Electrolysis for Simultaneous Hydrogen Evolution and Lignin Depolymerization. *ChemSusChem* **2017**, *10* (5), 847–854.
- (283) Wang, Y.-s.; Yang, F.; Liu, Z.-h.; Yuan, L.; Li, G. Electrocatalytic Degradation of Aspen Lignin over Pb/PbO₂ Electrode in Alkali Solution. *Catal. Commun.* **2015**, *67*, 49–53.
- (284) Chakthranont, P.; Woraphutthaporn, S.; Sanpitakseree, C.; Srisawad, K.; Faungnawakij, K. Kilogram-Scale Production of High Purity 2,5-Furandicarboxylic Acid Via Sustainable Leap in Continuous Electrochemical Oxidation of 5-Hydroxymethylfurfural. *Chem. Eng. J.* **2023**, *476*, 146478.
- (285) Kwon, Y.; Schouten, K. J. P.; Koper, M. T. M. Mechanism of the Catalytic Oxidation of Glycerol on Polycrystalline Gold and Platinum Electrodes. *ChemCatChem.* **2011**, *3* (7), 1176–1185.
- (286) de Souza, M. B. C.; Vicente, R. A.; Yukuhiro, V. Y.; V. M. T. Pires, C. T. G.; Cheuquepán, W.; Bott-Neto, J. L.; Solla-Gullón, J.; Fernández, P. S. Bi-Modified Pt Electrodes toward Glycerol Electrooxidation in Alkaline Solution: Effects on Activity and Selectivity. *ACS Catal.* **2019**, *9* (6), 5104–5110.
- (287) Hauke, P.; Klingenhof, M.; Wang, X.; de Araújo, J. F.; Strasser, P. Efficient Electrolysis of 5-Hydroxymethylfurfural to the Biopolymer-Precursor Furandicarboxylic Acid in a Zero-Gap Mea-Type Electrolyzer. *Cell Rep. Phys. Sci.* **2021**, *2* (12), 100650.
- (288) Suzuki, N. Y.; Santiago, P. V. B.; Galhardo, T. S.; Carvalho, W. A.; Souza-Garcia, J.; Angelucci, C. A. Insights of Glycerol Electrooxidation on Polycrystalline Silver Electrode. *J. Electroanal. Chem.* **2016**, *780*, 391–395.
- (289) Kubota, S. R.; Choi, K.-S. Electrochemical Valorization of Furfural to Maleic Acid. *ACS Sustainable Chem. Eng.* **2018**, *6* (8), 9596–9600.
- (290) Hasan, M.; Akbari, A.; Greenlee, L. F. Combined Electrocatalytic Oxidation and Reduction to Selectively Cleave β -O-4 Linkage of Lignin over Platinum Electrode in Organic Solvent: Secondary Treatment Opportunity for Celp Process. *ACS Sustainable Chem. Eng.* **2023**, *11* (42), 15262–15272.
- (291) Ma, L.; Zhou, H.; Kong, X.; Li, Z.; Duan, H. An Electrocatalytic Strategy for C-C Bond Cleavage in Lignin Model Compounds and Lignin under Ambient Conditions. *ACS Sustainable Chem. Eng.* **2021**, *9* (4), 1932–1940.
- (292) Li, P.; Zhou, H.; Tao, Y.; Ren, J.; Wu, C.; Wu, W. Recent Development and Perspectives of Solvents and Electrode Materials for Electrochemical Oxidative Degradation of Lignin. *Electroanalysis* **2022**, *34* (10), 1529–1539.
- (293) Reichert, E.; Wintringer, R.; Volmer, D. A.; Hempelmann, R. Electro-Catalytic Oxidative Cleavage of Lignin in a Protic Ionic Liquid. *Phys. Chem. Chem. Phys.* **2012**, *14* (15), 5214–5221.
- (294) Liu, G.; Wang, Q.; Yan, D.; Zhang, Y.; Wang, C.; Liang, S.; Jiang, L.; He, H. Insights into the Electrochemical Degradation of Phenolic Lignin Model Compounds in a Protic Ionic Liquid-Water System. *Green Chem.* **2021**, *23* (4), 1665–1677.
- (295) Liu, G.; Lu, Y.; Lu, J.; Wang, Y.; Liang, S.; He, H.; Jiang, L. Ionic Liquid-Trimetallic Electrocatalytic System for C-O Bond Cleavage in Lignin Model Compounds and Lignin under Ambient Conditions. *Nano Res.* **2024**, *17* (4), 2420–2428.
- (296) Zhu, Y.; Zhu, Y.; Zeng, H.; Chen, Z.; Little, R. D.; Ma, C. a. A Promising Electro-Oxidation of Methyl-Substituted Aromatic Compounds to Aldehydes in Aqueous Imidazole Ionic Liquid Solutions. *J. Electroanal. Chem.* **2015**, *751*, 105–110.
- (297) Liu, Y.; Deak, N.; Wang, Z.; Yu, H.; Hamelers, L.; Jurak, E.; Deuss, P. J.; Barta, K. Tunable and Functional Deep Eutectic Solvents for Lignocellulose Valorization. *Nat. Commun.* **2021**, *12* (1), 5424.
- (298) Kohli, K.; Katuwal, S.; Biswas, A.; Sharma, B. K. Effective Delignification of Lignocellulosic Biomass by Microwave Assisted Deep Eutectic Solvents. *Bioresour. Technol.* **2020**, *303*, 122897.
- (299) Di Marino, D.; Stöckmann, D.; Kriescher, S.; Stiefel, S.; Wessling, M. Electrochemical Depolymerisation of Lignin in a Deep Eutectic Solvent. *Green Chem.* **2016**, *18* (22), 6021–6028.
- (300) Sirés, I.; Brillas, E.; Oturan, M. A.; Rodrigo, M. A.; Panizza, M. Electrochemical Advanced Oxidation Processes: Today and Tomorrow. A Review. *Environ. Sci. Pollut. Res.* **2014**, *21* (14), 8336–8367.
- (301) Dewil, R.; Mantzavinos, D.; Poullos, I.; Rodrigo, M. A. New Perspectives for Advanced Oxidation Processes. *J. Environ. Manage.* **2017**, *195*, 93–99.
- (302) Barrera-Díaz, C.; Cañizares, P.; Fernández, F. J.; Natividad, R.; Rodrigo, M. A. Electrochemical Advanced Oxidation Processes: An Overview of the Current Applications to Actual Industrial Effluents. *J. Mex. Chem. Soc.* **2017**, *58* (3), 256–275.
- (303) Ma, Z.; Wang, L.; Li, G.; Song, T. Recent Advances in Electrocatalytic Oxidation of 5-Hydroxymethylfurfural to 2,5-Furandicarboxylic Acid by Heterogeneous Catalysts. *Catalysts* **2024**, *14* (2), 157.
- (304) Sherbo, R. S.; Delima, R. S.; Chiykowski, V. A.; MacLeod, B. P.; Berlinguette, C. P. Complete Electron Economy by Pairing Electrolysis with Hydrogenation. *Nat. Catal.* **2018**, *1* (7), 501–507.

- (305) Li, Z.; Yan, Y.; Xu, S.-M.; Zhou, H.; Xu, M.; Ma, L.; Shao, M.; Kong, X.; Wang, B.; Zheng, L.; Duan, H. Alcohols Electrooxidation Coupled with H₂ Production at High Current Densities Promoted by a Cooperative Catalyst. *Nat. Commun.* **2022**, *13* (1), 147.
- (306) Yin, K.; Chao, Y.; Lv, F.; Tao, L.; Zhang, W.; Lu, S.; Li, M.; Zhang, Q.; Gu, L.; Li, H.; et al. One Nanometer PtIr Nanowires as High-Efficiency Bifunctional Catalysts for Electrosynthesis of Ethanol into High Value-Added Multicarbon Compound Coupled with Hydrogen Production. *J. Am. Chem. Soc.* **2021**, *143* (29), 10822–10827.
- (307) Li, Y.; Wei, X.; Chen, L.; Shi, J.; He, M. Nickel-Molybdenum Nitride Nanoplate Electrocatalysts for Concurrent Electrolytic Hydrogen and Formate Productions. *Nat. Commun.* **2019**, *10* (1), 5335.
- (308) Xie, Y.; Zhou, Z.; Yang, N.; Zhao, G. An Overall Reaction Integrated with Highly Selective Oxidation of 5-Hydroxymethylfurfural and Efficient Hydrogen Evolution. *Adv. Funct. Mater.* **2021**, *31* (34), 2102886.
- (309) Sun, Y.; Wang, J.; Qi, Y.; Li, W.; Wang, C. Efficient Electrooxidation of 5-Hydroxymethylfurfural Using Co-Doped Ni₃S₂ Catalyst: Promising for H₂ Production under Industrial-Level Current Density. *Adv. Sci.* **2022**, *9* (17), 2200957.
- (310) Choi, S.; Balamurugan, M.; Lee, K.-G.; Cho, K. H.; Park, S.; Seo, H.; Nam, K. T. Mechanistic Investigation of Biomass Oxidation Using Nickel Oxide Nanoparticles in a CO₂-Saturated Electrolyte for Paired Electrolysis. *J. Phys. Chem. Lett.* **2020**, *11* (8), 2941–2948.
- (311) Bi, J.; Zhu, Q.; Guo, W.; Li, P.; Jia, S.; Liu, J.; Ma, J.; Zhang, J.; Liu, Z.; Han, B. Simultaneous CO₂ Reduction and 5-Hydroxymethylfurfural Oxidation to Value-Added Products by Electrocatalysis. *ACS Sustainable Chem. Eng.* **2022**, *10* (24), 8043–8050.
- (312) Xu, G.-R.; Batmunkh, M.; Donne, S.; Jin, H.; Jiang, J.-X.; Chen, Y.; Ma, T. Ruthenium(III) Polyethyleneimine Complexes for Bifunctional Ammonia Production and Biomass Upgrading. *J. Mater. Chem. A* **2019**, *7* (44), 25433–25440.
- (313) Liu, S.-Q.; Gao, M.-R.; Wu, S.; Feng, R.; Wang, Y.; Cui, L.; Guo, Y.; Fu, X.-Z.; Luo, J.-L. A Coupled Electrocatalytic System with Reduced Energy Input for CO₂ Reduction and Biomass Valorization. *Energy Environ. Sci.* **2023**, *16* (11), 5305–5314.
- (314) Liu, F.; Gao, X.; Guo, Z.; Tse, E. C. M.; Chen, Y. Sustainable Adipic Acid Production Via Paired Electrolysis of Lignin-Derived Phenolic Compounds with Water as Hydrogen and Oxygen Sources. *J. Am. Chem. Soc.* **2024**, *146* (22), 15275–15285.
- (315) Zhang, P.; Sheng, X.; Chen, X.; Fang, Z.; Jiang, J.; Wang, M.; Li, F.; Fan, L.; Ren, Y.; Zhang, B.; et al. Paired Electrocatalytic Oxygenation and Hydrogenation of Organic Substrates with Water as the Oxygen and Hydrogen Source. *Angew. Chem., Int. Ed.* **2019**, *58* (27), 9155–9159.
- (316) Ampelli, C.; Tavella, F.; Giusi, D.; Ronsisvalle, A. M.; Perathoner, S.; Centi, G. Electrode and Cell Design for CO₂ Reduction: A Viewpoint. *Catal. Today* **2023**, *421*, 114217.
- (317) Kleinhaus, J. T.; Wolf, J.; Pellumbi, K.; Wickert, L.; Viswanathan, S. C.; Junge Puring, K.; Siegmund, D.; Apfel, U.-P. Developing Electrochemical Hydrogenation Towards Industrial Application. *Chem. Soc. Rev.* **2023**, *52* (21), 7305–7332.
- (318) Han, G.; Li, G.; Sun, Y. Electrocatalytic Dual Hydrogenation of Organic Substrates with a Faradaic Efficiency Approaching 200%. *Nat. Catal.* **2023**, *6* (3), 224–233.
- (319) Stankovic, M. D.; Sperry, J. F.; Delima, R. S.; Rupnow, C. C.; Rooney, M. B.; Stolar, M.; Berlinguette, C. P. Electrochemical Production of Methyltetrahydrofuran, a Biofuel for Diesel Engines. *Energy Environ. Sci.* **2023**, *16* (8), 3453–3461.
- (320) Delima, R. S.; Stankovic, M. D.; MacLeod, B. P.; Fink, A. G.; Rooney, M. B.; Huang, A.; Jansonius, R. P.; Dvorak, D. J.; Berlinguette, C. P. Selective Hydrogenation of Furfural Using a Membrane Reactor. *Energy Environ. Sci.* **2022**, *15* (1), 215–224.
- (321) Itoh, N.; Xu, W. C.; Hara, S.; Sakaki, K. Electrochemical Coupling of Benzene Hydrogenation and Water Electrolysis. *Catal. Today* **2000**, *56* (1), 307–314.
- (322) Mitsushima, S.; Takakuwa, Y.; Nagasawa, K.; Sawaguchi, Y.; Kohno, Y.; Matsuzawa, K.; Awaludin, Z.; Kato, A.; Nishiki, Y. Membrane Electrolysis of Toluene Hydrogenation with Water Decomposition for Energy Carrier Synthesis. *Electrocatal.* **2016**, *7* (2), 127–131.
- (323) Takano, K.; Tateno, H.; Matsumura, Y.; Fukazawa, A.; Kashiwagi, T.; Nakabayashi, K.; Nagasawa, K.; Mitsushima, S.; Atobe, M. Electrocatalytic Hydrogenation of Toluene Using a Proton Exchange Membrane Reactor. *Bull. Chem. Soc. Jpn.* **2016**, *89* (10), 1178–1183.
- (324) Imada, T.; Iida, Y.; Ueda, Y.; Chiku, M.; Higuchi, E.; Inoue, H. Electrochemical Toluene Hydrogenation Using Binary Platinum-Based Alloy Nanoparticle-Loaded Carbon Catalysts. *Catalysts* **2021**, *11* (3), 318.
- (325) Inami, Y.; Ogihara, H.; Yamanaka, I. Selective Electrohydrogenation of Toluene to Methylcyclohexane Using Carbon-Supported Non-Platinum Electrocatalysts in the Hydrogen Storage System. *Chem. Select* **2017**, *2* (5), 1939–1943.
- (326) Inami, Y.; Ogihara, H.; Nagamatsu, S.; Asakura, K.; Yamanaka, I. Synergy of Ru and Ir in the Electrohydrogenation of Toluene to Methylcyclohexane on a Ketjenblack-Supported Ru-Ir Alloy Cathode. *ACS Catal.* **2019**, *9* (3), 2448–2457.
- (327) Inami, Y.; Ogihara, H.; Yamanaka, I. Effects of Carbon Supports on Ru Electrocatalysis for the Electrohydrogenation of Toluene to Methylcyclohexane. *Electrocatal.* **2018**, *9* (2), 204–211.
- (328) Inami, Y.; Iguchi, S.; Nagamatsu, S.; Asakura, K.; Yamanaka, I. Disposition of Iridium on Ruthenium Nanoparticle Supported on Ketjenblack: Enhancement in Electrocatalytic Activity toward the Electrohydrogenation of Toluene to Methylcyclohexane. *ACS Omega* **2020**, *5* (2), 1221–1228.
- (329) Nagasawa, K.; Kato, A.; Nishiki, Y.; Matsumura, Y.; Atobe, M.; Mitsushima, S. The Effect of Flow-Field Structure in Toluene Hydrogenation Electrolyzer for Energy Carrier Synthesis System. *Electrochim. Acta* **2017**, *246*, 459–465.
- (330) Nagasawa, K.; Sugita, Y.; Atienza-Márquez, A.; Kuroda, Y.; Mitsushima, S. Effect of the Cathode Catalyst Loading on Mass Transfer in Toluene Direct Electrohydrogenation. *J. Electroanal. Chem.* **2023**, *938*, 117431.
- (331) Shigemasa, K.; Atienza-Márquez, A.; Inoue, K.; Jang, S.; Peña, F. I. R.; Araki, T.; Terao, T.; Nagasawa, K.; Mitsushima, S. Visualization of Dragged Water and Generated Hydrogen Bubbles in a Direct Toluene Electro-Hydrogenation Electrolyzer. *J. Power Sources* **2023**, *554*, 232304.
- (332) Reyna-Peña, F. I.; Atienza-Márquez, A.; Jang, S.; Shiono, R.; Shigemasa, K.; Araki, T.; Nagasawa, K.; Mitsushima, S. In Situ X-Ray Ct Visualization of Hydrogen Bubbles inside the Porous Transport Layer of a Direct Toluene Electro-Hydrogenation Electrolyzer. *Int. J. Hydrogen Energy* **2024**, *50*, 787–798.
- (333) Nagasawa, K.; Sawaguchi, Y.; Kato, A.; Nishiki, Y.; Mitsushima, S. Chemical-Hydrogenation Functionalized Flow-Field in Toluene Direct Electro-Hydrogenation Electrolyzer for Energy-Carrier Synthesis System. *Electrochem.* **2018**, *86* (6), 339–344.
- (334) Wang, Y.; Tian, X.; Wang, S.; Cui, C.; Xin, Y.; Zhang, G.; Zhou, C. In Situ-Synthesized Amorphous Pd/N-C Microspheres Derived from Shrimp Shells as a Three-dimensional Electrocatalyst for Hydrodechlorination of Diclofenac. *Chem. Eng. J.* **2022**, *428*, 131231.
- (335) Koh, K.; Sanyal, U.; Lee, M.-S.; Cheng, G.; Song, M.; Glezakou, V.-A.; Liu, Y.; Li, D.; Rousseau, R.; Gutiérrez, O. Y.; et al. Electrochemically Tunable Proton-Coupled Electron Transfer in Pd-Catalyzed Benzaldehyde Hydrogenation. *Angew. Chem. Int. Ed.* **2020**, *59* (4), 1501–1505.
- (336) Chen, Y.; Liu, Z.; Liu, S.; Cheng, Y.; Zhang, C.; Jiao, J.; Lu, Y.; Wang, W.; Sun, K.; Bi, X.; et al. In-Situ Doping-Induced Crystal Form Transition of Amorphous Pd-P Catalyst for Robust Electrocatalytic Hydrodechlorination. *Appl. Catal., B* **2021**, *284*, 119713.
- (337) Brosnahan, J. T.; Zhang, Z.; Yin, Z.; Zhang, S. Electrocatalytic Reduction of Furfural with High Selectivity to Furfuryl Alcohol Using Agpd Alloy Nanoparticles. *Nanoscale* **2021**, *13* (4), 2312–2316.

(338) Kurisingal, J. F.; Rachuri, Y.; Gu, Y.; Kim, G.-H.; Park, D.-W. Binary Metal–Organic Frameworks: Catalysts for the Efficient Solvent-Free CO₂ Fixation Reaction Via Cyclic Carbonates Synthesis. *Appl. Catal., A* **2019**, *571*, 1–11.

(339) Zhao, L.; Zhang, Y.; Huang, L.-B.; Liu, X.-Z.; Zhang, Q.-H.; He, C.; Wu, Z.-Y.; Zhang, L.-J.; Wu, J.; Yang, W.; Gu, L.; Hu, J.-S.; Wan, L.-J. Cascade Anchoring Strategy for General Mass Production of High-Loading Single-Atomic Metal–Nitrogen Catalysts. *Nat. Commun.* **2019**, *10* (1), 1278.

(340) Yang, X.-F.; Wang, A.; Qiao, B.; Li, J.; Liu, J.; Zhang, T. Single-Atom Catalysts: A New Frontier in Heterogeneous Catalysis. *Acc. Chem. Res.* **2013**, *46* (8), 1740–1748.

(341) Yang, H.; Wang, B.; Kou, S.; Lu, G.; Liu, Z. Mott-Schottky Heterojunction of Co/Co₂P with Built-in Electric Fields for Bifunctional Oxygen Electrocatalysis and Zinc-Air Battery. *Chem. Eng. J.* **2021**, *425*, 131589.

(342) Wang, S.; Uwakwe, K.; Yu, L.; Ye, J.; Zhu, Y.; Hu, J.; Chen, R.; Zhang, Z.; Zhou, Z.; Li, J.; Xie, Z.; Deng, D. Highly Efficient Ethylene Production Via Electrocatalytic Hydrogenation of Acetylene under Mild Conditions. *Nat. Commun.* **2021**, *12* (1), 7072.

(343) Zhou, Y.; Gao, Y.; Zhong, X.; Jiang, W.; Liang, Y.; Niu, P.; Li, M.; Zhuang, G.; Li, X.; Wang, J. Electrocatalytic Upgrading of Lignin-Derived Bio-Oil Based on Surface-Engineered Pt₁Nb Nanostructure. *Adv. Funct. Mater.* **2019**, *29* (10), 1807651.

(344) Wang, Q.; Jin, T.; Hu, Z.; Zhou, L.; Zhou, M. TiO₂-Nts/SnO₂-Sb Anode for Efficient Electrocatalytic Degradation of Organic Pollutants: Effect of TiO₂-Nts Architecture. *Sep. Purif. Technol.* **2013**, *102*, 180–186.

(345) Massa, A.; Hernández, S.; Lamberti, A.; Galletti, C.; Russo, N.; Fino, D. Electro-Oxidation of Phenol over Electrodeposited MnOx Nanostructures and the Role of a TiO₂ Nanotubes Interlayer. *Appl. Catal., B* **2017**, *203*, 270–281.

(346) Huang, L.; Li, D.; Liu, J.; Yang, L.; Dai, C.; Ren, N.; Feng, Y. Construction of TiO₂ Nanotube Clusters on Ti Mesh for Immobilizing Sb-SnO₂ to Boost Electrocatalytic Phenol Degradation. *J. Hazard. Mater.* **2020**, *393*, 122329.

(347) Hou, Y.; Qu, J.; Zhao, X.; Lei, P.; Wan, D.; Huang, C. P. Electro-Photocatalytic Degradation of Acid Orange Ii Using a Novel TiO₂/Acf Photoanode. *Sci. Total Environ.* **2009**, *407* (7), 2431–2439.

(348) Panić, V. V.; Dekanski, A. B.; Vidaković, T. R.; Mišković-Stanković, V. B.; Javanović, B. Ž.; Nikolić, B. Ž. Oxidation of Phenol on RuO₂-TiO₂/Ti Anodes. *J. Solid State Electrochem.* **2005**, *9* (1), 43–54.

(349) Jin, P.; Chang, R.; Liu, D.; Zhao, K.; Zhang, L.; Ouyang, Y. Phenol Degradation in an Electrochemical System with TiO₂/Activated Carbon Fiber as Electrode. *J. Environ. Chem. Eng.* **2014**, *2* (2), 1040–1047.

(350) He, Y.; Lin, H.; Guo, Z.; Zhang, W.; Li, H.; Huang, W. Recent Developments and Advances in Boron-Doped Diamond Electrodes for Electrochemical Oxidation of Organic Pollutants. *Sep. Purif. Technol.* **2019**, *212*, 802–821.