

A Novel Technique to Investigate Thermal-Induced Cracking in Cement under In-Situ Conditions for CCS Wells [PPT]

Li, K.; Pluymakers, A.M.H.

Publication date

2022

Document Version

Final published version

Citation (APA)

Li, K., & Pluymakers, A. M. H. (2022). *A Novel Technique to Investigate Thermal-Induced Cracking in Cement under In-Situ Conditions for CCS Wells [PPT]*. EGU General Assembly 2022, Vienna, Austria.

Important note

To cite this publication, please use the final published version (if applicable). Please check the document version above.

Copyright

Other than for strictly personal use, it is not permitted to download, forward or distribute the text or part of it, without the consent of the author(s) and/or copyright holder(s), unless the work is under an open content license such as Creative Commons.

Takedown policy

Please contact us and provide details if you believe this document breaches copyrights. We will remove access to the work immediately and investigate your claim.



ACT-CCS Project CEMENTTEGRITY

Project number: 327311-CLIMIT



A Novel Technique to Investigate Thermal-Induced Cracking in Cement under In-Situ Conditions for CCS Wells

Kai Li, Anne Pluymakers

Applied Geophysics & Petrophysics
Delft University of Technology, the Netherlands

24 May, 2022




See abstract
by scanning
← QR code




CEMENTTEGRITY

Introduction - Effects of thermal stresses on cement integrity

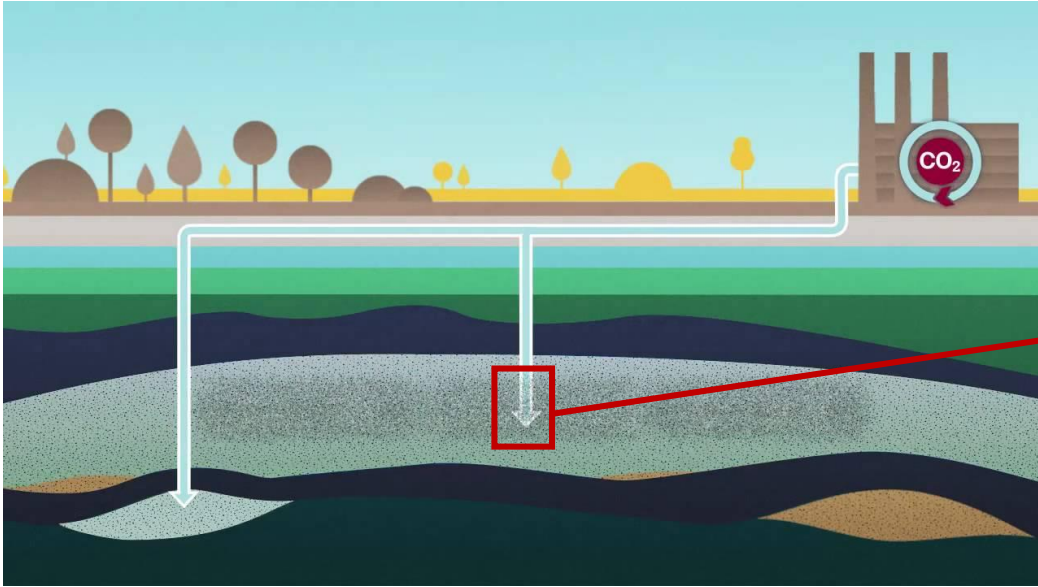

What happens to the subsurface wellbore and formation?

→ Reservoirs 1-4 km deep in the subsurface

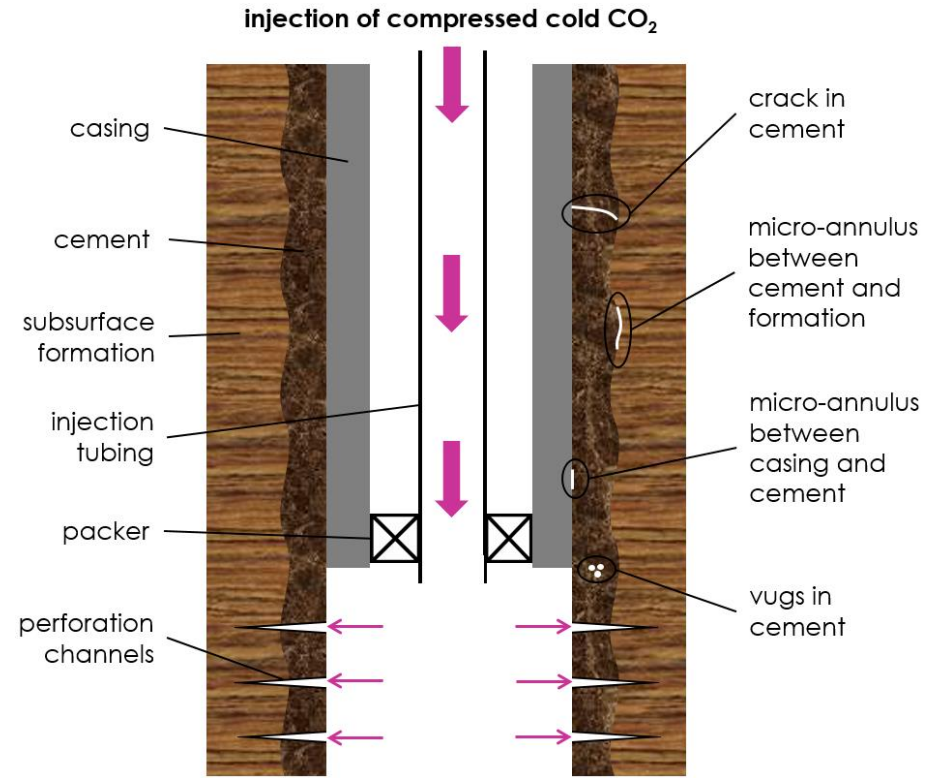


← Potential leakage pathways due to thermal stresses during CO₂ injection and storage in CCS.

→ Wellbore and subsurface formations cyclically contract and expand

- ❑ We investigate the thermal effects on the integrity of cement under in-situ conditions for CCS wells.
- ❑ To begin with, we present a novel technique to study effects of thermal shock under in-situ conditions.

Thermal effects without confinement

- Portland CEM I 42.5.
 - water-to-cement ratio: 0.3,
 - curing humidity at 96%,
 - curing P&T: 20°C, ambient pressure,
 - curing for or 28 days.
 - density 2.34 g/cm³.
- Heat the sample to 120°C.
- Quench it in 20°C water.
- Repeat the heating and quenching for 6 cycles.

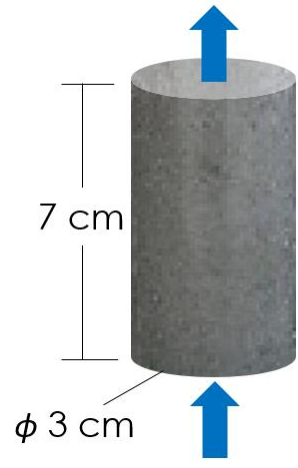


Intact sample




After thermal shocks

Thermal effects without confinement

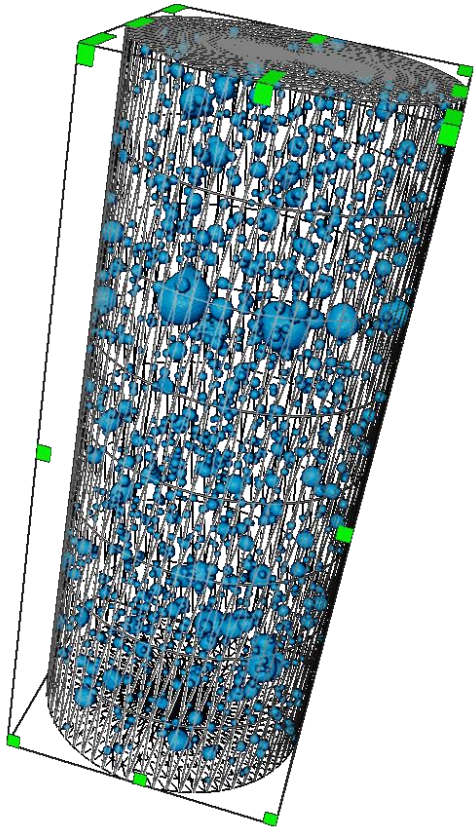


X-ray CT scan on intact sample. Pores shown in blue.

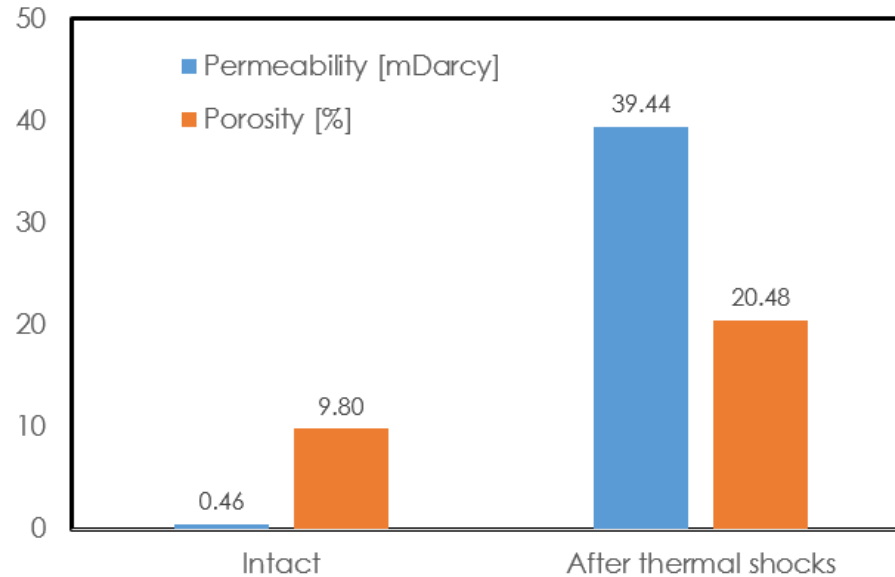

After thermal shocks, under no confinement:



- Micro-fractures develop and voids in cement are enlarged.
- We are working on reconstructing the microstructures of the cracks (aperture smaller than $30\ \mu\text{m}$) in images.

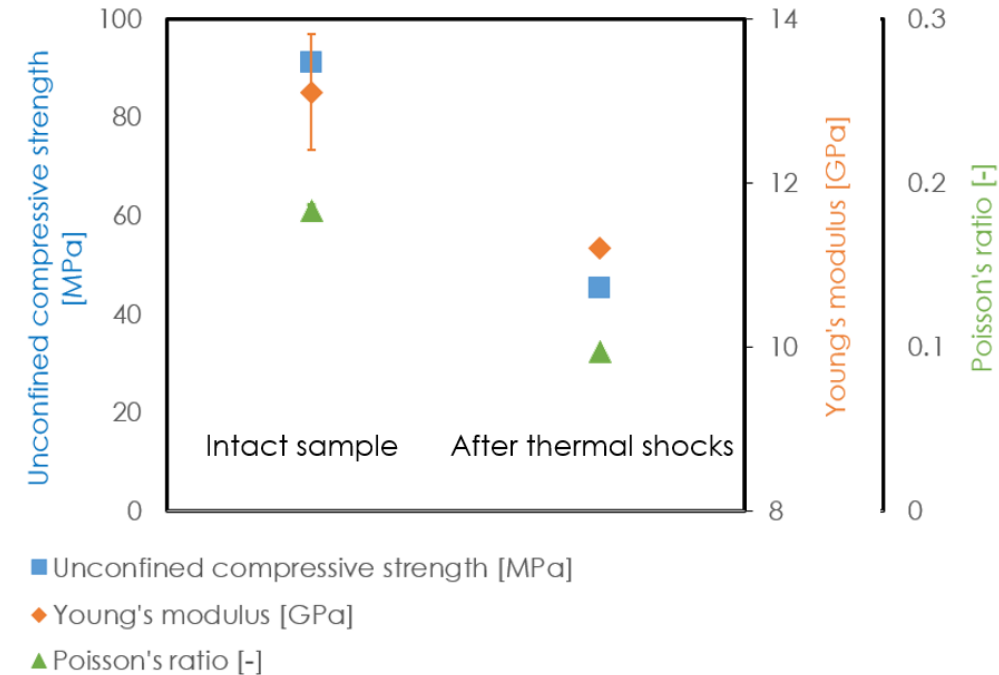

Thermal shocks impair the cement integrity.

- Conductivity increases.
- Cement weakens.


Triaxial deformation setup to study thermal shocks on cement under in-situ stresses and temperature

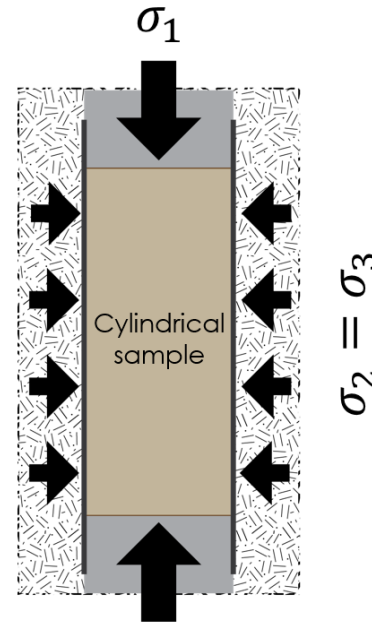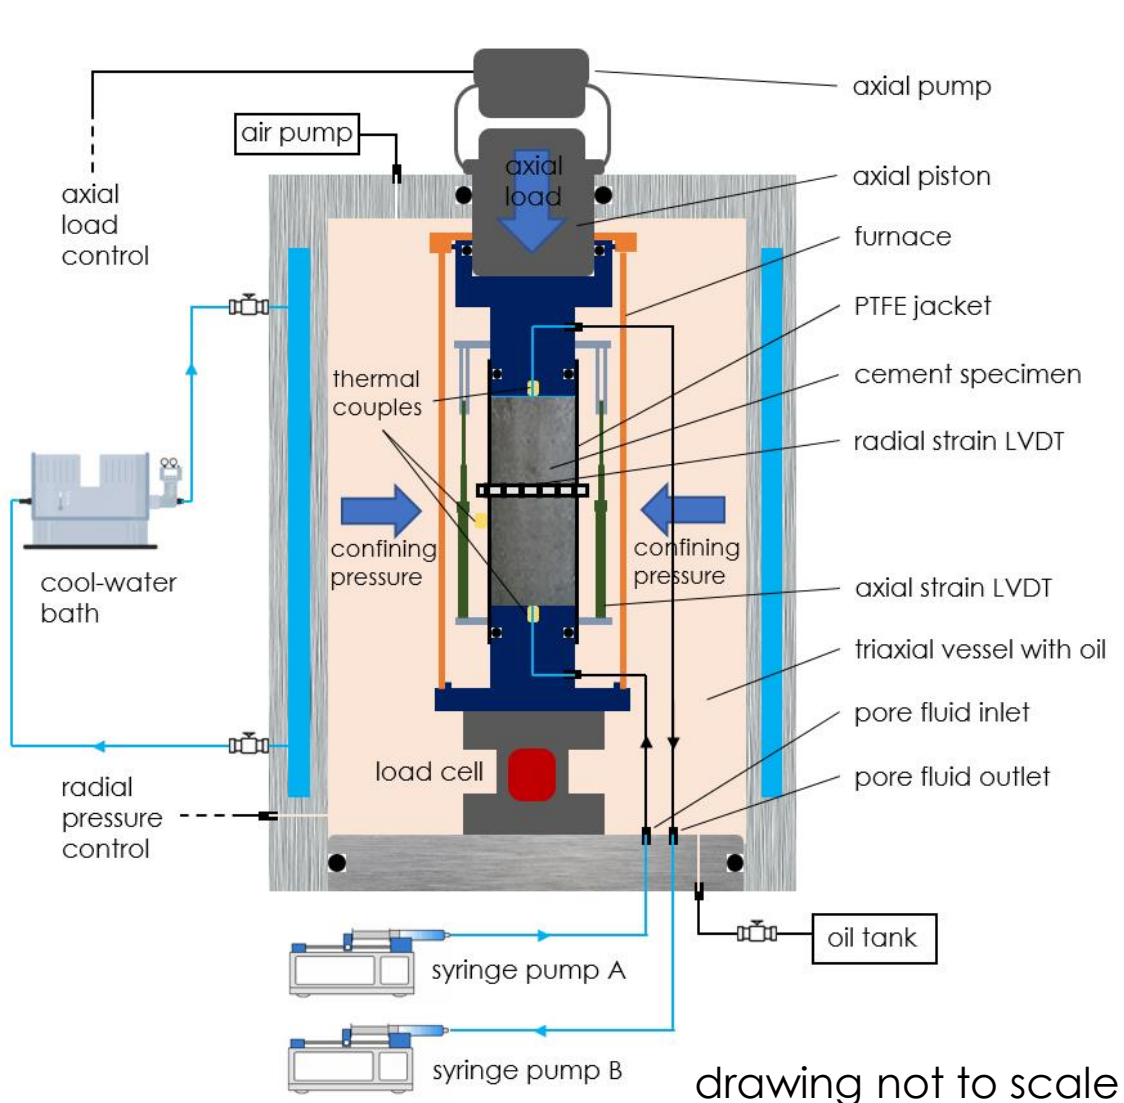

- Confining pressure up to 70 MPa, axial stress up to 424 MPa.
- Internal furnace for temperature up to 150°C.
- Triaxial vessel filled with heat-resistant oil that provides the confining pressure.
- Cold water through the sample using two pumps.
- Three linear variable differential transducers (LVDT) measure axial and radial deformation.
- Three thermocouples measure temperature.

Proof-of-concept test

Injection of 20°C water through red Pfaelzer sst core for 8 mins. Hydrostatic stresses of 15 MPa.

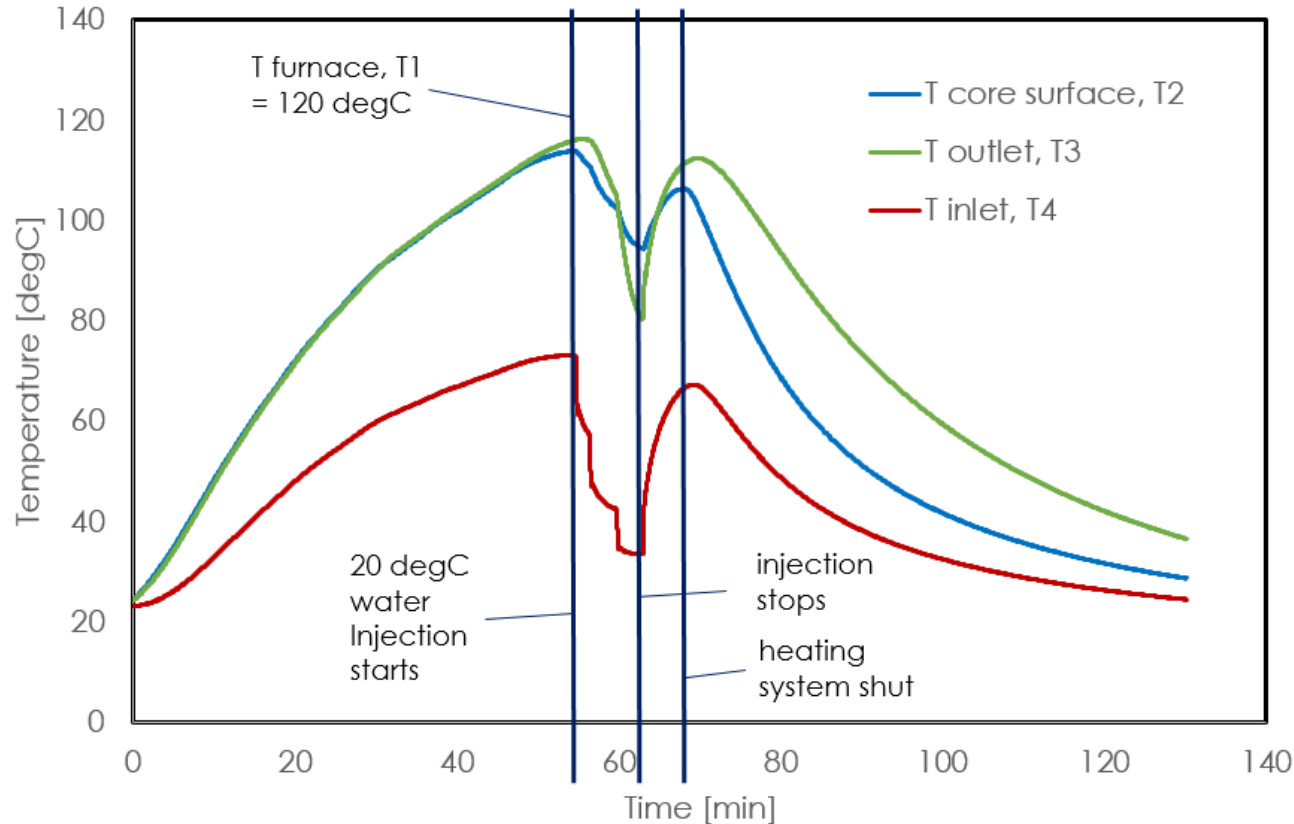

ΔT at inlet	40°C
ΔT at outlet	36°C
ΔT at core surface	19°C

- Temperature drops significantly at all locations.
- ΔT /time is important - Cracks happen because cement shrinks that create thermal stresses.
- ΔT /time depends on flow rate and T of injected water. SST is okay by increasing the flow rate. **How about cement – to drill a hole for flow-through.**
- Thermal expansion coefficient, thermal conductivity of the sample also affect on the cracking behavior.


Future work

- Effects of in-situ conditions (temperature profile, state of stresses).
- Exposure of intact cement samples **of different compositions** to thermal shocks under in-situ conditions.

Cement	TRL	Description
S1	7: Proven technology	1.92 SG class G cement with 35% BWOC silica flour
S2	7: Proven technology	1.90 SG ultra low permeability class G cement with 35% BWOC silica flour
S3	3: Prototype tested	1.90 SG class G cement with 35% BWOC silica flour with CO2 sequestering agent
S4	7: Proven technology	1.80 SG calcium aluminate based blend
S5	3: Prototype tested	1.90 SG Rock-based (Feldspar rich type of rock as a precursor) geopolymer for CCUS

- Exposure of composite cement samples (cement and casing) to thermal cycles under in-situ conditions.
 - Study of crack formation and de-bonding (micro-annulus) development.

Composite sample with steel tubing as the simulated casing. Flow cold water through model casing.

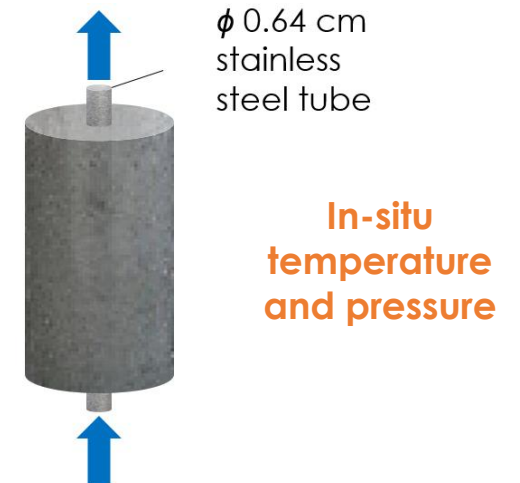

ACKNOWLEDGEMENTS

International consortium with partners in the Norway, the Netherlands, and the UK:



Funded through the ACT-CCS mechanism, by:



Forskingsrådet
The Research Council of Norway



Rijksdienst voor Ondernemend
Nederland



Department for
Business, Energy
& Industrial Strategy

CEMENTTEGRITY



ACT-CCS Project CEMENTTEGRITY

Project number: 327311-CLIMIT



THANK YOU

Kai Li, Anne Pluymakers

K.Li-2@tudelft.nl

Anne.Pluymakers@tudelft.nl

Applied Geophysics & Petrophysics
Delft University of Technology, the Netherlands



See abstract
by scanning
← QR code



CEMENTTEGRITY