

## Mode I fatigue delamination growth with fibre bridging in multidirectional composite laminates

Yao, Liaojun; Sun, Yi; Guo, Licheng; Lyu, Xiuqi; Zhao, Meiyong; Jia, Liyong; Alderliesten, R. C.; Benedictus, R.

**DOI**

[10.1016/j.engfracmech.2017.11.013](https://doi.org/10.1016/j.engfracmech.2017.11.013)

**Publication date**

2018

**Document Version**

Final published version

**Published in**

Engineering Fracture Mechanics

**Citation (APA)**

Yao, L., Sun, Y., Guo, L., Lyu, X., Zhao, M., Jia, L., Alderliesten, R. C., & Benedictus, R. (2018). Mode I fatigue delamination growth with fibre bridging in multidirectional composite laminates. *Engineering Fracture Mechanics*, 189, 221-231. <https://doi.org/10.1016/j.engfracmech.2017.11.013>

**Important note**

To cite this publication, please use the final published version (if applicable).  
Please check the document version above.

**Copyright**

Other than for strictly personal use, it is not permitted to download, forward or distribute the text or part of it, without the consent of the author(s) and/or copyright holder(s), unless the work is under an open content license such as Creative Commons.

**Takedown policy**

Please contact us and provide details if you believe this document breaches copyrights.  
We will remove access to the work immediately and investigate your claim.

***Green Open Access added to TU Delft Institutional Repository***

***'You share, we take care!' - Taverne project***

**<https://www.openaccess.nl/en/you-share-we-take-care>**

Otherwise as indicated in the copyright section: the publisher is the copyright holder of this work and the author uses the Dutch legislation to make this work public.



## Mode I fatigue delamination growth with fibre bridging in multidirectional composite laminates

Liaojun Yao<sup>a,c,\*</sup>, Yi Sun<sup>a</sup>, Licheng Guo<sup>a</sup>, Xiuqi Lyu<sup>b</sup>, Meiyong Zhao<sup>c</sup>, Liyong Jia<sup>d</sup>, R.C. Alderliesten<sup>e</sup>, R. Benedictus<sup>e</sup>

<sup>a</sup> Department of Astronautics Science and Mechanics, Harbin Institute of Technology, Harbin, PR China

<sup>b</sup> School of Aeronautics and Astronautics, Purdue University, USA

<sup>c</sup> School of Aeronautics, Northwestern Polytechnical University, Xi'an, PR China

<sup>d</sup> AVIC The First Aircraft Institute, Xi'an, PR China

<sup>e</sup> Structural Integrity and Composites Group, Faculty of Aerospace Engineering, Delft University of Technology, The Netherlands



### ARTICLE INFO

#### Article history:

Received 22 April 2017

Received in revised form 2 November 2017

Accepted 10 November 2017

Available online 16 November 2017

#### Keywords:

Fatigue

Delamination

Fibre bridging

Multidirectional composite laminates

### ABSTRACT

Fatigue delamination in multidirectional composite laminates was experimentally investigated in present study. Both the Paris relation and a modified Paris relation (with a new similitude parameter) were employed to interpret fatigue delamination with significant fibre bridging. The results clearly demonstrated that fatigue delamination was independent of fibre bridging, if a reasonable similitude parameter was used in data reduction. As a result, a master resistance curve can be fitted to determine fatigue crack growth with different amounts of fibre bridging. The energy principles were subsequently used to provide physical interpretation on fatigue delamination. The results indicated the energy release for the same fatigue crack growth remained constant with fibre bridging. Bridging fibres in most cases just periodically stored and released strain energy under fatigue loading, but had little contribution to real energy release. The master resistance curve was finally applied to predict fatigue delamination with fibre bridging. Acceptable agreement between predictions and experiments was achieved, demonstrating the validation of the modified Paris relation in fibre-bridged fatigue delamination study.

© 2017 Elsevier Ltd. All rights reserved.

## 1. Introduction

Advanced composite laminates have been widely used in aerospace engineering for the requirements on light-weight structures and fuel efficiency. These materials take advantages of excellent properties, i.e. high strength-to-weight and stiffness-to-weight ratios. However, they suffer disadvantage of poor interlaminar property, due to lack of reinforcement in thickness direction. This weak point can easily result in delamination propagation between neighbored layers under either quasi-static or fatigue loading. It has been widely admitted that delamination was one of the most important damage in composite laminates and must be well considered in composite structural design [1–15]. This damage indeed became a big obstacle and challenge in applications of composites in critical engineering parts and limited their weight saving potential. It is, therefore, meaningful and significant to have in-depth understanding on mechanisms and prediction models for delamination in composite laminates.

\* Corresponding author at: Department of Astronautics Science and Mechanics, Harbin Institute of Technology, Harbin, PR China.  
E-mail address: [L.Yao@hit.edu.cn](mailto:L.Yao@hit.edu.cn) (L. Yao).

A critical literature review on fatigue delamination growth in composite laminates and adhesive bonds has been completed by Pascoe et al. [1]. Four category methods have been used in the characterization of delamination behavior under fatigue loading. In this classification, methods based on the fracture mechanics were widely used, in which fatigue crack growth was correlated to the stress intensity factor  $K$  ( $SIF$ ) or the strain energy release rate  $G$  ( $SERR$ ). And the Paris relation has been admitted as one of the most important achievements in fatigue crack growth study in the last several decades. It has been widely used in scientific studies and structural designs, even though some researchers have noticed that it was no more than an empirical correlation and not based on physical understanding of fatigue crack growth [1]. In addition, there was no consensus on the similitude parameter in fatigue delamination studies in composite laminates. People alternatively employed the maximum  $SERR$   $G_{max}$ , the  $SERR$  range  $\Delta G$ , or combinations of them as similitude to determine fatigue crack growth [3–7].

It is worth noting that there is no standard for mode I fatigue delamination growth. To address this problem, the ASTM D30 Committee and the European Structural Integrity Society Technical Committee 4 (ESIS TC4) have performed separate round-robin mode I fatigue tests on unidirectional double cantilever beam (DCB) specimens to investigate the influence of a series of factors [7,14,15]. Even though some achievements have been obtained, the standard is still undergoing discussion at this moment. Unidirectional DCB specimens have been commonly used to determine mode I interlaminar crack growth behavior of a composite material under fatigue loading [3,6,8–13]. Hojo et al. [3] experimentally investigated fatigue delamination behavior under different stress ratios. And a two-parameter power law relation was proposed to determine fatigue delamination. In following studies [6,8], they provided research on fatigue delamination in composite laminates with interlaminar reinforcement. Cartié et al. [9] experimentally investigated fatigue delamination behavior in z-pin reinforced composite laminates. Shivakumar et al. [10] proposed a total fatigue life model to determine delamination behavior in sub-critical, linear and final fracture domains via mode I fatigue tests conducted on unidirectional DCB specimens. Argüelles et al. [11] investigated the onset and crack propagation behavior under fatigue loading with unidirectional DCB specimens. Coronado et al. [12] tried to determine fatigue delamination behavior at different temperatures. It was found that crack growth decreased with elevated temperatures. Khan et al. [13] developed a two-parameter power law relation to characterize fatigue delamination behavior via experiments conducted on unidirectional DCB specimens.

Referring to delamination results under quasi-static loading [16–18], interface configuration had important effects on crack growth behavior. It was reported that the use of unidirectional DCB specimens sometimes can cause conservative results and underestimate interlaminar property, especially for delamination with large-scale fibre bridging [17]. In detail, initiation crack growth may be independent of ply orientation, whereas crack propagation was significantly dependent of interface configuration. The presence of fibre bridging during delamination was the main reason for this dependence, as more bridging fibres were observed in delamination of multidirectional composite laminates. As a result, a growing number of research have been conducted on multidirectional laminates to have further understanding on delamination behavior under quasi-static loading [19,20].

For fatigue delamination, limited research has ever been reported to be performed on multidirectional composite laminates. Zhao et al. [18,21,22] conducted experiments on fatigue delamination with multidirectional composite laminates. Significant fibre bridging was observed as well. And a normalized power law relation was proposed to determine fatigue delamination behavior. Yao et al. [17,23] carried out fatigue delamination tests on DCB specimens with different ply orientations and gave thorough discussions on bridging effects on fatigue delamination. Banks-Sills et al. [24,25] experimentally examined fatigue delamination behavior in woven composites via DCB specimens with multidirectional interface. The fatigue delamination results were first interpreted via the Paris-type relations, and subsequently explained via a modified Hartman-Schijve equation.

According to the previous studies [17,18,21–23], even significant fibre bridging can exist in crack growth of multidirectional composite laminates. The presence of fibre bridging can significantly affect fatigue delamination behavior. One then reasonably ask what about fatigue delamination in this condition, and how to well characterize fatigue crack growth behavior. To this end, the present research is to explore fibre-bridged fatigue delamination in multidirectional composite laminates and to provide an evaluation on the effectiveness of both the Paris relation and a modified Paris relation in fatigue delamination study.

## 2. Material and experimental procedure

### 2.1. Material and specimen preparation

DCB specimens with 45//45 interface were manufactured and tested to investigate fatigue delamination with different amounts of fibre bridging. The stacking sequence was designed as  $[(\pm 45/0_{12}/\mp 45)]/[(\pm 45/0_{12}/\mp 45)]$ , with consideration of avoiding crack jumping and minimizing both residual thermal stress and non-uniform energy release rate distribution across the width of the crack front [19,20,26–28].

Composite laminates were fabricated by hand-lay-up of 32 thermosetting unidirectional carbon/epoxy prepreg layers of M30SC/DT120. A 12.7  $\mu\text{m}$  Teflon film was inserted in the middle plane of these laminates during the hand-lay-up process to act as an initial delamination with  $a_0 = 60$  mm. The laminates were cured in vacuum in an autoclave at a pressure of 6 bars and curing temperature of 120  $^{\circ}\text{C}$  for 90 min. After curing, all laminates, with a nominal cured thickness of 5 mm, were C-

scanned to detect potential imperfections. The panels were cut by a diamond coated saw into 25 mm width beams with 200 mm length. And only these samples where no obvious defects were detected were fatigue tested. A pair of aluminum loading blocks, 25 mm width by 20 mm length with 6 mm thickness, was adhesively bonded onto a specimen at the side of the Teflon insert for load introduction.

One side of a DCB specimen was coated with a thin layer of white typewriter correction fluid to enhance visibility of the delamination front during fatigue test. A strip of grid paper was pasted on the coated side of the specimen to aid in measuring crack propagation length.

## 2.2. Experimental procedure

All fatigue tests were conducted on a 10KN MTS machine under displacement control at a frequency of 5 Hz with the same stress ratio  $R = 0.5$  in ambient conditions. A computer controlled digital camera system was employed to monitor crack growth at the maximum displacement with pre-defined intervals during the tests. The force, displacement and cycle number information were automatically stored in an Excel file every 100 cycles, enabling data evaluation after the tests. The fatigue experimental set-up is demonstrated in Fig. 1.

It is worth noting that crack growth can gradually decrease with decreasing *SERR* in displacement controlled tests. The tests were, therefore, manually terminated to save test duration once crack growth nearly retarded. Subsequently, the specimen was tested with increased displacements at the same stress ratio. This sequence was repeated several times to generate fatigue delamination with different amounts of fibre bridging. With this test procedure, multiple delamination resistance curves were obtained, with each one representing the resistance equivalent to a specific fatigue crack length.

The concept of *R-curve* was a convenient way to determine the significance of fibre bridging. This method was also used in present study to represent the critical resistance increase in fatigue crack growth because of fibre bridging. However, the critical interlaminar resistance of a given fatigue delamination length cannot be directly determined in the fatigue test, as the fatigue load was much lower than the critical load. To address this problem, a loading-unloading cycle was conducted on the specimen after a fatigue test until load-displacement curve became nonlinear to measure delamination resistance as well as to determine the maximum and minimum displacements used in subsequent fatigue test.

## 2.3. Fatigue data reduction

The Paris relation has been widely used to determine fatigue crack growth in composite laminates. This relation can be summarized as Eq. (1). The *SERRs*, i.e.  $G_{max}$  and  $G_{min}$  under fatigue loading, can be calculated with the Modified Compliance Calibration (MCC) method, recommended in the ASTM D5528-01 standard, see Eq. (2). The 7-point Increment Polynomial Method, recommended in the ASTM E647-00 standard, was applied to determine the fatigue crack growth rate  $da/dN$ .

$$\frac{da}{dN} = c(\Delta G)^n = c \left[ (\sqrt{G_{max}} - \sqrt{G_{min}})^2 \right]^n \quad (1)$$

where  $c$  and  $n$  are two curve-fitting parameters of the Paris relation.

$$G = \frac{3P^2 C^{(1/3)}}{2A_1 B h} \quad (2)$$

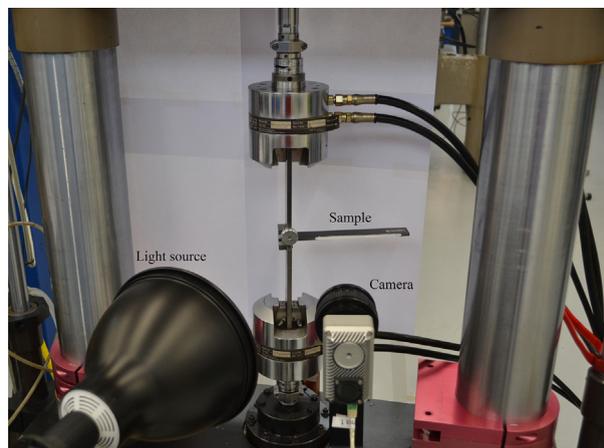


Fig. 1. Fatigue experimental set-up.

where  $P$  is the applied load;  $C$  is the compliance of the DCB specimen;  $B$  is the width of specimen and  $h$  is the thickness of specimen;  $A_1$  is the slope of the curve in the graph where  $a/h$  is plotted against  $C^{1/3}$ .

A modified Paris relation, in terms of  $da/dN$  against the *SERR* range around crack front  $\Delta G_{eff}$ , has been proposed in a recent study by the authors [31]. This new model can be summarized as Eq. (3). It was also used in fatigue data reduction in present study as a comparison to the Paris relation.

$$\frac{da}{dN} = c^* (\Delta G_{eff})^{n^*} = c^* \left[ \left( \sqrt{G_{tip,max}} - \sqrt{G_{tip,min}} \right)^2 \right]^{n^*} = c^* \left[ \frac{G_0}{G_{fc}(a-a_0)} \Delta G \right]^{n^*} \quad (3)$$

where  $c^*$  and  $n^*$  are two curve-fitting parameters of the modified Paris relation;  $G_0$  is the fatigue delamination resistance with no fibre bridging;  $G_{fc}(a-a_0)$  represents the critical resistance increase with fatigue crack extension.

Similitude principle plays an important role in fatigue crack characterization. According to this principle, *the same value of a similitude parameter should result in the same fatigue crack growth, and vice versa*. This can be used to verify whether a similitude parameter used in fatigue crack growth study is valid or not. Particularly, if the same value of a similitude can cause the same crack growth, it is a reasonable similitude parameter. Otherwise, it cannot well represent the similitude.

Apart from using the two Paris-type relations to interpret fatigue crack growth with fibre bridging in multidirectional composite laminates, energy principles were also applied to have physical understanding on fatigue delamination as well as to provide explanations on the effectiveness of different similitude parameters used in present study. In practice, it is easy to quantify the applied work  $U$  against fatigue cycle number  $N$  with the information recorded during the tests. Taking a derivative between  $U$  and  $N$ , the energy release rate  $dU/dN$  can be determined. And a correlation between  $da/dN$  against  $dU/dN$  can be obtained. With this correlation, energy release during fatigue delamination can be well evaluated and analyzed. In the perspective of energy balance, this evaluation can not only physically explain fatigue delamination behavior, but also improve one's understanding on the real role of fibre bridging in fatigue crack growth.

### 3. Results and discussion

One multidirectional DCB specimen was repeatedly fatigue tested with the same stress ratio  $R = 0.5$  to provide enough raw data for investigation on delamination growth with significant fibre bridging. A loading-unloading cycle was conducted on the specimen after each fatigue test to determine the critical interlaminar resistance  $G_{fc}$  with fatigue crack extension  $a-a_0$ . Both the Paris and the modified Paris relations were employed to interpret fatigue crack growth. The energy principles were subsequently applied to physically explain fatigue delamination behavior in the perspective of energy balance. And SEM examinations were finally conducted to explore damage mechanisms related to energy release in fatigue delamination.

#### 3.1. Interlaminar resistance increase in fatigue delamination of multidirectional composite laminates

In quasi-static delamination, the increase of interlaminar resistance with crack growth can be well characterized via the concept of *R-curve*, in terms of the critical resistance against crack extension. This method was employed here to determine the critical resistance increase in fibre-bridged fatigue delamination.

According to the test procedure introduced in Section 2.2, the critical interlaminar resistance at several fatigue crack lengths can be evaluated. Fig. 2 summarizes delamination resistance at several crack intervals. The critical resistance initially

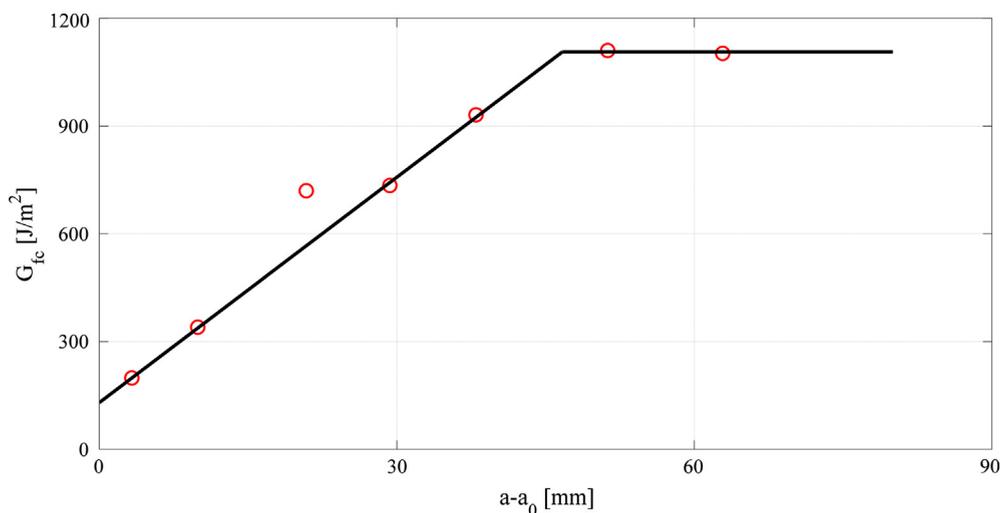


Fig. 2. Interlaminar critical resistance increase with fatigue delamination growth.

increased with crack growth and finally became constant if crack length exceeded a certain level (fatigue  $R$ -curve). It has been widely admitted that the presence of fibre bridging was the main reason for the increase of this critical resistance. More fibre bridging can be present in a longer crack, making more energy release of the same crack extension [17,29,30]. The plateau of the critical resistance indicated fibre bridging became saturated after crack propagation was long enough. In this state, the new generation of fibre bridging around crack front was comparable to the amount of fibre bridging disappearing at the end of bridging region, leading to an equilibrium state with further crack extension.

Linear and nonlinear models have been proposed to describe the critical resistance increase because of fibre bridging [32]. The results illustrated in Fig. 2 apparently demonstrate a linear increase between the critical resistance  $G_{fc}$  and crack extension  $a-a_0$ . Thus, the linear relationship was used in present study to represent resistance increase in fatigue delamination growth. This relation indeed played an important role in the use of the modified Paris relation in fatigue data reduction.

A higher magnitude of the  $R$ -curve means more fibre bridging in delamination growth. With a comparison to the fatigue  $R$ -curve of unidirectional composite laminates under the same stress ratio [33] (see Fig. 3(a)), one can draw a conclusion that more bridging fibres can be present in fatigue delamination of multidirectional composite laminates. This means the significance of fibre bridging in fatigue crack growth is dependent of ply orientation. Similar conclusion has been made in quasi-static delamination, in which the interlaminar resistance of 45//45 interface was much higher than that of 0//0 interface [17]. Furthermore, quasi-static results of 45//45 interface reported in previous study [17] were compared with corresponding fatigue data to highlight the resistance difference between quasi-static and fatigue delamination, as shown in Fig. 3(b). The results clearly indicate there is fibre bridging difference in monotonic and fatigue loading. In summary, fibre bridging significance is dependent on both interface configuration and load regimes (i.e. quasi-static vs. fatigue) in delamination growth in composite laminates.

### 3.2. Fatigue data reduction with the Paris and the modified Paris relations

All fatigue data were first explained with the Paris relation, as illustrated in Fig. 4. Fatigue delamination is apparently dependent of crack scale. It decreases significantly with crack propagation. Particularly, the obtained Paris resistance curves decrease shift from left to right in the graph and finally converge into a single one. The presence of fibre bridging is the main reason for the decrease shift of the resistance curves [17,23]. More fibre bridging can be present in the wake of the crack front of a longer delamination. These bridging fibres can significantly restrain crack opening and release stress concentration around crack front. The results also indicate the required  $\Delta G$  of a given crack propagation rate is not constant, but dependent of crack scale. It rises with crack extension and then forms a plateau if fibre bridging has fully developed.

From the results shown in Fig. 4, it is inappropriate to use a single Paris resistance curve to determine fatigue delamination with fibre bridging. The use of a single one can cause either overestimation or underestimation results. Particularly, the use of the most left one can lead to conservative predictions, whereas the use of the most right ones cannot guarantee safety. To address this problem, some attempts have been carried out to take account of the resistance curves located in-between in fatigue delamination studies [23]. And an empirical power law relation has been proposed to determine fatigue crack growth with significant fibre bridging.

According to the similitude principle, the same value of a similitude parameter, e.g.  $\Delta G$ , should result in the same crack growth. The results shown in Fig. 4 clearly demonstrate the same value of  $\Delta G$  can lead to different fatigue crack growths. Thus,  $\Delta G$  is not a reasonable similitude parameter for fatigue delamination with fibre bridging. Furthermore, it is worth noting that the original purpose of using  $\Delta G$  is to represent the load amplitude applied on crack front, i.e. crack driving force. It is valid for fatigue delamination with no fibre bridging. However, this is not true for delamination with fibre bridging. Because of bridging,  $\Delta G$  is the sum of  $SERR$  around crack front and  $SERR$  in bridging fibres. And it has been proven that only the former part had real contribution to fatigue crack growth [31,34]. Thus,  $\Delta G$  in this case cannot well determine the crack driving force for fatigue delamination. The magnitude of  $SERR$  in bridging fibres is significantly dependent of crack length, leading to increase of  $\Delta G$  at a given value of  $da/dN$  with crack extension. Recalling the original purpose of using  $\Delta G$  in fatigue delam-

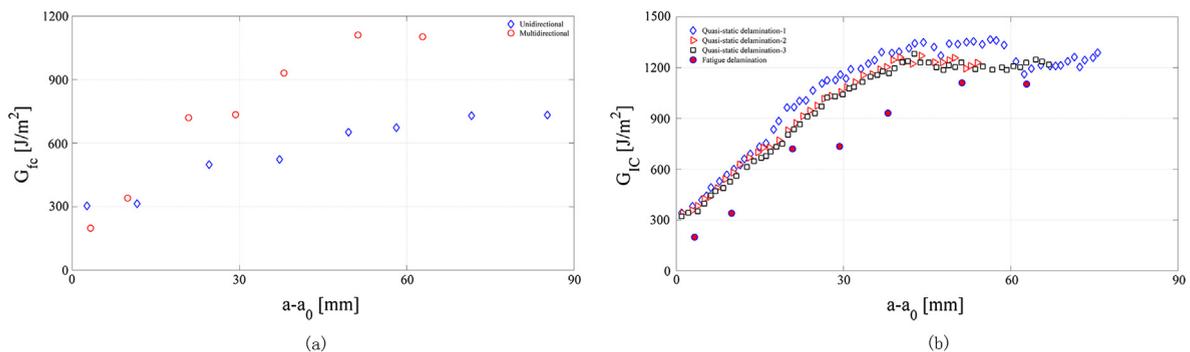


Fig. 3. Comparison of critical resistance increase. (a) Unidirectional vs. Multidirectional; (b) Quasi-static vs. Fatigue.

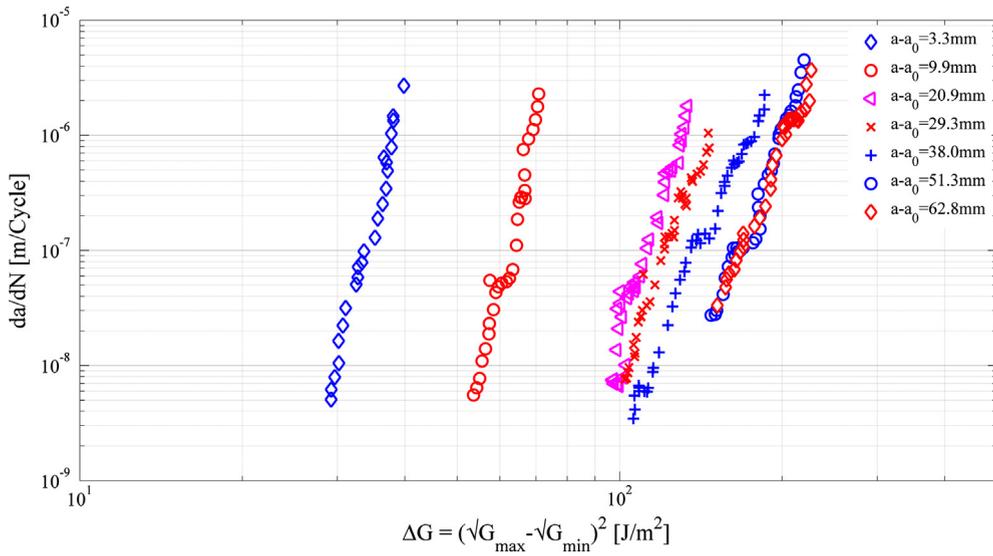


Fig. 4. Fatigue data representations via the Paris relation.

ination, the *SERR* around crack front should be employed to appropriately correlate fatigue delamination with significant fibre bridging. And a modified Paris relation based on this parameter has been proposed in previous study, see Eq. (3) [31].

For comparison, the same data sets were interpreted with the modified Paris relation and summarized in Fig. 5. Obvious difference shown in Fig. 4 is eliminated and fatigue delamination with different amounts of fibre bridging becomes the same, indicating the same crack growth of the same value of  $\Delta G_{eff}$ . And a master resistance curve can be fitted to determine fatigue crack growth. This agrees well with the results observed in fatigue delamination in unidirectional composite laminates, in which a master resistance curve can be fitted to determine fatigue delamination with different amounts of fibre bridging [31,33]. According to the similitude principle, the *SERR* range indeed applied on crack front seems a reasonable similitude parameter in the characterization of fatigue crack growth with fibre bridging.

It should be stressed that the applications of the modified Paris relation can significantly reduce experimental workloads and save test duration in determining fibre-bridged fatigue delamination. Once the master resistance curve shown in Fig. 5 is established with limited tests, fatigue delamination with different amounts of fibre bridging can be well determined. This is really useful and important for engineering. Additionally, one should note that this new power law relation is not only valid for delamination with significant fibre bridging, but also effective for delamination with no fibre bridging. In the later situation,  $G_{fc}(a-a_0)$  keeps constant and equates to  $G_0$ . As a result, Eq. (3) is reduced to Eq. (1). In the opinion of the authors, this

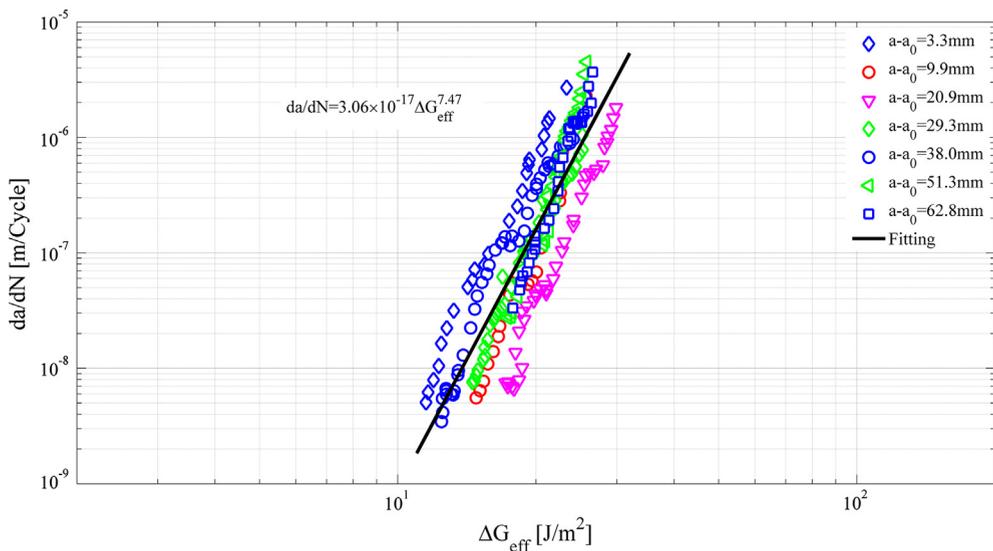


Fig. 5. Fatigue delamination representations via the modified Paris relation.

means delamination with no fibre bridging can be treated as a special case of delamination with fibre bridging. And the modified Paris relation is an even more general form of the Paris relation for fatigue crack growth study.

Fig. 6 gives a comparison on fatigue data analysis with the Paris and the modified Paris relations of one time fatigue test, to highlight an advantage of applying the modified Paris relation in fatigue data analysis. Obvious difference was observed between different data representations. Particularly, the data set explained via the modified Paris relation locates on the left side of the results interpreted via the Paris relation, due to the extraction of fibre bridging in data reduction. Additionally, the slopes of different data representations are not the same. It is much steeper in the Paris representation, in comparison with the modified Paris representation. This feature is really important for the applications of the modified Paris relation in engineering designs. A larger value of the slope indicates strong sensitivity between  $da/dN$  and the  $SERR$ . This means a small uncertainty in the  $SERR$  calculation can cause significant error in fatigue delamination prediction. The decrease in the slope can significantly reduce this sensitivity, which is really beneficial to accuracy improvement as well as to engineering applications.

### 3.3. Fatigue delamination analysis with energy principles

One should note that the Paris type relations are phenomenological methods to represent fatigue crack growth in metals and composite laminates. Delamination is an energy consumption procedure, obeying the first law of thermodynamics. Energy principles were therefore employed to physically explain fatigue crack growth behavior. Particularly, the amount of energy release in fatigue delamination with fibre bridging can be schematically represented via Eq. (4) [34].

$$\frac{dU}{dN} = \frac{dU}{da} \frac{da}{dN} = \left( \frac{dU_a}{da} + \frac{dU_{br}}{da} \right) \frac{da}{dN} \quad (4)$$

where  $dU_a/da$  represents energy dissipation because of new crack generation;  $dU_{br}/da$  represents energy dissipation in bridging fibres.

Fig. 7 provides a typical example of energy release during an entire displacement controlled fatigue delamination test. One should keep in mind that  $da/dN$  can continuously decrease with crack extension in this test. The experimental data with high magnitude shown in Fig. 7 obviously deviate from the straight line. This means extra energy should be consumed in crack growth at the beginning of the fatigue test. Indeed, the extra energy release is related to failure occurring in bridging fibres [34]. The total energy release  $dU/da$  in this stage, therefore, is the sum of  $dU_a/da$  and  $dU_{br}/da$ . The results shown in Fig. 7 also demonstrate that the energy release of a unit crack generation can finally become constant with decrease in  $da/dN$ . This means  $dU_a/da$  plays a dominant role in this stage and  $dU_{br}/da$  has no or negligible contribution. As a result, a straight line can well characterize the energy release in fatigue delamination. It should be stressed that the number of fatigue cycles in the second stage takes up more than 95% of the total number of fatigue cycles. Thus, one can believe that energy dissipation keeps constant in most time of a fatigue delamination test and is independent of fibre bridging.

According to the energy principles, all fatigue data were analyzed and expressed in terms of  $da/dN$  against energy dissipation per cycle  $dU/dN$ , as illustrated in Fig. 8. All experimental results tend to locate in a narrow band region, indicating the same or at least similar energy release of the same  $da/dN$  with crack propagation. This agrees well with the results illustrated

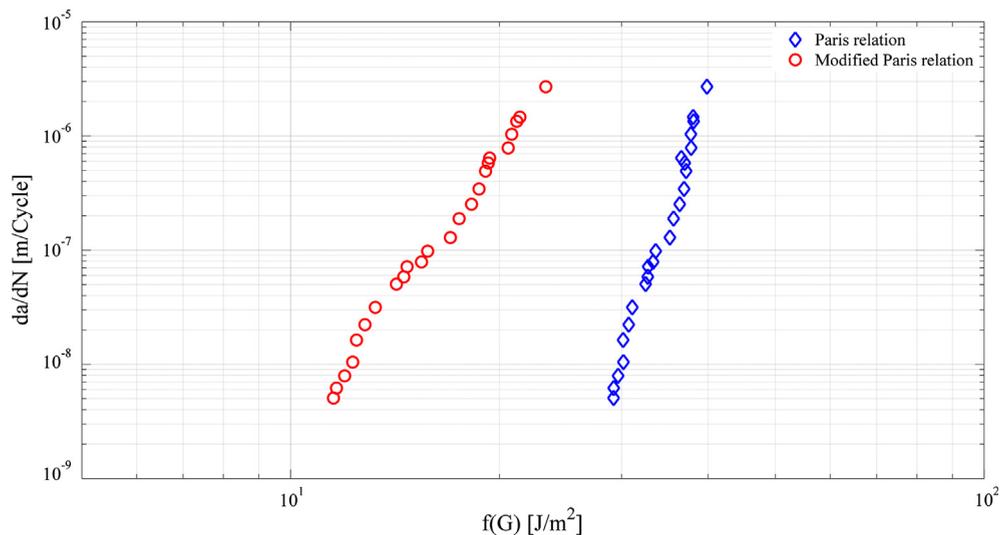


Fig. 6. Data reduction with the Paris and modified Paris relations ( $f(G) = \Delta G$  for the Paris representation and  $f(G) = \Delta G_{eff}$  for the modified Paris representation).

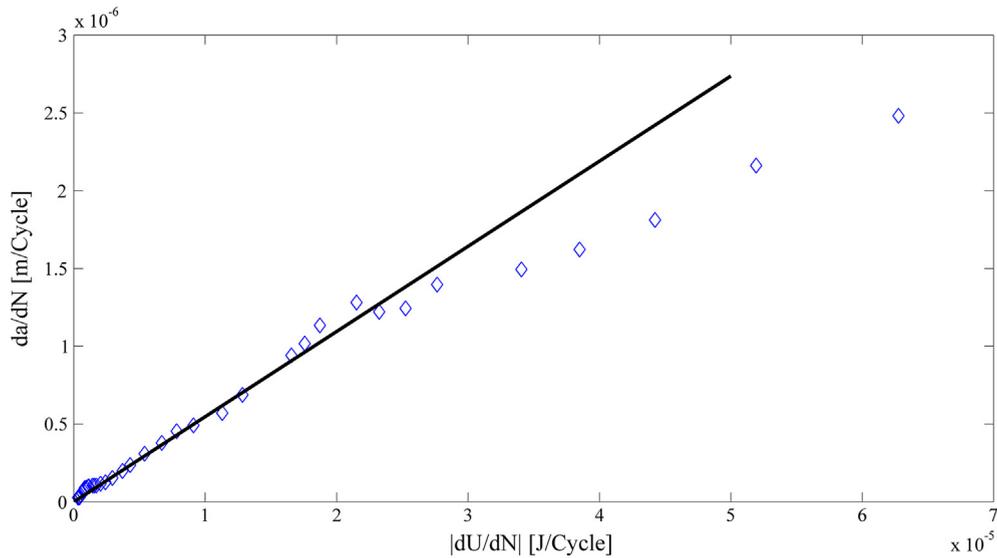


Fig. 7. Correlation between  $da/dN$  and  $dU/dN$  during fatigue delamination.

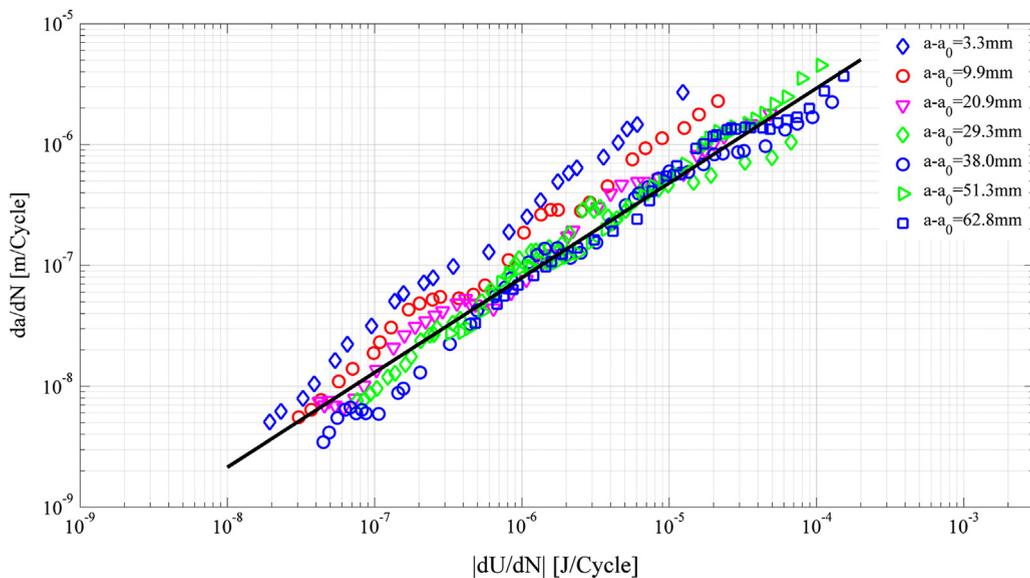


Fig. 8. Energy release in fatigue delamination with different amounts of fibre bridging.

in Fig. 7, as most energy dissipation in fatigue delamination is concentrated on damage evolution around crack front, regardless of fibre bridging. As a result, a single curve can be fitted to determine the relationship between  $da/dN$  and  $dU/dN$ . This also means fatigue delamination resistance in most cases remains constant with fibre bridging development.

According to the above discussion and analysis, the use of the Paris relation in data reduction not only violates the similitude principle, but also disagrees with the energy release results. On the contrary, the use of the modified Paris relation is in line with the similitude principle as well as the energy release results. The application of the energy principles can provide important physical basis on the selection of a reasonable similitude parameter in fatigue data analysis. And it can provide solid evidence on the validation of using the modified Paris relation in fibre-bridged fatigue delamination characterization.

Fractography analysis was conducted to explore damage mechanisms related to energy release shown in Fig. 8. The SEM samples, 10 mm length and 25 mm width, were prepared with gold sputter-coating in vacuum for 10 min to avoid static charging in SEM due to the non-conductive nature of the material used in present study. The prepared samples were examined in a JOEL SEM at the Delft Aerospace Structural & Materials Laboratory. Fig. 9 provides the SEM observations on fracture surfaces at different crack lengths with magnification of 1000 times. The typical micro-features in fatigue delamination with

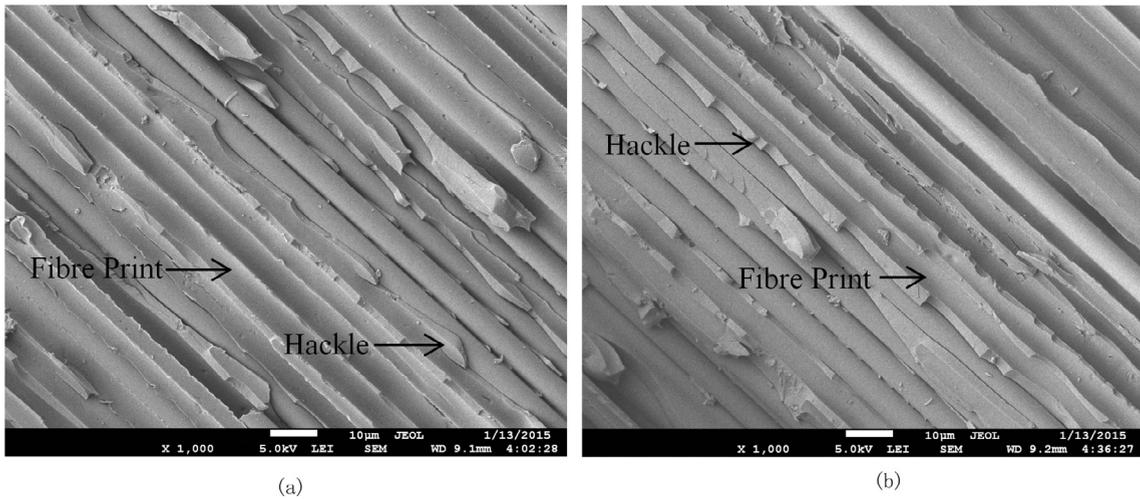


Fig. 9. SEM observations on fatigue fracture surfaces. (a) At a short crack length; (b) At a long crack length.

fibre bridging are the same. Particularly, fibre prints play a dominant role on fracture surfaces and hackles are also observed in some local locations, indicating the same damage mechanisms in fatigue delamination with crack growth (i.e. fibre bridging development). This is the physical reason for the same energy release in fatigue delamination. The presence of fibre prints is a result of debonding occurring between fibres and matrix around crack front. And hackle is a typical feature generated in shear stress state, which is usually observed in mode II or mixed-mode I/II delamination. Its appearance in mode I delamination mainly attributes to local shear stress state occurring in fibre pullout from matrix in the wake of the crack front.

#### 4. Fatigue delamination predictions via the modified Paris relation

From the above discussion, the modified Paris relation can be used to well represent fatigue delamination with different amounts of fibre bridging in multidirectional composite laminates. In order to provide extra evidence on its validation and accuracy in fatigue delamination characterization, the master resistance curve illustrated in Fig. 5 was used to predict fatigue delamination with different amounts of fibre bridging.

Another multidirectional DCB specimen was repeatedly fatigue tested four times with the same stress ratio  $R = 0.5$ . Fig. 10 summarizes the predictions and the experimental data in terms of  $da/dN$  against  $\Delta G$ . Acceptable agreements between predictions and experiments are observed in all four cases, demonstrating the effectiveness of the modified Paris relation in fatigue delamination study.

#### 5. Concluding remarks

Fatigue delamination with large-scale fibre bridging in multidirectional composite laminates was experimentally investigated. The use of the Paris relation, with  $\Delta G$  as the similitude parameter, can artificially make crack scale dependence of fatigue delamination. In the application of the modified Paris relation, with  $\Delta G_{eff}$  as the similitude parameter, a master resistance curve can be obtained to determine fatigue delamination with different amounts of fibre bridging, which agreed well with the similitude principle and the energy release results. As a result,  $\Delta G_{eff}$ , rather than  $\Delta G$ , is recommended as a reasonable parameter to represent the similitude in fatigue delamination with fibre bridging. The modified Paris relation can be treated as an even more general form of the Paris relation, which is not only valid for delamination with fibre bridging, but also effective for delamination without fibre bridging. The results derived from the modified Paris relation indicated that fatigue delamination was independent of fibre bridging, if the similitude was well characterized.

A physical explanation on fatigue delamination was conducted with the energy principles. It was found that the energy release during fatigue delamination in multidirectional composite laminates remained constant with fibre bridging development. Particularly, bridging fibres only had contribution to energy release at the beginning of several thousand cycles. In most cases, these bridging fibres just periodically stored and released strain energy, but had no real effect on permanent energy release. A SEM observation demonstrated the morphology on fracture surfaces at different crack lengths remained the same, indicating the same damage mechanisms during fatigue delamination with fibre bridging. Particularly, fibre prints and hackles were two micro-features generated during fatigue growth. This was the physical reason for the same energy release of the same  $da/dN$  in fatigue delamination growth.

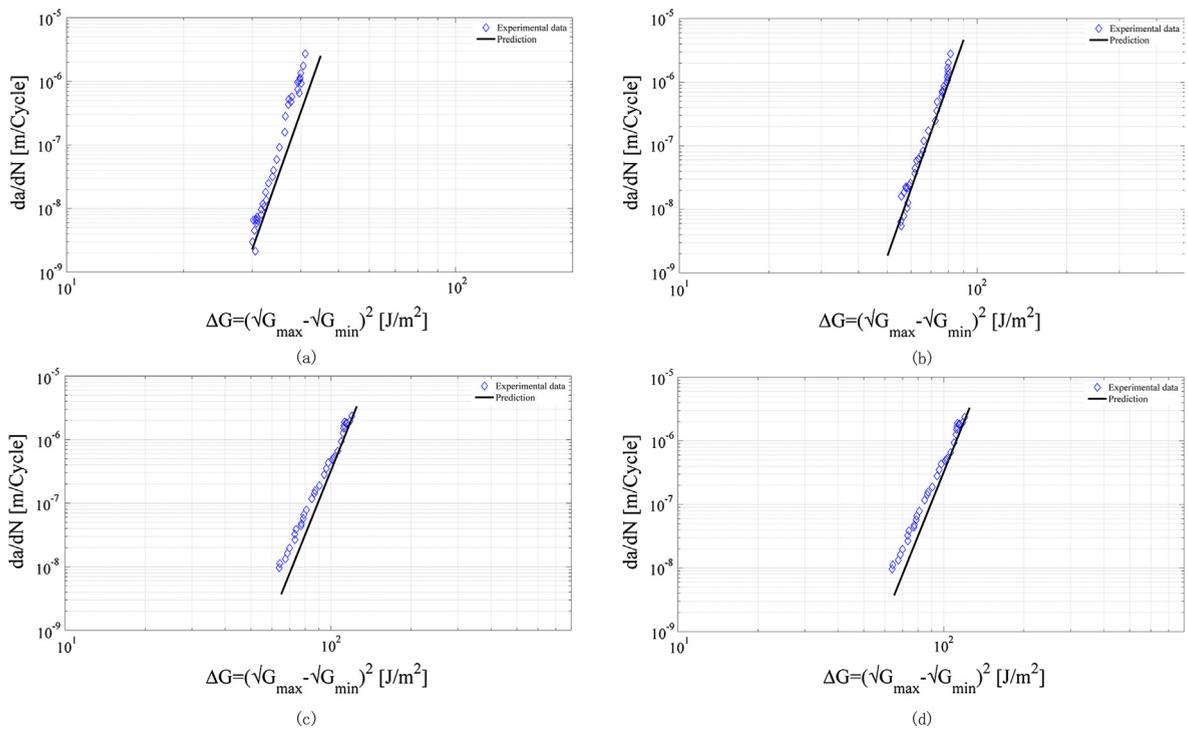


Fig. 10. Fatigue delamination predictions. (a)  $a-a_0 = 4.1$  mm; (b)  $a-a_0 = 11.8$  mm; (c)  $a-a_0 = 20.0$  mm; (d)  $a-a_0 = 28.4$  mm.

The obtained master resistance curve was employed to quantify fatigue delamination with different amounts of fibre bridging. In all cases, the predictions agreed well with the experiments, demonstrating the effectiveness of the modified Paris relation in fatigue delamination characterization.

## Acknowledgements

The authors gratefully acknowledge financial support from the International Postdoctoral Exchange Fellowship Program, Harbin Institute of Technology, P. R. China. The research work is also supported by the China Postdoctoral Science Foundation with grant No. 2016M601422 and No. 2017T100231, and Heilongjiang Postdoctoral Fund with grant No. LBH-Z16071.

## References

- [1] Pascoe JA, Alderliesten RC, Benedictus R. Methods for the prediction of fatigue delamination growth in composites and adhesive bonds – a critical review. *Eng Fract Mech* 2013;112–113:72–96.
- [2] Bak BLV, Sarrado C, Turon A, Costa J. Delamination under fatigue loads in composite laminates: a review on the observed phenomenology and computational methods. *Appl Mech Rev* 2014;66:060803-1–0608032-4.
- [3] Hojo M, Tanaka K, et al. Effect of stress ratio on near-threshold propagation of delamination fatigue cracks in unidirectional CFRP. *Compos Sci Technol* 1987;29(4):273–92.
- [4] Atodaria DR, Putatunda SK, Mallick PK. Delamination growth behavior of fabric reinforced laminated composite under mode I fatigue. *J Eng Mater Technol* 1999;121:381–5.
- [5] Blanco N, Gmastedt EK, Asp LE, Costa J. Mixed mode delamination growth in carbon-fibre composite laminates under cyclic loading. *Int J Solids Struct* 2004;41:4219–35.
- [6] Hojo M, Matsuda S, Tanaka M, et al. Mode I delamination fatigue properties of interlayer-toughened CF/epoxy laminates. *Compos Sci Technol* 2006;66:665–75.
- [7] Brunner AJ, Murphy N, Pinter G. Development of a standardized procedure for the characterization of interlaminar delamination propagation in advanced composites under fatigue mode I loading conditions. *Eng Fract Mech* 2009;76:2678–89.
- [8] Hojo M, Nakashima K, Kusaka T, et al. Mode I fatigue delamination of Zanchor-reinforced CF/epoxy laminates. *Int J Fatigue* 2010;32:37–45.
- [9] Cartié DDR, Laffaille JM, Partridge IK, Brunner AJ. Fatigue delamination behaviour of unidirectional carbon fibre/epoxy laminates reinforced by Z-Fiber pinning. *Eng Fract Mech* 2009;76:2834–45.
- [10] Shivakumar K, Chen H, Abali F, Le D, Davis C. A total fatigue life model for mode I delaminated composite laminates. *Int J Fatigue* 2006;28:33–42.
- [11] Argüelles A, Vina J, Canteli AF, et al. Interlaminar crack initiation and growth rate in a carbon-fibre epoxy composite under mode-I fatigue loading. *Compos Sci Technol* 2008;68:2325–31.
- [12] Coronado P, Argüelles A, Vina J, Vina I. Influence of low temperatures on the phenomenon of delamination of mode I fracture in carbon-fibre/epoxy composites under fatigue loading. *Compos Struct* 2014;112:188–93.
- [13] Khan R, Alderliesten R, Benedictus R. Two-parameter model for delamination growth under mode I fatigue loading (Part B: Model development). *Compos Part A Appl Sci Manuf* 2014;65:201–10.
- [14] Murri GB. Effect of data reduction and fiber-bridging on mode I delamination characterization of unidirectional composites. *J Compos Mater* 2014;48:2413–24.

- [15] Stelzer S, Brunner AJ, Argüelles A, et al. Mode I delamination fatigue crack growth in unidirectional fiber reinforced composites: results from ESIS TC4 round-robins. *Eng Fract Mech* 2014;116:92–107.
- [16] Pereira AB, de Moraes AB. Mode I interlaminar fracture of carbon/epoxy multidirectional laminates. *Compos Sci Technol* 2004;64:2261–70.
- [17] Yao L, Alderliesten R, Zhao M, Benedictus R. Bridging effect on mode I fatigue delamination behavior in composite laminates. *Compos Part A Appl Sci Manuf* 2014;63:103–9.
- [18] Peng L, Zhang J, Zhao L, et al. Mode I delamination growth of multidirectional composite laminates under fatigue loading. *J Compos Mater* 2010;45:1077–90.
- [19] Sebaey TA, Blanco N, Lopes CS, Costa J. Numerical investigation to prevent crack jumping in Double Cantilever Beam tests of multidirectional composite laminates. *Compos Sci Technol* 2011;1587–1592.
- [20] Sebaey TA, Blanco N, Lopes CS, Costa J. Characterization of crack propagation in mode I delamination of multidirectional CFRP laminates. *Compos Sci Technol* 2012;1251–1256.
- [21] Peng L, Xu J, Zhang J, Zhao L. Mixed-mode delamination growth of multidirectional composite laminates under fatigue loading. *Eng Fract Mech* 2012;96:676–86.
- [22] Zhang J, Peng L, Zhao L, Fei B. Fatigue delamination growth rates and thresholds of composite laminates under mixed-mode loading. *Int J Fatigue* 2012;40:7–15.
- [23] Yao L, Sun Y, Alderliesten RC, Benedictus R, Zhao M. Fibre bridging effect on the Paris relation for mode I fatigue delamination growth in composites with consideration of interface configuration. *Compos Struct* 2017;159:471–8.
- [24] Ishibir C, Banks-Sills L, Fourman V, Eliasi R. Delamination propagation in a multi-directional woven composite DCB specimen subjected to fatigue loading. *Compos Part B Eng* 2014;66:180–9.
- [25] Simon I, Banks-Sills L, Fourman V. Mode I delamination propagation and R-ratio effects in woven composite DCB specimens for a multi-directional layup. *Int J Fatigue* 2017;96:237–51.
- [26] Robinson P, Song DQ. A modified DCB specimen for mode I testing of multidirectional laminates. *J Compos Mater* 1992;26:1554–77.
- [27] Polaha JJ, Davidson BD, Hudson RC, Pieracci A. Effects of mode ratio, ply orientation and precracking on the delamination toughness of a laminated composite. *J Reinf Plast Compos* 1996;16:141–73.
- [28] Hudson RC, Davidson BD, Polaha JJ. Effect of remote ply orientation on the perceived mode I and mode II toughness of  $0/0$  and  $0/-0$  interfaces. *Appl Compos Mater* 1998;5:123–38.
- [29] Shokrieh MM, Heidari-Rarani M, Ayatollahi MR. Delamination R-curve as a material property of unidirectional glass/epoxy composites. *Mater Des* 2012;34:211–8.
- [30] Suo Z, Bao G, Fan B. Delamination R-curve phenomena due to damage. *J Mech Phys Solids* 1992;40:1–16.
- [31] Yao L, Sun Y, Guo L, Zhao M, Jia L, Alderliesten RC, et al. A modified Paris relation for fatigue delamination with fibre bridging in composite laminates. *Compos Struct* 2017;176:556–64.
- [32] Dávila CG, Rose CA, Camanho PP. A procedure for superposing linear cohesive laws to represent multiple damage mechanisms in the fracture of composites. *Int J Fract* 2009;158:211–23.
- [33] Yao L, Sun Y, Guo L, Zhao M. A validation of a modified Paris relation for fatigue delamination growth in composite laminates. *Compos Part B Eng* 2018;132:97–106.
- [34] Yao L, Alderliesten RC, Benedictus R. Interpreting the stress ratio effect on delamination growth in composite laminates using the concept of fatigue fracture toughness. *Compos Part A Appl Sci Manuf* 2015;78:135–42.