

## Distortion of DNA Origami on Graphene Imaged with Advanced TEM Techniques

Kabiri, Yoones; Ananth, Adithya N.; van der Torre, Jaco; Katan, Allard; Hong, Jin Yong; Malladi, Sairam; Kong, Jing; Zandbergen, Henny; Dekker, Cees

**DOI**

[10.1002/smll.201700876](https://doi.org/10.1002/smll.201700876)

**Publication date**

2017

**Document Version**

Accepted author manuscript

**Published in**

Small

**Citation (APA)**

Kabiri, Y., Ananth, A. N., van der Torre, J., Katan, A., Hong, J. Y., Malladi, S., Kong, J., Zandbergen, H., & Dekker, C. (2017). Distortion of DNA Origami on Graphene Imaged with Advanced TEM Techniques. *Small*, 13(31), 1-8. Article 1700876. <https://doi.org/10.1002/smll.201700876>

**Important note**

To cite this publication, please use the final published version (if applicable).  
Please check the document version above.

**Copyright**

Other than for strictly personal use, it is not permitted to download, forward or distribute the text or part of it, without the consent of the author(s) and/or copyright holder(s), unless the work is under an open content license such as Creative Commons.

**Takedown policy**

Please contact us and provide details if you believe this document breaches copyrights.  
We will remove access to the work immediately and investigate your claim.

## Small

### Distortion of DNA origami on graphene imaged with advanced TEM techniques

--Manuscript Draft--

|   |   |
|---|---|
| <b>Manuscript Number:</b>   | smlI.201700876R1  |
| <b>Full Title:</b>  | Distortion of DNA origami on graphene imaged with advanced TEM techniques   |
| <b>Article Type:</b>  | Full Paper  |
| <b>Section/Category:</b>  |   |
| <b>Keywords:</b>  | DNA origami; transmission electron microscopy; graphene   |
| <b>Corresponding Author:</b>  | Cees Dekker<br>Kavli Institute of Nanoscience, Delft University of Technology<br>NETHERLANDS  |
| <b>Additional Information:</b>  |   |
| <b>Question</b>   | <b>Response</b>   |
| Please submit a plain text version of your cover letter here.<br><br><b>If you are submitting a revision of your manuscript, please do not overwrite your original cover letter. There is an opportunity for you to provide your responses to the reviewers later; please do not add them here.</b> | Dear Editor,<br><br>Please find enclosed our manuscript entitled "Distortion of DNA origami on graphene imaged with advanced TEM techniques" by Kabiri et al, which we request you to consider for publication as a "full paper" in Small.<br><br>Since the introduction of graphene, there has been a tremendous interest to exploit its properties as an ultrathin support for high-resolution electron microscopy of DNA nanostructures. In the current study, we have shown for the first time that DNA origami, which is only 2 nm thick as dsDNA, can be imaged on single layer graphene, which is indeed a major leap towards imaging DNA nanostructures. We were able to visualize the conformational heterogeneity of the origami nanoplates on graphene with high contrast, which enabled us to observe a peculiar distortion behavior of the origami plates on graphene. From an extensive number of control experiments, we demonstrate that neither staining agents, nor screening ions, nor the level of electron-beam irradiation cause this distortion. Instead, the data indicate that origami nanoplates are distorted due to hydrophobic interaction of the DNA bases with graphene upon adsorption of the DNA origami nanoplates.<br><br>We are excited about the novel findings reported in this paper that provide new insights into how DNA interacts with graphene. Furthermore, the work examines the potential of graphene as a TEM support, and guides the way to future high-resolution imaging of DNA origami on functionalized graphene. We estimate that this study will be of keen interest to the interdisciplinary readership of Small that will have an interest in graphene, DNA origami, and TEM imaging.<br><br>For your convenience, we include some suggestions for knowledgeable referees<br><br>Yours sincerely,<br><br>Prof.dr. Cees Dekker<br>Antoni van Leeuwenhoek Professor<br>Professor of Molecular Biophysics<br>Distinguished University Professor<br>Director of the Kavli Institute of Nanoscience Delft<br>Royal Academy Professor of the Royal Netherlands Academy of Arts and Sciences (KNAW) |
| Do you or any of your co-authors have a conflict of interest to declare?  | No. The authors declare no conflict of interest.  |
| <b>Corresponding Author Secondary Information:</b>  |   |

|  |   |
|--|---|
| <b>Corresponding Author's Institution:</b>           | Kavli Institute of Nanoscience, Delft University of Technology  |
| <b>Corresponding Author's Secondary Institution:</b> |   |
| <b>First Author:</b>                                 | Yoones Kabiri   |
| <b>First Author Secondary Information:</b>           |   |
| <b>Order of Authors:</b>                             | Yoones Kabiri   |
|  | Adithya N. Ananth   |
|  | Jaco van der Torre  |
|  | Allard Katan  |
|  | Jin-Yong Hong   |
|  | Sairam Malladi  |
|  | Jing Kong   |
|  | Henny Zandbergen  |
| Cees Dekker  |   |
| <b>Order of Authors Secondary Information:</b>       |   |
| <b>Abstract:</b>                                     | <p>While graphene may appear to be the ultimate support membrane for transmission electron microscopy (TEM) imaging of DNA nanostructures, very little is known if it poses an advantage over conventional carbon supports in terms of resolution and contrast. We carry out microscopic investigations on DNA origami nanoplates that are supported onto free-standing graphene, using advanced TEM techniques, including a new dark-field technique that was recently developed in our lab. TEM images of stained and unstained DNA origami are presented with high contrast on both graphene and amorphous carbon membranes. On graphene, the images of the origami plates show severe unwanted distortions, where the rectangular shape of the nanoplates is significantly distorted. From a number of comparative control experiments, we demonstrate that neither staining agents, nor screening ions, nor the level of electron-beam irradiation cause this distortion. Instead, we suggest that origami nanoplates are distorted due to hydrophobic interaction of the DNA bases with graphene upon adsorption of the DNA origami nanoplates.</p> |

DOI: 10.1002/xxxx

**Full Paper****Distortion of DNA origami on graphene imaged with advanced TEM techniques***Yoonas Kabiri, Adithya N. Ananth, Jaco van der Torre, Allard Katan, Jin-Yong Hong, Sairam Malladi, Jing Kong, Henny Zandbergen\* and Cees Dekker\**

Y. Kabiri, A. N. Ananth, J. van der Torre, Dr. A. Katan, Dr. S. Malladi, Prof. H. Zandbergen, Prof. C. Dekker

Kavli Institute of Nanoscience Delft, Delft University of Technology, 2629HZ Delft, The Netherlands

E-mail: h.w.zandbergen@tudelft.nl; c.dekker@tudelft.nl

Dr. Jin-Yong Hong, Prof. J. Kong

Department of Electrical Engineering and Computer Science, Massachusetts Institute of Technology, Cambridge MA 02139, USA

Keywords: DNA origami, transmission electron microscopy, graphene

While graphene may appear to be the ultimate support membrane for transmission electron microscopy (TEM) imaging of DNA nanostructures, very little is known if it poses an advantage over conventional carbon supports in terms of resolution and contrast. We carry out microscopic investigations on DNA origami nanoplates that are supported onto free-standing graphene, using advanced TEM techniques, including a new dark-field technique that was recently developed in our lab. TEM images of stained and unstained DNA origami are presented with high contrast on both graphene and amorphous carbon membranes. On graphene, the images of the origami plates show severe unwanted distortions, where the rectangular shape of the nanoplates is significantly distorted. From a number of comparative control experiments, we demonstrate that neither staining agents, nor screening ions, nor the level of electron-beam irradiation cause this distortion. Instead, we suggest that origami nanoplates are distorted due to hydrophobic interaction of the DNA bases with graphene upon adsorption of the DNA origami nanoplates.

## 1. Introduction

1  
2  
3  
4 Graphene features tantalizing properties suitable for a wide range of applications, from next-  
5  
6 generation nanoelectronics and biosensing to TEM imaging of biomolecules. <sup>[1-3]</sup> Graphene  
7  
8 gained an interest in the TEM community as a support substrate because it can be as thin as  
9  
10 one carbon atom, which provides the lowest cross-section for elastic and inelastic scattering.  
11  
12 <sup>[4]</sup> Moreover, graphene mitigates electron-beam-associated damage. <sup>[4,5]</sup> As a result, high-  
13  
14 resolution high-contrast images can be obtained for weak-phase objects that are supported  
15  
16 onto or sandwiched between graphene layers. <sup>[4,6]</sup>  
17  
18  
19  
20  
21  
22

23 Can graphene also facilitate the imaging of (unstained) nucleic acids with TEM? Here, we  
24  
25 address this question by utilizing DNA origami test structures. Such DNA origami, DNA that  
26  
27 is folded into well-defined shapes, is an emerging workhorse for synthetic biology and  
28  
29 programmable materials due to its accessible and compelling self-assembly principle. <sup>[7-10]</sup>  
30  
31 Two-dimensional (2D) DNA origami is an excellent microscopy test object as it features the  
32  
33 same scattering properties as double stranded DNA while it comes with a bigger and defined  
34  
35 size, which helps the observation and investigation.  
36  
37  
38  
39  
40  
41  
42

43 To the best of our knowledge, no high-resolution TEM (HRTEM) imaging of origami have  
44  
45 been reported without staining or class averaging since various challenges arise for HRTEM  
46  
47 imaging of biological specimens in general and DNA macromolecular assemblies in particular,  
48  
49 such as sample preparation, beam damage, inherently low contrast of nucleic acids, and  
50  
51 substrate signal contributions. <sup>[11]</sup> [Some attempts of direct imaging of unstained DNA have](#)  
52  
53 [been already reported.](#) <sup>[12-14]</sup> However, even when deposited onto an atomically-thin layer of  
54  
55 graphene, unstained DNA structures are barely distinguishable in normal TEM mode due to  
56  
57 their low scattering elements. <sup>[4,15]</sup> This necessitates further developments in electron optics  
58  
59  
60  
61  
62  
63  
64  
65

1 for their visualization. The common practice in life-science TEM is to enhance the contrast at  
2 the expense of losing resolution by strongly defocusing the objective lens (by 1-10 $\mu$ m), i.e.,  
3  
4 transforming part of the phase information into amplitude. Such a methodology, however, is  
5  
6 not suitable for high-resolution imaging due to information delocalization.<sup>[16]</sup>  
7  
8  
9

10  
11 In order to boost the in-focus contrast for nucleic acids, we employ two complementary TEM  
12  
13 techniques, viz., scanning transmission electron microscopy (STEM) and a special type of  
14  
15 dark-field (DF) microscopy. STEM and DF allowed us to shed light on the conformational  
16  
17 polymorphism of DNA origami on graphene without the need for any staining compound and  
18  
19 class averaging. So far, only stained or class-averaged images of origami on carbon  
20  
21 membranes were reported in literature. Since our imaging techniques provide good contrast as  
22  
23 well as sufficient resolution for visualization, we could notice an unexpected behavior of the  
24  
25 origami plates onto graphene, namely, that crumpled and deformed rectangles were obtained  
26  
27 instead of fully flat and rectangular structures which are normally observed onto amorphous  
28  
29 carbon supports. A range of complementary characterization techniques, provided in this  
30  
31 manuscript, examines various parameters on the imaging of the origami plates, such as  
32  
33 staining or screening ions, the level of electron-beam irradiation, and surface interaction of the  
34  
35 origami plates with graphene.  
36  
37  
38  
39  
40  
41  
42  
43

## 44 **2. Results and Discussions**

45  
46 We first characterized the DNA origami plates using liquid-cell atomic force microscopy  
47  
48 (AFM). **Figure 1b** depicts a typical AFM image of the origami on a mica surface in liquid. It  
49  
50 is seen that nanoplates are well dispersed on the mica surface with a suitable density for  
51  
52 imaging. AFM was the fastest way to control the folding and purification success and was the  
53  
54 basic control that we did prior to TEM sample preparations. Liquid-cell AFM was essential,  
55  
56 as we found problems in AFM imaging in dry condition, such as curvature at the bottom of  
57  
58  
59  
60  
61  
62  
63  
64  
65

1 the plates, side arms sticking to one another, and concealment of the smaller cavity (observed  
2 for more than 95% of the plates tested for various  $Mg^{2+}$  ionic strength, see supporting  
3 information (SI), Figure S1). In liquid, on the other hand, the AFM images (Figure 1b)  
4 conform to the computer design. A slight distortion in aspect ratio is noticed, similar to earlier  
5 reports by Rothmund in his original paper,<sup>[9]</sup> where he observed origami rectangles  
6 changing into a slightly hourglass-shaped structure due to imaging artifacts. The dsDNA loop  
7 at the bottom of the plate was quite floppy in liquid and we added 1mM  $NiCl_2$  in the buffer to  
8 immobilize the loop onto the surface.  
9  
10  
11  
12  
13  
14  
15  
16  
17  
18  
19  
20

21 After characterization of the origami structures with AFM, we turned to TEM for imaging  
22 them on free-standing graphene, which is the main focus of this paper. We started by imaging  
23 uranyl-stained origami on graphene by STEM, which provides the best contrast. We mostly  
24 found white "blobs", which were hardly distinguishable as DNA origami plate. Extensive  
25 imaging was carried out to make sure that our observation was indeed valid for all TEM  
26 samples. Figure 1c shows the best image that we could acquire in our dataset. The most  
27 striking observation is that the majority of the investigated nanoplates seem to show very  
28 crumpled conformations. To our surprise, DNA origami plates thus appear to be severely  
29 distorted upon adsorption onto graphene. Several attempts were made to improve the images  
30 such as graphene cleaning, changing  $Mg^{2+}$  concentration in a range of 15-60 mM, and  
31 removing EDTA from the buffer (SI, Figure S2). All these efforts failed to tackle the  
32 distortion problem. In the remaining part of the manuscript, we will examine what underlies  
33 this distortion.  
34  
35  
36  
37  
38  
39  
40  
41  
42  
43  
44  
45  
46  
47  
48  
49  
50  
51

52 We found out that distortion occurs regardless of the staining. DNA nanostructures are weak-  
53 phase objects for TEM, and staining agents that contain high-scattering elements such as  
54 heavy metals, are commonly utilized to increase the contrast. As a consequence of the binding  
55  
56  
57  
58  
59  
60  
61  
62  
63  
64  
65

1 of staining agents, artifacts can occur, e.g., double helix unwinding, DNA lengthening, kink  
2 formation, and intrastrand crosslinking.<sup>[17]</sup> In view of the distortion shown in Figure 1c, we  
3  
4 wondered whether the staining could be the reason. To examine this, we acquired images of  
5  
6 unstained origami on graphene. It should be noted that this is not possible with conventional  
7  
8 TEM, even on graphene.<sup>[4]</sup> A better approach is using STEM, where a high-angle annular  
9  
10 dark-field (HAADF) detector is utilized to collect the Rutherford-scattered electrons. The  
11  
12 STEM contrast scales with  $Z^2$  (or more precisely, the exponent of  $Z$  is reported to be between  
13  
14 1.6-1.8 instead of the classical value of 2),<sup>[18]</sup> which theoretically makes possible to  
15  
16 distinguish DNA (rich in phosphorous with  $Z=15$ ) on graphene ( $Z=6$ ). One example of a  
17  
18 STEM image of unstained origami on graphene is presented in Figure 1d. Incidentally, we  
19  
20 mention that it is noteworthy to present such an image since TEM images of single-layer  
21  
22 unstained DNA origami are rare. Similar to our observations for the stained origami, we  
23  
24 present the best image for the unstained one. It can be seen that the majority of the nanoplates  
25  
26 depict the same severe structural deformation despite the absence of uranyl acetate stain.  
27  
28 Again, various attempts such as changing  $Mg^{2+}$  concentration, removing EDTA from the  
29  
30 buffer, or testing on different batch of graphene did not improve the images in terms of seeing  
31  
32 DNA origami structures with all the design components. The comparison of Figure 1c and 1d  
33  
34 thus shows that uranyl staining does not cause the origami distortion. Later in the manuscript,  
35  
36 we show that our TEM techniques are indeed able to visualize even a single DNA helix.  
37  
38 However, the severe distortion of DNA on graphene greatly smears the contrast that can be  
39  
40  
41  
42  
43  
44  
45  
46  
47  
48  
49  
50  
51  
52  
53  
54  
55  
56  
57  
58  
59  
60  
61  
62  
63  
64  
65

The distortion of the DNA origami is also not caused by the electron beam, as could be  
conceived for a highly focused STEM probe. The good contrast in Figure 1c-d is due to high  
signal-to-noise (SNR) of the focused STEM beam, but the strongly focused beam can cause  
severe structural damage.<sup>[19-21]</sup> In general, the applicability of STEM to image polymeric



1 materials, including nucleic acid macromolecules, should be cautiously examined. We thus  
2 speculated whether the distortion might be due to STEM-induced damage, leading to  
3  
4 crumpling of nanoplates. Therefore we also probed the nanoplates with a broad parallel beam,  
5  
6 where we circumvented the low SNR problem in wide-field TEM using our newly developed  
7  
8 DF technique (see the experimental section for more details on the DF technique in detail).<sup>[22]</sup>  
9  
10 For a fair comparison, we acquired images on the exact same area, first exposing the region of  
11  
12 interest with wide-field (DF image in **Figure 2**) and subsequently with a focused beam  
13  
14 (STEM image in Figure 2). No difference was seen between sequential images in panel (c)  
15  
16 and (b), not only for this particular region but also for the entire area of the TEM grids. Thus,  
17  
18 these experiments exclude STEM-associated damage as the origin of the observed nanoplate  
19  
20 crumpling.  
21  
22  
23  
24  
25  
26  
27  
28

29 Before we move on, we address several points in Figure 2 that are worthy of consideration:  
30

31 (1) In contrast to TEM imaging on amorphous carbon substrates, electron-induced  
32  
33 contamination<sup>[23]</sup> is not observed on the graphene substrates such as in Figure 2a, even after  
34  
35 several exposures on the boxed area. This hints on the damage-mitigation property of  
36  
37 graphene reported earlier by Algara-Siller et al,<sup>[24]</sup> which was attributed to the high thermal  
38  
39 and electrical conductivity of graphene. The properties of graphene are also advantageous in  
40  
41 terms of sample drift and charging, allowing improved HRTEM imaging. (2) By comparing  
42  
43 Figure 2b and 2c, it is seen that the contrast enhancement obtained in the DF is comparable to  
44  
45 that of STEM. Considering that most TEM labs around the world lack access to deflecting-  
46  
47 coil STEM, using a "Mercedes star" in the objective aperture cassette suggests a cheap and  
48  
49 easy alternative for contrast enhancement. Since the central beam is absent, the intensity  
50  
51 reaching the camera is too low in DF technique, where the noise becomes an important factor  
52  
53 (the central beam contributes to more than 99% of the intensity in a normal bright-field image  
54  
55 <sup>[22]</sup>). Therefore, contrast can be further improved by removing the noise in the CCD cameras.  
56  
57  
58  
59  
60  
61  
62  
63  
64  
65

Obviously, using the recent direct electron detection technology is advantageous in this regard.

1  
2 [25] (3) We also examined whether the distortion was an effect of sample orientation relative to  
3  
4 the electron beam, i.e., if the electrons first hit the sample and then the graphene, or vice versa  
5  
6 (note the two arrow directions in Figure 2d). Several studies reported such an orientation-  
7  
8 dependent damage response in beam-sensitive materials, especially for materials containing  
9  
10 light elements. [5,19,24] For our origami sample, sputtering of light atoms from the DNA  
11  
12 structure might be a reason behind the crumpling of nanoplates. However, we did not observe  
13  
14 any dependence on sample orientation relative to the electron beam, as in both cases, distorted  
15  
16 plates were seen. (4) The background of the DNA origami images on graphene indicates the  
17  
18 presence of contaminants. Likely, these are origami buffer constituents, [4] hydrocarbon  
19  
20 contaminations, [4,26] or contaminants that result from graphene transfer.  
21  
22  
23  
24  
25  
26  
27  
28

29 Finally, we show that the distortion is dependent on which substrate the origami plates are  
30  
31 deposited on. So far, we ruled out staining and imaging artifacts as the origin of origami  
32  
33 damage on graphene. One other parameter to consider is the interaction of origami with  
34  
35 graphene. It has been suggested that this interaction is mediated through  $\pi$ - $\pi$  stacking of the  
36  
37 aromatic purine and pyrimidine DNA bases with the delocalized  $\pi$  bonds of graphene. [27] To  
38  
39 test this, we examined origami behavior on amorphous carbon film as an alternative substrate,  
40  
41 where such  $\pi$ - $\pi$  interactions will be absent. **Figure 3** shows that the origami is well flattened  
42  
43 on the amorphous carbon, depicting all the details encoded in the computer design (cf. Figure  
44  
45 1a). Note that remarkably we obtain good contrast of a 2 nm thin uranyl-stained DNA on a 15  
46  
47 nm thick carbon support (thickness of carbon measured by electron energy loss spectroscopy  
48  
49 (EELS)). The nice images in Figure 3 incidentally prove that origami is stable under vacuum  
50  
51 condition of the microscope ( $10^{-7}$  mbar) as well as during image acquisitions (both with  
52  
53 STEM and DF at 300kV at room temperature).  
54  
55  
56  
57  
58  
59  
60  
61  
62  
63  
64  
65

1 We find that DNA origami is also distorted when deposited onto highly oriented pyrolytic  
2 graphite (HOPG) graphite, which has a surface very similar to that of graphene. Although this  
3  
4 may seem trivial, there is no consensus on whether and how DNA origami interacts with the  
5  
6 HOPG surface. <sup>[27–31]</sup> The different reported results may be due to different experimental  
7  
8 conditions including buffer, pH, salt concentrations, or biased sampling of the imaging area.  
9  
10 Lacking a proper comprehensive study, we carried out our own AFM experiments. **Figure 4a**  
11  
12 shows the DNA origami structures on HOPG that are so heavily disconfigured that they are  
13  
14 barely identifiable as rectangles. Control experiments (SI, Figure S3) proved that the observed  
15  
16 structures on HOPG are indeed DNA and not hydrophobic contaminants.  
17  
18  
19  
20  
21  
22  
23

24 The interaction of the origami plates and graphene can be prevented by surface  
25  
26 functionalization. We passivated HOPG and graphene surfaces with polylysine (PLL) and  
27  
28 with 1-pyrenecarboxylic acid (1PCA) <sup>[32]</sup> respectively, and performed AFM and TEM  
29  
30 analysis. Figure 4b shows a typical AFM image of the origami plates onto a PLL-coated  
31  
32 HOPG surface. By comparing the images of the DNA origami onto bare HOPG and PLL-  
33  
34 coated HOPG surfaces (panel a and b in Figure 4), it is clear that PLL coating on HOPG  
35  
36 prevents adverse interactions between the HOPG and the origami. Although the origami  
37  
38 plates in Figure 4b are a bit distorted compared to Figure 1b (onto mica), the integrity of the  
39  
40 structure is well maintained. We see a similar trend in TEM images of origami plates  
41  
42 deposited onto bare and 1PCA-functionalized graphene. Figure 4c illustrates a typical STEM  
43  
44 image that we acquired onto 1PCA-functionalized graphene. Whereas the images of the  
45  
46 origami plates on bare graphene show very distorted conformation (cf. Figures 1 and 2), we  
47  
48 see much less distortion in Figure 4c, where for example, the cavities inside the plates become  
49  
50 visible. From both AFM and TEM experiments on functionalized HOPG and graphene  
51  
52 surfaces, we thus can conclude that the interactions between the origami plates and graphene  
53  
54 plays a crucial role in the observed distortion.  
55  
56  
57  
58  
59  
60  
61

1  
2 To quantify the distortion, we define a parameter  $D$  as the surface area of the observed  
3  
4 origami image divided by its theoretical surface area. For example, a value of  $D=0.5$   
5  
6 represents a distorted nanoplate that has a surface area equal to only half the expected size.  
7  
8 For calculation of the theoretical size according to the design sketch in Figure 1a, we need to  
9  
10 consider a subtle point, namely that the origami structures are extended along the y-axis.  
11  
12 Multiple works have previously demonstrated that 2D origami plates can not strictly be  
13  
14 modeled as a series of closely-packed parallel double helices.<sup>[9,33]</sup> In typical buffer conditions,  
15  
16 electrostatic forces between the negatively charged strands cause inter-helical gaps (see  
17  
18 **Figure 5a**). Hence, we calculate the size of the origami plate as follows. With  $n$  as the number  
19  
20 of base pairs along the x-axis, the width  $X$  of the origami plate can be estimated as  $X= n*0.34$   
21  
22 nm. However, the height  $Y$  of the origami does not simply follow a  $2*h$  equation (with  $h$  as  
23  
24 the number of double-stranded helices along the y-axis, and 2 nm as the width for B-form  
25  
26 DNA; note that  $h=25$  in our design). Instead, a modified expression  $Y= 2h + g(h-1)$  should be  
27  
28 used, where  $g$  is the size of the inter-helical gap caused by the electrostatic repulsion between  
29  
30 the strands.<sup>[33]</sup> The gap size  $g$  may vary depending on ionic strength or the design parameters.  
31  
32 Since there is no computational method available for size estimation, liquid-cell AFM remains  
33  
34 the easiest experimental way to measure the true dimensions of the origami. Figure 5b  
35  
36 summarizes our liquid-cell AFM measurements of the origami size. In accord with the TEM  
37  
38 data as well as with theoretical calculations, we find a consistent value for the nanoplate width  
39  
40 of  $X = 72.8 \pm 2.2$  nm (mean  $\pm$  standard deviation), whereas the height of the structure is  $Y =$   
41  
42  $67.2 \pm 4.4$  nm. From these values, we extracted the surface area of the nanoplate. Based on  
43  
44 the obtained true size from the AFM experiments, we now return to the TEM image analysis.  
45  
46 We processed the distortion of about 50 randomly selected origami plates in the TEM images  
47  
48 taken from each substrate (graphene, 1PCA-functionalized graphene, and amorphous carbon),  
49  
50 and report the result in Figure 5c. In accord with the shown TEM data (Figure 1-3), the  
51  
52  
53  
54  
55  
56  
57  
58  
59  
60  
61  
62  
63  
64  
65

1 statistical analysis in Figure 5c shows that most nanoplates are indeed severely crumpled to  
2 almost one third of their size,  $D=0.37 \pm 0.08$  (mean  $\pm$  standard deviation), whereas they are  
3  
4 much less distorted on carbon substrate,  $D=0.85 \pm 0.10$ . For the 1PCA-functionalized  
5  
6 graphene,  $D$  equals  $0.58 \pm 0.14$ , which falls in between the values for the graphene and carbon  
7  
8 substrates. The statistical analysis thus shows that the substrates made from the same carbon  
9  
10 element but with different hydrophobic surface properties result in significantly different  $D$   
11  
12 values.  
13  
14  
15  
16  
17  
18

### 19 3. Conclusion

20  
21  
22 With high-resolution STEM and DF techniques, we were able to image for the first time both  
23  
24 stained and unstained DNA origami nanoplates on graphene and amorphous carbon  
25  
26 membranes with good contrast. We observed that origami nanoplates exhibited a structural  
27  
28 distortion when deposited onto graphene. Through a range of complementary control  
29  
30 experiments, we conclude that the distortion can be attributed to the interaction of DNA with  
31  
32 graphene, likely through  $\pi$ - $\pi$  bonds. After quantification of the distortion onto different  
33  
34 substrates, we found significant different mean values of the relative area of the origami plates,  
35  
36 which quantitatively supports our observation in the presented TEM images. We conclude  
37  
38 that while graphene provides the ultimate thin and strong sample support for materials science  
39  
40 or some biological samples, <sup>[3]</sup> its applicability to DNA nanostructures is hindered by  $\pi$ - $\pi$   
41  
42 interactions.  
43  
44  
45  
46  
47  
48  
49

### 50 4. Experimental Section

51  
52  
53 *Graphene growth, transfer, and quality characterization:* Single-layer CVD-grown graphene  
54  
55 was used to have large available areas for TEM investigations. Details of CVD growth and  
56  
57 Raman spectroscopy for the growth characterization are given in the supplementary  
58  
59  
60  
61  
62  
63  
64  
65

1 information (SI), Figure S4. In order to avoid polymer residues, graphene was transferred to  
2 TEM grids (Quantifoil, gold coated, 200 mesh) using a dry-transfer method (SI, Figure S5).

3  
4 [34] Grids were examined by a number of TEM techniques to ensure layer thickness and  
5 cleanliness (SI, Figure S6). Note that no hydrophilic treatment such as glow discharging was  
6 performed on the grids, as graphene is very susceptible to even gentle plasma treatment.  
7  
8  
9

10  
11  
12  
13  
14 *Origami design, assembly, and purification:* As a test object for TEM imaging, we designed a  
15 2D DNA origami structure (Figure 1a) using caDNA package.<sup>[10]</sup> We aimed to create a  
16 symmetric structure that can be well recognized in imaging. A 50x72 nm rectangular plate  
17 was designed with a number of different elements such as cavities in the middle (4 and 8 nm  
18 wide, 19 nm long), DNA bundles on the side arms (4 nm wide, 27 and 43 nm long), and a  
19 floppy dsDNA loop at the bottom (2 nm wide). For a [detailed scheme](#) of the design see SI,  
20 Figure S7. Note that the structure is a 2D design, which means that it is only one dsDNA thick  
21 (2 nm), which is desired as we aim for TEM visualization of single dsDNA structures. The  
22 structure is a suitable microscopy test object in order to check if different TEM techniques  
23 (STEM, DF) can provide enough resolution to visualize DNA at various length scales in the  
24 design.  
25  
26  
27  
28  
29  
30  
31  
32  
33  
34  
35  
36  
37  
38  
39  
40  
41  
42

43 To fold the origami plate, a 7560 base-long scaffold (M13mp18 phage-derived genomic  
44 DNA), and staple oligonucleotide strands were purchased from Tilibit®, Munich, Germany.  
45 Folding reactions consisted of folding buffer (5 mM Tris-base, 1 mM EDTA, 5 mM NaCl and  
46 12.5 mM MgCl<sub>2</sub> at pH8), 20 nM scaffold strand supplied with 10x excess oligo staples (200  
47 nM). A thermocycler was used to fold the structure by heating first to 65 °C and then ramping  
48 the temperature from 60 to 40 °C at a cooling rate of 1 °C/h and subsequently keeping the  
49 nanostructures at 12 °C. After folding, origami plates were purified from excess staple  
50 oligonucleotides using Amicon cutoff filters (100 kDa MWCO, Milipore). Prior to  
51  
52  
53  
54  
55  
56  
57  
58  
59  
60  
61  
62  
63  
64  
65

1 centrifugation, the filter membranes were preconditioned with the working buffer (10 mM  
2 Tris-base, 1 mM EDTA, pH8, 15 mM MgCl<sub>2</sub>, 5 mM NaCl at pH8). Four cycles of  
3  
4 purification (2200 rcf, 4 °C) removed most oligos (SI, Figure S8). The remaining solution in  
5  
6 the dead volume of the filter was collected and diluted to a final origami concentration of 5  
7  
8 nM for TEM sample preparation. Oligomer sequences, finite-element simulations, and gel  
9  
10 electrophoresis results (for both purified and unpurified plates) are given in SI.  
11  
12  
13  
14  
15  
16

17 *TEM sample preparations:* 5 µL of origami nanoplates (oligo purified, 5 nM) was drop casted  
18  
19 onto graphene-coated TEM grids and incubated for 2 minutes. Subsequently, the samples  
20  
21 were washed with Milli-Q (MQ) water to remove unadhered origamis, and excess MQ from  
22  
23 the washing step was blotted away. For the stained samples, immediately after washing away  
24  
25 the excess origamis, staining agent was applied (2% uranyl acetate in MQ, filtered through a  
26  
27 0.2 µm PTFE membrane), incubated for 1 minute, and washed with MQ. We also prepared  
28  
29 origami samples onto amorphous carbon grids (nominal 4 nm carbon onto 6 nm formvar-  
30  
31 coated TEM grids, Electron Microscopy Science, USA), followed by the same protocol as  
32  
33 mentioned for origami on graphene, but after rendering the carbon hydrophilic with nitrogen  
34  
35 plasma.  
36  
37  
38  
39  
40  
41  
42  
43

44 *TEM imaging:* All STEM/DF images were taken with a FEI Titan microscope equipped with  
45  
46 post-specimen aberration corrector under 300 kV operating voltage. The third-order spherical-  
47  
48 aberration coefficient ( $C_s$ ) was tuned to zero in the image corrector for all S/TEM alignments  
49  
50 to minimize the delocalization. Utilization of a HAADF detector at a camera length of 28.3  
51  
52 cm resulted in mass-thickness dominated contrast. No class averaging was done and all  
53  
54 images are single acquisitions at near zero focus.  
55  
56  
57

58 In the conventional dark-field technique, certain spatial frequencies in the back-focal plane  
59  
60 are collected by the objective aperture to form the image. In our DF method, in contrast, all  
61  
62

1 scattered frequencies are let through, except the noise-bearing central beam. <sup>[22]</sup> To realize this,  
2 we fabricated a "Mercedes star"-shaped aperture on a 5  $\mu\text{m}$ -thick-platinum foil and ion-milled  
3  
4 the Mercedes star using a FEI Helios microscope. Special care was taken to fabricate an as-  
5  
6 smooth-as-possible aperture to avoid beam charging and image drift. Detailed geometry and  
7  
8 dimensions of the delicate DF aperture is provided in SI, Figure S9, as well as an electron  
9  
10 optical comparison with STEM (SI, Figure S10). The DF aperture achieves a 1- $\text{\AA}$ -information  
11  
12 cutoff (SI, Figure S10c). We have previously shown that an information cutoff beyond 1  $\text{\AA}$   
13  
14 would have a minimal effect on the contrast of weak-phase objects such as DNA origami  
15  
16 supported onto graphene, whereas removal of the central beam has a major effect due to  
17  
18 elimination of the Poisson noise. <sup>[22]</sup> Therefore, 1  $\text{\AA}$  information cutoff seems satisfactory for  
19  
20 the DF aperture. Collection of all scattered electrons while omitting the central beam results in  
21  
22 a dramatic contrast enhancement, as shown on a graphene test sample in SI, Figure S11. In  
23  
24 contrast to conventional bright-field imaging, the interference of diffracted beams enhances  
25  
26 the contrast in our DF technique (non-linear imaging). <sup>[22]</sup> Note that for complete blockade of  
27  
28 the central beam, parallel illumination is a prerequisite. Hence, the C3 lens in the condenser  
29  
30 system of the Titan microscope should be well tuned. We did DF image simulations to find  
31  
32 the optimum focus for imaging. Based on our simulations (SI, Figure S12 and Figure S13),  
33  
34 the best contrast is achieved at near zero focus with a  $C_s$ -corrected microscope. Finally, it  
35  
36 should be mentioned that the temperature rise during STEM/DF imaging is negligible (only 1-  
37  
38 2 K) <sup>[23]</sup> and will not cause any structural melting under the electron beam (as double-helix  
39  
40 unwinding only occurs above 50° C).  
41  
42  
43  
44  
45  
46  
47  
48  
49  
50

51  
52  
53 *AFM imaging:* AFM investigations were carried out on freshly cleaved surfaces of mica and  
54  
55 HOPG under dry condition unless indicated otherwise. 4  $\mu\text{L}$  of origami sample (5 nM) was  
56  
57 drop casted onto 3 mm wide mica or HOPG disks, incubated for 1 minute, washed three times  
58  
59 with MQ, and finally blown dry with nitrogen gas. Image acquisition was carried out in  
60  
61  
62  
63  
64  
65



1 tapping mode and data analysis was done with NanoScope (Bruker, USA) and the open-  
2 source Gwyddion package. [35] For liquid-cell AFM imaging, DNA origami was incubated on  
3 mica for 1 minute, buffer-washed to remove the unbound plates, while the structure was kept  
4 in liquid for imaging without any further drying. The washing and imaging buffer was  
5 supplemented with an additional 1mM NiCl<sub>2</sub> for better attachment of the origami to mica,  
6 which resulted in more stable AFM imaging.  
7  
8  
9  
10  
11  
12  
13  
14  
15  
16  
17

### 18 **Supporting Information**

19 Supporting Information is available from the Wiley Online Library or from the author.  
20  
21  
22  
23  
24

### 25 **Acknowledgements**

26  
27 This work was supported by the Netherlands organization for scientific research  
28 (NWO/OCW), as part of the Frontiers of Nanoscience program. Funding from the ERC  
29 advanced grants, NEMinTEM 267922 and SynDiv 669598, is also appreciated. We  
30 acknowledge FEI NanoPort in Eindhoven for access to the Helios dual beam microscope,  
31 especially the kind efforts of Nico Clemens. J.Y.H and J.K acknowledge support from the US  
32 AFOSR FATE MURI, Grant No. FA9550-15-1-0514. A.N.A acknowledges funding from  
33 NanoNextNL (program 07A.05) and thanks Philip Ketterer (TU Munich) for valuable  
34 discussions.  
35  
36  
37  
38  
39  
40  
41  
42  
43  
44  
45  
46  
47  
48  
49  
50  
51  
52  
53  
54  
55  
56  
57  
58  
59  
60  
61  
62  
63  
64  
65

## References

- 1  
2 [1] R. M. Westervelt, *Science* **2008**, *320*, 324.  
3  
4 [2] Y. Liu, X. Dong, P. Chen, *Chem Soc Rev* **2012**, *41*, 2283.  
5  
6 [3] J. Jeon, M. S. Lodge, B. D. Dawson, M. Ishigami, F. Shewmaker, B. Chen, *Biochim.*  
7  
8 *Biophys. Acta* **2013**, *1830*, 3807.  
9  
10 [4] R. S. Pantelic, J. W. Suk, C. W. Magnuson, J. C. Meyer, P. Wachsmuth, U. Kaiser, R.  
11  
12 S. Ruoff, H. Stahlberg, *J. Struct. Biol.* **2011**, *174*, 234.  
13  
14 [5] R. Zan, Q. M. Ramasse, R. Jalil, T. Georgiou, U. Bangert, K. S. Novoselov, *ACS Nano*  
15  
16 **2013**, *7*, 10167.  
17  
18 [6] C. Wang, Q. Qiao, T. Shokuhfar, R. F. Klie, *Adv. Mater.* **2014**, *26*, 3410.  
19  
20 [7] M. R. Jones, N. C. Seeman, C. A. Mirkin, *Science* **2015**, *347*, 1260901.  
21  
22 [8] S. Woo, P. W. K. Rothmund, *Nat. Chem.* **2011**, *3*, 620.  
23  
24 [9] P. W. K. Rothmund, *Nature* **2006**, *440*, 297.  
25  
26 [10] S. M. Douglas, A. H. Marblestone, S. Teerapittayanon, A. Vazquez, G. M. Church, W.  
27  
28 M. Shih, *Nucleic Acids Res.* **2009**, *37*, 5001.  
29  
30 [11] J. D. Griffith, S. Lee, Y. H. Wang, *Curr. Opin. Struct. Biol.* **1997**, *7*, 362.  
31  
32 [12] M. Marini, A. Falqui, M. Moretti, T. Limongi, M. Allione, A. Genovese, S. Lopatin, L.  
33  
34 Tirinato, G. Das, B. Torre, A. Giugni, F. Gentile, P. Candeloro, E. Di Fabrizio, *Sci. Adv.*  
35  
36 **2015**, *1*, 1.  
37  
38 [13] M. Marini, T. Limongi, A. Falqui, A. Genovese, M. Allione, M. Moretti, S. Lopatin, L.  
39  
40 Tirinato, G. Das, B. Torre, A. Giugni, F. Cesca, F. Benfenati, E. Di Fabrizio,  
41  
42 *Nanoscale* **2017**, *9*, 2768.  
43  
44 [14] F. Gentile, M. Moretti, T. Limongi, A. Falqui, G. Bertoni, A. Scarpellini, S. Santoriello,  
45  
46 L. Maragliano, R. Proietti Zaccaria, E. Di Fabrizio, *Nano Lett.* **2012**, *12*, 6453.  
47  
48 [15] S. Buckhout-White, J. T. Robinson, N. D. Bassim, E. R. Goldman, I. L. Medintz, M. G.  
49  
50 Ancona, *Soft Matter* **2013**, *9*, 1414.  
51  
52  
53  
54  
55  
56  
57  
58  
59  
60  
61  
62  
63  
64  
65



- 1  
2  
3  
4  
5  
6  
7  
8  
9  
10  
11  
12  
13  
14  
15  
16  
17  
18  
19  
20  
21  
22  
23  
24  
25  
26  
27  
28  
29  
30  
31  
32  
33  
34  
35  
36  
37  
38  
39  
40  
41  
42  
43  
44  
45  
46  
47  
48  
49  
50  
51  
52  
53  
54  
55  
56  
57  
58  
59  
60  
61  
62  
63  
64  
65
- [16] K. Nagayama, R. Danev, *Philos. Trans. R. Soc. Lond. B. Biol. Sci.* **2008**, *363*, 2153.
- [17] B. J. Pages, D. L. Ang, E. P. Wright, J. R. Aldrich-Wright, *Dalt. Trans.* **2015**, *44*, 3505.
- [18] R. Erni, *Aberration-Corrected Imaging in Transmission Electron Microscopy*, Imperial College Press, **2010**.
- [19] R. F. Egerton, F. Wang, P. A. Crozier, *Microsc. Microanal.* **2006**, *12*, 65.
- [20] P. A. Midgley, M. Weyland, J. M. Thomas, B. F. G. Johnson, *Chem. Commun.* **2001**, 907.
- [21] R. M. Glaeser, *J. Ultrastructure Res.* **1971**, *36*, 466.
- [22] C. Zhang, Q. Xu, P. J. Peters, H. Zandbergen, *Ultramicroscopy* **2013**, *134*, 200.
- [23] R. F. Egerton, P. Li, M. Malac, *Micron* **2004**, *35*, 399.
- [24] G. Algara-Siller, S. Kurasch, M. Sedighi, O. Lehtinen, U. Kaiser, *Appl. Phys. Lett.* **2013**, *103*, 203107.
- [25] R. M. Glaeser, *Nat Methods* **2016**, *13*, 28.
- [26] G. Algara-Siller, O. Lehtinen, A. Turchanin, U. Kaiser, *Appl. Phys. Lett.* **2014**, *104*, 153115.
- [27] B. S. Husale, S. Sahoo, A. Radenovic, F. Traversi, P. Annibale, A. Kis, *Langmuir* **2010**, *26*, 18078.
- [28] N. S. Green, M. L. Norton, *Anal. Chim. Acta* **2015**, *853*, 127.
- [29] W. Liu, H. Zhong, R. Wang, N. C. Seeman, *Angew. Chemie - Int. Ed.* **2011**, *50*, 264.
- [30] R. Campos, S. Zhang, J. M. Majikes, L. C. C. Ferraz, T. H. LaBean, M. D. Dong, E. E. Ferapontova, *Chem. Commun.* **2015**, *51*, 14111.
- [31] J. M. Yun, K. N. Kim, J. Y. Kim, D. O. Shin, W. J. Lee, S. H. Lee, M. Lieberman, S. O. Kim, *Angew. Chemie - Int. Ed.* **2012**, *51*, 912.
- [32] R. S. Pantelic, W. Fu, C. Schoenenberger, H. Stahlberg, *Appl. Phys. Lett.* **2014**, *104*, 134103.
- [33] C. E. Castro, F. Kilchherr, D.-N. Kim, E. L. Shiao, T. Wauer, P. Wortmann, M. Bathe,

H. Dietz, *Nat. Methods* **2011**, *8*, 221.

[34] W. Regan, N. Alem, B. Alemán, B. Geng, Ç. Girit, L. Maserati, F. Wang, M. Crommie, A. Zettl, *Appl. Phys. Lett.* **2010**, *96*, 113102.


[35] D. Nečas, P. Klapetek, *Cent. Eur. J. Phys* **2012**, *10*, 181.

1  
2  
3  
4  
5  
6  
7  
8  
9  
10  
11  
12  
13  
14  
15  
16  
17  
18  
19  
20  
21  
22  
23  
24  
25  
26  
27  
28  
29  
30  
31  
32  
33  
34  
35  
36  
37  
38  
39  
40  
41  
42  
43  
44  
45  
46  
47  
48  
49  
50  
51  
52  
53  
54  
55  
56  
57  
58  
59  
60  
61  
62  
63  
64  
65

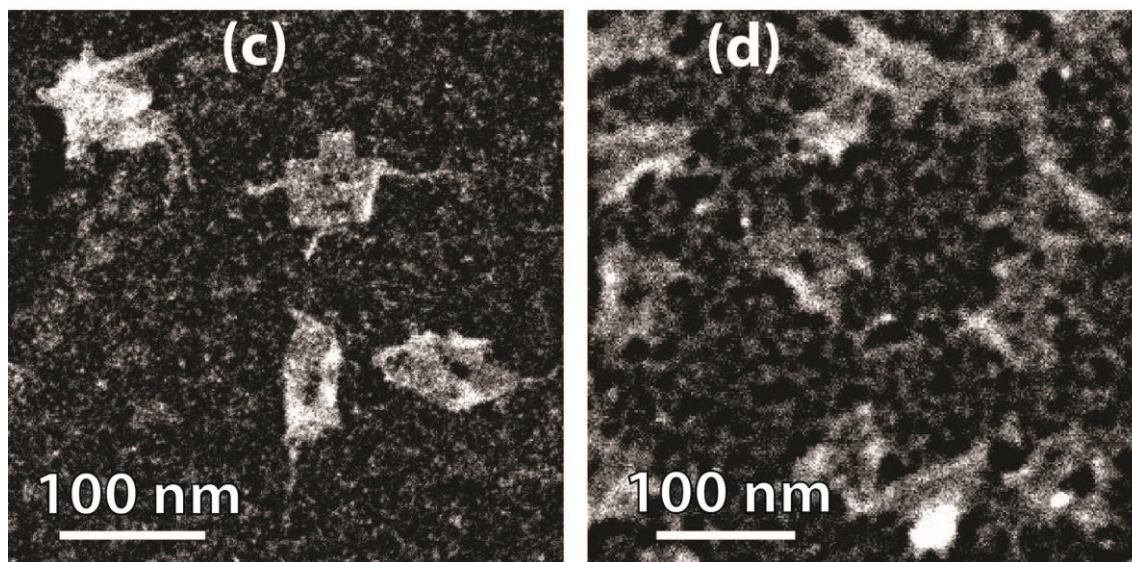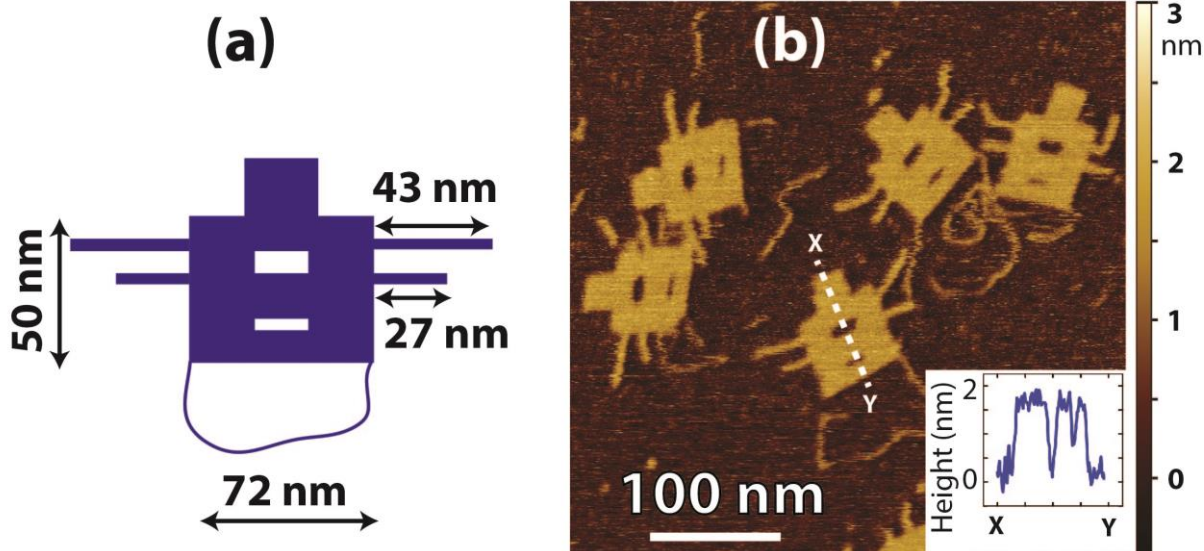


38 **Figure 1.** (a) Design schematic of the symmetric DNA origami nanoplate. (b) Liquid-cell  
39 AFM image of DNA origami on mica. (C) Uranyl acetate-stained DNA origami plates on  
40 suspended graphene imaged with STEM. (d) Same, but without any staining.  
41  
42  
43  
44  
45  
46  
47  
48  
49  
50  
51  
52  
53  
54  
55  
56  
57  
58  
59  
60  
61  
62  
63  
64  
65



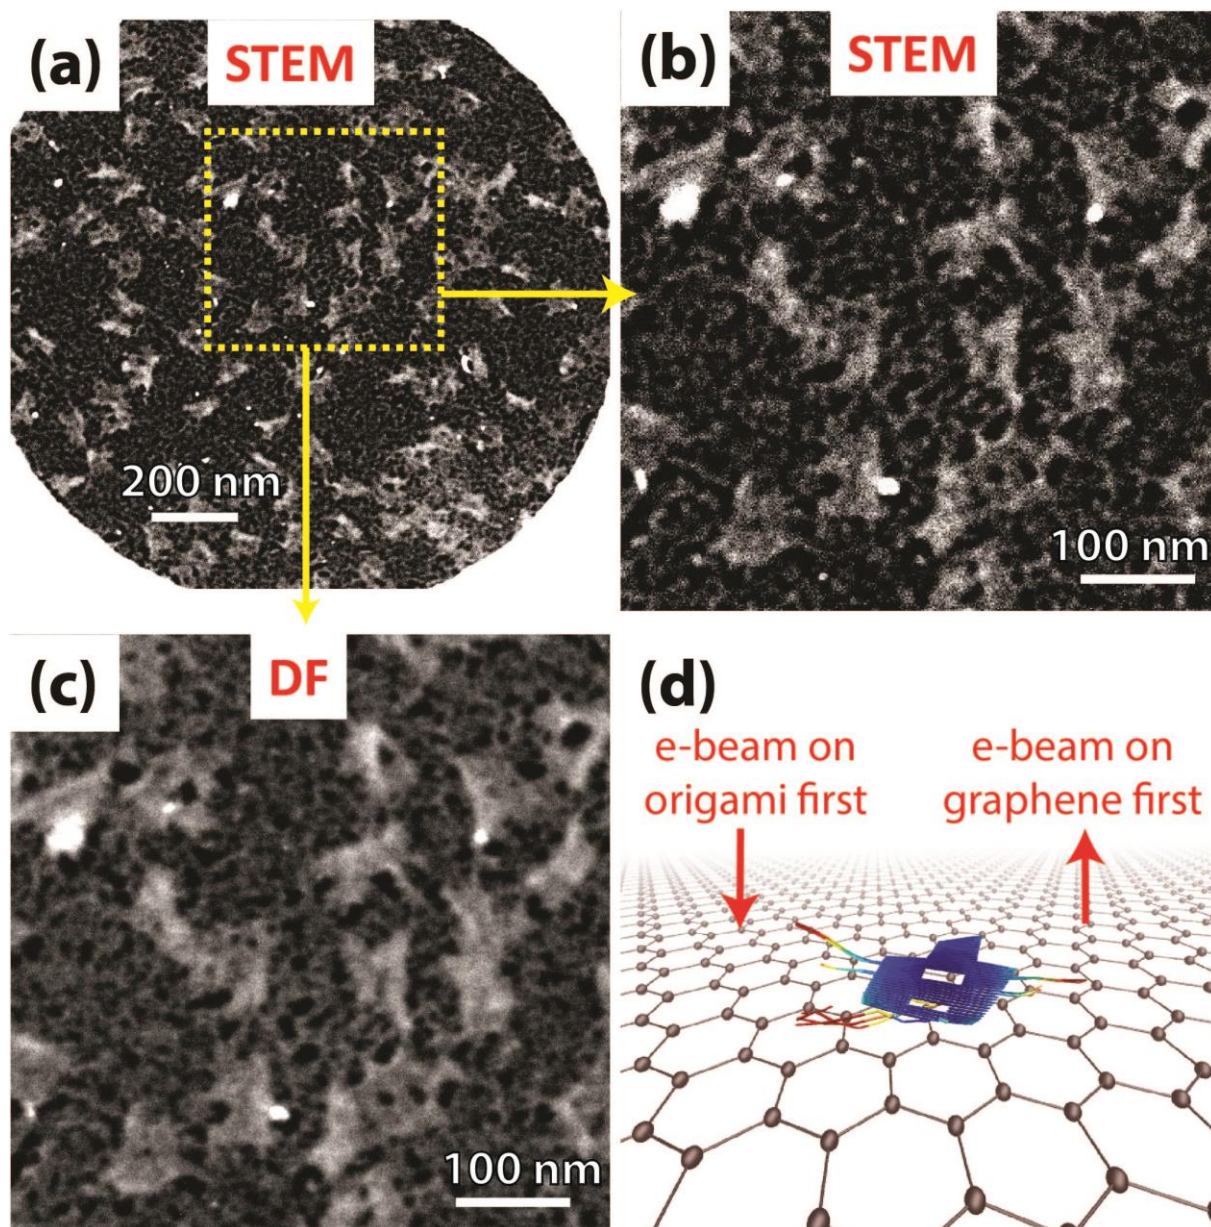


**Figure 2.** Comparison of STEM and DF to examine the effect of beam exposure on DNA origami distortion. (a) STEM overview image of the investigated area of unstained DNA origami on graphene. (b) Close-up of the boxed area in (a) imaged with STEM (c) Same for DF. Note that the sequence of events during imaging was from (c) to (a) in order to expose the area first with DF and only then with STEM. The DNA origami appears to be the same in panel (c) and (b), which shows that the intense STEM beam does not cause the distortion. Focus setting of the microscope was carried out in the neighboring area to avoid beam damage on the region of interest. The electron dose for the DF image in (c) corresponds to  $25 \text{ e}/\text{\AA}^2$ . Similar distorted DNA plates were seen when imaged with lower electron doses. (d) Artistic impression of origami on graphene (not to scale). Two different orientations were investigated: one where the electron beam first hits the origami and then graphene (left arrow), or the other way around (right arrow). We did not observe any difference in terms of damage response.



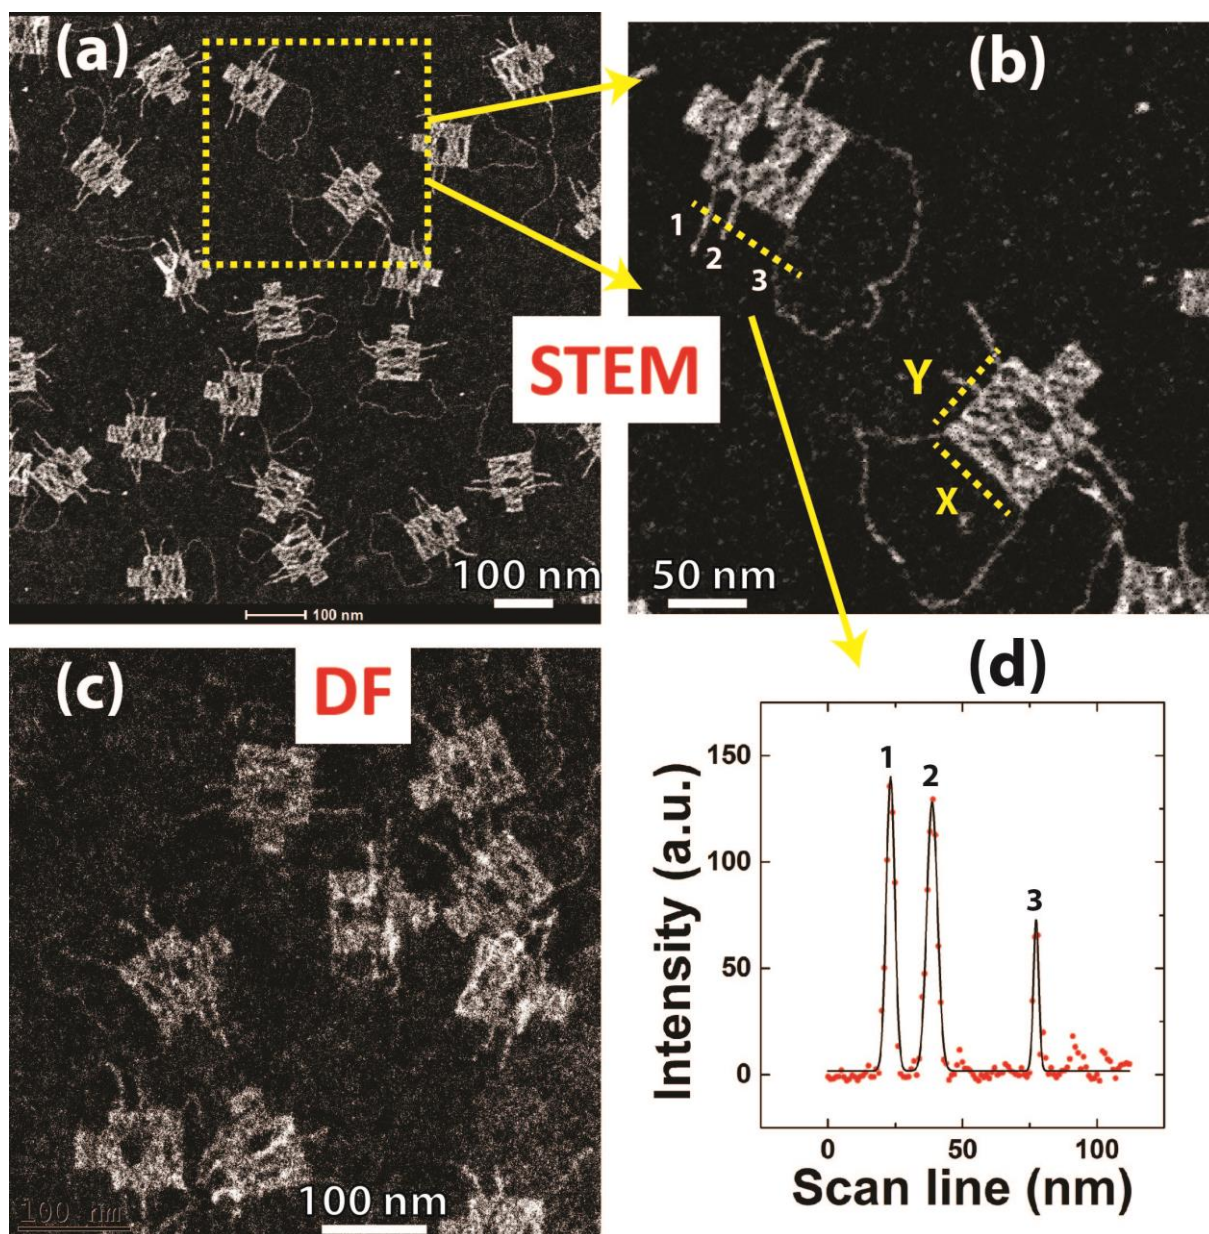


**Figure 3.** Distortion of the DNA origami is found to be substrate dependent. On amorphous carbon, origami is well spread and all details of the nanoplates become visible. (a) STEM image of uranyl-stained origami on 15 nm amorphous carbon (thickness measured by EELS). (b) Close-up of dashed area in (a). All structural features in the nanoplate design (cf. Figure 1a) are resolved. X and Y correspond to 71 and 65 nm respectively. (c) DF image on the same carbon membrane but from a different area. DF can also visualize the structures, however, with a lower SNR. (d) Line profile of the detector signal passing through the DNA bundles and single dsDNA loop indicated by the dashed line in panel (b). The peaks depict an excellent contrast with high SNR. We find full widths at half maxima of 3.4, 4.3 and 2.1 nm corresponding to peaks 1 to 3 respectively. These values conform to the widths of 2-helix DNA bundles (4 nm wide) and single dsDNA (2 nm wide) (cf. Figure 1a).

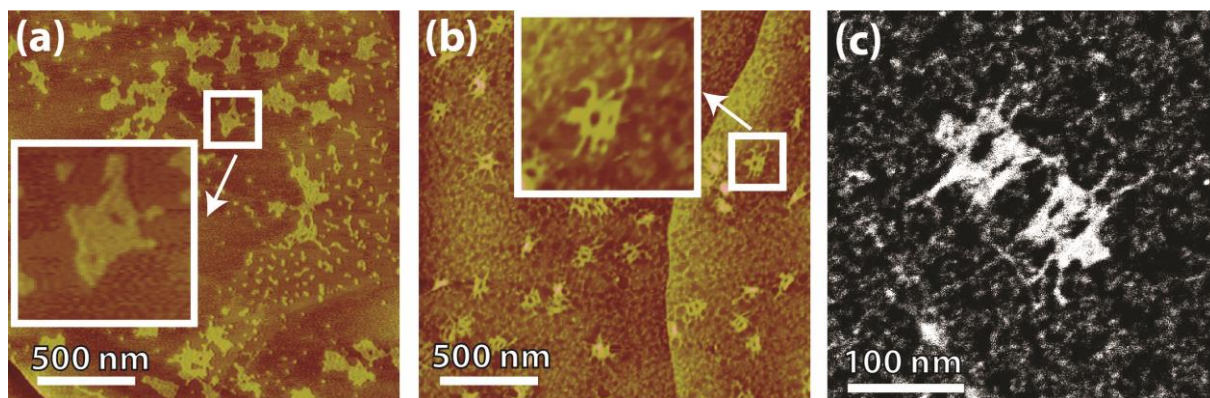

**Figure 4.** Graphene functionalization prevents  $\pi$ - $\pi$  stacking with the hydrophobic DNA bases. (a) AFM image of origami on a HOPG surface. (b) Origami on a PLL-coated HOPG. Insets are enlargements of the plates marked inside the boxes in (a) and (b). (c) STEM image of a stained origami on 1PCA-functionalized graphene, showing less distorted plates compared to bare graphene.




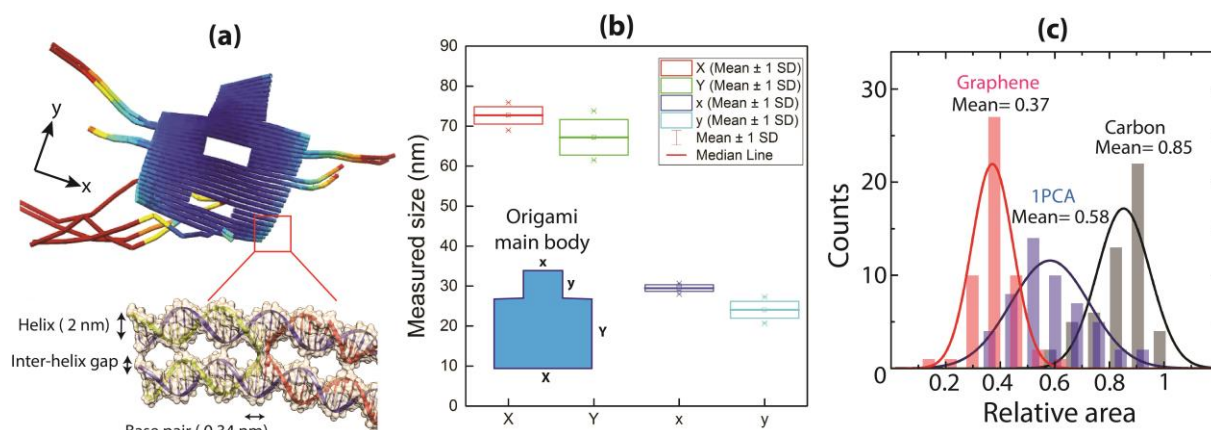

**Figure 5.** Quantification of the distortion of DNA origami on graphene-like substrates. (a) Inter-helical gaps along the y-axis of the nanoplate caused by electrostatic repulsions between the strands (the origami snapshot is exported from the caDNAano package) (b) Liquid-cell AFM measurements of the nanoplate dimensions (c) Statistical analysis of the relative area of origami plates extracted from TEM images onto different substrates (graphene, 1PCA-functionalized graphene, and amorphous carbon). We find significant different mean values for the relative area on different size substrates.



Click here to access/download  
**Supporting Information**  
Small-Revise-Supplementary.docx





Click here to access/download

**Production Data**  
2296\_checklist.pdf

