

Superconducting nanowire single photon detectors operating at temperature from 4 to 7 K

Gourgues, Ronan; Los, Johannes W.N.; Zichi, Julien; Chang, Jin; Kalhor, Nima; Bulgarini, Gabriele; Dorenbos, Sander N.; Zwiller, Val; Zadeh, Iman Esmaeil

DOI

[10.1364/OE.27.024601](https://doi.org/10.1364/OE.27.024601)

Publication date

2019

Document Version

Final published version

Published in

Optics Express

Citation (APA)

Gourgues, R., Los, J. W. N., Zichi, J., Chang, J., Kalhor, N., Bulgarini, G., Dorenbos, S. N., Zwiller, V., & Zadeh, I. E. (2019). Superconducting nanowire single photon detectors operating at temperature from 4 to 7 K. *Optics Express*, 27(17), 24601-24609. <https://doi.org/10.1364/OE.27.024601>

Important note

To cite this publication, please use the final published version (if applicable).
Please check the document version above.

Copyright

Other than for strictly personal use, it is not permitted to download, forward or distribute the text or part of it, without the consent of the author(s) and/or copyright holder(s), unless the work is under an open content license such as Creative Commons.

Takedown policy

Please contact us and provide details if you believe this document breaches copyrights.
We will remove access to the work immediately and investigate your claim.



Superconducting nanowire single photon detectors operating at temperature from 4 to 7 K

RONAN GOURGUES,^{1,*} JOHANNES W. N. LOS,¹ JULIEN ZICHI,² JIN CHANG,³ NIMA KALHOR,¹ GABRIELE BULGARINI,¹ SANDER N. DORENBOS,¹ VAL ZWILLER,² AND IMAN ESMAEL ZADEH³

¹Single Quantum B.V., 2628 CH Delft, The Netherlands

²Department of Applied Physics, Royal Institute of Technology (KTH), SE-106 91 Stockholm, Sweden

³Optics Research Group, ImPhys Department, Faculty of Applied Sciences, Delft University of Technology, Lorentzweg 1, 2628 CJ Delft, The Netherlands

*ronan@singlequantum.com

Abstract: We experimentally investigate the performance of NbTiN superconducting nanowire single photon detectors above the base temperature of a conventional Gifford-McMahon cryocooler (2.5 K). By tailoring design and thickness (8 - 13 nm) of the detectors, high performance, high operating temperature, single-photon detection from the visible to telecom wavelengths are demonstrated. At 4.3 K, a detection efficiency of 82 % at 785 nm wavelength and a timing jitter of 30 ± 0.3 ps are achieved. In addition, for 1550 nm and similar operating temperature we measured a detection efficiency as high as 64 %. Finally, we show that at temperatures up to 7 K, unity internal efficiency is maintained for the visible spectrum. Our work is particularly important to allow for the large scale implementation of superconducting single photon detectors in combination with heat sources such as free-space optical windows, cryogenic electronics, microwave sources and active optical components for complex quantum optical experiments and bio-imaging.

© 2019 Optical Society of America under the terms of the [OSA Open Access Publishing Agreement](#)

1. Introduction

Since Superconducting Nanowire Single Photon Detectors (SNSPDs) were introduced in 2001 [1], their performance has been dramatically improved to become the leading technology in single photon detection. Nowadays, SNSPDs offer outstanding performance, with system detection efficiencies of 80 - 95 %, from the visible to the infrared [2–6], dark count rates in the mHz range [5, 7], detection count rates up to 1.5 GHz [8], and timing jitter as low as < 10 ps [9–12]. High performance SNSPDs operating at 4 K and above, are particularly interesting due to the vast number of potential applications. It has been proposed that for superconducting quantum computing, part of the qubit readout can be performed with optical signals within the dilution refrigerator. Due to limited cooling power available at the quantum processor stage (below 1 K), the readout device has to be located at a higher temperature stage of the cryostat (4 K) [13]. Another potential application is optical quantum information processing, which is based on efficient generation and detection of on demand entangled single photons with effective electronic control of the single photon source spin. Promising candidates are solid state emitters such as quantum dots (QDs) and nitrogen-vacancy (NV) centres in diamond which emit in the range of 600 - 1550 nm [14–17]. To achieve scalability and more efficient photon extraction [18–20], it is required to integrate single photon sources and single photon detectors with photonic circuits [21]. Extending the complexity of integrated photonic circuit with active optical components such as modulators [22] will increase the base temperature of the cryostat due to the heat load of the wiring connecting the components with external room temperature control electronics. Thus, this will have a detrimental effect on the performance

of the SNSPD. Currently, SNSPDs require sophisticated cooling systems with sizeable power consumption (>1 kW) which restricts their use mainly to the research community. Several high critical temperature (T_c) superconducting materials, such as magnesium diboride (MgB_2) have been investigated to detect single photons but efficient detectors have yet to be demonstrated [23]. On the other hand, semiconductor avalanche photodiodes (APDs) are an alternative technology in the VIS - NIR range, operating at room temperature and being relatively inexpensive. However, APDs suffer from after-pulsing, higher dark count rates, long non-Gaussian instrument response function and thus limited time resolution [24]. Subsequently, APDs presents difficult challenges to be integrated efficiently with photonic platform such as quantum information processing application with single photons. Recently, a low power consumption and compact closed-cycle cooling cryostat suitable for space applications has been developed and engineered by different international research laboratories [25, 26]. For such cryocoolers, the base temperature reached is ~ 4 K which drastically limits performance of existing SNSPDs.

In this work, we engineer NbTiN SNSPDs to achieve high efficiency and high time resolution at 4 K and above, paving the way for integration of SNSPDs in complex, large scale and portable optical experiments.

2. SNSPDs fabrication

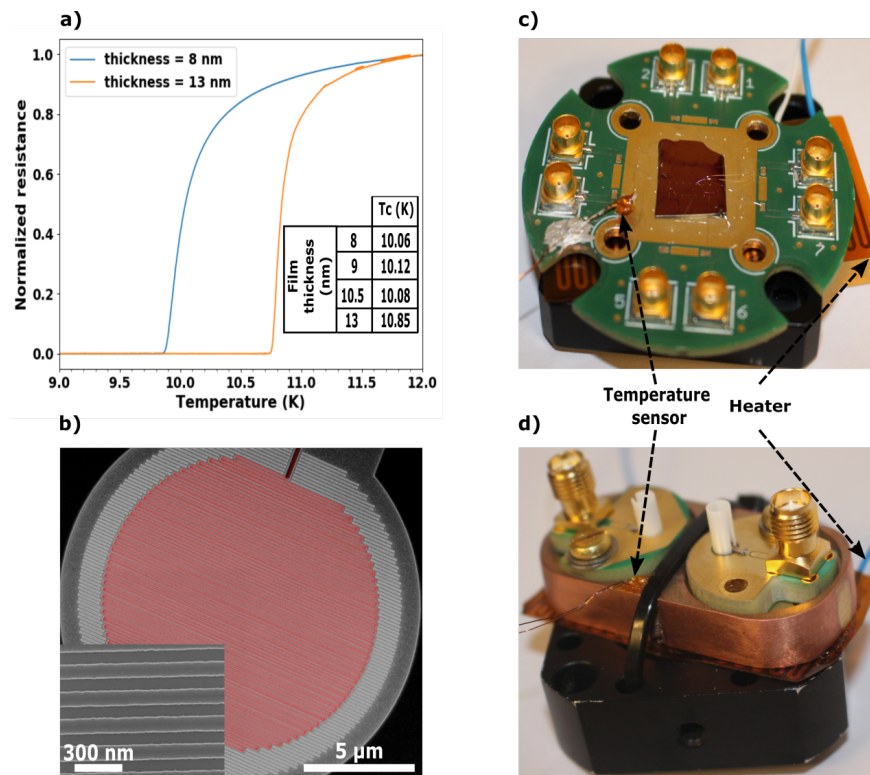


Fig. 1. (a) Measurements of the superconducting transition temperature for 8 nm and 13 nm film thickness. The table in the inset summarizes the T_c for the studied films. The error is estimated to be ± 0.1 K. (b) False-color SEM image of the superconducting single photon detector meander. The inset shows the 70 nm nanowire width of the superconducting device. (c) Free-space holder with the sample wire-bonded in the center of the PCB. (d) Fiber-coupled superconducting detector wire-bonded to the PCB, mounted on the oxygen free copper block.

The first fabrication step of the SNSPD is the deposition of NbTiN films by magnetron co-sputtering in an Ar and N₂ atmosphere on a Distributed Bragg Reflector (DBR) mirror optimized for the wavelength of interest. The sputtering recipe was, in a separate study [27], optimized for saturation of internal efficiency and critical current which lead us to choose Nb_{0.85}Ti_{0.15}N and Nb_{0.62}Ti_{0.38}N as compositions for the VIS-NIR range and 1550 nm, respectively. The film thicknesses processed in this manuscript are 8 nm, 9 nm, 10.5 nm and 13 nm. The nominal thickness was estimated from the sputtering time and the deposition rate which has been verified by Atomic Force Microscopy. After film deposition, the wafers were cleaved in small and large pieces. The small pieces were used for determining the superconducting transition temperature in a four-point probe cryogenic setup and the large pieces were used to fabricate the detectors. Figure. 1(a) shows the normalized resistance versus base temperature for 8 nm and 13 nm thick films. In the inset, the table summarizes the critical temperature (T_c) for different film thicknesses studied in this work. We observe that the critical temperature increases with the film thickness. This behavior can be explained by the proximity effect [28], in addition to a decrease of the 3-dimensional disorder of the film [29]. Subsequently, we used photolithography to deposit gold contact pads for the fiber-coupled devices. The meanders were patterned using the positive AR-P 6200 e-beam resist and a 100 keV electron beam lithography system, then the pattern was transferred to the NbTiN layer by dry etching using SF₆ and O₂ chemistry. Devices with different widths of nanowires were fabricated, from 50 nm to 100 nm, while keeping the filling factor (50 %) and diameter (14 μm) constant. Figure. 1(b) presents a scanning electron microscope (SEM) image of a fabricated detector with the meander highlighted in red. The inset of Fig. 1(b) shows a magnified view of the detector with a nanowire width of 70 nm. To fiber couple the detectors, an additional etching step is needed to etch keyhole shaped chips [30]. Next, the samples were mounted on two different printed circuit boards (PCB) covered with gold-plated copper: Fig. 1(c) presents a picture of a flood illumination holder whereas Fig. 1(d) shows a fiber-coupling holder made from oxygen free copper. We placed our detector chips in direct contact with PCB and fixed it with thermally conductive glue, such as silver paste for free space samples and stycast for fiber coupled ones. In both cases, a heater element which consists of a flat flexible resistor embedded in Kapton film (Iceoxford), is placed below the PCB to control the detector temperature. Moreover a cryogenic sensor is glued with varnish in the proximity of the detector. The temperature diode is calibrated by using a reference calibrated diode and the error on the temperature measurement is estimated to be about 0.1K. Finally, the detectors were wire-bonded to the selected PCB for electrical bias and readout. We investigated the internal efficiency performance of devices made from different film thicknesses by using the flood illumination holder (Fig. 1(c)) as described in the first part of section 4. The measurements were performed with a home-made exchange gas dipstick immersed into a transportable liquid helium dewar.

3. Measurements of SNSPDs critical current and dark count rate as a function of temperature

Figure. 2(a) shows the critical currents of SNSPDs made from films with different thicknesses and nanowire widths, operated at temperatures ranging from 4.3 K to 8.1 K. In order to have a stable temperature at the detector, we waited 5 - 10 minutes before each measurements. Above ~ 8 K, the critical current is too low to resolve a detection pulse from the noise (root mean square noise ~ 30 mV) of our setup. We observe that the critical current decreases when the temperature increases, as expected. Additionally, the use of thicker films and wider nanowires increase the critical current of the superconducting devices [31]. The red dashed curve in Fig. 2(a) is a fit from the Ginzburg-Landau theory ($I_c \propto (1 - \frac{T}{T_c})^{\frac{3}{2}}$), which defines the behavior of the critical current as function of the temperature. For 70 nm wide nanowires, the fit leads to T_c= 8.55 K and T_c= 9.18 K instead of T_c=10.12 K and T_c= 10.85 K that was measured before etching the superconducting film into a meander shape, for 9 nm and 13 nm film thickness, respectively.

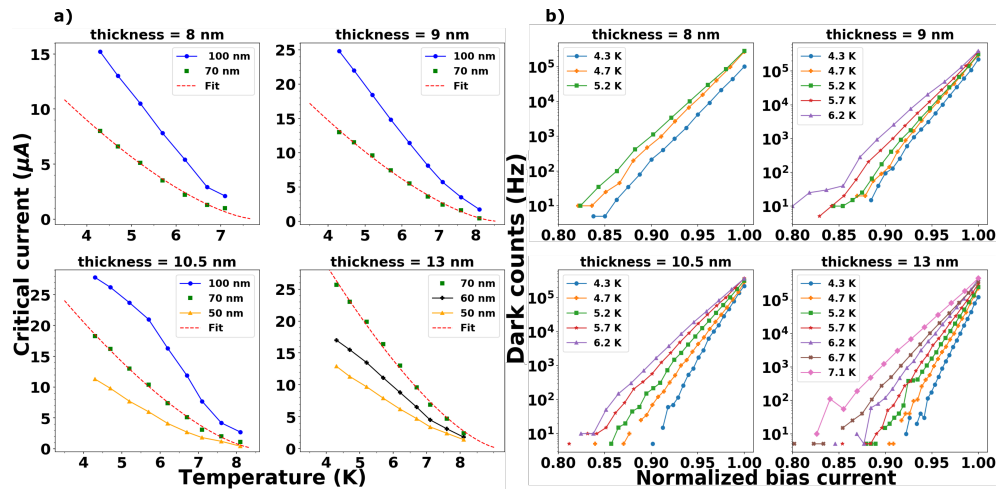


Fig. 2. (a) Measurements of the critical current vs. base temperature for different film thicknesses (8 nm, 9 nm, 10.5 nm and 13 nm) and nanowire width (50 nm, 60 nm, 70 nm and 100 nm). The red dashed line is a fit from the Ginzburg-Landau theory. (b) Measurements of the dark count rates vs. bias current for different film thicknesses (8 nm, 9 nm, 10.5 nm and 13 nm) with 70 nm nanowire width.

Figure 2(b) presents the Dark Count Rate (DCR) of 70 nm wide nanowire SNSPDs as function of the bias current for different film thickness, in a temperature range from 4.3 K to 7.1 K. For these measurements, we used the flood illumination holder (Fig. 1(c)) in order to minimize the influence of black-body radiation that could be transmitted by the fiber and we assumed that only the intrinsic dark counts were recorded. We notice that the DCR raises exponentially with the bias current and the absolute value increases with the temperature. This behavior suggests that the dominant mechanism responsible for dark count is the current-assisted unbinding of vortex-antivortex pairs caused by thermal fluctuations [32]. Moreover, for thicker films the exponential increases of DCR starts at higher bias current compared to the critical current. For instance, at 4.3 K (blue curves in Fig. 2(b)) we can compare the starting bias current values for which the DCR curve starts to increase exponentially. It corresponds to a bias current of $0.85I_c$ and $0.93I_c$ for 8 nm and 13 nm film thickness, respectively. A similar trend is observed for all the investigated temperatures. To conclude this section, we have shown that it is possible to reduce the intrinsic DCR and increase the switching current (by up to a factor of 3 for 70 nm nanowire width) by using thick film for SNSPDs.

4. SNSPDs efficiencies and timing jitter characterization as a function of temperature

To characterize the single photon detectors, we used different laser diodes emitting at 400 nm, 515 nm, 642 nm, 670 nm, 785 nm and 1550 nm. The wavelength range of 400 - 700 nm is significant for fluorescence microscopy [33, 34] and for studying celestial objects from space and ground-based observatories. Many high purity III-V QDs emit at ~ 800 nm [35, 36] likewise quantum memories based on electromagnetically induced transparency in Rubidium cells operating at similar wavelength [37]. 1550 nm wavelength is the widely used wavelength for quantum communication technology.

Figure 3(a) presents the normalized detection efficiency of the device as a function of the bias current for 70 nm wide nanowire and 9 nm film thickness, from 4.3 K to 6.2 K. Each data point is an average of three measurements with an integration time of 200 ms, and the DCR is

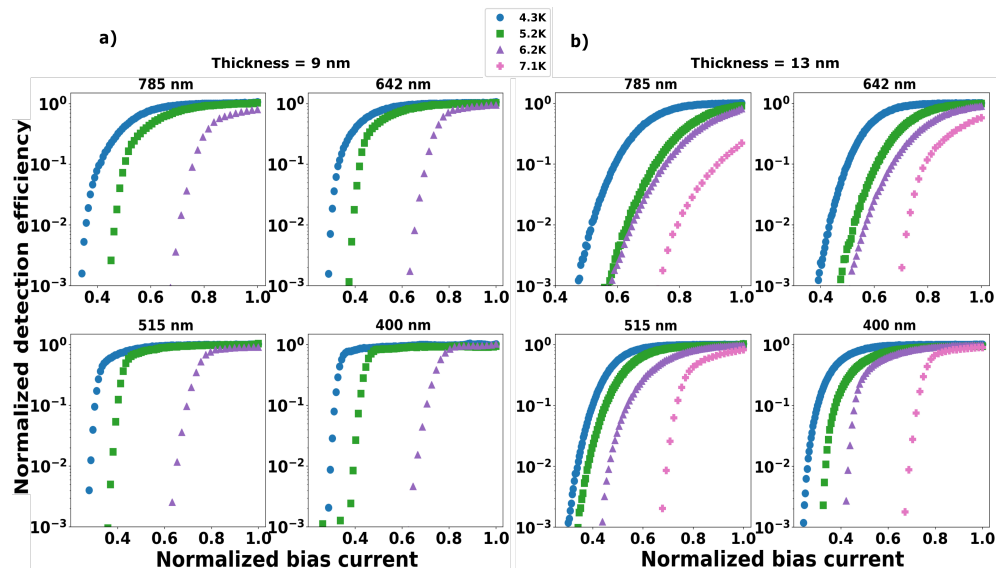


Fig. 3. (a) Normalized detection efficiency vs. bias current at 4.3 K, 5.2 K and 6.2 K for 9 nm thick film. (b) Normalized detection efficiency vs. bias current at 4.3 K, 5.2 K, 6.2 K and 7.1 K for 13 nm thick film. The measurements are performed with CW laser diodes at 785 nm, 642 nm, 515 nm and 400 nm.

subtracted. From 4.3 K to 6.2 K, we observe a strong saturation of the internal efficiency for all wavelengths, except for 785 nm at 6.2 K where the saturation is weak. By increasing the film thickness, we enhance the optical absorption for longer wavelengths but the internal efficiency gets weaker [4]. Figure 3(b) presents the normalized detection efficiency from 4.3 K to 7.1 K as a function of the bias current, for 70 nm wide nanowire and 13 nm film thickness. Similar to 9 nm thickness, the saturation of the internal efficiency is reached from 4.3 K to 6.2 K, but decreases with higher photon wavelength. At 7.1 K, the saturation regime is attained for 400 nm and 515 nm. As expected, at low temperatures (4.3 K) devices made from the thinner 9 nm films exhibit stronger saturation of internal efficiency than devices from the thicker 13 nm films. However, at 7.1 K, 13 nm film thickness still demonstrates saturation for 515 nm and 400 nm. The electrical output signal from 9 nm film is too weak to expose any saturation behavior. Therefore, at higher temperatures 13 nm film outperforms 9 nm film.

Finally, we fabricated fully packaged devices in order to measure the efficiencies at ~ 800 nm and 1550 nm as well as the temporal resolution at higher base temperatures. The fiber-coupled lasers were attenuated with a NIST-traceable attenuator to a level corresponding to a photon flux of ~ 80 kphotons/s. The light polarization was set by using a fiber paddle polarization controller to the transverse electric mode such that the SNSPD has maximum optical absorption. The efficiency of SNSPD light absorption, as a subwavelength grating, is polarization dependent. The polarization sensitivity is also dependent on the thickness and fill factor of SNSPD. As these parameters are not significantly affected by temperature, the polarization sensitivity is expected to be temperature independent. The integration time for measuring the efficiency is 1 s and the DCR is subtracted. The main contribution to the experimental error originates from the power meter, 3% for 785 nm and 5% for 1550 nm, the error from the attenuator accounts for 2.5% while the laser power is stable within 1% for both wavelengths. Thus, we estimated the measurement error to be 4% for 785 nm and less than 6% for 1550 nm. Figure 4(a) shows the detection efficiency of a detector with a thickness of 10 nm and 70 nm nanowires width (filling factor of 0.5) at 785 nm in the temperature range of 2.5 K to 6.2 K. The inset is the normalized efficiency at 670 nm for

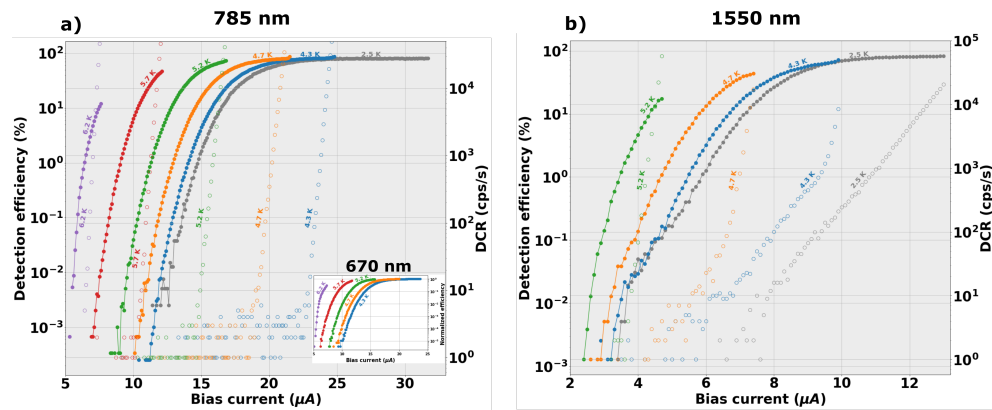


Fig. 4. (a) Detection efficiency measurements at 785 nm and dark counts rate for $T=2.5 - 6.2$ K vs. bias current. The inset presents the normalized detection efficiency at 670 nm vs. bias current in the same temperature range. (b) Detection efficiency measurements at 1550 nm and dark counts rate for $T=2.5 - 5.2$ K vs. bias current.

the same device, in the temperature range of 4.3 K to 6.2 K. The measurements at 2.5 K display in gray in Figs. 4(a)-4(b) were carried out in a Gifford-McMahon closed cycle system. At 2.5 K in Fig. 4(a), the detection efficiency starts to saturate at $25.5 \mu\text{A}$ and reaches 80%. Accounting for underestimation of the optical power at the input fiber due to the reflection at fiber/air interface, a maximum of 3.6%, the system detection efficiency is $\sim 77\%$. At liquid helium temperature, the saturation plateau gets weaker but the high detection efficiency is maintained and yield to 82%. The few percent difference in detection efficiency between 2.5 K and 4.3 K, which should be otherwise identical, is attributed to the difference in the fiber transmission/interconnections in the two systems. Until 5.2 K, the detection efficiency remains above 70% and reaches 15% at 6.2 K. At 670 nm the saturation behavior is maintained until 5 K. Figure 4(b) shows the detection efficiency of a detector with a thickness of 9 nm and 50 nm nanowires width (filling factor of 0.5) at 1550 nm for the temperatures of 2.5 K to 5.2 K. At 2.5 K, the detection efficiency plateaus to 81%. Similar to 785 nm, at 4.3 K the saturation gets weaker and detection efficiency drops to 64%. For 4.7 K and 5.2 K the detection efficiency is about 40% and 15%, respectively.

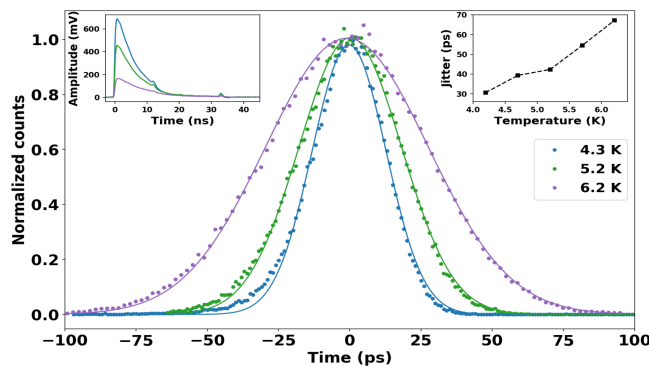


Fig. 5. Timing jitter measurements (dots) and their corresponding fits (lines) at base temperature of 4.3 K, 5.2 K and 6.2 K. The left inset is the detection pulse of the SNSPD at base temperature of 4.3 K, 5.2 K and 6.2 K. The right inset is the timing jitter as a function of the temperature.

The timing jitter was measured as function of the base temperature and to get an optimal result,

we replaced the room-temperature amplification (standard ZFL-1000+ ZFL) with a home-build cryogenic amplifier cooled down to 77 K. We used a picosecond pulsed laser which has a center wavelength of 1064 nm, 50 MHz repetition rate, and a full width at half maximum (FWHM) pulse length of 4.2 ps. Moreover the correlation histogram measurements is recorded with a fast digital oscilloscope (Lecroy Waverunner 640Zi 4 GHz, 40 GS/s). Similar to the efficiency measurements, the laser was attenuated to obtain a mean photon number per pulse much less than one resulting in a detector count rate of 50-100 KHz. Figure. 5 presents the timing jitter measurement results of the detector biased at 90 % of its critical current for temperatures of 4.3 K, 5.2 K and 6.2 K. The signal to noise ratio decreases with temperature which results in a deterioration of the temporal resolution of the detector [4]. From 4.3 K to 6.2 K, the amplitude of the electrical output pulse of the superconducting device is lowered by a factor ~ 3 , as shown in the left inset of Fig. 5. The right inset of Fig. 5 presents the timing jitter of the detector depending on the base temperature. The fitted data gives a FWHM timing-jitter of 30.6 ± 0.3 ps and 67.2 ± 0.3 ps at 4.3 K and 6.2 K, respectively.

5. Conclusion

In summary, we have demonstrated that NbTiN superconducting material is suitable to operate in cryostats with base temperatures as high as 7 K. By optimizing the film thickness and nanowire width of the superconducting single photon detector, we showed a detection efficiency of 82 % at 785 nm combined with a temporal resolution as high as 30.6 ± 0.3 ps at 4.3 K. For a similar operating temperature, we measured a detection efficiency of 64 % at 1550 nm. Moreover, we reached saturation of the internal efficiency for the whole visible spectrum up to 7 K while preserving a high critical current and by increasing the film thickness of the superconducting device, we decrease the intrinsic dark count rate. The devices reported in this work pave the way for integration of large arrays of high performance SNSPDs in emerging or well established applications such as astronomy, quantum applications and bio-imaging.

Funding

Phonsi (H2020-MSCA-ITN-642656); NWO LIFT-HTSM (680-91-202).

Acknowledgments

We would like to thank Dr. M.J.A. de Dood for valuable discussions and A. W. Elshaari for his help with the publication.

References

1. G. N. Goltsman, O. Okunev, G. Chulkova, A. Lipatov, A. Semenov, K. Smirnov, B. Voronov, A. Dzardanov, C. Williams, and R. Sobolewski, "Picosecond superconducting single-photon optical detector," *Appl. Phys. Lett.* **79**, 705–707 (2001).
2. E. E. Wollman, V. B. Verma, A. D. Beyer, R. M. Briggs, B. Korzh, J. P. Allmaras, F. Marsili, A. E. Lita, R. P. Mirin, S. W. Nam, and M. D. Shaw, "UV superconducting nanowire single-photon detectors with high efficiency, low noise, and 4 K operating temperature," *Opt. Express* **25**, 26792–26801 (2017).
3. H. Wang, H. Li, L. You, Y. Wang, L. Zhang, X. Yang, W. Zhang, Z. Wang, and X. Xie, "Fast and high efficiency superconducting nanowire single-photon detector at 630 nm wavelength," *Appl. Opt.* **58**, 1868–1872 (2019).
4. I. Esmail Zadeh, J. W. N. Los, R. B. M. Gourgues, V. Steinmetz, G. Bulgarini, S. M. Dobrovolskiy, V. Zwiller, and S. N. Dorenbos, "Single-photon detectors combining high efficiency, high detection rates, and ultra-high timing resolution," *APL Photonics* **2**, 111301 (2017).
5. F. Marsili, V. B. Verma, J. A. Stern, S. Harrington, A. E. Lita, T. Gerrits, I. Vayshenker, B. Baek, M. D. Shaw, R. P. Mirin, and S. W. Nam, "Detecting single infrared photons with 93% system efficiency," *Nat. Photonics* **7**, 210 (2013).
6. W. Zhang, L. You, H. Li, J. Huang, C. Lv, L. Zhang, X. Liu, J. Wu, Z. Wang, and X. Xie, "NbN superconducting nanowire single photon detector with efficiency over 90% at 1550 nm wavelength operational at compact cryocooler temperature," *Sci. China Physics, Mech. & Astron.* **60**, 120314 (2017).
7. C. Schuck, W. H. P. Pernice, and H. X. Tang, "Waveguide integrated low noise NbTiN nanowire single photon detectors with milli-hz dark count rate," *Sci. Reports* **3**, 1893 (2013). Article.

8. W. Zhang, J. Huang, C. Zhang, L. You, C. Lv, L. Zhang, H. Li, Z. Wang, and X. Xie, "A 16-Pixel interleaved superconducting nanowire single-photon detector array with a maximum count rate exceeding 1.5 GHz," *IEEE Transactions on Appl. Supercond.* **29**, 1–4 (2019).
9. I. Esmail Zadeh, J. W. N. Los, R. B. M. Gourgues, G. Bulgarini, S. M. Dobrovolskiy, V. Zwiller, and S. N. Dorenbos, "A single-photon detector with high efficiency and sub - 10 ps time resolution," *ArXiv e-prints* (2018).
10. M. Sidorova, A. Semenov, H.-W. Hübers, A. Kuzmin, S. Doerner, K. Ilin, M. Siegel, I. Charaev, and D. Vodolazov, "Timing jitter in photon detection by straight superconducting nanowires: Effect of magnetic field and photon flux," *Phys. Rev. B* **98**, 134504 (2018).
11. B. A. Korzh, Q.-Y. Zhao, S. Frasca, J. P. Allmaras, T. M. Autry, E. A. Bersin, M. Colangelo, G. M. Crouch, A. E. Dane, T. Gerrits, F. Marsili, G. Moody, E. Ramirez, J. D. Rezac, J. Stevens, M., E. E. Wollman, D. Zhu, P. D. Hale, K. L. Silverman, R. P. Mirin, S. W. Nam, M. D. Shaw, and K. K. Berggren, "Demonstrating sub-3 ps temporal resolution in a superconducting nanowire single-photon detector," *ArXiv e-prints* (2018).
12. M. Caloz, B. Korzh, E. Ramirez, C. Schönenberger, R. J. Warburton, H. Zbinden, M. D. Shaw, and F. Bussiès, "Intrinsically-limited timing jitter in molybdenum silicide superconducting nanowire single-photon detectors," *ArXiv e-prints* (2019).
13. B. Patra, R. M. Incandela, J. P. G. van Dijk, H. A. R. Homulle, L. Song, M. Shahmohammadi, R. B. Staszewski, A. Vladimirescu, M. Babaie, F. Sebastiano, and E. Charbon, "Cryo-CMOS circuits and systems for quantum computing applications," *IEEE J. Solid-State Circuits* **53**, 309–321 (2018).
14. M. Montinaro, G. Wüst, M. Munsch, Y. Fontana, E. Russo-Averchi, M. Heiss, A. Fontcuberta i Morral, R. J. Warburton, and M. Poggio, "Quantum dot opto-mechanics in a fully self-assembled nanowire," *Nano Lett.* **14**, 4454–4460 (2014).
15. Y. Chen, M. Zopf, R. Keil, F. Ding, and O. G. Schmidt, "Highly-efficient extraction of entangled photons from quantum dots using a broadband optical antenna," *Nat. Commun.* **9**, 2994 (2018).
16. N. B. Manson, M. Hedges, M. S. J. Barson, R. Ahlefeldt, M. W. Doherty, H. Abe, T. Ohshima, and M. J. Sellars, "NV--N+ pair centre in 1b diamond," *New J. Phys.* **20**, 113037 (2018).
17. S. Haffouz, K. D. Zeuner, D. Dalacu, P. J. Poole, J. Lapointe, D. Poitras, K. Mnaymneh, X. Wu, M. Couillard, M. Korkusinski, E. Schöll, K. D. Jöns, V. Zwiller, and R. L. Williams, "Bright single inasp quantum dots at telecom wavelengths in position-controlled inp nanowires: The role of the photonic waveguide," *Nano Lett.* **18**, 3047–3052 (2018). PMID: 29616557.
18. I. E. Zadeh, A. W. Elshaari, K. D. Jöns, A. Fognini, D. Dalacu, P. J. Poole, M. E. Reimer, and V. Zwiller, "Deterministic integration of single photon sources in silicon based photonic circuits," *Nano Lett.* **16**, 2289–2294 (2016).
19. S. L. Mouradian, T. Schröder, C. B. Poitras, L. Li, J. Goldstein, E. H. Chen, M. Walsh, J. Cardenas, M. L. Markham, D. J. Twitchen, M. Lipson, and D. Englund, "Scalable integration of long-lived quantum memories into a photonic circuit," *Phys. Rev. X* **5**, 031009 (2015).
20. W. B. Gao, A. Imamoglu, H. Bernien, and R. Hanson, "Coherent manipulation, measurement and entanglement of individual solid-state spins using optical fields," *Nat. Photonics* **9**, 363 (2015). Review Article.
21. R. Gourgues, I. E. Zadeh, A. W. Elshaari, G. Bulgarini, J. W. N. Los, J. Zichi, D. Dalacu, P. J. Poole, S. N. Dorenbos, and V. Zwiller, "Controlled integration of selected detectors and emitters in photonic integrated circuits," *Opt. Express* **27**, 3710–3716 (2019).
22. M. Gehl, C. Long, D. Trotter, A. Starbuck, A. Pomerene, J. B. Wright, S. Melgaard, J. Siirola, A. L. Lentine, and C. DeRose, "Operation of high-speed silicon photonic micro-disk modulators at cryogenic temperatures," *Optica* **4**, 374–382 (2017).
23. H. Shibata, T. Akazaki, and Y. Tokura, "Fabrication of MgB₂ nanowire single-photon detector with meander structure," *Appl. Phys. Express* **6**, 023101 (2013).
24. M. J. Stevens, R. H. Hadfield, R. E. Schwall, S. W. Nam, R. P. Mirin, and J. A. Gupta, "Fast lifetime measurements of infrared emitters using a low-jitter superconducting single-photon detector," *Appl. Phys. Lett.* **89**, 031109 (2006).
25. N. R. Gemmill, M. Hills, T. Bradshaw, T. Rawlings, B. Green, R. M. Heath, K. Tsimvrakidis, S. Dobrovolskiy, V. Zwiller, S. N. Dorenbos, M. Crook, and R. H. Hadfield, "A miniaturized 4 K platform for superconducting infrared photon counting detectors," *Supercond. Sci. Technol.* **30**, 11LT01 (2017).
26. H. Dang, T. Zhang, R. Zha, J. Tan, J. Li, Y. Zhao, B. Zhao, H. Tan, and R. Xue, "Development of 2 K space cryocoolers for cooling the superconducting nanowire single photon detector," *IEEE Transactions on Appl. Supercond.* **29**, 1–4 (2019).
27. J. Zichi, J. Chang, S. Steinhauer, K. von Fieandt, J. W. Los, G. Visser, N. Kalhor, T. Lettner, A. Elshaari, I. E. Zadeh, and V. Zwiller, "Nb_xTi_{1-x}N low timing jitter single-photon detectors with unity internal efficiency at 1550 nm and 2.5 k," *ArXiv e-prints* (2019).
28. K. Ilin, R. Schneider, D. Gerthsen, A. Engel, H. Bartolf, A. Schilling, A. Semenov, H.-W. Huebers, B. Freitag, and M. Siegel, "Ultra-thin NbN films on Si: crystalline and superconducting properties," *J. Physics: Conf. Ser.* **97**, 012045 (2008).
29. A. Semenov, B. Günther, U. Böttger, H.-W. Hübers, H. Bartolf, A. Engel, A. Schilling, K. Ilin, M. Siegel, R. Schneider, D. Gerthsen, and N. A. Gippius, "Optical and transport properties of ultrathin NbN films and nanostructures," *Phys. Rev. B* **80**, 054510 (2009).
30. A. J. Miller, A. E. Lita, B. Calkins, I. Vayshenker, S. M. Gruber, and S. W. Nam, "Compact cryogenic self-aligning fiber-to-detector coupling with losses below one percent," *Opt. Express* **19**, 9102–9110 (2011).

31. M. Hofherr, D. Rall, K. Ilin, M. Siegel, A. Semenov, H.-W. Hübers, and N. A. Gippius, "Intrinsic detection efficiency of superconducting nanowire single-photon detectors with different thicknesses," *J. Appl. Phys.* **108**, 014507 (2010).
32. T. Yamashita, S. Miki, K. Makise, W. Qiu, H. Terai, M. Fujiwara, M. Sasaki, and Z. Wang, "Origin of intrinsic dark count in superconducting nanowire single-photon detectors," *Appl. Phys. Lett.* **99**, 161105 (2011).
33. E. Oliveira, E. Bértolo, C. Núñez, V. Pilla, H. M. Santos, J. Fernández-Lodeiro, A. Fernández-Lodeiro, J. Djafari, J. L. Capelo, and C. Lodeiro, "Green and red fluorescent dyes for translational applications in imaging and sensing analytes: A dual-color flag," *ChemistryOpen* **7**, 3 (2018).
34. Rockland Immunochemicals Inc., "Fluorescent dye overview," <https://rockland-inc.com/fluorescent-dyes.aspx>.
35. L. Schweickert, K. D. Jöns, K. D. Zeuner, S. F. Covre da Silva, H. Huang, T. Lettner, M. Reindl, J. Zichi, R. Trotta, A. Rastelli, and V. Zwiller, "On-demand generation of background-free single photons from a solid-state source," *Appl. Phys. Lett.* **112**, 093106 (2018).
36. E. Schäll, L. Hanschke, L. Schweickert, K. D. Zeuner, M. Reindl, S. F. Covre da Silva, T. Lettner, R. Trotta, J. J. Finley, K. Müller, A. Rastelli, V. Zwiller, and K. D. Jöns, "Resonance fluorescence of GaAs quantum dots with near-unity photon indistinguishability," *Nano Lett.* **19**, 2404–2410 (2019).
37. J. Appel, E. Figueroa, D. Korystov, M. Lobino, and A. I. Lvovsky, "Quantum memory for squeezed light," *Phys. Rev. Lett.* **100**, 093602 (2008).