

Quantum Non-linear Optics with a Diamond Tin-Vacancy Center in a Fiber-based Microcavity

Herrmann, Yanik; Fischer, Julius; Brevoord, Julia M.; Sauerzapf, Colin; Wienhoven, Leonardo G.C.; Feije, Laurens J.; Pasini, Matteo; Eschen, Martin; Ruf, Maximilian; Weaver, Matthew J.

DOI

[10.1364/CLEO_FS.2024.FM3F.1](https://doi.org/10.1364/CLEO_FS.2024.FM3F.1)

Publication date

2024

Document Version

Final published version

Published in

CLEO 2024: Conference on Lasers and Electro-Optics

Citation (APA)

Herrmann, Y., Fischer, J., Brevoord, J. M., Sauerzapf, C., Wienhoven, L. G. C., Feije, L. J., Pasini, M., Eschen, M., Ruf, M., Weaver, M. J., & Hanson, R. (2024). Quantum Non-linear Optics with a Diamond Tin-Vacancy Center in a Fiber-based Microcavity. In *CLEO 2024: Conference on Lasers and Electro-Optics* Optical Society of America (OSA). https://doi.org/10.1364/CLEO_FS.2024.FM3F.1

Important note

To cite this publication, please use the final published version (if applicable).
Please check the document version above.

Copyright

Other than for strictly personal use, it is not permitted to download, forward or distribute the text or part of it, without the consent of the author(s) and/or copyright holder(s), unless the work is under an open content license such as Creative Commons.

Takedown policy

Please contact us and provide details if you believe this document breaches copyrights.
We will remove access to the work immediately and investigate your claim.

Quantum Non-linear Optics with a Diamond Tin-Vacancy Center in a Fiber-based Microcavity

Yanik Herrmann,^{1,*} Julius Fischer,¹ Julia M. Brevoord,¹ Colin Sauerzapf,¹ Leonardo G. C. Wienhoven,¹ Laurens J. Feije,¹ Matteo Pasini,¹ Martin Eschen,^{1,2} Maximilian Ruf,¹ Matthew J. Weaver,¹ and Ronald Hanson¹

¹ QuTech and Kavli Institute of Nanoscience, Delft University of Technology, 2628 CJ Delft, The Netherlands

² Netherlands Organisation for Applied Scientific Research (TNO), P.O. Box 155, 2600 AD Delft, The Netherlands

*y.s.herrmann@tudelft.nl

Abstract: We demonstrate coherent coupling of a single diamond Tin-Vacancy center to a fiber-based microcavity, showing a cavity transmission dip of 50 % on resonance, and altered photon statistics in cavity transmission. © 2024 The Author(s)

1. Introduction

Quantum networks are interesting for application like secure communication or distributed quantum computing, as well as for experiments in fundamental sciences. One of the central challenges is the realization of a coherent interface between a single stationary qubit and a flying qubit, to distribute entanglement between the network nodes. Utilizing their spin as a stationary qubit, quantum networking has been demonstrated with color centers in diamond [1], but their optical properties are limiting the performance and scalability. However, optical cavities can be used to dramatically improve the efficiency of this interface [2, 3]. Due to their full spectral and spatial tunability, fiber-based microcavities are a promising platform to realize such a cavity-enhanced spin-photon interface. We demonstrate the integration of a micrometer-thin diamond membrane, hosting implanted Tin-Vacancy (SnV) centers into a microcavity. The microcavity is composed of a fiber tip with a concave mirror [4], and a flat macroscopic mirror, to which the diamond membrane is bonded. We operate the system in a closed-cycle cryostat with a sample temperature reaching 8 K. The coupling of SnV centers is shown in Fig. 1, where the tunability of the cavity is employed to sweep its resonance frequency, which allows to couple to a specific SnV center.

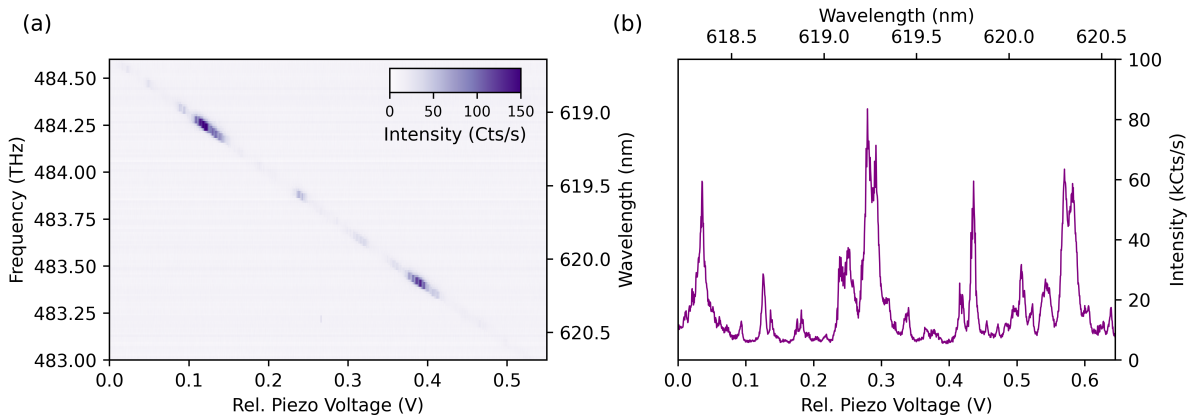


Fig. 1. Coupling SnV centers to the microcavity. (a) Off-resonant excitation of the cavity and zero-phonon line detection of the coupled SnV centers with a spectrometer. Once the cavity resonance (straight line) becomes resonant with the 619 nm or 620 nm transition of a SnV center, fluorescence is observed. (b) The detection light is filtered and sent to a single photon detector. Multiple emission lines from various SnV centers can be observed. The full tunability of the cavity can be used to selectively enhance an individual SnV center.

2. Results

The high quality factor Q of the microcavity of about 7×10^4 and the simulated mode volume of $V = 55 \lambda^3$ enables a Purcell factor of 7. We confirm this by measuring the corresponding Purcell-broadening of the SnV linewidth. With these parameters, a coherent cooperativity of $C_{\text{coh}} = 0.69 \pm 0.07$ can be evaluated [5], which puts the system in the regime of coherent coupling and makes it possible to measure quantum non-linear effects for the first time with SnV centers. We demonstrate this by showing a SnV-modulated microcavity transmission signal, measured in the low-power regime (shown in Fig. 2). The cavity-emitter system is very well explained by a Lindblad master equation approach, and described by the parameters $\{g, \kappa, \gamma\}/2\pi = \{0.30, 6.86, 0.032\}$ GHz, with g being the single photon Rabi frequency, κ the total loss rate of the cavity and γ the SnV centers lifetime-limited linewidth. We characterize the microcavity transmission dip dependent on detuning and excitation power and show the altered photon statistics for transmitted light.

The versatility of the platform allows to transfer these methods to other solid-state emitters like the Nitrogen-Vacancy center or defects in Silicon Carbide. Furthermore, an improved microcavity would allow to reach the regime of strong coupling and this system can be supplemented with the recently demonstrated spin qubit control of SnV centers [6] in strained nanometer-thin diamond membranes to an efficient spin-photon interface.

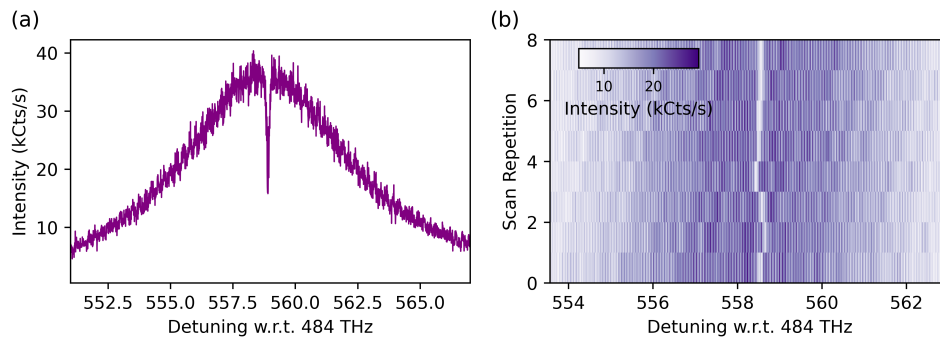


Fig. 2. Quantum Non-linear effects. (a) The cavity resonance is probed with a resonant laser. A transmission dip, reaching a contrast of 50 % can be observed once the excitation laser becomes resonant with the SnV transition. (b) The cavity transmission is resonantly scanned, showing the spectral wandering of the single SnV center.

3. Acknowledgment

We acknowledge financial support from the Dutch Research Council (NWO) through the Spinoza prize 2019 (project number SPI 63-264) and from the Dutch Ministry of Economic Affairs and Climate Policy (EZK), as part of the Quantum Delta NL programme. We gratefully acknowledge that this work was partially supported by the joint research program “Modular quantum computers” by Fujitsu Limited and Delft University of Technology, co-funded by the Netherlands Enterprise Agency under project number PPS2007.

References

1. S. Hermans, M. Pompili, H. Beukers, S. Baier, J. Borregaard, and R. Hanson, “Qubit teleportation between non-neighbouring nodes in a quantum network,” *Nature* **605**, 663–668 (2022).
2. E. Janitz, M. K. Bhaskar, and L. Childress, “Cavity quantum electrodynamics with color centers in diamond,” *Optica* **7**, 1232 (2020).
3. M. Ruf, N. H. Wan, H. Choi, D. Englund, and R. Hanson, “Quantum networks based on color centers in diamond,” *J. Appl. Phys.* **130**, 070901 (2021).
4. D. Hunger, T. Steinmetz, Y. Colombe, C. Deutsch, T. W. Hänsch, and J. Reichel, “A fiber Fabry–Perot cavity with high finesse,” *New J. Phys.* **12**, 065038 (2010).
5. Y. Herrmann, J. Fischer, J. M. Brevoord, C. Sauerzapf, L. G. C. Wienhoven, L. J. Feije, M. Pasini, M. Eschen, M. Ruf, M. J. Weaver, and R. Hanson, “Coherent coupling of a diamond tin-vacancy center to a tunable open microcavity,” *ArXiv:2307.11916* (2023).
6. X. Guo, A. M. Stramma, Z. Li, W. G. Roth, B. Huang, Y. Jin, R. A. Parker, J. A. Martínez, N. Shofer, C. P. Michaels, C. P. Purser, M. H. Appel, E. M. Alexeev, T. Liu, A. C. Ferrari, D. D. Awschalom, N. Deegan, B. Pingault, G. Galli, F. J. Heremans, M. Atatüre, and A. A. High, “Microwave-based quantum control and coherence protection of tin-vacancy spin qubits in a strain-tuned diamond membrane heterostructure,” *ArXiv:2307.11916* (2023).