

## Microstructural evolution during high-temperature partitioning of a medium-Mn Q&P steel

Ayenampudi, Sudhindra; Celada-Casero, Carola; Sietsma, Jilt; Santofimia, Maria Jesus

**Publication date**

2017

**Document Version**

Final published version

**Citation (APA)**

Ayenampudi, S., Celada-Casero, C., Sietsma, J., & Santofimia, M. J. (2017). *Microstructural evolution during high-temperature partitioning of a medium-Mn Q&P steel*. EUROMAT, Thessaloniki, Greece.

**Important note**

To cite this publication, please use the final published version (if applicable). Please check the document version above.

**Copyright**

Other than for strictly personal use, it is not permitted to download, forward or distribute the text or part of it, without the consent of the author(s) and/or copyright holder(s), unless the work is under an open content license such as Creative Commons.

**Takedown policy**

Please contact us and provide details if you believe this document breaches copyrights. We will remove access to the work immediately and investigate your claim.

# Microstructural evolution during high-temperature partitioning of a medium-Mn Q&P steel


Sudhindra Ayenampudi, C. Celada-Casero, J. Sietsma and M.J. Santofimia

Department of Materials Science and Engineering, Delft University of Technology, Mekelweg 2, 2628 CD Delft, The Netherlands




Thessaloniki 17 – 22 September 2017

# Introduction : 3<sup>rd</sup> generation AHSS

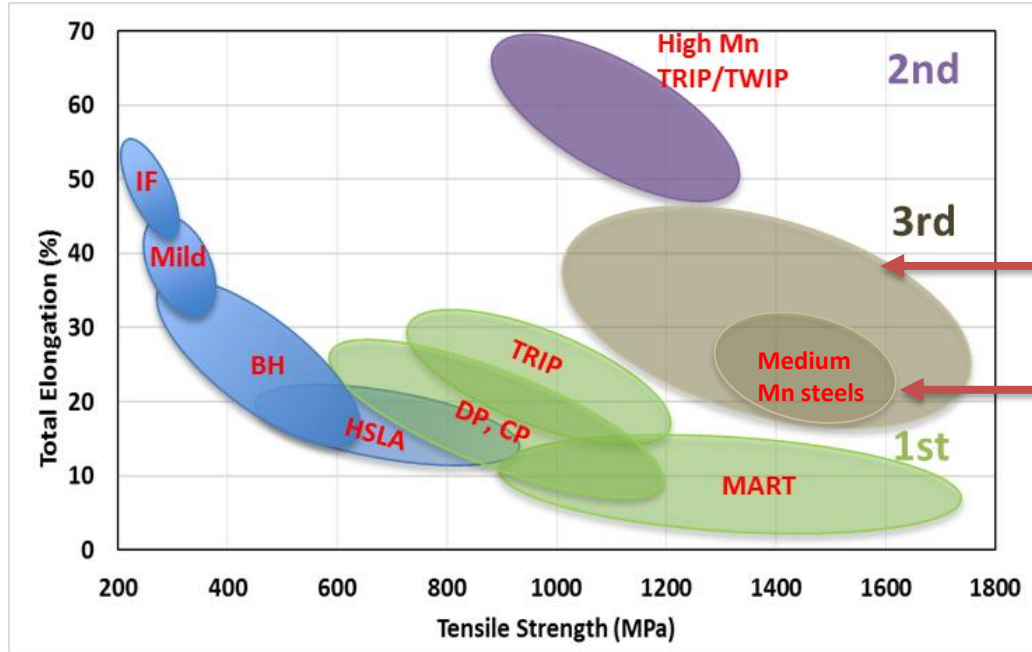

- Quenching & partitioning (Q&P) process: Combination of **high strength** and **ductility**
- Medium Mn steels are considered as potential candidates for 3rd generation AHSS
- Mn – Strong austenite ( $\gamma$ ) stabilizer.

# Introduction: Quenching & partitioning (Q&P) process

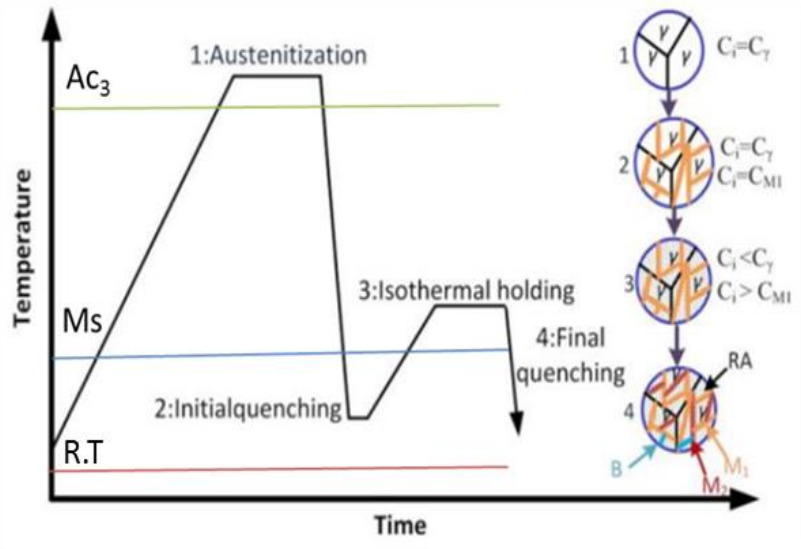

Partitioning of interstitial/substitutional alloying elements from martensite ( $\alpha'$ ) to austenite ( $\gamma$ )


Retained austenite (RA): **Ductility**

Martensite (primary & fresh): **Strength**

In the current research work, we investigated:

**The evolution of microstructure at high partitioning temperatures in the medium Mn steels.**

# Approach: Experiments & characterization techniques

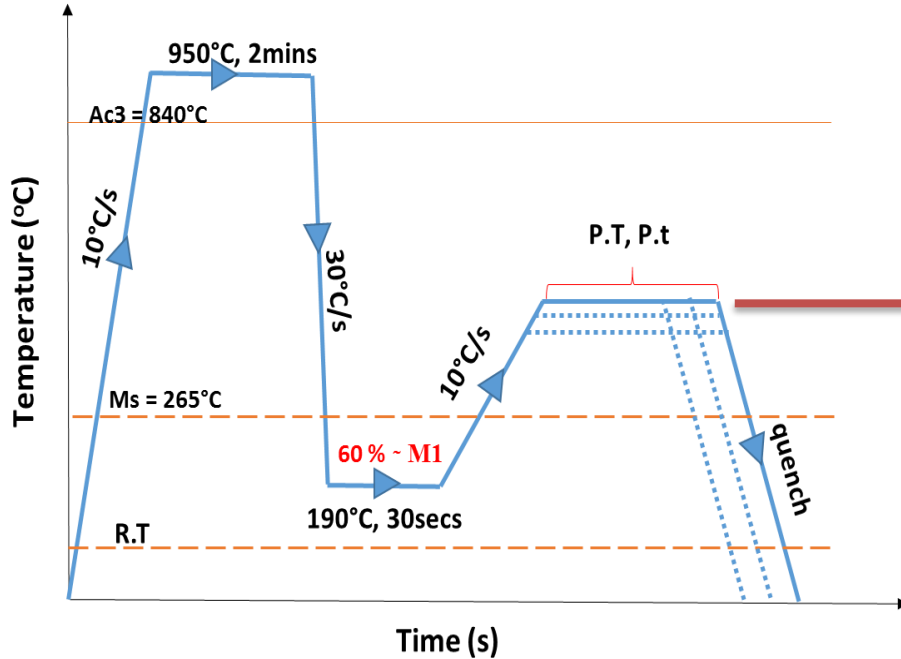

Steel grade: **0.31C-4.58Mn-1.52Si (in wt. %)**

## Partitioning conditions

- Partitioning temp., : 400, 450, 550 °C
- Partitioning times : 180, 900, 3600 s



## Competitive reactions

- Carbide precipitation
- Alloying element (C/Mn) partitioning
- Bainite formation
- Pearlite formation

## Microstructure characterization techniques

- Dilatometer
- SEM
- XRD
- Vickers Micro-hardness




# Results & discussion

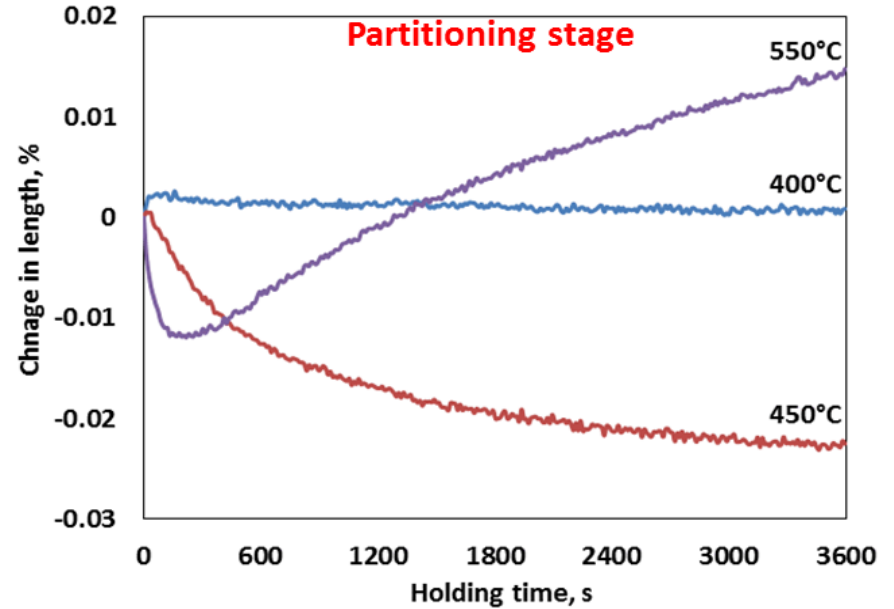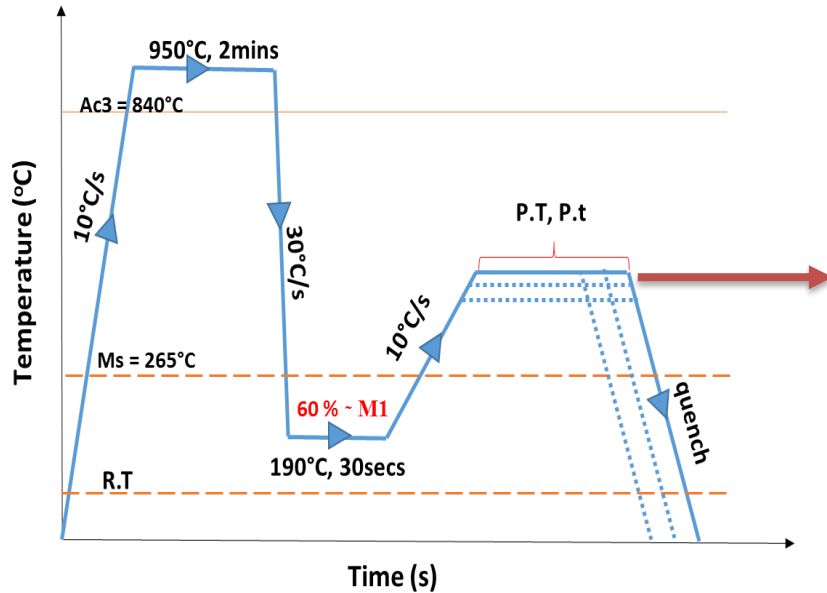

Different dilatometry response during the partitioning stage

Several competitive reactions taking place




# Results & discussion

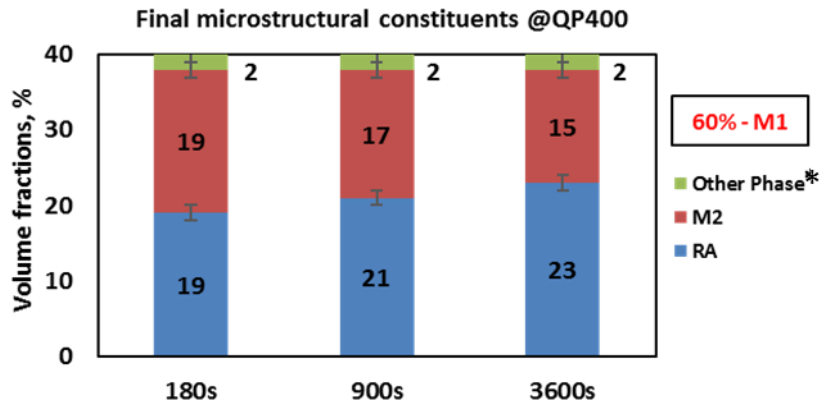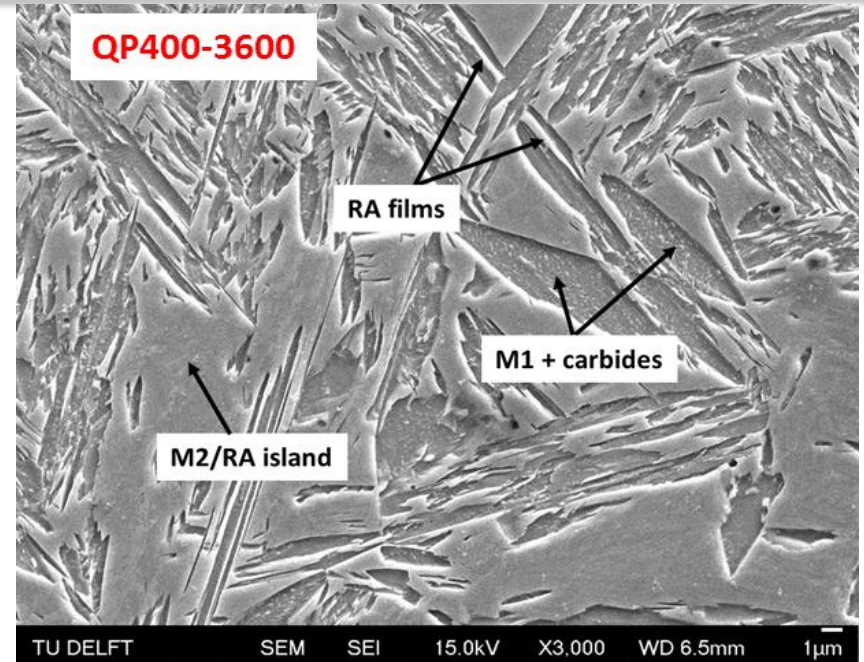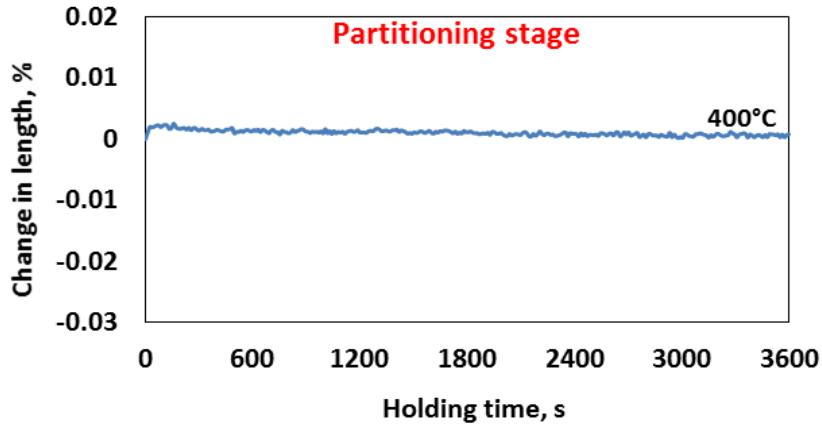

- Precipitation of carbides in M1
- Increase in RA fraction along with holding time.






# Results & discussion

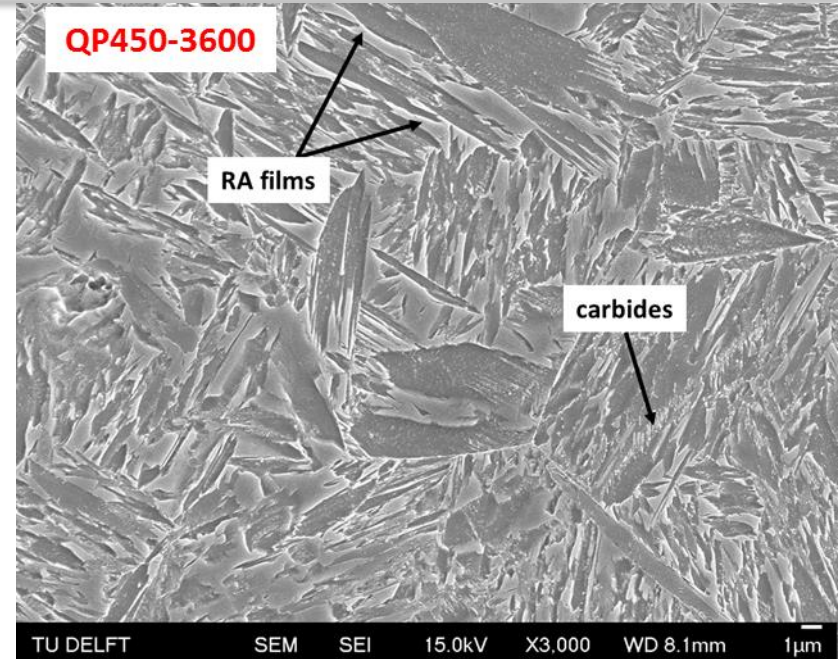
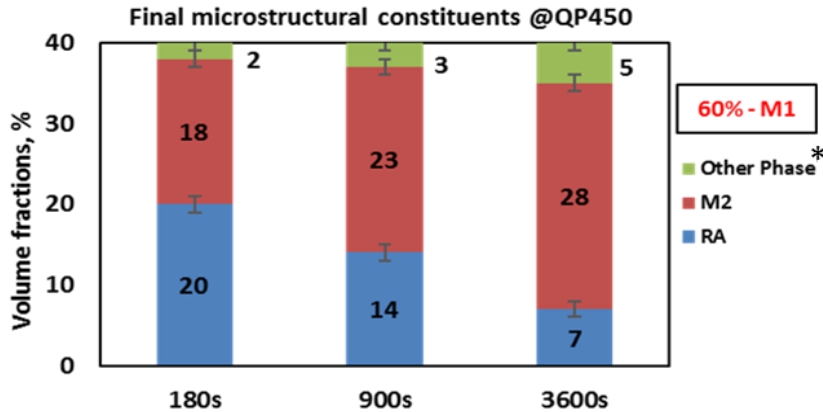
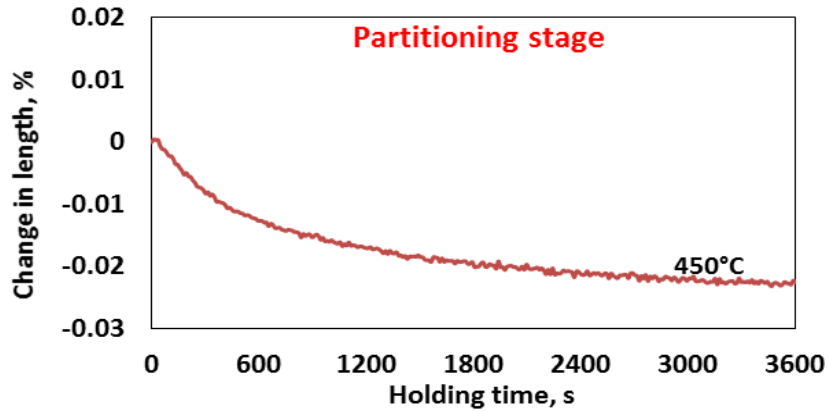


- Strong precipitation of carbides in the  $\gamma$  grains.
- Decrease in RA fraction along with holding time.

# Results: Dilatometer, SEM (500°C - 3600s) & final fractions

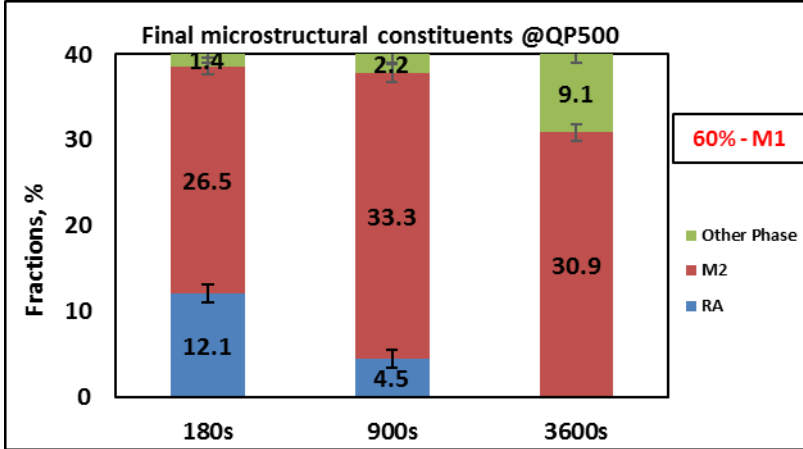
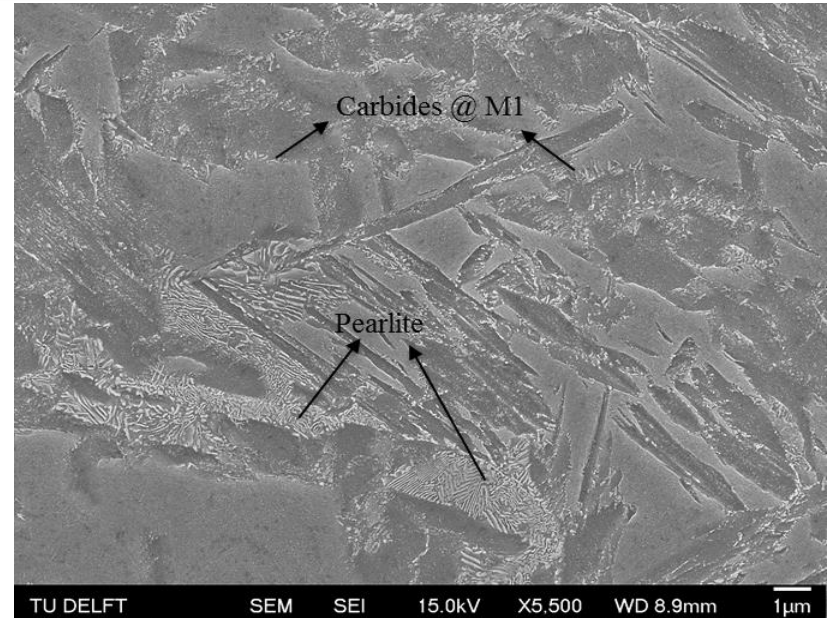
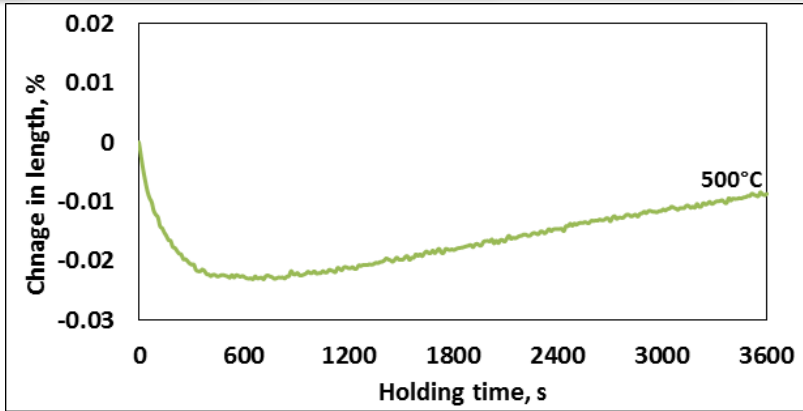


# Results & discussion

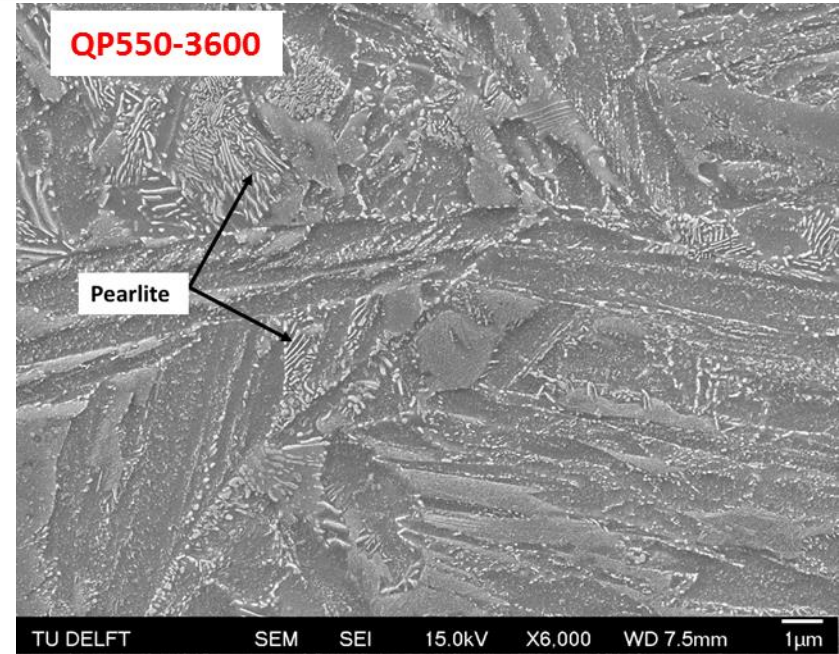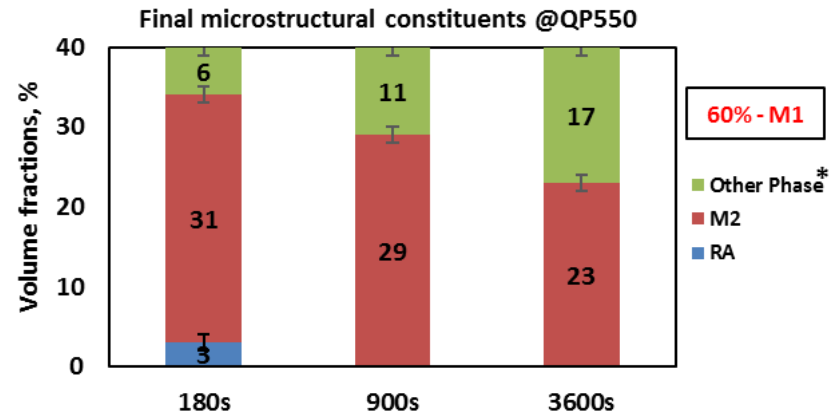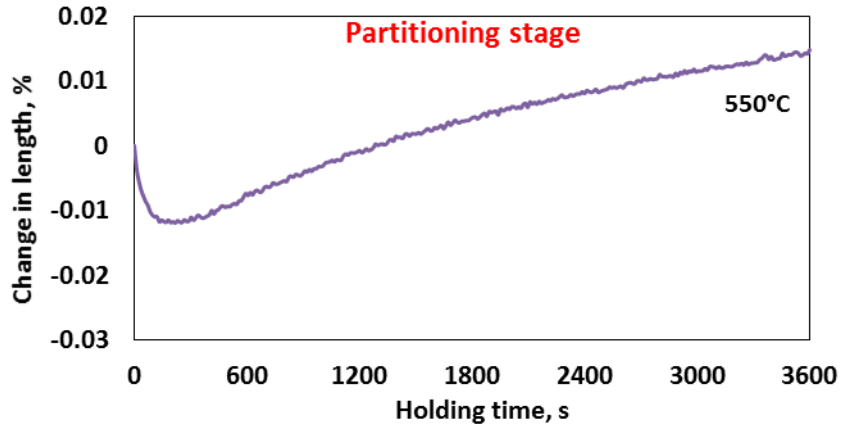


- Strong carbide pptn at short holding times,  $\Delta L \downarrow$ .
- Pearlite formation at longer holding times,  $\Delta L \uparrow$ .
- No RA was detected.

# Results: Dilatometer, SEM (600°C - 3600s) & final fractions

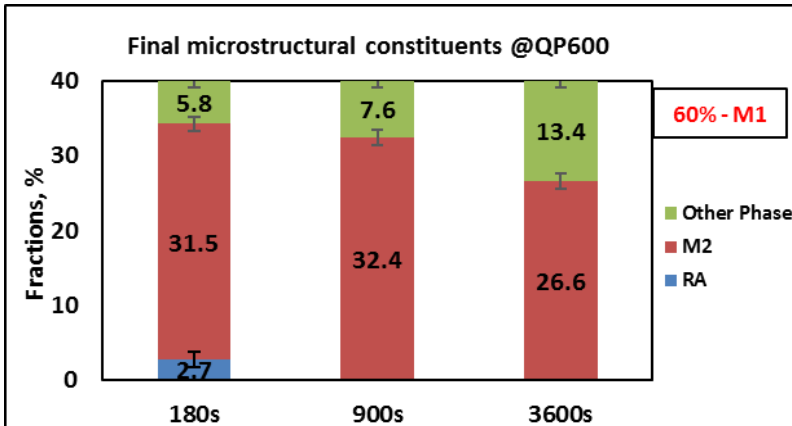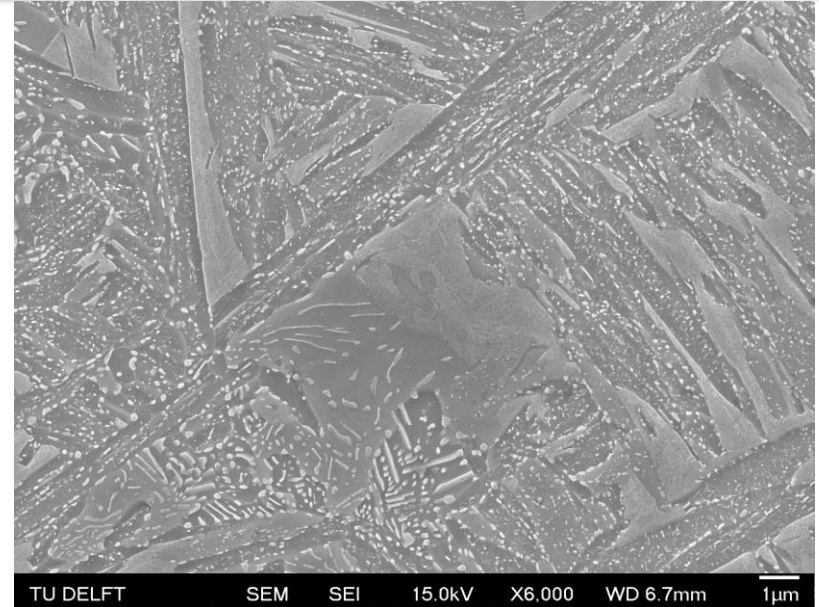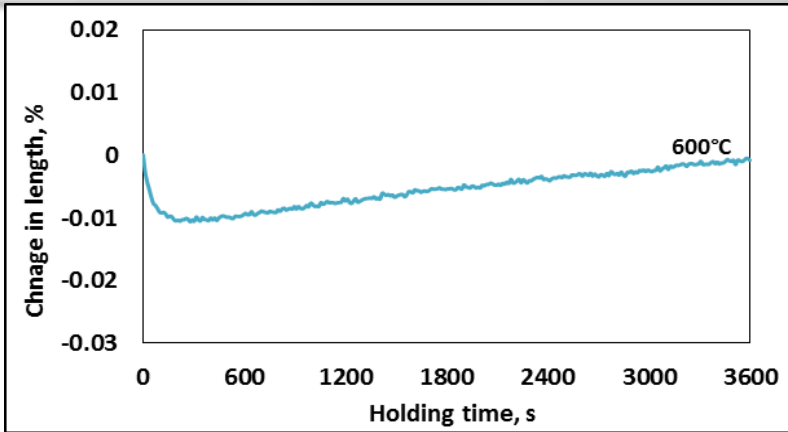

# Results & discussion

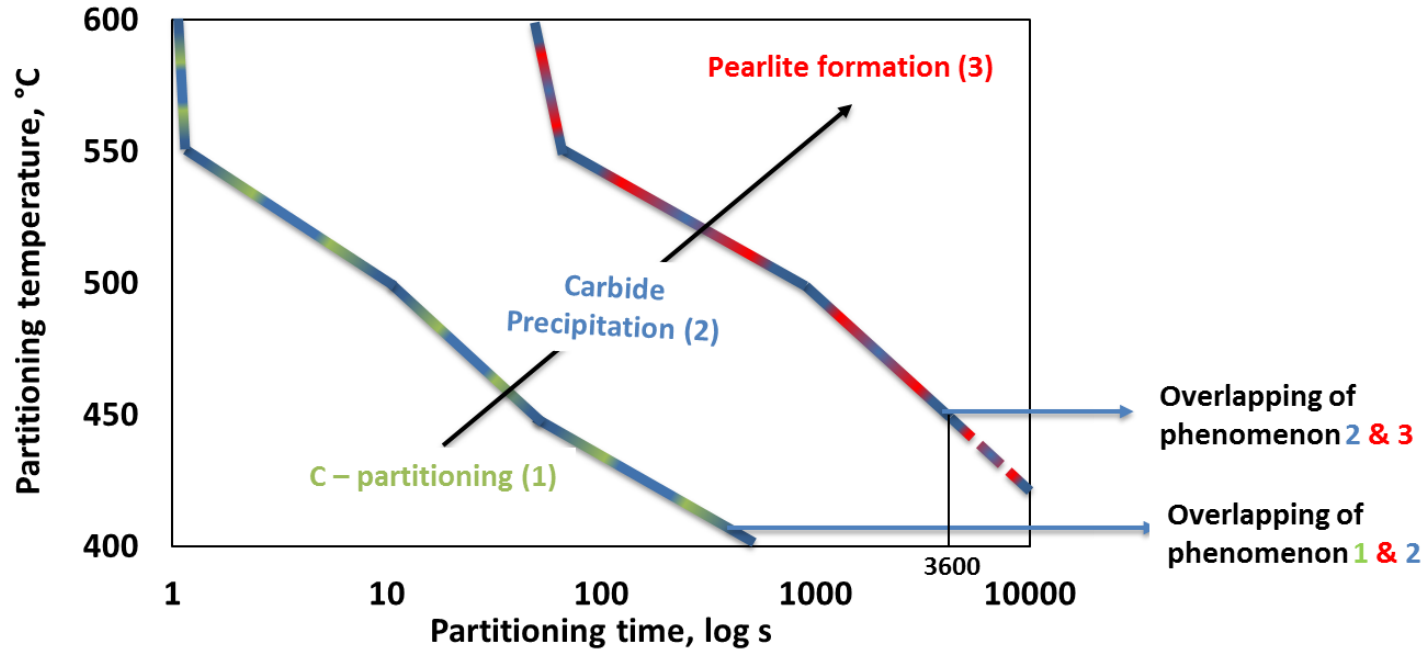


- Figure showing various phenomenon taking place at different partitioning temperatures and times, that are determined from the current work.




# Results & discussion

Vickers Micro Hardness, HV

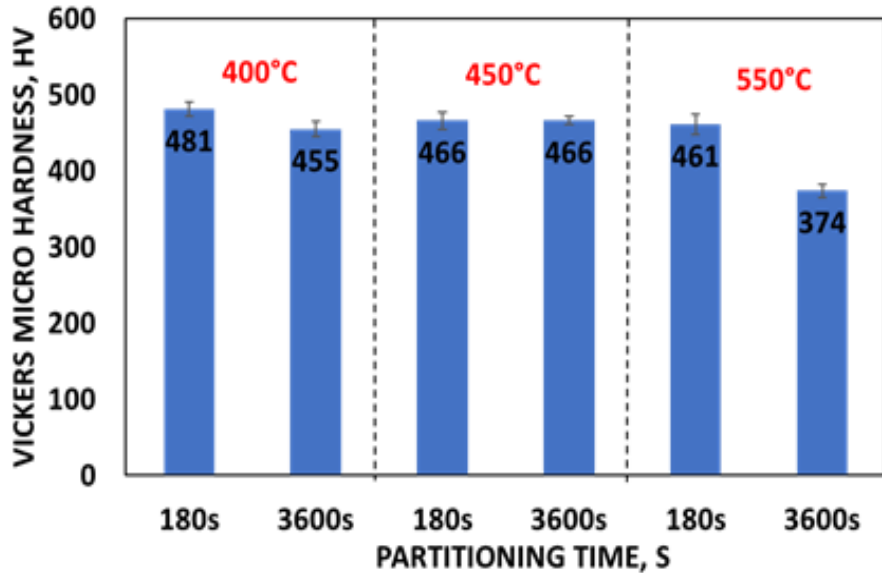

P.T (°C)	Long holding times (3600s)
400	Tempering of M1, lower fraction of M2
450	Tempering of M1, <b>higher fraction of M2 and carbide precipitation</b>
550	Tempering of M1, <b>M2 is C depleted due to pearlite formation</b>


Final microstructural constituents

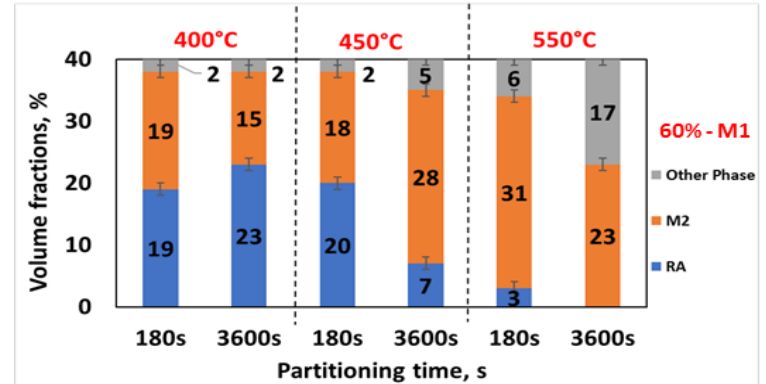

## Conclusions

- In this research work, the evolution of microstructure at high partitioning temperatures, during partitioning times up to 1 hour, in the medium Mn steels was investigated

- 1) Overlapping phenomenon (carbide precipitation and pearlite formation) are activated at high partitioning temperatures. This counteracts the stabilizing effect of C and Mn partitioning.
- 2) At higher partitioning temperatures, carbon partitioning stimulates pearlite formation.
- 3) The control of other competitive reactions during the partitioning stage plays a key role in the stabilisation of the austenite in medium-Mn steels.

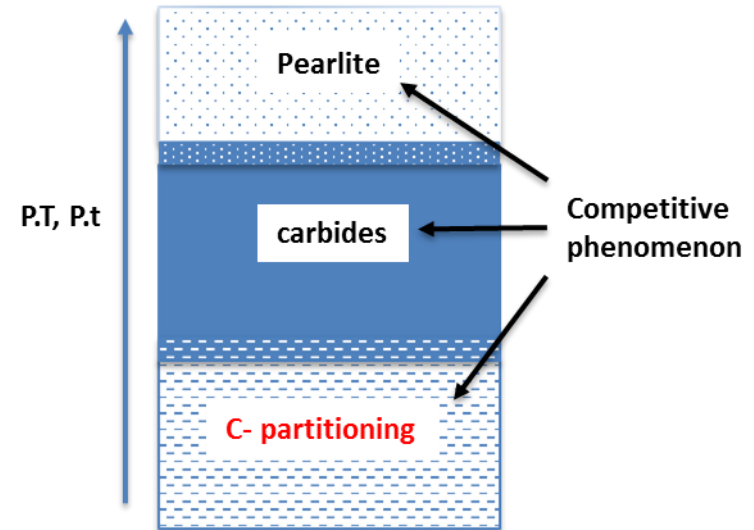


# Conclusions

- In this research work, the evolution of microstructure at high partitioning temperatures, during partitioning times up to 1 hour, in the medium Mn steels was investigated.

1) Overlapping phenomenon (carbide precipitation and pearlite formation) are activated at high partitioning temperatures. This counteracts the stabilizing effect of C and Mn partitioning.

2) At higher partitioning temperatures, carbon partitioning stimulates pearlite formation.

3) The control of competitive reactions during the partitioning stage plays a key role in the stabilisation of the austenite in medium-Mn steels.

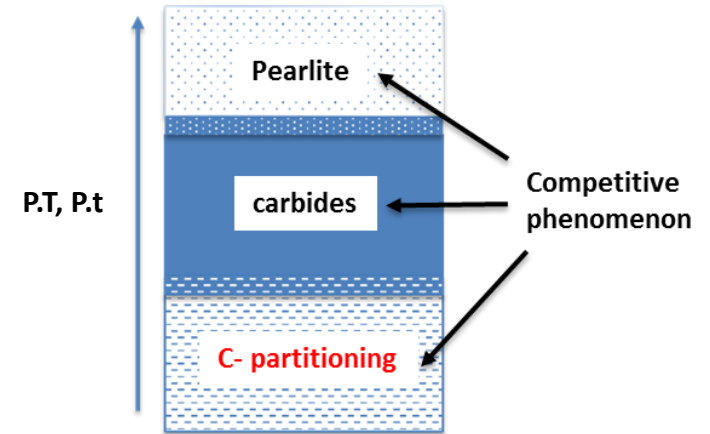

HIGHQP- RFCS '15

THANK YOU