

Strain engineering the topological type-II Dirac semimetal NiTe₂

Ferreira, P. P.; Manesco, A. L.R.; Dorini, T. T.; Correa, L. E.; Weber, G.; Machado, A. J.S.; Eleno, L. T.F.

DOI

[10.1103/PhysRevB.103.125134](https://doi.org/10.1103/PhysRevB.103.125134)

Publication date

2021

Document Version

Final published version

Published in

Physical Review B

Citation (APA)

Ferreira, P. P., Manesco, A. L. R., Dorini, T. T., Correa, L. E., Weber, G., Machado, A. J. S., & Eleno, L. T. F. (2021). Strain engineering the topological type-II Dirac semimetal NiTe₂. *Physical Review B*, *103*(12), Article 125134. <https://doi.org/10.1103/PhysRevB.103.125134>

Important note

To cite this publication, please use the final published version (if applicable).
Please check the document version above.

Copyright

Other than for strictly personal use, it is not permitted to download, forward or distribute the text or part of it, without the consent of the author(s) and/or copyright holder(s), unless the work is under an open content license such as Creative Commons.

Takedown policy

Please contact us and provide details if you believe this document breaches copyrights.
We will remove access to the work immediately and investigate your claim.


Strain engineering the topological type-II Dirac semimetal NiTe₂

P. P. Ferreira^{1,*}, A. L. R. Manesco^{1,2,†}, T. T. Dorini³, L. E. Correa¹, G. Weber¹,
A. J. S. Machado¹ and L. T. F. Eleno^{1,‡}

¹Computational Materials Science Group (ComputEEL/MatSci), Escola de Engenharia de Lorena,
Universidade de São Paulo, Materials Engineering Department, Lorena, Brazil

²Kavli Institute of Nanoscience, Delft University of Technology, Delft, The Netherlands

³Université de Lorraine, CNRS, IJL, Nancy, France

 (Received 21 November 2020; revised 23 February 2021; accepted 24 February 2021; published 15 March 2021)

In the present work, we investigate the electronic and elastic properties in equilibrium and under strain of the type-II Dirac semimetal NiTe₂ using density functional theory. Our results demonstrate the tunability of Dirac nodes' energy and momentum with strain and that it is possible to bring them closer to the Fermi level, while other metallic bands are suppressed. We also derive a minimal 4-band effective model for the Dirac cones, which accounts for the aforementioned strain effects by means of lattice regularization, providing an inexpensive way for further theoretical investigations and easy comparison with experiments. On an equal footing, we propose the static control of the electronic structure by intercalating alkali species into the van der Waals gap, resulting in the same effects obtained by strain engineering and removing the requirement of *in situ* strain. Finally, evaluating the wave-function's symmetry evolution as the lattice is deformed, we discuss possible consequences, such as Lifshitz transitions and the coexistence of type-I and type-II Dirac cones, thus motivating future investigations.

DOI: [10.1103/PhysRevB.103.125134](https://doi.org/10.1103/PhysRevB.103.125134)

I. INTRODUCTION

The existence of quasiparticle excitations with no counterpart in high energy physics became relevant, not only due to mere scientific interest, but also for the possibility of using their properties as building blocks for new electronic devices. From the description of the quantum spin Hall effect in graphene by Kane and Mele [1,2] and the first realization of three-dimensional topological band insulators [3–9] to the proposal of topological metallic states [10–12], as Weyl and Dirac semimetals [13], the existence of such novel quasiparticles has drawn a heightened interest in the last few years. Among their properties, one could highlight the ultrahigh electronic mobility and conductivity [14–17], negative/giant magnetoresistance [18–20], chiral anomaly [21–24], and quantum anomalous Hall effect [25–27].

The simplest example of a Dirac material is graphene, for which valence and conduction bands touch at discrete points in the first Brillouin zone and disperse linearly in all momentum directions [28,29]. In three dimensions, twofold (Weyl) or fourfold (Dirac) symmetry-protected degenerate points host bulk massless fermionic quasiparticle excitations and surface spin-textures, robust against perturbations [30–34]. Thus, breaking the twofold degeneracy ensured by either inversion- or time-reversal symmetries, a Dirac cone will decouple into a pair of opposite-chirality Weyl fermions [35–37].

Different from their high energy physics counterparts, massless quasiparticles in solids move at the Fermi velocity, thus their dispersion is not effectively constrained by Lorentz invariance. Therefore, the energy-momentum dispersion explicitly depends on its direction in momentum space [38]. The resulting tilted cones are the characteristic signature of the so-called type-II Weyl and Dirac semimetals [39–44], and show, for instance, anisotropic transport and magnetoresistance properties [45–48], in contrast to type-I materials.

In this context, the transition metal dichalcogenide NiTe₂ was recently rediscovered as a type-II Dirac semimetal [49–51]. Transport measurements revealed a nonsaturating linear magnetoresistance and quantum oscillations confirmed the existence of a nontrivial Berry phase for the light mass carriers [49]. The existence of topological surface states with chiral spin-texture over a wide range of energies was supported by spin- and angle-resolved photoemission spectroscopy [52]. Additionally, superconductivity was observed in NiTe₂ under pressure [53] and with the intercalation of Ti into the van der Waals gap (the space between two adjacent chalcogenide layers) [50], and was also predicted in atomically thin systems [54]. Moreover, the energy position of its Dirac node, closer to the Fermi level when compared with similar systems [42,55,56], combined with accessible high-quality single crystals [57–59] substantiate the interest on the material.

In the present work, we study, from first-principles calculations, strain effects on the electronic structure of NiTe₂. Our results show that it is possible to systematically tune both the energy relative to the Fermi level and the point in the Brillouin zone where the type-II Dirac cone is located, as illustrated

*Corresponding author: pedroferreira@usp.br

†Corresponding author: antoniolrm@usp.br

‡Corresponding author: luizeleno@usp.br

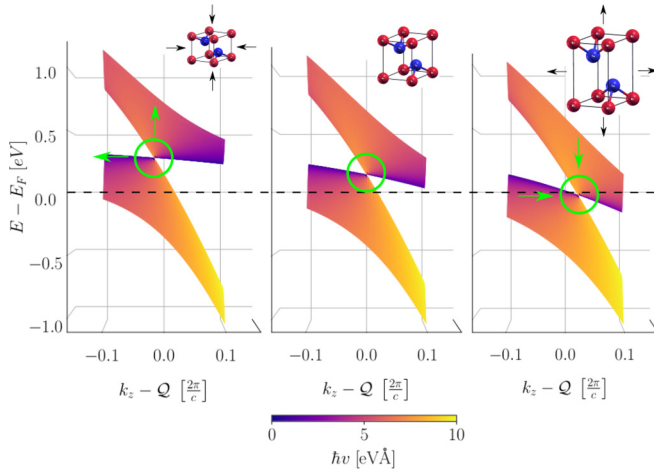


FIG. 1. Dirac cone tunability as a function of isostatic pressure according to our effective model. The middle plot shows the Dirac cone for the ground-state structure. The left and right plots show the Dirac cone under compressive and tensile strain, respectively. Under compressive strain the Dirac cone energy increases while the Dirac node's k_z -component decrease, while the opposite happens under tensile strain (indicated by the green arrows in both cases). It is possible to see that the Dirac cone crosses the Fermi energy level under tensile strain, making NiTe₂ an exciting platform for electronic transport experiments.

in Fig. 1, which summarizes some of our findings. While the energy of the cone is relevant for enhancing/suppressing the effects of states with massless dispersion on transport properties, its position in the Brillouin zone provides a route to create artificial magnetic fields in this material [60,61]. Additionally, the evolution of the irreducible representations for the electronic states under strain shows the appearance of a type-I Dirac cone in the same pair of bands as the type-II Dirac cone, establishing a hybrid pseudorelativistic topological phase. Finally, we also demonstrate that alkali metal intercalation into the van der Waals gap acts effectively as a static chemical-pressure source inside the crystal-structure, simulating the effects obtained by strain engineering.

The paper is organized as follows. Section II describes the computational methods and numerical parameters used in the first-principles electronic-structure calculations. In Sec. III, we present a comprehensive investigation of the electronic and elastic properties of the ground-state structure. Section IV shows the key results related to the strain-engineering of the electronic states of NiTe₂ in the vicinity of the Fermi level. Finally, Sec. V is devoted to constructing a 4-band low-energy effective model for the type-II Dirac cone.

II. COMPUTATIONAL METHODS

First-principles electronic-structure calculations were carried out in the framework of the density functional theory (DFT) within the Kohn-Sham scheme [62,63], using the pseudopotential approach as implemented in QUANTUM ESPRESSO [64,65] and auxiliary postprocessing tools [66,67]. The calculations were performed using a series of different approximations for the exchange and correlation (XC) functional, within its relativistic and nonrelativistic forms:

local-density-approximation (LDA) of Perdew-Zhang (PZ) [68] and the generalized gradient approximation with the Perdew-Burke-Ernzerhof (PBE) [69] parametrization and its modified version, known as PBEsol [70]; as well as nonlocal functionals, including the van der Waals interactions [71], namely vdW-DF [72,73], optB86b-vdW [74], and optB88-vdW [75]. To guarantee the energy eigenvalues convergence from the Kohn-Sham self-consistent solution, we adopted a wave function energy cutoff of 260 Ry and a sampling of $16 \times 16 \times 8$ k -points in the first Brillouin zone according to the Monkhorst-Pack scheme [76]. To compute the electronic properties, a denser k -mesh grid was considered, with $32 \times 32 \times 16$ k -points. All lattice parameters and internal degrees of freedom were fully relaxed to reach a ground-state convergence of 10^{-6} Ry in total energy and 10^{-4} Ry/ a_0 ($a_0 \approx 0.529$ Å) for forces acting on the nuclei.

The full second-order elastic stiffness tensor was obtained from a set of deformations imposed on the underformed reference ground-state ($\eta = 0$) structures, as implemented in the ELASTIC tool [77]. To obtain the six independent second-order elastic constants of the trigonal symmetry, we used six different types of deformation, with 15 distorted structures each and strain intensities in the range $-0.05 \leq \eta \leq +0.05$. The macroscopic mechanical moduli and their crystallographic-orientation dependence was derived from the stiffness tensor [78]. Details on this topic are provided in Appendix A.

Finally, the effective model was constructed using QSMM [79]. We found a family of Hamiltonians up to second order in momentum, satisfying the same set of discrete symmetries as NiTe₂ and restricted to the orbitals forming the type-II Dirac cone. The strain-dependency was implemented using a lattice regularization scheme [61]. All free parameters were then fitted with DFT data.

All code and data used to prepare this paper is freely available on the Zenodo repository [80].

III. GROUND-STATE PROPERTIES

A. Elastic properties

NiTe₂ is a layered compound that crystallizes in a trigonal centrosymmetric structure within CdI₂-prototype (spacegroup $P\bar{3}m1$, no. 164), as shown in Fig. 2. A Ni layer is sandwiched between two Te layers, with the stacking of adjacent Te layers mediated by weak van der Waals interactions [82]. The optimized cell parameters and the relaxed Te-position degree of freedom are presented in Table I. Regardless of the choice of the exchange and correlation functional for the Kohn-Sham Hamiltonian, the relative error, compared with the experimental crystallographic data available, for both calculated cell parameters and atomic positions does not exceed 3% in our calculations. However, we observed that spin-orbit coupling (SOC) effects are more expressive over the electronic energy dispersion than van der Waals interactions between adjacent layers. Thus, all the results presented in this paper, except when explicitly mentioned, correspond to the PBE parametrization including SOC effects.

The six independent second-order elastic constants $c_{\alpha\beta}$, calculated with different approximations for the exchange and correlation functional, are listed in Table II and show good

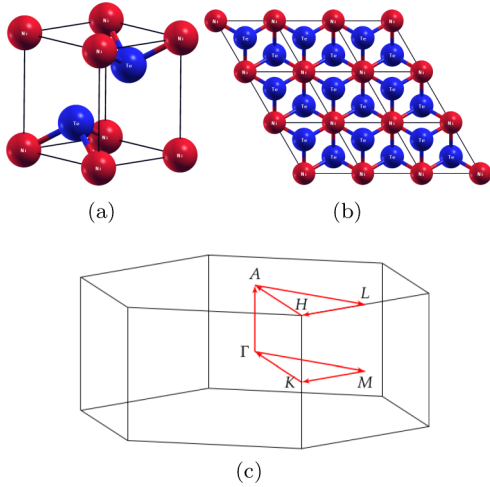


FIG. 2. (a) Trigonal unit cell of NiTe₂ alongside (b) a top view of a $3 \times 3 \times 1$ supercell (blue: Te; red: Ni atoms). (c) First Brillouin zone of NiTe₂, with the path along high-symmetry points used to plot the dispersion curves [81].

agreement when compared with the experimental data available. Elastic constants with a shear component, such as c_{14} and c_{44} , are better predicted by the optB86b-vdW functional, evidencing the weak interaction between the adjacent layers of tellurium. However, when stronger interatomic bonds are required by the deformation, such as Ni-Te and Ni-Ni bonds, related to c_{11} , c_{12} , and c_{33} , the GGA-type functionals provide more accurate descriptions.

The mechanical stability can be easily verified using the Mouhat and Coudert criteria [85]. The elastic anisotropy and mechanical moduli were also computed from the stiffness tensor. Surprisingly, we found that NiTe₂ possesses a ductile regime, favoring the strain-engineering route to manipulate its low-energy excitations. These results are presented in detail in Appendix A.

B. Electronic properties

The projected density of states (DOS) of NiTe₂ is presented in Fig. 3(a). The populated Fermi level confirms the semimetal nature of the compound. The total DOS at the Fermi energy (E_F) is 1.67 states/eV, with nearly 59% of the electronic states

TABLE I. NiTe₂ fully optimized cell-parameters (a and c) and atomic position degree of freedom of Te atoms (z_{Te}) using different XC functionals.

XC functional	a (Å)	c (Å)	V (Å ³)	z_{Te}
PZ	3.814	5.105	64.31	0.2522
PZ + SOC	3.797	5.186	64.75	0.2511
PBE	3.894	5.372	70.54	0.2442
PBE + SOC	3.897	5.377	70.72	0.2452
vdW-DF	3.971	5.377	73.43	0.2369
optB88-vdW	3.902	5.331	70.29	0.2535
optB86b-vdW	3.863	5.277	68.20	0.2494
Expt. [57]	3.858	5.264	67.85	–
Calc. [83]	3.808	5.236	65.75	–

TABLE II. Independent second-order elastic constants (in GPa) calculated for trigonal NiTe₂.

	c_{11}	c_{12}	c_{13}	c_{14}	c_{33}	c_{44}
PBE	110.8	38.20	22.90	−5.00	45.50	10.20
PBE + SOC	113.7	36.60	27.20	−6.50	45.70	11.20
PZ + SOC	145.5	54.00	43.30	−14.30	76.60	26.80
optB86b-vdW	127.4	47.10	26.80	−9.40	75.70	20.20
Expt. [84]	109.5	41.90	–	−10.70	52.60	20.40
Calc. [83]	147.6	50.80	44.10	7.91	83.90	17.58

derived from Te-5*p* orbitals and 34% from Ni-3*d* manifold. Figure 3(b) shows the projected electronic band structure along path in the first Brillouin zone shown in Fig. 2(c). There are four distinct bands crossing the Fermi level, giving rise to the four independent sheets of the Fermi surface shown in Figs. 3(c) to 3(f).

Despite the layered quasi-two-dimensional nature of NiTe₂, weakly coupled along the c direction, the Fermi surface possesses a strong three-dimensional character. The sheets consist of a closed [Fig. 3(a)] and an open [Fig. 3(b)] hole pocket, and electron pockets [Figs. 3(c) and 3(d)] around the M and K points. The hole pockets have a strong Te- p character, whereas the electron pockets have a nearly equal contribution from Ni- d and Te- p states.

The valence and conduction bands touch each other at a discrete point along Γ - A , as well as the point with opposite momentum. The presence of inversion- and time-reversal symmetry ensures that each band is doubly degenerate. Therefore, the linear crossing of the valence and conduction bands originate a pair of gapless Dirac nodes (fourfold degenerate) located at $\mathbf{k}_D = (0, 0, \pm 0.665)$, in units of π/c . The tilted Dirac cone lies at $E_D = 0.15$ eV. For comparison, the Pd- and Pt-based dichalcogenides host Dirac points high above the Fermi level, between 0.6 and 1.2 eV [42–44].

The trigonal crystal-field with the strong intralayer hybridization between the Te- p manifold of different sites breaks the original p -orbitals threefold degeneracy, resulting in bonding and antibonding combinations of the in-plane (p_x , p_y) and out-of-plane (p_z) states. The spin-orbit coupling further splits the p -derived electronic states due to the double group symmetry representation, including the spin degree of freedom. Since the Γ - A direction preserves the C_3 rotational symmetry (the system is invariant under rotations by $2\pi/3$ around the z axis), the p -derived states will split into two distinct irreducible representations, R_4 and $R_{5,6}$, with R_4 being bidimensional and $R_{5,6}$ degenerate. The irreducible representations and their parities in high-symmetry points are shown in Fig. 4.

The crossing between R_4^\pm and $R_{5,6}^\mp$ states will lead to the bulk type-II Dirac node (circled in Fig. 4). This crossing is symmetrically allowed and is protected against hybridization/gap-opening mechanisms due to the C_3 rotational symmetry. On the other hand, the crossings between R_4^\pm and R_4^\mp bands are not allowed, as they both share the same symmetry and angular momentum. Therefore, due to their opposite parities, their hybridization leads to a gap with band inversion, establishing a \mathbb{Z}_2 invariant. This single-orbital

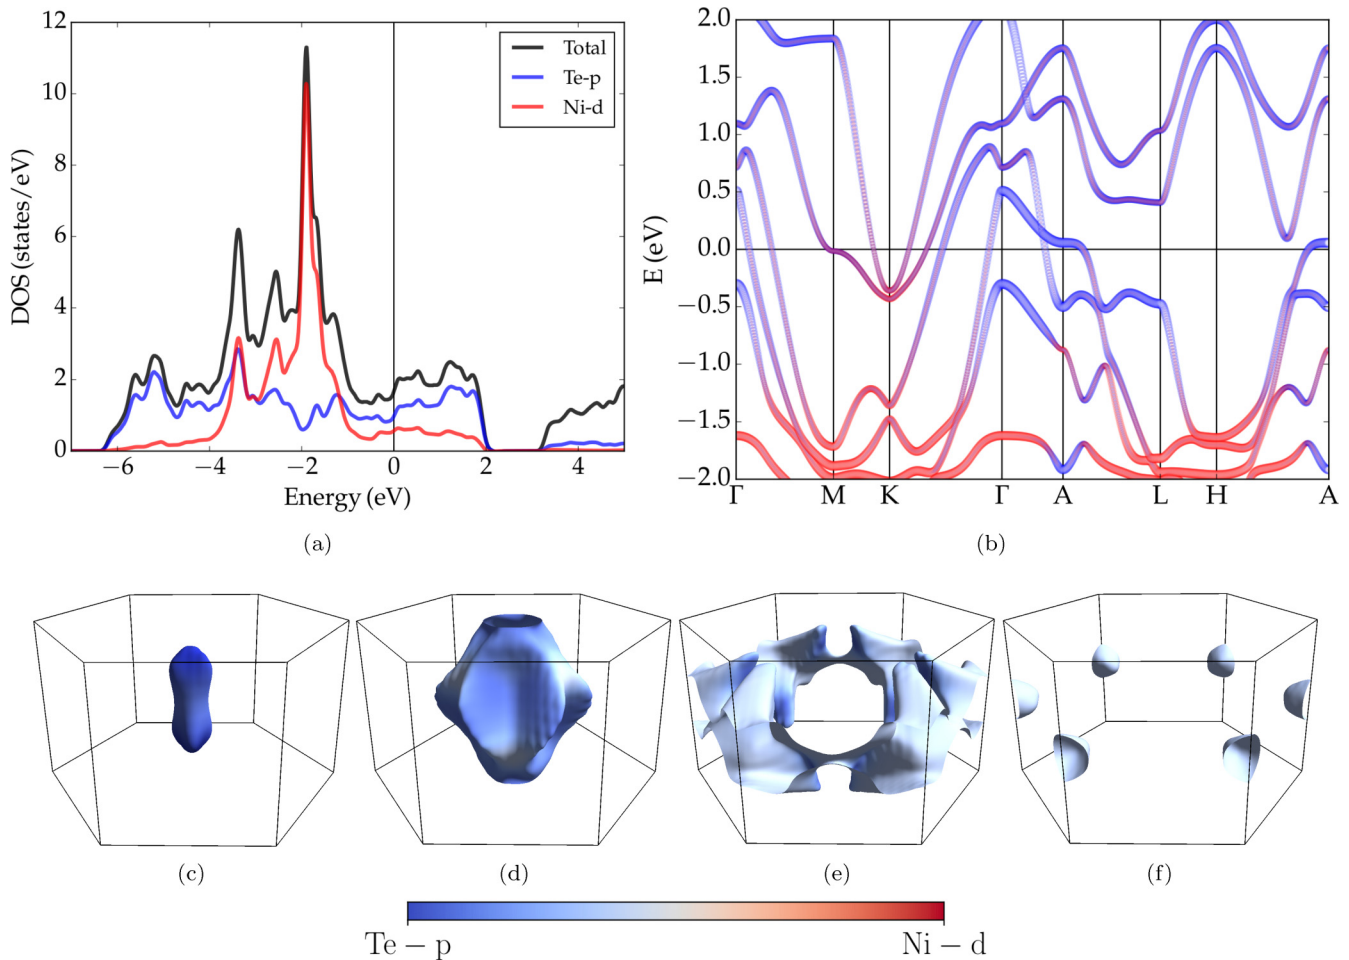


FIG. 3. (a) NiTe₂ projected density of states and (b) electronic band-structure with SOC. (c)–(f) The four independent sheets of the Fermi surface. The color map shows the contributions of Te-5*p* (blue) and Ni-3*d* (red) manifold to the electronic wave function.

manifold mechanism of bulk Dirac cones is widely discussed elsewhere [86–88].

Lastly, just above the Dirac point, located in close vicinity of the Fermi level, there is another band crossing giving rise to type-I Dirac fermions at $\mathbf{k}_D = (0, 0, \pm 0.388)$ with R_4^\pm and $R_{5,6}^\mp$ representations and energy $E_D = 1.36$ eV, an energy level comparable to type-II Dirac nodes in Pd- and Pt-based dichalcogenides [42–44].

IV. STRAIN ENGINEERING

We now turn to investigate how different strain states modify the electronic properties of NiTe₂. To this end, calculations were performed with three types of strain: uniaxial deformation along the [001] direction (*z* axis); biaxial deformation within the basal plane, perpendicular to the *z* direction; and an isostatic deformation. For each type, at least six deformations were performed, going from -5% to $+5\%$ with respect to the ground-state structure.

A. Effects of strain in the band structure

Figure 5 shows selected strained band structures taking into account spin-orbit coupling effects. We observe that strain drives the hybridization of atomic orbital states and the

dispersion of the bands. With compressive strain, the intralayer and interlayer couplings increase, enhancing the hybridization of electronic wave functions. In this way, the hopping parameters increase, culminating in bands with high effective velocities, as can be seen in Figs. 5(a), 5(c) and 5(e). Otherwise, as we move the atoms away from each other with tensile strain, the overlap between the wave functions decreases, resulting in bands with lower velocities, as shown in Figs. 5(b), 5(d), and 5(f). Consequently, it is possible to tune the tilt parameter of the Dirac cone, promoting controlled changes in the anisotropic transport properties. The Dirac point energy with respect to the Fermi level is also tunable.

We can also check that some non-Dirac bands crossing the Fermi level are suppressed when the structure is expanded, and extra bands become part of the Fermi surface when the structure is compressed. To illustrate this, the velocity operator projected onto the Fermi surface under isostatic deformation is shown in Fig. 6. When the structure is compressed [Fig. 6(a)], an additional branch, corresponding to the irreducible representation R_4 , shows up in the Fermi surface along the Γ -A direction. On the other hand, by separating the adjacent layers [Fig. 6(b)], we suppress the crossing along the A-L direction and create an intersection along Γ -A. As a result, we will have a disconnected holepocket and an electronpocket surrounding the Γ point and two electron-pockets

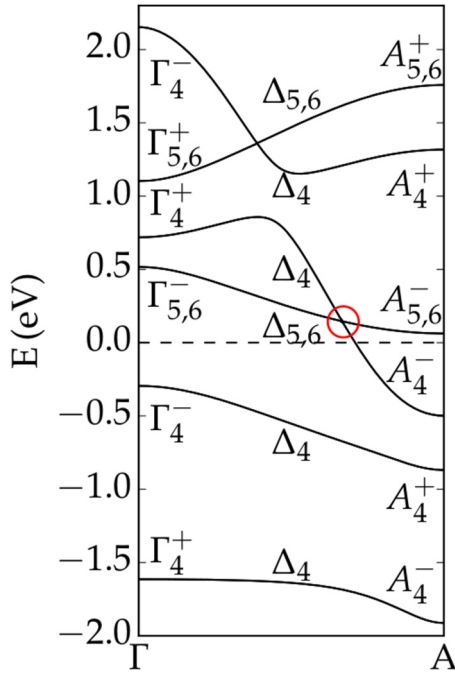


FIG. 4. Detailed electronic band structure with irreducible representations and parity analysis along the Γ – A direction. The type-II Dirac cone is circled in red.

surrounding the K point, with lower Fermi velocity. As expected, the type-II Dirac point appears in the contact between the electron pocket and the hole pocket that are located around Γ as we bring the chemical potential to $E = E_D$. If we lower the chemical potential further, the surfaces disconnect again and the electron pockets will gradually decrease in size. From this perspective, the isoenergetic surfaces will evolve rapidly and undergo a sudden change in their topology due to lattice deformations, paving the way for Lifshitz transitions [89,90].

B. Dynamically controlling the Dirac cone

In Fig. 7 we show the type-II Dirac node evolution under strain. For a biaxial strain, the Dirac cone moves towards the Fermi level and closer to A in k -space, at the border of the Brillouin zone, crossing the chemical potential at approximately $\eta = 2\%$. For a state of compression, the cone departs from the Fermi level, reaching around 0.6 eV at -5% , and approaches the center of the BZ. The opposite effect is observed for the deformation $(0, 0, \eta)$. In this situation, the cone will cross E_F around -2% , coming close to 0.4 eV at $+5\%$. Hence, for an isostatic deformation, the type-II Dirac point dynamics could be described as a combination of uniaxial and biaxial deformations. The crossing at the Fermi level occurs only close to $+4\%$, and the curve suggests that a compression greater than 5% brings the cone below the Fermi energy. It is also worth noticing that, extrapolating both the Dirac node energy as well as the position in k -space of non-Dirac bands (see Fig. 5), there is a parameter range for which only the Dirac bands cross the Fermi level, and the node is just a few hundreds of meV below it.

It is also possible to observe regions in the parameter space with the coexistence of type-II and type-I Dirac cones, as

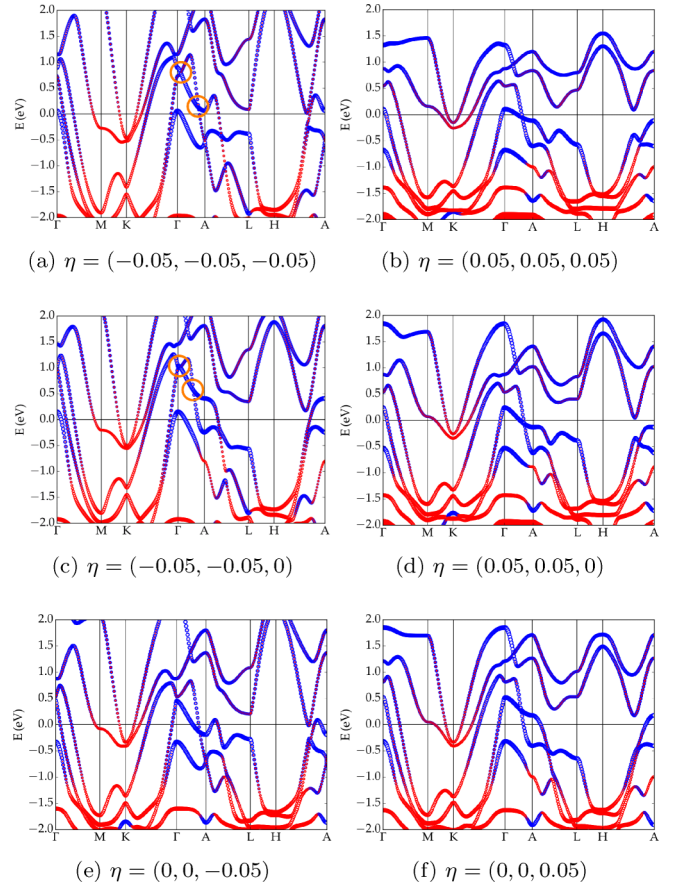


FIG. 5. Projected band structure of NiTe_2 for some selected deformed structures. Strain states are indicated below each plot. Red points indicate the Ni- d orbital contribution and blue points, the Te- p derived states. The coexisting type-I and type-II Dirac cones in (a) and (c) are circled in orange.

shown in Fig. 8. The state Γ_4^+ is nearly insensitive to isostatic pressure, while $\Gamma_{5,6}^-$ decreases monotonically. Combined, both behaviors result in a crossing between the bands with different irreducible representations. Thus, a new pair of no tilted (type-I) Dirac cones is created close to Γ for approximately $\eta = -3\%$ and $E - E_F = 0.8$ eV [see Fig. 5(a)]. The same effect is found for uniaxial and biaxial deformations. In the case of $(\eta, \eta, 0)$, for example, the type-I Dirac pair will form at $\eta \approx -4.2\%$ [see Fig. 5(c)]. Thus, under strain NiTe_2 harbors both type-I and type-II Dirac fermions in the same pair of energy bands.

The coexistence of type-I and type-II Dirac cones provides a route to unique and unexplored magnetoresistive and transport signatures, barely understood until now. While Dirac type-I semimetals exhibit a negative magnetoresistance in all directions [15,17], the transport properties in Dirac type-II semimetals are expected to be anisotropic and present a negative magnetoresistance only in directions where the potential component of the energy spectrum is higher than the kinetic component [38]. PdTe_2 [56] and the family of compounds CaAgBi [91] are the few materials in which the coexistence of Dirac cones of type-I and type-II is expected to occur in the same pair of bands. However, the type-II Dirac node

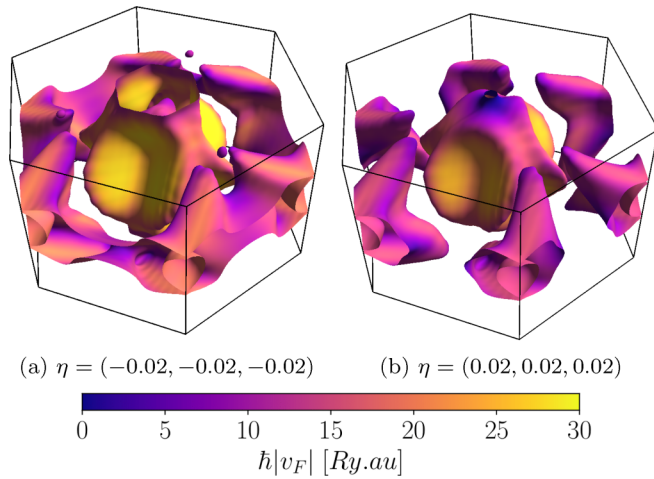


FIG. 6. Fermi surfaces of NiTe₂ under isostatic strain. Strain states are indicated below each plot. The color map indicates the magnitude of the Fermi velocity.

on NiTe₂ is much closer to the Fermi level, and, also, their momentum separation is smaller, providing a better platform to investigate interaction between quasiparticles with different pseudorelativistic signatures.

The type-II Dirac cone strain-engineering seems an exciting route for electronic transport experiments. For example, magnetoresistance for conventional metals grows quadratically at low fields and tends to a saturation value at high fields. However, in materials where conventional charge carriers and Dirac fermions coexist and populate the Fermi surface, the magnetoresistance curve as a function of the applied magnetic field reveals an additional (and predominant) linear term

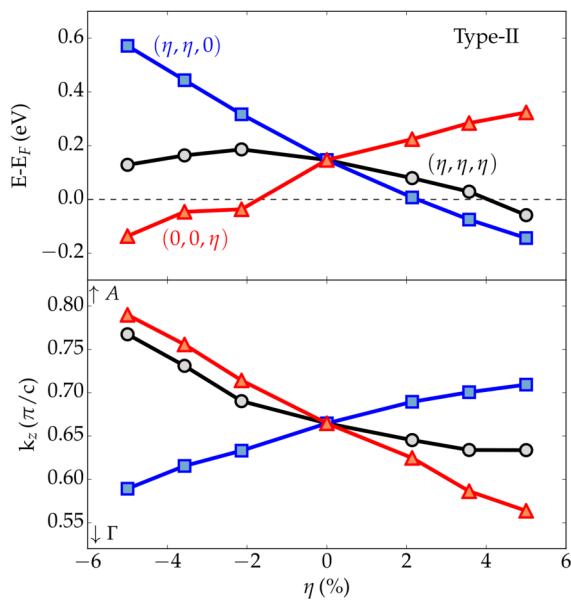


FIG. 7. Type-II Dirac node energy and momentum evolution as a function of the following: (i) biaxial deformation (squares) within the x - y plane $(\eta, \eta, 0)$; (ii) uniaxial strain (triangles) along the z -axis, $(0, 0, \eta)$; and (iii) isostatic pressure (circles), (η, η, η) . A and Γ are at $k_z = \pi/c$ and $k_z = 0$, respectively.

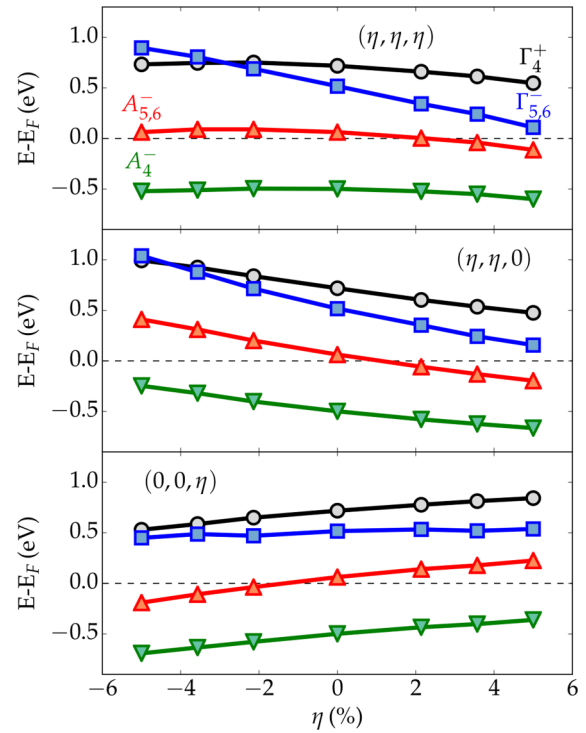


FIG. 8. Energy evolution of the irreducible representations Γ_4^+ , $\Gamma_{5,6}^-$, $A_{5,6}^-$, and A_4^- for the deformations (η, η, η) , $(\eta, \eta, 0)$, and $(0, 0, \eta)$.

[92,93]. Thus, it is expected that, with the presence of Dirac cones at the Fermi level, the contributions of these quasiparticles to the magnetoresistance will be accentuated. Also, in many topological semimetals it is possible to observe a pronounced growth of the resistivity curve as temperature goes down at high fields. Enhancing the contribution from pseudorelativistic carriers, combined with the suppression of carriers derived from the other nonrelativistic metallic bands, it is expected that this signature will be evidenced, resulting, invariably, in a significant increase in the magnetoresistance.

C. Statically controlling the Dirac cone: Chemical doping

Here, we show that it is possible to deform the structure without causing significant hybridization effects in the low-energy states by increasing the interlayer gap with the intercalation of alkali species. As a proof of concept, we performed first-principle calculations using the supercell method for Li_xNiTe_2 varying the Li content in the range $0 \leq x \leq 1$. Figure 9(a) presents the electronic density of states of LiNiTe_2 projected onto Te- $5p$, Ni- $3d$, and Li- $2s + 2p$ orbitals. In fact, the Li- $2s$ and Li- $2p$ states are negligible, with a very small hybridization with Te- $5p$ and Ni- $3d$ manifolds at the Fermi level. Considering a homogeneous, perfectly randomly disordered distribution of Li atoms in the lattice, all irreducible representations are conserved with Li intercalation, as shown in Fig. 9(b), preserving the type-II Dirac cones and its topology, reproducing, therefore, the strain-modulated effects discussed in Sec. IV A. For instance, in the hypothetical situation of a full sheet into the van der Waals gap, type-II Dirac node goes below the Fermi level, at approximately -0.2 eV.

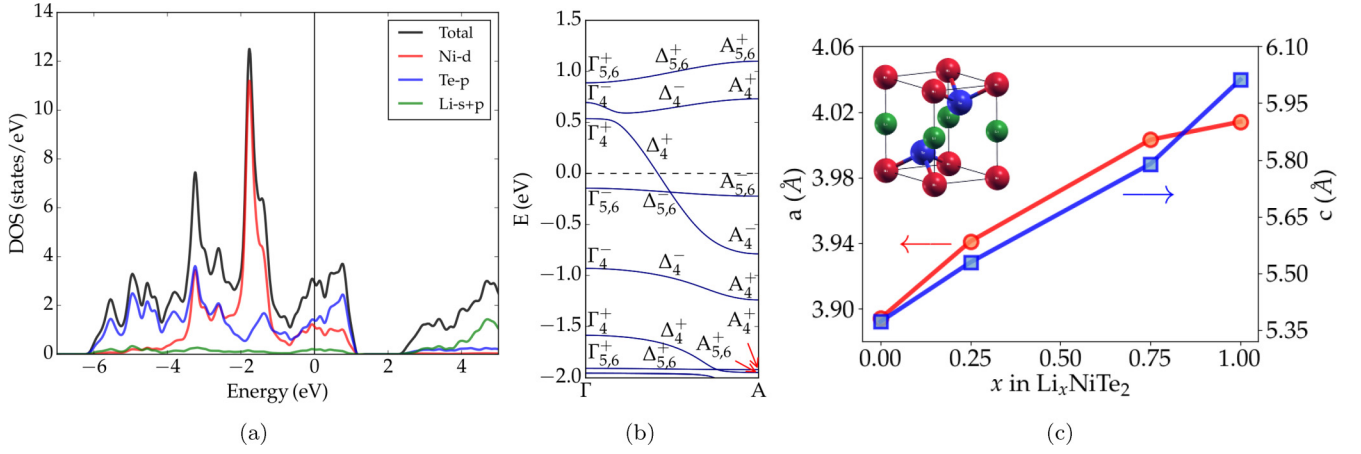


FIG. 9. (a) Electronic density of states of LiNiTe_2 projected onto Te-5p (blue), Ni-3d (red), and Li-2s + 2p (green) orbitals. (b) Irreducible representations and parity symmetry of the low-energy electronic states of LiNiTe_2 along Γ -A. The arrows point to distinct irreducible representations in A. (c) Evolution of the a (circles) and c (squares) lattice parameters as a function of Li content in Li_xNiTe_2 system. The arrows in (c) indicate the corresponding axis for each curve. The inset shows the positions of the Li atoms (in green).

Interestingly, the $R_{5,6}^-$ symmetry representation is nearly flat and close to the Fermi level, opening the way for strong correlations [94–96].

We can see in Fig. 9 a monotonic change in both lattice parameters as a function of Li content, reflecting the expansion of the cell in all axes. At $x = 0.25$, which is an experimentally feasible doping level [97–101], we achieve 3% of deformation on the c axis and 1.2% of deformation on the a direction. Additionally, at the same composition, Na and K atoms will promote greater deformations in the lattice as they possess a larger atomic radii than Li. Hence, it is possible to access different strain states by controlling the type and the quantity of the dopant species.

V. MINIMAL EFFECTIVE MODEL FOR TYPE-II DIRAC CONES

With the information collected from the first-principle calculations presented in Sec. III, we construct an effective model that describes the type-II Dirac cones. First, we note that a minimal Hamiltonian should include NiTe_2 discrete symmetries, namely, C_3 rotations, inversion, reflection along the x axis and time-reversal. We restrict the Hilbert space to Te- p orbitals, based on the orbital-projected band structure shown in Fig. 3 and fix the representation with the corresponding angular momentum states:

$$\psi = \begin{pmatrix} J = 1/2, J_z = 1/2 \\ J = 1/2, J_z = -1/2 \\ J = 3/2, J_z = 3/2 \\ J = 3/2, J_z = -3/2 \end{pmatrix}. \quad (1)$$

We then search for a family of Hamiltonians compatible with the symmetry group with QSYMM [79]. We also restrict to a $k \cdot p$ model up to second order. The family of

Hamiltonians is

$$\mathcal{H}(\mathbf{k}) = \epsilon(\mathbf{k})\mathbb{1} + \begin{pmatrix} M(\mathbf{k}) & 0 & iAk_+ & Bk_+ \\ 0 & M(\mathbf{k}) & Bk_- & iAk_- \\ -iAk_- & Bk_+ & -M(\mathbf{k}) & 0 \\ Bk_- & -iAk_+ & 0 & -M(\mathbf{k}) \end{pmatrix}, \quad (2)$$

with

$$\epsilon(\mathbf{k}) = \epsilon_0 + \epsilon_1(k_x^2 + k_y^2) + \epsilon_2k_z^2, \quad (3)$$

$$M(\mathbf{k}) = M_0 + M_1(k_x^2 + k_y^2) + M_2k_z^2, \quad (4)$$

$$k_{\pm} = k_x \pm ik_y. \quad (5)$$

Finally, fitting the DFT data, we find $M_0 = 0.562$ eV, $M_1 = -1.33$ meV \AA^2 , $M_2 = -5.10$ eV \AA^2 , $\epsilon_0 = 0.873$ eV, $\epsilon_1 = -3.38$ eV \AA^2 , $\epsilon_2 = -6.58$ eV \AA^2 , and $A = B = 3.82$ eV \AA .

The dispersion around the Dirac cone obtained with the effective model is shown in Fig. 10, where we clearly see the characteristic tilt of type-II Dirac cones. Furthermore, it is straightforward to check that the Dirac nodes are located at $\mathbf{k}_D = (0, 0, \pm Q)$, with $Q = \sqrt{-M_0/M_2}$ and at the energy $E_D = \epsilon_0 + \epsilon_2Q^2$.

Investigating the third-order terms in momentum, available in the Supplemental Material [80], we noticed a slight difference with respect to the description of a similar system, PtSe_2 [55]. The reason is that the model used in that case is compatible with $A_3\text{Bi}$ systems [35], which show C_6 rotation symmetry, whereas both NiTe_2 and PtSe_2 present C_3 -symmetry, lacking C_6 . The model with C_6 rotation symmetry is also derived in our Supplementary Material for the sake of comparison [80]. Moreover, we also noticed that, as expected, a gap opens at the Dirac node when C_3 symmetry is broken, as discussed in Appendix B.

We also capture the effects of strain in the type-II Dirac cones with the effective model. We build a model restricted to strain states keeping all discrete symmetries, such that Eq. (2) holds, but with different parameter values. Thus, we restrict

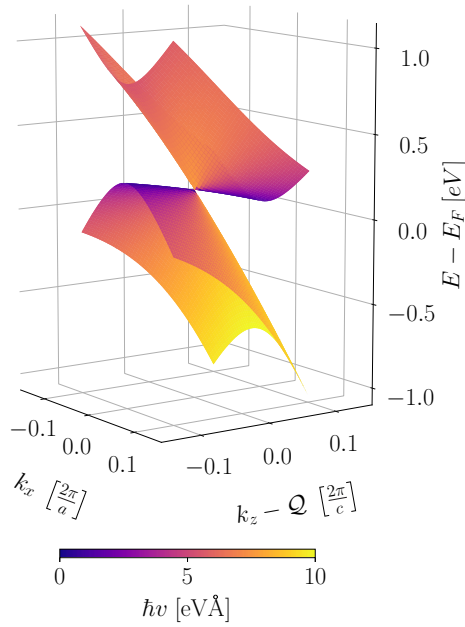


FIG. 10. Dispersion around the Dirac cone obtained by diagonalizing Eq. (2). The characteristic tilt of type-II Dirac cones is visible. The colors indicate the absolute value of the velocity at each point.

strain states to (η_x, η_y, η_z) , with $\eta_x = \eta_y = \eta_{xy}$. To recover the notion of a crystal we perform lattice regularization, and then all Hamiltonian parameters are expanded up to first order on strain (more details in Appendix C). Finally, we performed a $k \cdot p$ expansion to find that the Hamiltonian is modified as

$$M_0 \mapsto M_0 + \frac{4M_1}{\tilde{a}^2} \eta_{xy} \beta_{xy}^M + \frac{2M_2}{\tilde{c}^2} \beta_z^M \eta_z, \quad (6)$$

$$\epsilon_0 \mapsto \epsilon_0 + \frac{4\epsilon_1}{\tilde{a}^2} \eta_{xy} \beta_{xy}^\epsilon + \frac{2\epsilon_2}{\tilde{c}^2} \beta_z^\epsilon \eta_z, \quad (7)$$

$$M_1 \mapsto (1 - \beta_{xy}^M \eta_{xy}) M_1, \quad (8)$$

$$\epsilon_1 \mapsto (1 - \beta_{xy}^\epsilon \eta_{xy}) \epsilon_1, \quad (9)$$

$$M_2 \mapsto (1 - \beta_z^M \eta_z) M_2, \quad (10)$$

$$\epsilon_2 \mapsto (1 - \beta_z^\epsilon \eta_z) \epsilon_2, \quad (11)$$

$$A(B) \mapsto (1 - \beta_{xy}^{A(B)} \eta_{xy}) A(B), \quad (12)$$

where $\tilde{a} = (1 + \eta_{xy})a$ and $\tilde{c} = (1 + \eta_z)c$ are the lattice parameters under strain and the fitted Grüneisen parameters from DFT data are $\beta_{xy}^M = -5875$, $\beta_{xy}^\epsilon = -0.354$, $\beta_z^M = 10.9$, $\beta_z^\epsilon = 5.14$, $\beta_{xy}^{A(B)} = 0.083$. Moreover, the Dirac cone location in the Brillouin zone is shifted as

$$Q \mapsto Q \left(1 - \frac{2M_1 \beta_{xy}^M \eta_{xy}}{M_2 Q^2 \tilde{a}^2} - \frac{\beta_z^M \eta_z}{Q^2 \tilde{c}^2} \right), \quad (13)$$

while the Dirac node energy changes as

$$E_D \mapsto E_D + \frac{4\epsilon_1}{\tilde{a}^2} \eta_{xy} \beta_{xy}^\epsilon + \frac{2\epsilon_2}{\tilde{c}^2} \beta_z^\epsilon \eta_z + (1 - \beta_z^\epsilon \eta_z) \epsilon_2 Q. \quad (14)$$

The Dirac cone tunability with isostatic pressure is shown in Fig. 1, which summarizes the effects, on the position of the Dirac cone, of strain states that do not break the C_3 rotation symmetry.

In the present work, we considered only uniform strain states, but it is worth to emphasize effects of nonuniform strain. Equation (13) suggests that, in this case, a local dependency of the Dirac cone momentum, generating pseudo-Landau levels, with direct consequences to transport properties [60]. Furthermore, when combined with electromagnetic fields, it results in a chiral anomaly [61]. With nonuniform strain, however, Eq. (2) hardly holds, since nonuniform strain will likely break some of the discrete symmetries. However, the Dirac cone will split into two Weyl cones and the observable consequences will still be present [60,61].

It is worth mentioning that the model derived here, including the effects of strain, is not restricted to NiTe₂, but works for any system within the same symmetry group, for example, other TMDs which are type-II Dirac semimetals, such as PtSe₂, PdSe₂, and PtTe₂ [42,55,56].

VI. CONCLUSION

We presented the elastic behavior of NiTe₂ and its electronic structure dependency on the strain state. By analyzing the electronic states' irreducible representations at high-symmetry points in the first Brillouin zone, we concluded that a type-II Dirac cone is formed by a single-orbital manifold band-inversion mechanism. Furthermore, we showed that bulk NiTe₂ possesses a ductile regime, making it a candidate for electronic structure strain-engineering. Our first-principle calculations show that it is possible to tune the type-II Dirac point to the Fermi energy, making it a suitable platform for transport experiments when compared with materials of the same class [55]. It is important to highlight that strain-engineering is achievable in real electronic devices using piezoelectric actuators, even in mechanically delicate samples [102]. We also proposed a method for a static tunability with alkali-metal intercalation, a process already exhaustively tested in TMDs, removing the requirement of *in situ* strain control. All these effects were captured by an effective model, providing an inexpensive way for further theoretical investigations and easy comparison with experiments. In addition, the static approach with Li doping shows the formation of dispersionless bands close to the Fermi level, favoring strong-correlation effects. Moreover, with finite strain it is possible to access hybrid type-I and type-II topological Dirac phases and promote Lifshitz transitions. Therefore, our work puts forward NiTe₂ as an ideal assaying platform for exploring coexisting electronic correlations and topological phenomena.

VII. SUPPLEMENTAL MATERIAL

All code and data used to prepare this paper is freely available on Zenodo [80], with instructions to properly open the PYTHON codes as JUPYTER notebooks. We also added a Binder link to our Zenodo page.

TABLE III. Bulk modulus (B), shear modulus (G), Young modulus (E), and Poisson's ratio (ν) for NiTe₂ according to the Voigt-Heuss-Hill approximation. All values are in GPa (except dimensionless quantities).

	B_V	B_R	B_H	G_V	G_R	G_H	B/G	E_V	E_R	E_H	ν_V	ν_R	ν_H
PBE	48.34	38.60	43.47	23.54	15.60	19.57	2.22	60.75	41.24	51.04	0.29	0.32	0.30
PBE + SOC	50.58	40.56	45.57	24.34	16.05	20.19	2.26	62.93	42.53	52.79	0.29	0.33	0.31
PZ + SOC	72.09	64.26	68.17	34.98	27.80	31.39	2.17	90.34	72.90	81.65	0.29	0.31	0.30
optB86b-vdW	59.12	53.84	56.48	31.44	25.41	28.43	1.99	80.11	65.88	73.03	0.27	0.30	0.28
Calc. [83]	–	–	70.12	–	–	28.75	2.44	–	–	50.95	–	–	0.32

VIII. AUTHOR CONTRIBUTIONS

P.P.F. performed and analysed the DFT calculations and wrote the first draft of the manuscript. A.L.R.M. and G.W. created the route for constructing the effective model; A.L.R.M. implemented the code and performed the calculations. T.T.D. carried out the Li-doped calculations. L.E.C. and A.J.S.M. validated the experimental considerations. L.T.F.E. supervised this project. All co-authors revised the manuscript.

ACKNOWLEDGMENTS

We gratefully acknowledge the financial support of the São Paulo Research Foundation (FAPESP) under Grants No. 2016/10167-8, No. 2018/10835-6, No. 2018/08819-2, No. 2019/07082-9, No. 2019/14359-7, No. 2019/05005-7, and No. 2020/08258-0. This study was also financed in part by the Coordenação de Aperfeiçoamento de Pessoal de Nível Superior (CAPES) – Brasil – Finance Code 001. The research was carried out using high-performance computing resources made available by the Superintendência de Tecnologia da Informação (STI), Universidade de São Paulo. The authors also thank Daniel Varjas, Artem Pulkin, and Anton Akhmerov for fruitful discussions.

APPENDIX A: ELASTIC ANISOTROPY AND MECHANICAL PROPERTIES

The second-order elastic constants $c_{\alpha\beta}$ provide valuable information about the mechanical response of a compound to a certain applied strain condition. The c_{11} and c_{33} constants, for instance, represent the resistance to an uniaxial deformation along the [100] and [001] directions, respectively, while the c_{44} elastic constant is related to the resistance to a shear deformation in the $(hk0)$ planes. Therefore, NiTe₂ has a low resistance to shearing in planes parallel to the tellurium sheets, with $c_{44} = 20.2$ GPa, according to the optB86-vdW functional. Nevertheless, in [100] and [001] crystallographic directions we find Ni-Te and Ni-Ni bonds, offering, thereupon, greater resistance to structural changes along these directions. Thus, the constant $c_{11} = 110.8$ GPa reflects a strong intralayer interaction, whereas the value of 45.5 GPa for c_{33} indicates that the van der Waals gap will undergo a significant structural change when strain is applied in the [001] direction. On the other hand, nickel and tellurium will continue to interact to establish ionic/covalent bonds, preserving the mechanical stability and exerting some resistance.

The mechanical properties within the Voigt-Reuss-Hill approximation [103] are shown in Table III. It is interesting to note the B/G ratio, used as a general measure of ductility

[104], for different exchange and correlation functionals. Values higher than 1.75 indicate the compound is ductile, while smaller than 1.75 indicate a brittle behavior. The calculated value, therefore, shows that NiTe₂, presents a good ductility for an intermetallic compound. This assessment is consistent with a Poisson ratio higher than 0.26 [105]. However, the PBE + SOC approach, as expected, overestimate the ductile regime when compared to the optB86b-vdW values. This result establishes that NiTe₂ is a decent candidate for strain engineering.

Knowledge of the degree of anisotropy in the single-crystal elastic properties is essential to strain engineering. The reciprocal linear compressibility (B_c) and Young's modulus (E) directional dependencies for several exchange and correlation functionals are shown in Fig. 11, showing large anisotropies for B_c and E . We observe a large resistance to elastic deformation in the [110] direction and a slight resistance along [001]. Such mechanical manifestations occur due to, as discussed based on the second-order elastic constants, the weak van der

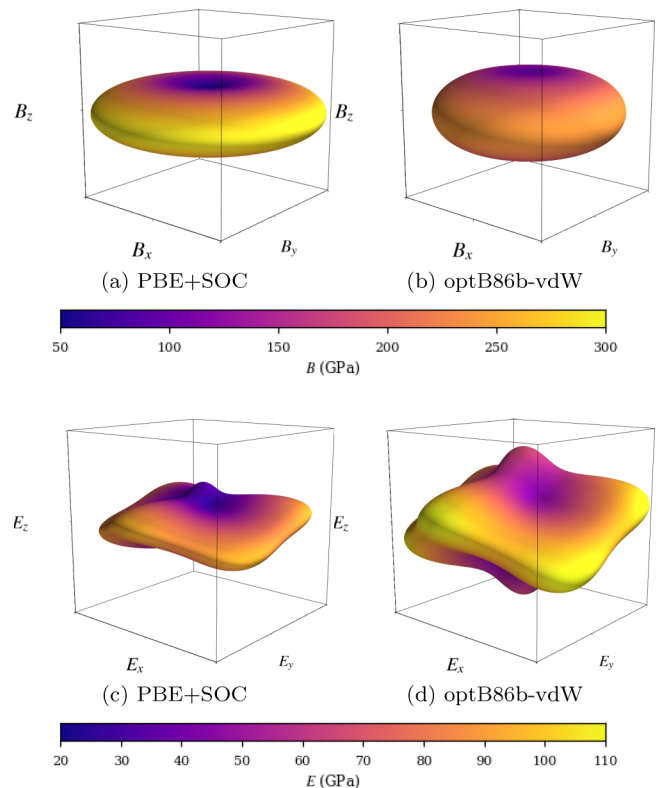


FIG. 11. Directional dependence of the reciprocal linear compressibility (a, b) B_c and (c, d) Young's modulus E for NiTe₂ (in GPa) using different exchange and correlation functionals.

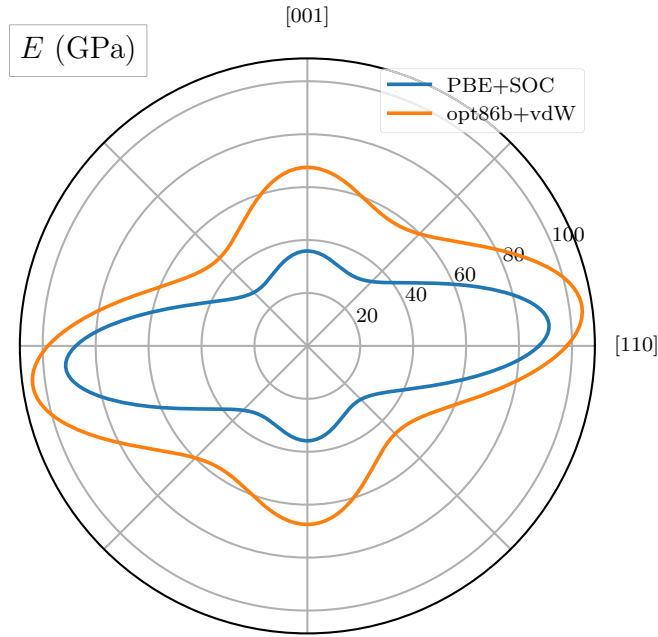


FIG. 12. Polar plot of the Young's modulus E (in GPa) in the (110) crystallographic plane.

Waals interactions between adjacent Te layers and a stronger in-plane electronic density.

It is also important to depict the changes in the elastic anisotropy profiles for different exchange and correlation functionals. Figure 12 shows a planar projection of the Young's modulus using PBE + SOC and optB89B-vdW for directions in (110) crystallographic planes. The different mechanical resistance between the [001] and [110] directions is clear. The Young's modulus projection curve within (110) plane is visibly tilted. The origin of this elastic behavior is the opposite positions of the Te atoms in the unit cell, generating this anisotropy. Since different exchange and correlation functionals provide different force and energy minimizations to the Te atomic position degree of freedom, as well as different interatomic interactions and effective electronic densities, the net effect is a rotation of the Young's modulus projection, changing its tilting angle and its absolute values.

APPENDIX B: EFFECTS OF C_3 SYMMETRY BREAKING

In Sec. V we considered only strain states that break no discrete symmetry in the system. Here, we briefly discuss the consequences of breaking the C_3 rotation symmetry. The procedure is straightforward: We follow the same approach as before, but we remove the constrain of 3-fold rotations. The new family of Hamiltonians, then, has four additional parameters:

$$\epsilon(\mathbf{k}) \mapsto \epsilon(\mathbf{k}) + \epsilon_3 k_y k_z, \quad M(\mathbf{k}) \mapsto M(\mathbf{k}) + M_3 k_y k_z, \quad (\text{B1})$$

$$H(\mathbf{k}) \mapsto H(\mathbf{k}) + \begin{pmatrix} 0 & 0 & Ck_z & iDk_z \\ 0 & 0 & -iDk_z & -Ck_z \\ Ck_z & iDk_z & 0 & 0 \\ -iDk_z & -Ck_z & 0 & 0 \end{pmatrix}. \quad (\text{B2})$$

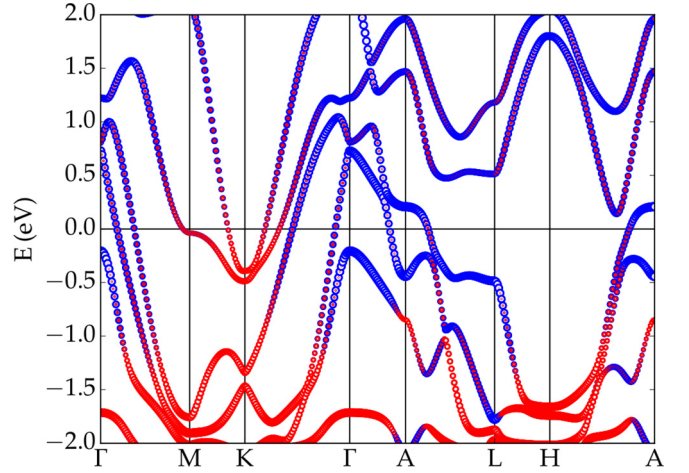


FIG. 13. Projected electronic band structure of NiTe₂ under in-plane uniaxial strain $\eta = (0.05, 0, 0)$. It is possible to see the gap opening at the former Dirac node position due to the C_3 -broken symmetry. The color map shows the contribution of Te-5p (blue) and Ni-3d (red) manifold to the electronic wave function.

It is noticeable then that there is a gap opening that is proportional to $Q\sqrt{C^2 + D^2}$. We confirm that this is indeed the case by performing DFT calculations with uniaxial strain, as shown in Fig. 13, that should be compared to Fig. 3(b).

APPENDIX C: LATTICE REGULARIZATION AND EFFECTS OF STRAIN IN THE DIRAC CONE

To take into account the effects of strain without deriving a full tight-binding Hamiltonian, i.e., keeping the simple 4-band model presented in Sec. V, we first need to restore the idea of a lattice model. This is done via lattice regularization, implemented using the following transformations [61]:

$$k_i \mapsto \frac{1}{L_i} \sin(k_i L_i), \quad (\text{C1})$$

$$k_i^2 \mapsto \frac{2}{L_i^2} [1 - \cos(k_i L_i)], \quad (\text{C2})$$

where $L_x = L_y = a$ and $L_z = c$ in the new tetragonal lattice. Thus, the Hamiltonian is now rewritten as

$$\mathcal{H}(\mathbf{k}) = \tilde{\epsilon}(\mathbf{k})\mathbb{1} + \begin{pmatrix} \tilde{M}(\mathbf{k}) & 0 & i\tilde{A}_+(k_{\parallel}) + \tilde{B}_+(k_{\parallel}) & \tilde{B}_+(k_{\parallel}) \\ 0 & \tilde{M}(\mathbf{k}) & \tilde{B}_-(k_{\parallel}) & i\tilde{A}_-(k_{\parallel}) \\ -i\tilde{A}_-(k_{\parallel}) & \tilde{B}_+(k_{\parallel}) & -\tilde{M}(\mathbf{k}) & 0 \\ \tilde{B}_-(k_{\parallel}) & -i\tilde{A}_+(k_{\parallel}) & 0 & -\tilde{M}(\mathbf{k}) \end{pmatrix}, \quad (\text{C3})$$

where

$$\tilde{M}(\mathbf{k}) = \tilde{M}_0 - \tilde{M}_1 [\cos(k_z a) + \cos(k_y a)] - \tilde{M}_2 \cos(k_z c), \quad (\text{C4})$$

$$\tilde{\epsilon}(\mathbf{k}) = \tilde{\epsilon}_0 - \tilde{\epsilon}_1 [\cos(k_z a) + \cos(k_y a)] - \tilde{\epsilon}_2 \cos(k_z c), \quad (\text{C5})$$

$$\tilde{A}_{\pm} = \frac{A}{a} [\sin(k_x a) \pm i \sin(k_y a)], \quad (\text{C6})$$

$$\tilde{B}_{\pm} = \frac{B}{a} [\sin(k_x a) \pm i \sin(k_y a)], \quad (\text{C7})$$

and

$$\tilde{M}_0 = M_0 + \frac{4M_1}{a^2} + \frac{2M_2}{c^2}, \quad (\text{C8})$$

$$\tilde{M}_1 = \frac{2M_1}{a^2}, \quad (\text{C9})$$

$$\tilde{M}_2 = \frac{2M_2}{c^2}, \quad (\text{C10})$$

$$\tilde{\epsilon}_0 = \epsilon_0 + \frac{4\epsilon_1}{a^2} + \frac{2\epsilon_2}{c^2}, \quad (\text{C11})$$

$$\tilde{\epsilon}_1 = \frac{2\epsilon_1}{a^2}, \quad (\text{C12})$$

$$\tilde{\epsilon}_2 = \frac{2\epsilon_2}{c^2}. \quad (\text{C13})$$

It is straightforward to see that Eq. (2) is recovered if we take the $k \cdot p$ expansion of Eq. (C3).

Now we consider strain states $(\eta_{xy}, \eta_{xy}, \eta_z)$, that keep all the discrete symmetries of NiTe₂, and, therefore, preserves the Hamiltonian form of Eq. (2). Then, we expand all parameters up to first order on strain as

$$\alpha_i \mapsto \alpha_i(1 - \eta_j \beta_j^{\alpha_i}), \quad (\text{C14})$$

where β_j^i are the corresponding Grüneisen constants for parameter α_i relative to a strain state along the j direction. Finally, taking a $k \cdot p$ expansion of the Hamiltonian, we obtain Eqs. (6) to (14).

-
- [1] C. L. Kane and E. J. Mele, *Phys. Rev. Lett.* **95**, 146802 (2005).
 [2] C. L. Kane and E. J. Mele, *Phys. Rev. Lett.* **95**, 226801 (2005).
 [3] L. Fu, C. L. Kane, and E. J. Mele, *Phys. Rev. Lett.* **98**, 106803 (2007).
 [4] L. Fu and C. L. Kane, *Phys. Rev. B* **76**, 045302 (2007).
 [5] D. Hsieh, D. Qian, L. Wray, Y. Xia, Y. S. Hor, R. J. Cava, and M. Z. Hasan, *Nature* **452**, 970 (2008).
 [6] D. Hsieh, Y. Xia, L. Wray, D. Qian, A. Pal, J. Dil, J. Osterwalder, F. Meier, G. Bihlmayer, C. L. Kane, Y. S. Hor, R. J. Cava, and M. Z. Hasan, *Science* **323**, 919 (2009).
 [7] Y. Xia, D. Qian, D. Hsieh, L. Wray, A. Pal, H. Lin, A. Bansil, D. H. Y. S. Grauer, Y. S. Hor, R. J. Cava, and M. Z. Hasan, *Nat. Phys.* **5**, 398 (2009).
 [8] H. Zhang, C.-X. Liu, X.-L. Qi, X. Dai, Z. Fang, and S.-C. Zhang, *Nat. Phys.* **5**, 438 (2009).
 [9] Y. Chen, J. G. Analytis, J.-H. Chu, Z. Liu, S.-K. Mo, X.-L. Qi, H. Zhang, D. Lu, X. Dai, Z. Fang, S. C. Zhang, I. R. Fisher, Z. Hussain, and Z.-X. Shen, *Science* **325**, 178 (2009).
 [10] O. Vafek and A. Vishwanath, *Annu. Rev. Condens. Matter Phys.* **5**, 83 (2014).
 [11] A. A. Burkov, *Nat. Mater.* **15**, 1145 (2016).
 [12] H. Weng, X. Dai, and Z. Fang, *J. Phys.: Condens. Matter* **28**, 303001 (2016).
 [13] N. P. Armitage, E. J. Mele, and A. Vishwanath, *Rev. Mod. Phys.* **90**, 015001 (2018).
 [14] C. Shekhar, A. K. Nayak, Y. Sun, M. Schmidt, M. Nicklas, I. Leermakers, U. Zeitler, Y. Skourski, J. Wosnitza, Z. Liu, Y. Chen, W. Schnelle, H. Borrmann, Y. Grin, C. Felser, and B. Yan, *Nat. Phys.* **11**, 645 (2015).
 [15] T. Liang, Q. Gibson, M. N. Ali, M. Liu, R. J. Cava, and N. P. Ong, *Nat. Mater.* **14**, 280 (2015).
 [16] Y. Zhao, H. Liu, C. Zhang, H. Wang, J. Wang, Z. Lin, Y. Xing, H. Lu, J. Liu, Y. Wang, S. M. Brombosz, Z. Xiao, S. Jia, X. C. Xie, and J. Wang, *Phys. Rev. X* **5**, 031037 (2015).
 [17] J. Xiong, S. K. Kushwaha, T. Liang, J. W. Krizan, M. Hirschberger, W. Wang, R. J. Cava, and N. P. Ong, *Science* **350**, 413 (2015).
 [18] X. Huang, L. Zhao, Y. Long, P. Wang, D. Chen, Z. Yang, H. Liang, M. Xue, H. Weng, Z. Fang, X. Dai, and G. Chen, *Phys. Rev. X* **5**, 031023 (2015).
 [19] H. Li, H. He, H.-Z. Lu, H. Zhang, H. Liu, R. Ma, Z. Fan, S.-Q. Shen, and J. Wang, *Nat. Commun.* **7**, 10301 (2016).
 [20] W. Gao, N. Hao, F.-W. Zheng, W. Ning, M. Wu, X. Zhu, G. Zheng, J. Zhang, J. Lu, H. Zhang, C. Xi, J. Yang, H. Du, P. Zhang, Y. Zhang, and M. Tian, *Phys. Rev. Lett.* **118**, 256601 (2017).
 [21] A. A. Zyuzin and A. A. Burkov, *Phys. Rev. B* **86**, 115133 (2012).
 [22] S. A. Parameswaran, T. Grover, D. A. Abanin, D. A. Pesin, and A. Vishwanath, *Phys. Rev. X* **4**, 031035 (2014).
 [23] C.-L. Zhang, S.-Y. Xu, I. Belopolski, Z. Yuan, Z. Lin, B. Tong, G. Bian, N. Alidoust, C.-C. Lee, S.-M. Huang, T.-R. Chang, G. Chang, C.-H. Hsu, H.-T. Jeng, M. Neupane, D. S. Sanchez, H. Zheng, J. Wang, H. Lin, C. Zhang, H.-Z. Lu, S.-Q. Shen, T. Neupert, M. Zahid Hasan, and S. Jia, *Nat. Commun.* **7**, 10735 (2016).
 [24] A. A. Burkov and Y. B. Kim, *Phys. Rev. Lett.* **117**, 136602 (2016).
 [25] F. D. M. Haldane, *Phys. Rev. Lett.* **93**, 206602 (2004).
 [26] G. Xu, H. Weng, Z. Wang, X. Dai, and Z. Fang, *Phys. Rev. Lett.* **107**, 186806 (2011).
 [27] H. Weng, R. Yu, X. Hu, X. Dai, and Z. Fang, *Adv. Phys.* **64**, 227 (2015).
 [28] P. R. Wallace, *Phys. Rev.* **71**, 622 (1947).
 [29] A. H. Castro Neto, F. Guinea, N. M. R. Peres, K. S. Novoselov, and A. K. Geim, *Rev. Mod. Phys.* **81**, 109 (2009).
 [30] X. Wan, A. M. Turner, A. Vishwanath, and S. Y. Savrasov, *Phys. Rev. B* **83**, 205101 (2011).
 [31] Z. Liu, B. Zhou, Y. Zhang, Z. Wang, H. Weng, D. Prabhakaran, S.-K. Mo, Z. Shen, Z. Fang, X. Dai, Z. Hussain, and Y. L. Chen, *Science* **343**, 864 (2014).
 [32] H. Yi, Z. Wang, C. Chen, Y. Shi, Y. Feng, A. Liang, Z. Xie, S. He, J. He, Y. Peng, X. Liu, Y. Liu, L. Zhao, G. Liu, X. Dong, J. Zhang, M. Nakatake, M. Arita, K. Shimada, H. Namatame, M. Taniguchi, Z. Xu, C. Chen, X. Dai, Z. Fang, and X. J. Zhou, *Sci. Rep.* **4**, 6106 (2014).
 [33] S.-M. Huang, S.-Y. Xu, I. Belopolski, C.-C. Lee, G. Chang, B. Wang, N. Alidoust, G. Bian, M. Neupane, C. Zhang, S. Jia, A. Bansil, H. Lin, and M. Zahid Hasan, *Nat. Commun.* **6**, 7373 (2015).
 [34] S.-Y. Xu, I. Belopolski, N. Alidoust, M. Neupane, G. Bian, C. Zhang, R. Sankar, G. Chang, Z. Yuan, C.-C. Lee, S.-M. Huang, H. Zheng, J. Ma, D. S. Sanchez, B. K. Wang, A.

- Bansil, F. Chou, P. P. Shibayev, H. Lin, S. Jia, and M. Zahid Hasan, *Science* **349**, 613 (2015).
- [35] Z. Wang, Y. Sun, X.-Q. Chen, C. Franchini, G. Xu, H. Weng, X. Dai, and Z. Fang, *Phys. Rev. B* **85**, 195320 (2012).
- [36] A. A. Zyuzin, S. Wu, and A. A. Burkov, *Phys. Rev. B* **85**, 165110 (2012).
- [37] R. Okugawa and S. Murakami, *Phys. Rev. B* **89**, 235315 (2014).
- [38] A. A. Soluyanov, D. Gresch, Z. Wang, Q. Wu, M. Troyer, X. Dai, and B. A. Bernevig, *Nature* **527**, 495 (2015).
- [39] K. Deng, G. Wan, P. Deng, K. Zhang, S. Ding, E. Wang, M. Yan, H. Huang, H. Zhang, Z. Xu, J. Denlinger, A. Fedorov, H. Yang, W. Duan, H. Yao, Y. Wu, S. Fan, H. Zhang, X. Chen, and S. Zhou, *Nat. Phys.* **12**, 1105 (2016).
- [40] K. Koepernik, D. Kasinathan, D. V. Efremov, S. Khim, S. Borisenko, B. Büchner, and J. van den Brink, *Phys. Rev. B* **93**, 201101(R) (2016).
- [41] G. Chang, S.-Y. Xu, D. S. Sanchez, S.-M. Huang, C.-C. Lee, T.-R. Chang, G. Bian, H. Zheng, I. Belopolski, N. Alidoust, H.-T. Jeng, A. Bansil, H. Lin, and M. Zahid Hasan, *Sci. Adv.* **2**, e1600295 (2016).
- [42] K. Zhang, M. Yan, H. Zhang, H. Huang, M. Arita, Z. Sun, W. Duan, Y. Wu, and S. Zhou, *Phys. Rev. B* **96**, 125102 (2017).
- [43] H.-J. Noh, J. Jeong, E.-J. Cho, K. Kim, B. I. Min, and B.-G. Park, *Phys. Rev. Lett.* **119**, 016401 (2017).
- [44] M. Yan, H. Huang, K. Zhang, E. Wang, W. Yao, K. Deng, G. Wan, H. Zhang, M. Arita, H. Yang, M. Arita, H. Yang, Z. Sun, H. Yao, Y. Wu, S. Fan, W. Duan, and S. Zhou, *Nat. Commun.* **8**, 257 (2017).
- [45] Y. Wang, E. Liu, H. Liu, Y. Pan, L. Zhang, J. Zeng, Y. Fu, M. Wang, K. Xu, Z. Huang, Z. Wang, H.-Z. Lu, D. Xing, B. Wang, X. Wan, and F. Miao, *Nat. Commun.* **7**, 13142 (2016).
- [46] F. C. Chen, H. Y. Lv, X. Luo, W. J. Lu, Q. L. Pei, G. T. Lin, Y. Y. Han, X. B. Zhu, W. H. Song, and Y. P. Sun, *Phys. Rev. B* **94**, 235154 (2016).
- [47] N. Kumar, Y. Sun, N. Xu, K. Manna, M. Yao, V. Süß, I. Leermakers, O. Young, T. Förster, M. Schmidt, H. Borrmann, B. Yan, U. Zeitler, M. Shi, C. Felser, and C. Shekhar, *Nat. Commun.* **8**, 1642 (2017).
- [48] J. Lai, Y. Liu, J. Ma, X. Zhuo, Y. Peng, W. Lu, Z. Liu, J. Chen, and D. Sun, *ACS nano* **12**, 4055 (2018).
- [49] C. Xu, B. Li, W. Jiao, W. Zhou, B. Qian, R. Sankar, N. D. Zhigadlo, Y. Qi, D. Qian, F.-C. Chou, and X. Xu, *Chem. Mater.* **30**, 4823 (2018).
- [50] B. S. de Lima, R. R. de Cassia, F. B. Santos, L. E. Correa, T. W. Grant, A. L. R. Manesco, G. W. Martins, L. T. F. Eleno, M. S. Torikachvili, and A. J. S. Machado, *Solid State Commun.* **283**, 27 (2018).
- [51] W. Zheng, R. Schönemann, S. Mozaffari, Y.-C. Chiu, Z. B. Goraum, N. Aryal, E. Manousakis, T. M. Siegrist, K. Wei, and L. Balicas, *Phys. Rev. B* **102**, 125103 (2020).
- [52] B. Ghosh, D. Mondal, C.-N. Kuo, C. S. Lue, J. Nayak, J. Fujii, I. Vobornik, A. Politano, and A. Agarwal, *Phys. Rev. B* **100**, 195134 (2019).
- [53] Z. Feng *et al.*, *Mater. Today Phys.* **17**, 100339 (2021).
- [54] F. Zheng, X.-B. Li, P. Tan, Y. Lin, L. Xiong, X. Chen, and J. Feng, *Phys. Rev. B* **101**, 100505(R) (2020).
- [55] H. Huang, S. Zhou, and W. Duan, *Phys. Rev. B* **94**, 121117(R) (2016).
- [56] R. C. Xiao, P. L. Gong, Q. S. Wu, W. J. Lu, M. J. Wei, J. Y. Li, H. Y. Lv, X. Luo, P. Tong, X. B. Zhu, and Y. P. Sun, *Phys. Rev. B* **96**, 075101 (2017).
- [57] J. F. H. L. Monteiro, M. B. Marciniak, A. R. Jurelo, E. C. Siqueira, F. T. Dias, and J. L. P. Júnior, *J. Cryst. Growth* **478**, 129 (2017).
- [58] B. Zhao, W. Dang, Y. Liu, B. Li, J. Li, J. Luo, Z. Zhang, R. Wu, H. Ma, G. Sun, Y. Huang, X. Duan, and X. Duan, *J. Am. Chem. Soc.* **140**, 14217 (2018).
- [59] Q. Liu, F. Fei, B. Chen, X. Bo, B. Wei, S. Zhang, M. Zhang, F. Xie, M. Naveed, X. Wan, F. Song, and B. Wang, *Phys. Rev. B* **99**, 155119 (2019).
- [60] A. G. Grushin, J. W. F. Venderbos, A. Vishwanath, and R. Ilan, *Phys. Rev. X* **6**, 041046 (2016).
- [61] D. I. Pikulin, A. Chen, and M. Franz, *Phys. Rev. X* **6**, 041021 (2016).
- [62] P. Hohenberg and W. Kohn, *Phys. Rev.* **136**, B864 (1964).
- [63] W. Kohn and L. J. Sham, *Phys. Rev.* **140**, A1133 (1965).
- [64] P. Giannozzi, S. Baroni, N. Bonini, M. Calandra, R. Car, C. Cavazzoni, D. Ceresoli, G. L. Chiarotti, M. Cococcioni, I. Dabo, A. Dal Corso, S. de Gironcoli, S. Fabris, G. Fratesi, R. Gebauer, U. Gerstmann, C. Gougoussis, A. Kokalj, M. Lazzeri, L. Martin-Samos, N. Marzari, F. Mauri, R. Mazzarello, S. Paolini, A. Pasquarello, L. Paulatto, C. Sbraccia, S. Scandolo, G. Sclauzero, A. P. Seitsonen, A. Smogunov, P. Umari, and R. M. Wentzcovitch, *J. Phys.: Condens. Matter* **21**, 395502 (2009).
- [65] P. Giannozzi, O. Andreussi, T. Brumme, O. Bunau, M. B. Nardelli, M. Calandra, R. Car, C. Cavazzoni, D. Ceresoli, M. Cococcioni, N. Colonna, I. Carnimeo, A. Dal Corso, S. de Gironcoli, P. Delugas, R. A. DiStasio, Jr., A. Ferretti, A. Floris, G. Fratesi, G. Fugallo, R. Gebauer, U. Gerstmann, F. Giustino, T. Gorni, J. Jia, M. Kawamura, H.-Y. Ko, A. Kokalj, E. Küçükbenli, M. Lazzeri, M. Marsili, N. Marzari, F. Mauri, N. L. Nguyen, H.-V. Nguyen, A. Otero-de-la-Roza, L. Paulatto, S. Poncè, D. Rocca, R. Sabatini, B. Santra, M. Schlipf, A. P. Seitsonen, A. Smogunov, I. Timrov, T. Thonhauser, P. Umari, N. Vast, X. Wu, and S. Baroni, *J. Phys.: Condens. Matter* **29**, 465901 (2017).
- [66] A. Kokalj, *J. Mol. Graphics Modell.* **17**, 176 (1999).
- [67] M. Kawamura, *Comput. Phys. Commun.* **239**, 197 (2019).
- [68] J. P. Perdew and A. Zunger, *Phys. Rev. B* **23**, 5048 (1981).
- [69] J. P. Perdew, K. Burke, and M. Ernzerhof, *Phys. Rev. Lett.* **77**, 3865 (1996).
- [70] J. P. Perdew, A. Ruzsinszky, G. I. Csonka, O. A. Vydrov, G. E. Scuseria, L. A. Constantin, X. Zhou, and K. Burke, *Phys. Rev. Lett.* **100**, 136406 (2008).
- [71] F. Tran, L. Kalantari, B. Traoré, X. Rocquefelte, and P. Blaha, *Phys. Rev. Materials* **3**, 063602 (2019).
- [72] M. Dion, H. Rydberg, E. Schröder, D. C. Langreth, and B. I. Lundqvist, *Phys. Rev. Lett.* **92**, 246401 (2004).
- [73] M. Dion, H. Rydberg, E. Schröder, D. C. Langreth, and B. I. Lundqvist, *Phys. Rev. Lett.* **95**, 109902(E) (2005).
- [74] J. Klimeš, D. R. Bowler, and A. Michaelides, *J. Phys.: Condens. Matter* **22**, 022201 (2009).
- [75] J. Klimeš, D. R. Bowler, and A. Michaelides, *Phys. Rev. B* **83**, 195131 (2011).
- [76] H. J. Monkhorst and J. D. Pack, *Phys. Rev. B* **13**, 5188 (1976).
- [77] R. Golesorkhtabar, P. Pavone, J. Spitaler, P. Puschnig, and C. Draxl, *Comput. Phys. Commun.* **184**, 1861 (2013).

- [78] P. P. Ferreira, T. T. Dorini, F. B. Santos, A. J. S. Machado, and L. T. F. Eleno, *Materialia* **4**, 529 (2018).
- [79] D. Varjas, T. O. Rosdahl, and A. R. Akhmerov, *New J. Phys.* **20**, 093026 (2018).
- [80] A. Manesco, P. P. Ferreira, T. T. Dorini, L. E. Correa, G. Weber, A. J. da Silva Machado, and L. T. F. Eleno, *Strain-engineering the topological type-II Dirac semimetal NiTe₂*, (Zenodo, 2020), <http://doi.org/10.5281/zenodo.4455260>.
- [81] W. Setyawan and S. Curtarolo, *Comput. Mater. Sci.* **49**, 299 (2010).
- [82] S. Manzeli, D. Ovchinnikov, D. Pasquier, O. V. Yazyev, and A. Kis, *Nature Rev. Mater.* **2**, 17033 (2017).
- [83] J.-Q. Lei, K. Liu, S. Huang, X.-C. Mao, B.-S. Hou, J. Tan, and X.-L. Zhou, *Chem. Phys. Lett.* **687**, 250 (2017).
- [84] M. Sato and K. Abe, *J. Phys. C: Solid State Phys.* **12**, L613 (1979).
- [85] F. Mouhat and F.-X. Coudert, *Phys. Rev. B* **90**, 224104 (2014).
- [86] M. S. Bahramy, O. J. Clark, B.-J. Yang, J. Feng, L. Bawden, J. M. Riley, I. Marković, F. Mazzola, V. Sunko, D. Biswas, S. P. Cooil, M. Jorge, J. W. Wells, M. Leandersson, T. Balasubramanian, J. Fujii, I. Vobornik, J. E. Rault, T. K. Kim, M. Hoesch, K. Okawa, M. Asakawa, T. Sasagawa, T. Eknapakul, W. Meevasana, and P. D. C. King, *Nat. Mater.* **17**, 21 (2018).
- [87] O. J. Clark, F. Mazzola, I. Marković, J. M. Riley, J. Feng, B. J. Yang, K. Sumida, T. Okuda, J. Fujii, I. Vobornik, T. K. Kim, K. Okawa, T. Sasagawa, M. S. Bahramy, and P. D. C. King, *Electron. Struct.* **1**, 014002 (2019).
- [88] S. Mukherjee, S. W. Jung, S. F. Weber, C. Xu, D. Qian, X. Xu, P. K. Biswas, T. K. Kim, L. C. Chapon, M. D. Watson *et al.*, *Sci. Rep.* **10**, 12957 (2020).
- [89] F. Liu, J. Li, K. Zhang, S. Peng, H. Huang, M. Yan, N. Li, Q. Zhang, S. Guo, X. Lü, P. Cai, L. F. Yin, S. Y. Zhou, W. H. Duan, J. Shen, and W. G. Yang, *Sci. China Phys. Mech.* **62**, 48211 (2019).
- [90] M. Qi, C. An, Y. Zhou, H. Wu, B. Zhang, C. Chen, Y. Yuan, S. Wang, Y. Zhou, X. Chen, R. Zhang, and Z. Yang, *Phys. Rev. B* **101**, 115124 (2020).
- [91] C. Chen, S.-S. Wang, L. Liu, Z.-M. Yu, X.-L. Sheng, Z. Chen, and S. A. Yang, *Phys. Rev. Materials* **1**, 044201 (2017).
- [92] A. A. Abrikosov, *Phys. Rev. B* **58**, 2788 (1998).
- [93] A. A. Abrikosov, *J. Phys. A: Math. Gen.* **36**, 9119 (2003).
- [94] N. B. Kopnin, T. T. Heikkilä, and G. E. Volovik, *Phys. Rev. B* **83**, 220503(R) (2011).
- [95] V. J. Kauppila, F. Aikebaier, and T. T. Heikkilä, *Phys. Rev. B* **93**, 214505 (2016).
- [96] B. Roy and V. Juričić, *Phys. Rev. B* **99**, 121407(R) (2019).
- [97] E. Morosan, H. W. Zandbergen, B. S. Dennis, J. W. G. Bos, Y. Onose, T. Klimczuk, A. P. Ramirez, N. Ong, and R. J. Cava, *Nat. Phys.* **2**, 544 (2006).
- [98] K. E. Wagner, E. Morosan, Y. S. Hor, J. Tao, Y. Zhu, T. Sanders, T. M. McQueen, H. W. Zandbergen, A. J. Williams, D. V. West, and R. J. Cava, *Phys. Rev. B* **78**, 104520 (2008).
- [99] E. Morosan, K. E. Wagner, L. L. Zhao, Y. Hor, A. J. Williams, J. Tao, Y. Zhu, and R. J. Cava, *Phys. Rev. B* **81**, 094524 (2010).
- [100] M. Kamitani, M. S. Bahramy, R. Arita, S. Seki, T. Arima, Y. Tokura, and S. Ishiwata, *Phys. Rev. B* **87**, 180501(R) (2013).
- [101] G. Ryu, *J. Supercond. Novel Magn.* **28**, 3275 (2015).
- [102] J. Park, J. M. Bartlett, H. M. Noad, A. Stern, M. E. Barber, M. König, S. Hosoi, T. Shibauchi, A. P. Mackenzie, A. Steppke, and C. W. Hicks, *Rev. Sci. Instrum.* **91**, 083902 (2020).
- [103] R. Hill, *Proc. Phys. Soc. London, Sect. A* **65**, 349 (1952).
- [104] S. F. Pugh, *London Edinburgh Philos. Mag. J. Sci.* **45**, 823 (1954).
- [105] X.-Q. Chen, H. Niu, D. Li, and Y. Li, *Intermetallics* **19**, 1275 (2011).