

**Surface characterization of carbonated recycled concrete fines and its effect on the rheology, hydration and strength development of cement paste**

Ouyang, Xiaowei; Wang, Liquan; Xu, Shida; Ma, Yuwei; Ye, Guang

**DOI**

[10.1016/j.cemconcomp.2020.103809](https://doi.org/10.1016/j.cemconcomp.2020.103809)

**Publication date**

2020

**Document Version**

Final published version

**Published in**

Cement and Concrete Composites

**Citation (APA)**

Ouyang, X., Wang, L., Xu, S., Ma, Y., & Ye, G. (2020). Surface characterization of carbonated recycled concrete fines and its effect on the rheology, hydration and strength development of cement paste. *Cement and Concrete Composites*, 114, 1-10. Article 103809. <https://doi.org/10.1016/j.cemconcomp.2020.103809>

**Important note**

To cite this publication, please use the final published version (if applicable). Please check the document version above.

**Copyright**

Other than for strictly personal use, it is not permitted to download, forward or distribute the text or part of it, without the consent of the author(s) and/or copyright holder(s), unless the work is under an open content license such as Creative Commons.

**Takedown policy**

Please contact us and provide details if you believe this document breaches copyrights. We will remove access to the work immediately and investigate your claim.



# Surface characterization of carbonated recycled concrete fines and its effect on the rheology, hydration and strength development of cement paste

Xiaowei Ouyang<sup>a,\*</sup>, Liqun Wang<sup>a</sup>, Shida Xu<sup>a</sup>, Yuwei Ma<sup>a</sup>, Guang Ye<sup>b</sup>

<sup>a</sup> Guangzhou University—Tamkang University Joint Research Center for Engineering Structure Disaster Prevention and Control, Guangzhou University, Guangzhou, 510006, China

<sup>b</sup> Department of Materials and Environment (Microlab), Faculty of Civil Engineering and Geosciences, Delft University of Technology, 2628CN Delft, the Netherlands

## ARTICLE INFO

### Keywords:

Carbonation treatment  
Recycled concrete fines  
Recycled concrete aggregate  
Rheology  
Hydration  
Strength development

## ABSTRACT

Carbonation treatment can effectively improve the performance of recycled concrete aggregate and fines due to the reactions of CO<sub>2</sub> with CH and C–S–H gel of cement paste. To better understand the mechanisms involved in the performance improvement, the surface properties of carbonated recycled cement paste powder (CRP) and its effect on the rheology, hydration and strength development of cement paste was studied. The results showed that during the carbonation, the surface of CRP was covered by a layer of amorphous silica gel. The generated CaCO<sub>3</sub> was wrapped by the silica gel and seldom exposed. The silica layer led to the poor flowability of CRP-cement paste due to that the silica gel on the surface of CRP has a strong affinity for H<sub>2</sub>O. During the very early hydration, the silica gel dissolved and then CaCO<sub>3</sub> was exposed. CaCO<sub>3</sub> is capable of chemically absorbing Ca<sup>2+</sup>, which facilitated the nucleation of C–S–H nuclei and stabilized the C–S–H phase. As a result, the C–S–H grew densely, uniformly and perpendicularly on the surface of CRP. In addition, the chemically absorbing Ca<sup>2+</sup> enabled the chemical bond to be formed between CaCO<sub>3</sub> and C–S–H. Due to increased C–S–H resulted from reactions of silica gel with CH at the interface and the stronger bond formed between CaCO<sub>3</sub> and C–S–H, the interface between CRP and hydration products was much stronger than that between recycled cement paste powder (RP) and hydration products.

## 1. Introduction

Reusing the demolished concrete not only reduces the pollution caused by concrete production and waste disposal but also preserves natural resources. In general, the demolished concrete is recycled to produce aggregate. However, compared with natural aggregate, the recycled aggregate has the characteristics of high porosity, strong water absorption, poor bonding ability and low strength [1–4]. These drawbacks limit the wide application of recycled concrete. Using carbonation treatment can effectively improve the performance of recycled concrete [5–12]. This is attributed to the fact that CO<sub>2</sub> reacts with CH and C–S–H gel of cement paste adhere to recycled aggregate to reduce water absorption and the porosity, and improve the strength [13–15]. The waste cement paste powder generated in the production of recycled aggregate also has a better performance after carbonation treatment when used in concrete to replace part of cement [16].

Hydration products (mainly C–S–H and CH) and unhydrated cement clinker (mainly C<sub>3</sub>S and C<sub>2</sub>S) in recycled cement paste can react with

CO<sub>2</sub> to form CaCO<sub>3</sub>, amorphous silica gel and amorphous alumina-silica gel [14,17–21]. The calcite can fill the pores and increase the density of cement paste. The formed amorphous silica gel will react with CH, thus accelerates the early age hydration of cement and increases the amount of hydration products [9,22,23]. Furthermore, the calcite can also react with the aluminate phase in cement paste resulting in a denser and higher strength cement paste [16]. However, the carbonation mechanisms of CH and C–S–H in the recycled cement paste are still not fully understood [14,24]. The surface properties of the particles determine the interactions of particles with H<sub>2</sub>O and ions in the solution of cement paste. These interactions play a crucial role in the C–S–H nucleation and growth on the particles [25,26], the strength of the interface between the particles and C–S–H [27] and rheology of the blended cement paste [28]. The surface properties have a significant influence on flowability, hydration and strength development of the blended cement paste. However, the surface properties of carbonated cement paste remain obscure.

Therefore, to deeply understand the mechanisms behind the

\* Corresponding author.

E-mail address: [xwouyang@gzhu.edu.cn](mailto:xwouyang@gzhu.edu.cn) (X. Ouyang).

performance improvement caused by carbonation treatment for recycled cement paste powder, as well as recycled aggregate, the surface properties of recycled cement paste (RP) and carbonated recycled cement paste powder (CRP) were first characterized in this paper. X-ray diffraction (XRD), thermogravimetric analysis (TGA),  $^{29}\text{Si}$  NMR analysis and zeta potential test will be utilized. Parallel to the surface properties characterization, the rheology of cement paste made of RP and CRP was compared. The morphology of the hydrates on the surface of RP and CRP at different hydration times was observed using a scanning electron microscope (SEM). Furthermore, the mechanical properties of the interface between RP or CRP and hydration products were analyzed. The effect of carbonation treatment on the performance of recycled cement paste powder as a cement replacement in terms of the rheology, hydration and strength development was discussed.

## 2. Materials and methods

### 2.1. Materials and mixture

The chemical composition of the ordinary Portland cement P II 42.5 used in this study is listed in Table 1. The RP was obtained by grinding the crushed cement paste specimens after hydration for 120 days. The cement used for the preparation of RP was also the ordinary Portland cement P II 42.5. CRP was produced by placing the RP in a carbonation chamber at a temperature of  $20 \pm 2^\circ\text{C}$ , relative humidity of  $70 \pm 5\%$ ,  $\text{CO}_2$  concentration of  $20 \pm 3\%$  and pressure of 0.1 MPa for 12 days. The particle size distributions of PC, RP and CRP were determined by Mastersizer 2000 (Malvern instruments Ltd. UK), as shown in Fig. 1. It can be seen that the particle size of CRP is larger than that of RP. It is due to that in the carbonation process the silica gel generated from the carbonation made some particles stick together to form a big particle, and the new phase formed at the surface of RP also enlarged the particle-size. The mixture compositions of pure cement paste and the cement paste blended with RP and CRP are given in Table 2. The mixtures prepared for the microscopic observation of the crack propagation are denoted as R1 and C1, respectively. The mixtures prepared for morphology analysis of the hydration products on the surfaces of RP and CRP are referred to R2 and C2, respectively. In order to make the RP or CRP particles more discoverable in the morphological investigation of hydration products on their surface, the content of RP or CRP is set as 40% instead of 30%.

### 2.2. X-ray diffraction analysis (XRD)

XRD analysis was performed to study the phase composition of RP and CRP using a Bruker D max/RB diffractometer (Billerica, MA, USA) applying  $\text{CuK}_\alpha$  radiation ( $\lambda = 1.5418 \text{ \AA}$ ). The samples were scanned from  $2\theta = 5^\circ$  to  $2\theta = 80^\circ$  with a step size of  $0.02^\circ$ .

### 2.3. Thermogravimetric analysis (TGA)

The thermogravimetric data of the RP and CRP were collected using PerkinElmer TGA4000 with a heating rate of  $10^\circ\text{C}/\text{min}$  from  $30^\circ\text{C}$  to  $800^\circ\text{C}$ . A  $\text{N}_2$ -gas flowing atmosphere at 1.5 bar was used in this measurement.



### 2.4. NMR measurement

NMR measurements were performed using a VNMRs spectrometer (Varian Inc. USA) operating at a field strength of 14.09 T (600 MHz) with a 54 mm bore. The  $^{29}\text{Si}$  operating frequency was 119.17 MHz.

**Table 1**

Chemical compositions of P II 42.5 ordinary Portland cement (wt%).

Components	$\text{SiO}_2$	$\text{Al}_2\text{O}_3$	$\text{Fe}_2\text{O}_3$	CaO	MgO	$\text{K}_2\text{O}$	$\text{SO}_3$	Loss
Cement	20.07	5.72	2.78	63.06	3.17	0.77	2.74	2.73

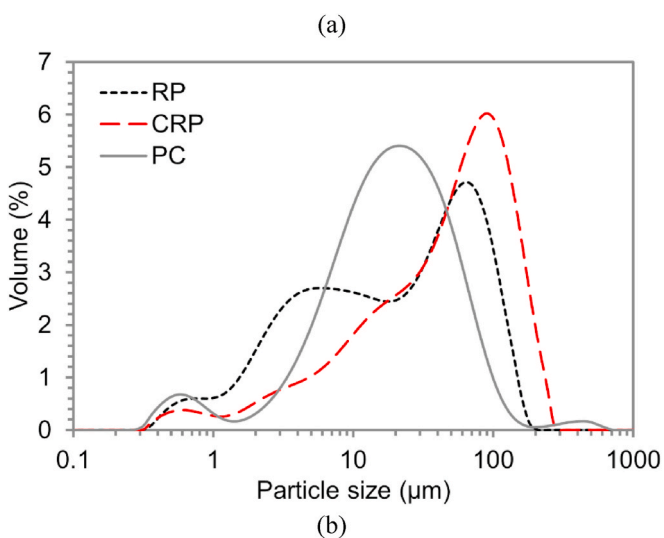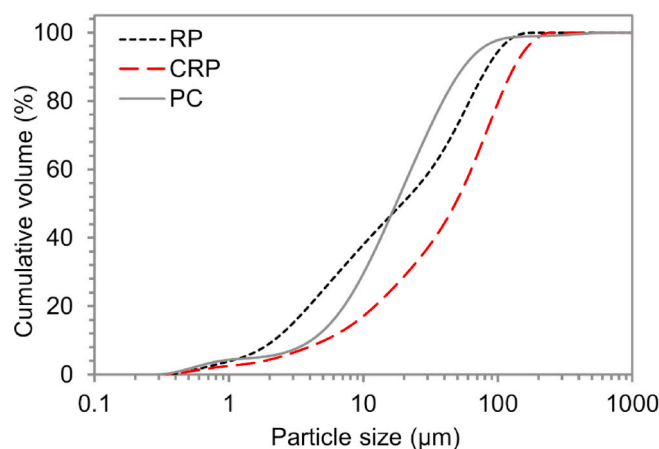

**Fig. 1.** Cumulative distribution (a) and volume distribution (b) of particle size of cement, RP and CRP.

**Table 2**

Mixture compositions of blended cement paste.

Mixture	Cement (%)	RP (%)	CRP (%)	w/b
PC	100	–	–	0.4
R1	70	30	–	0.4
C1	70	–	30	0.4
R2	60	40	–	0.4
C2	60	–	40	0.4

Powder samples were packed into zirconium dioxide standard double bearing 7.5-mm rotors. The spinning frequency for all samples was 6000 Hz and was stabilized to  $\pm 3$  Hz using an internal stabilization device. The samples were collected for 2048 scans, which consist of a single pulse of width  $3.6 \mu\text{s}$  followed by a relaxation delay of 3 s. All  $^{29}\text{Si}$  chemical shift data were externally referenced to the TMS resonance.

### 2.5. Zeta potential test

To characterize the surface chemical properties of RP and CRP, zeta

potential measurement was performed to study the interactions between the particle's surface and  $\text{Ca}^{2+}$  in a model solution. With these interactions, the chemical properties of the surface can be characterized [25]. The Malvern Zetasizer Nano (Malvern Instruments Ltd. UK) was used in this study.

$\text{Ca}^{2+}$  is an important ion in the pore solution of cement paste. The interactions of  $\text{Ca}^{2+}$  with the particle's surface play a key role in the C-S-H nucleation and growth on the particles [25,27,29]. Therefore,  $\text{Ca}(\text{OH})_2$  was used to prepare the model solutions. In this experiment, 12 model solutions with different  $\text{Ca}^{2+}$  concentrations from 0.2 to 20 mmol/l were designed to evaluate the effect of  $\text{Ca}^{2+}$  on particle surface potential.

## 2.6. SEM analysis

Morphological investigation of hydration products at a very early age and crack characterization of cement paste at a late age was performed using Phenom ProX electron microscope (Phenom, FEI). Sample preparations for the morphological investigation are as follows:

- 1) The mixtures for investigating the hydrates on the surface of RP and CRP are shown in Table 2 (R2 and C2). At each required time (15min, 1, 4 and 7 h), about 1 g of the cement paste with RP or CRP was taken to stop hydration by using anhydrous alcohol. The samples in the alcohol were filtered and dried in a 35 °C oven for 12 h. The dried powder was then collected for the morphological investigation.
- 2) The mixtures for crack characterization are shown in Table 2 (R1 and C1). The samples were prepared according to the standard procedure of ASTM C305 [30]. At the ages of 7, 28, 96 and 120 d, the samples were loaded under compression stress of 80% of the peak load for 5 s. After loading, the specimens were taken to stop hydration using anhydrous alcohol. Then, the samples were submerged in an epoxy resin. After epoxy resin hardened, the samples were ground and polished for the morphological investigation of cracks propagation.

## 2.7. Rheological measurement

A rheometer (Brookfield DV3T model) with a coaxial cylinder geometry was used to test the rheological properties of the cement paste blended with RP and CRP. The mixtures for this test are shown in Table 2 (R1 and C1). An 80 s pre-shear at  $100 \text{ s}^{-1}$  followed by 60 s of rest was involved before the test. Afterward, the strain rate was increased gradually over 60 s to a final value of  $100 \text{ s}^{-1}$ . Bingham-Plastic model was applied to fit the shear stress versus strain-rate curves.

## 3. Results and discussion

### 3.1. Material characterization

#### 3.1.1. XRD analysis

XRD data is shown in Fig. 2. As can be seen, RP and CRP have different XRD patterns. The crystalline phase of RP is mainly CH and ettringite (Aft). The diffraction peak of  $\text{C}_2\text{S}$  and  $\text{C}_3\text{S}$  also shows in RP indicating unhydrated cement remained in RP. The main crystalline phase in CRP is  $\text{CaCO}_3$ . This indicates that most of CH, Aft,  $\text{C}_2\text{S}$  and  $\text{C}_3\text{S}$  in RP had reacted with  $\text{CO}_2$  to form  $\text{CaCO}_3$  during carbonation.

#### 3.1.2. TGA analysis

The thermal decomposition of RP and CRP obtained by TGA-DTG analyses is shown in Fig. 3. The TG/DTG spectra of RP shows a weight loss between 100 °C and 300 °C, corresponding to the dehydration of C-S-H and Aft. The steep weight loss between 400 °C and 500 °C refers to the dehydroxylation of CH. A small weight loss after 600 °C from the decarbonation of  $\text{CaCO}_3$  indicates the presence of the natural carbonation in RP. Compared with RP, the TG/DTG spectra of CRP shows a steep weight loss after 550 °C and only a small amount of weight loss

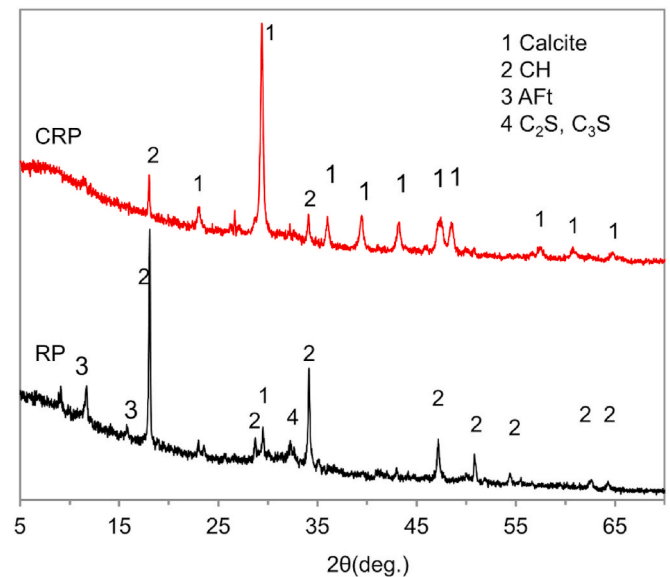


Fig. 2. XRD patterns of RP and CRP.

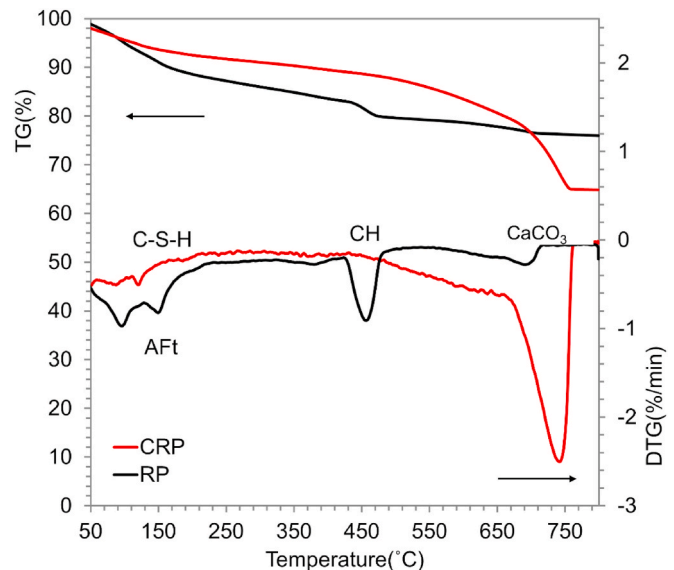


Fig. 3. Thermal decomposition of RP and CRP by TGA-DTG analyses.

before 550 °C. These results are matched with the findings in XRD analysis. The calculation based on the TGA-DTG results indicates that about 12.46% CH and 8.30%  $\text{CaCO}_3$  existed in RP, 4.03% CH and 52.30%  $\text{CaCO}_3$  were present in CRP.

#### 3.1.3. $^{29}\text{Si}$ NMR analysis

The  $^{29}\text{Si}$  MAS NMR spectra of RP and CRP is presented in Fig. 4. In silicate minerals,  $\text{Q}^n$  ( $n = 0, 1, 2, 3, 4$ ) is commonly used to represent the chemical environment of  $^{29}\text{Si}$  atoms, and  $n$  represents the number of shared oxygen atoms in each silicon-oxygen tetrahedron. The range of chemical shifts indicates different polymerization states of Si [18, 31–34]. Polymerization state of Si corresponds to different chemical displacement intervals. Five polymerization states of Si in silicon-oxygen tetrahedron can be characterized by  $^{29}\text{Si}$  NMR test. The change from  $\text{Q}^0$  to  $\text{Q}^4$  indicates the increasing degree of polymerization of silicon-oxygen tetrahedron.  $\text{Q}^0$  refers to an isolated silica tetrahedron commonly found in cement clinkers.  $\text{Q}^1$  denotes a silicon-oxygen tetrahedron connected to only one  $[\text{SiO}_4]$ , which originates from the C-S-H phase.  $\text{Q}^2$  refers to

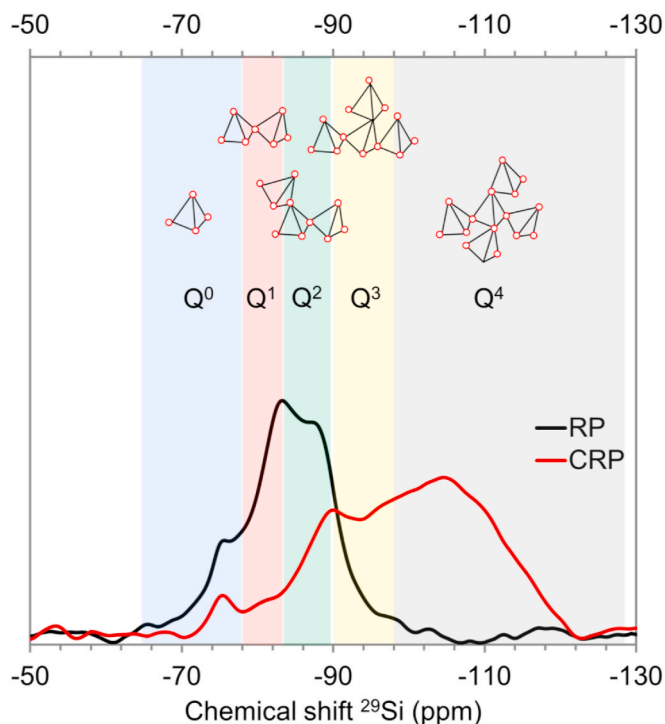


Fig. 4. <sup>29</sup>Si MAS NMR spectra for RP and CRP.

the silicon-oxygen tetrahedron connected with two silicon-oxygen tetrahedra, mainly from cement hydration to form C-S-H. Q<sup>3</sup> represents the silicon-oxygen tetrahedron linked to the other three silicon-oxygen tetrahedra, and Q<sup>4</sup> refers to the structure of a three-dimensional network with four silicon-oxygen tetrahedra. Q<sup>3</sup> and Q<sup>4</sup> mainly exist in silica gel [35,36].

As can be seen from Fig. 4, the <sup>29</sup>Si MAS NMR spectra of RP shows the characteristic peaks of RP with the resonance of Q<sup>0</sup> (-74.9 ppm), Q<sup>1</sup> (-82.9 ppm) and Q<sup>2</sup> (-87.8 ppm). It indicates that Si in RP mainly comes from unhydrated cement (Q<sup>0</sup>) and C-S-H (Q<sup>1</sup> and Q<sup>2</sup>). The main characteristic peaks of CRP shift to Q<sup>3</sup> (-90.5 ppm) and Q<sup>4</sup> (-104.5 ppm) corresponding to the silica gel. It is also noted that a small shoulder at Q<sup>0</sup> (-74.9 ppm) exists in CRP, which is attributed to the insufficient carbonatization of recycled cement paste powder. The <sup>29</sup>Si MAS NMR results are strongly matched with the TGA-DTG results, as well as XRD analysis. Fig. 4 reveals that the carbonation decreased the amount of unhydrous phases (Q<sup>0</sup>) and C-S-H (Q<sup>1</sup> and Q<sup>2</sup>), and increased the amount of silica gel (Q<sup>3</sup> and Q<sup>4</sup>). It indicates that most of the C-S-H and anhydrous phases in RP had reacted with CO<sub>2</sub> to form silica gel.

### 3.1.4. Morphology analysis

Morphology of RP and CRP was observed by SEM, as shown in Fig. 5. As can be seen, the surface of RP and CRP is not significantly different. The CaCO<sub>3</sub> resulted from the carbonation in CRP is not observed from the SEM figures. Another product of carbonation, silica gel, is also hard to be distinguished since it has no clear shape and structure as a non-crystallized and amorphous material. It is likely that the products covered the surface of the CRP particle are silica gel.

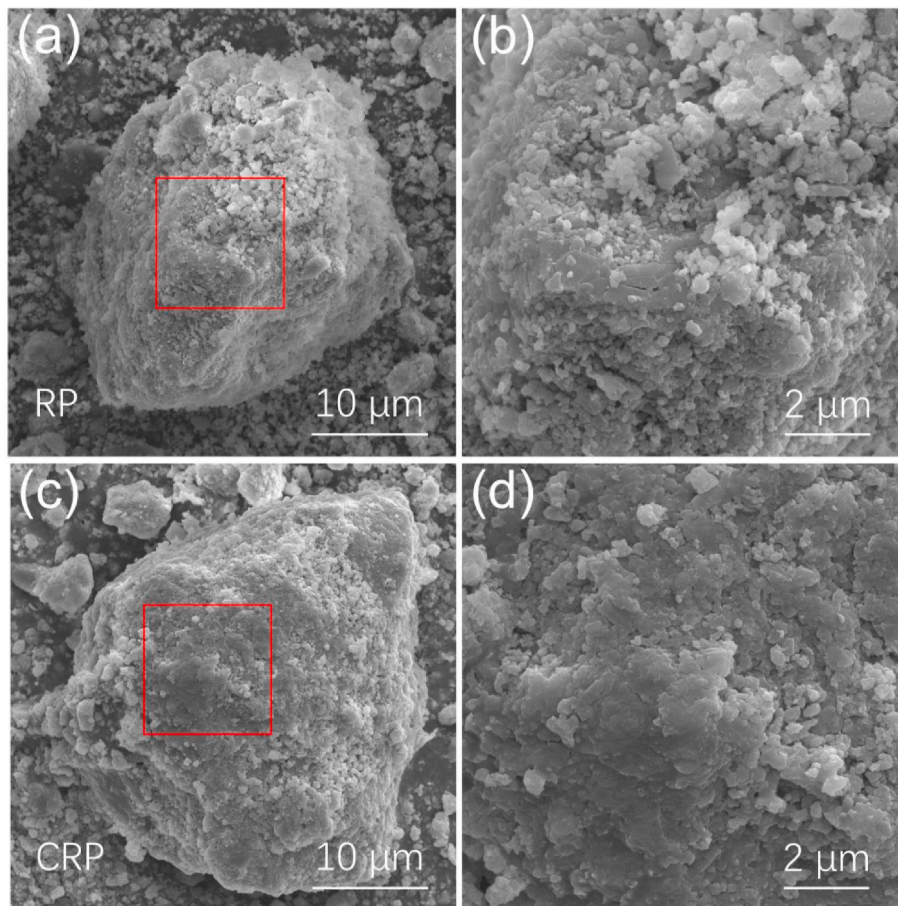


Fig. 5. Morphology of RP (a, b) and CRP (c, d).

### 3.1.5. Surface chemical properties analysis

Zeta potential test was performed to characterize the surface charge properties of RP and CRP, which are correlated with the surface chemical properties. The zeta potential of RP and CRP, together with the reference particles of limestone powder (LP), quartz powder and C-S-H particles tested by Helene et al. [37] in Ca(OH)<sub>2</sub> solutions is shown in Fig. 6. As can be seen, compared with quartz and CRP, RP has a higher potential at low Ca<sup>2+</sup> concentration (<2 mmol/L) because of the dissolution of Ca(OH)<sub>2</sub> on its surface. When the concentration of Ca<sup>2+</sup> exceeds 2 mmol/L, the RP and CRP have similar zeta potential as quartz powder and C-S-H. It indicates that the surface chemical properties of RP and CRP are similar to quartz and C-S-H, both of which are rich in silica phase. This is not consistent with the expectation that CRP is rich in calcium carbonate and that its surface potential should be similar to that of limestone particles with much higher zeta potential. The silica phase on the surface of CRP is thus believed to be a silica gel resulted from a carbonation reaction rather than CaCO<sub>3</sub>. The generated CaCO<sub>3</sub> was likely wrapped within the silica gel layer instead of exposed.

### 3.2. Rheology of blended cement paste

Fig. 7 shows the shear stress versus a shear rate of pure cement paste and cement paste blended with 30% RP and CRP. It can be seen that the shear stress of CRP-cement paste is much higher compared with RP-cement paste through all tested shear rate. Considering that the surface charge properties of CRP and RP are similar, which play an important role in the rheological properties of cement paste, the filler with higher surface area and smaller particle size should have a higher shear stress. The particle size of CRP (D<sub>50</sub>: 55.41 μm) is significantly larger than that of CR (D<sub>50</sub>: 22.23 μm), and the specific surface areas of CRP (0.56 m<sup>2</sup>/g) is much less than that of CR (0.86 m<sup>2</sup>/g). However, the shear stress of CRP-cement paste is significantly higher than that of RP-cement paste. It is possible due to RP has a favorable particle size distribution (PSD). The small particle in RP can fill up the voids and make they RP-cement paste more compact. Consequently, pore water can be released and the paste system would become more flowable.

However, the packing effect on the rheological properties is not that significant, as the smaller particle with a larger surface, on the other hand, needs more water to keep paste flow. It is believed that the silica gel on the surface of CRP plays a key role in the rheological properties of CRP-cement paste. As mentioned, the CRP's surface was covered with the silica gel. As is well known, the silica gel has a strong affinity for H<sub>2</sub>O. As a result, a larger amount of water was absorbed on CRP's surface. It makes CRP-cement paste has much higher shear stress despite that it has a larger particle size and lower surface area.

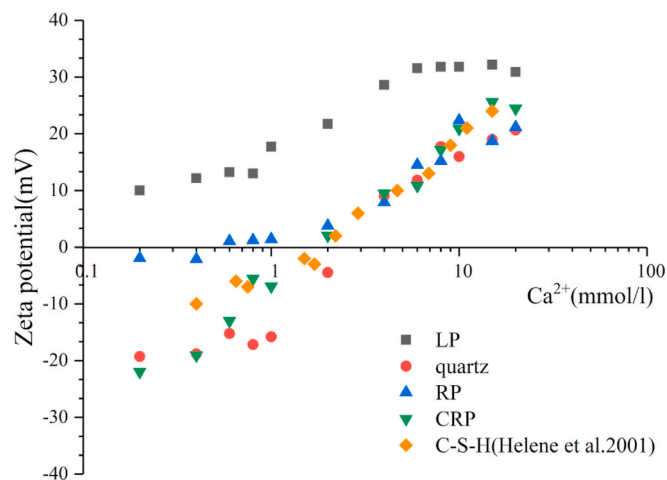


Fig. 6. The zeta potential of RP and CRP as a function of Ca<sup>2+</sup> concentration in Ca(OH)<sub>2</sub> solution.


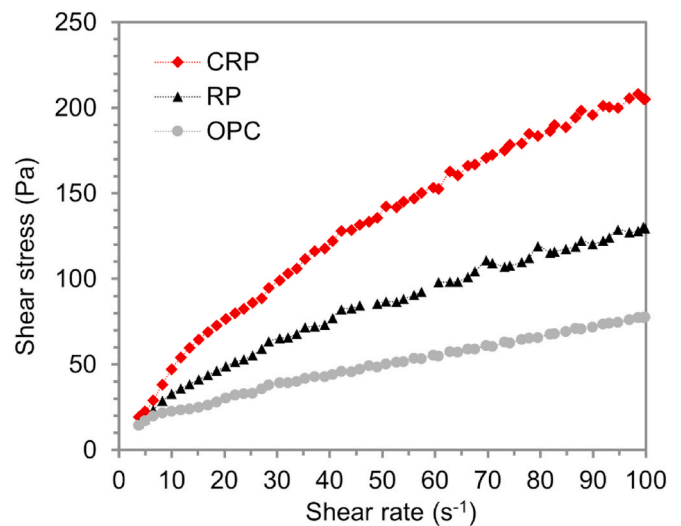


Fig. 7. Shear stress vs shear rate experimental data for cement paste and cement paste blended with 30% RP and 30% CRP.

The performance of carbonated cement paste powder seems contrary to the performance of carbonated recycled aggregate on the rheology. It was reported that the mortar or concrete with carbonated recycled aggregate has better flowability than that with uncarbonated recycled aggregate, due to carbonation reduces the porosity and thus water absorption of the recycled aggregate [11,22,38]. This can be explained by the fact that the recycled cement paste powder has a much larger surface area than the recycled aggregate. The surface area of recycled cement paste powder is around 1 m<sup>2</sup>/g, while the surface area of recycled aggregate is only about 0.001 m<sup>2</sup>/g. The effect of silica gel of carbonated recycled aggregate on the water absorption is subtle. While the water absorption reduced because of the decrease of porosity in the carbonated recycled aggregate is significant. Therefore, carbonated recycled cement paste powder has a poor performance in flowability, whereas the carbonation of recycled aggregate enhances the performance in terms of flowability.

### 3.3. Morphology of hydrates on the surface of RP and CRP

The morphology of the hydrates on the surface of RP and CRP particles at different hydration time is illustrated in Fig. 8. Fig. 8a and b (local enlarged image) show the surface of RP after hydration for 15 min. Fig. 8c and d (local enlarged image) present the surface of CRP after hydration for 15 min. At that time, there is no difference between the two particles and no hydration products are observed on their surface. After 1 h hydration, as can be seen from Fig. 8e and f there are still no hydration products on the surface of RP. Whereas, there are many granular substances on the surface of CRP, which are probably C-S-H nuclei, as shown in Fig. 8g and h. After 4 h of hydration, there are still no hydration products on the surface of RP, as shown in Fig. 8i and j, while the granular nuclei on the surface of CRP grow into acicular C-S-H, as shown in Fig. 8k and l. After hydration for 7 h, a bit of hydration product appears on the surface of RP particles (Fig. 8m and n), while the C-S-H further growth on the surface of CRP. This C-S-H gel presents a fine needle-like appearance and is perpendicular to the particle surface, as shown in Fig. 8o and p. Moreover, as can be seen from Fig. 8o the CRP's surface is covered by the perpendicular needle C-S-H. In the resulted from Ref. [25], it is concluded that the strong chemical interactions between CaCO<sub>3</sub> and C-S-H enable the C-S-H to grow perpendicularly and uniformly on its surface. Therefore, it is believed that there is a CaCO<sub>3</sub> layer underneath the silica gel layer covered on the surface of CRP. When the CRP and cement particles mixed with water, the silica gel layer dissolves and reacts in the solution. It makes CaCO<sub>3</sub> exposed and

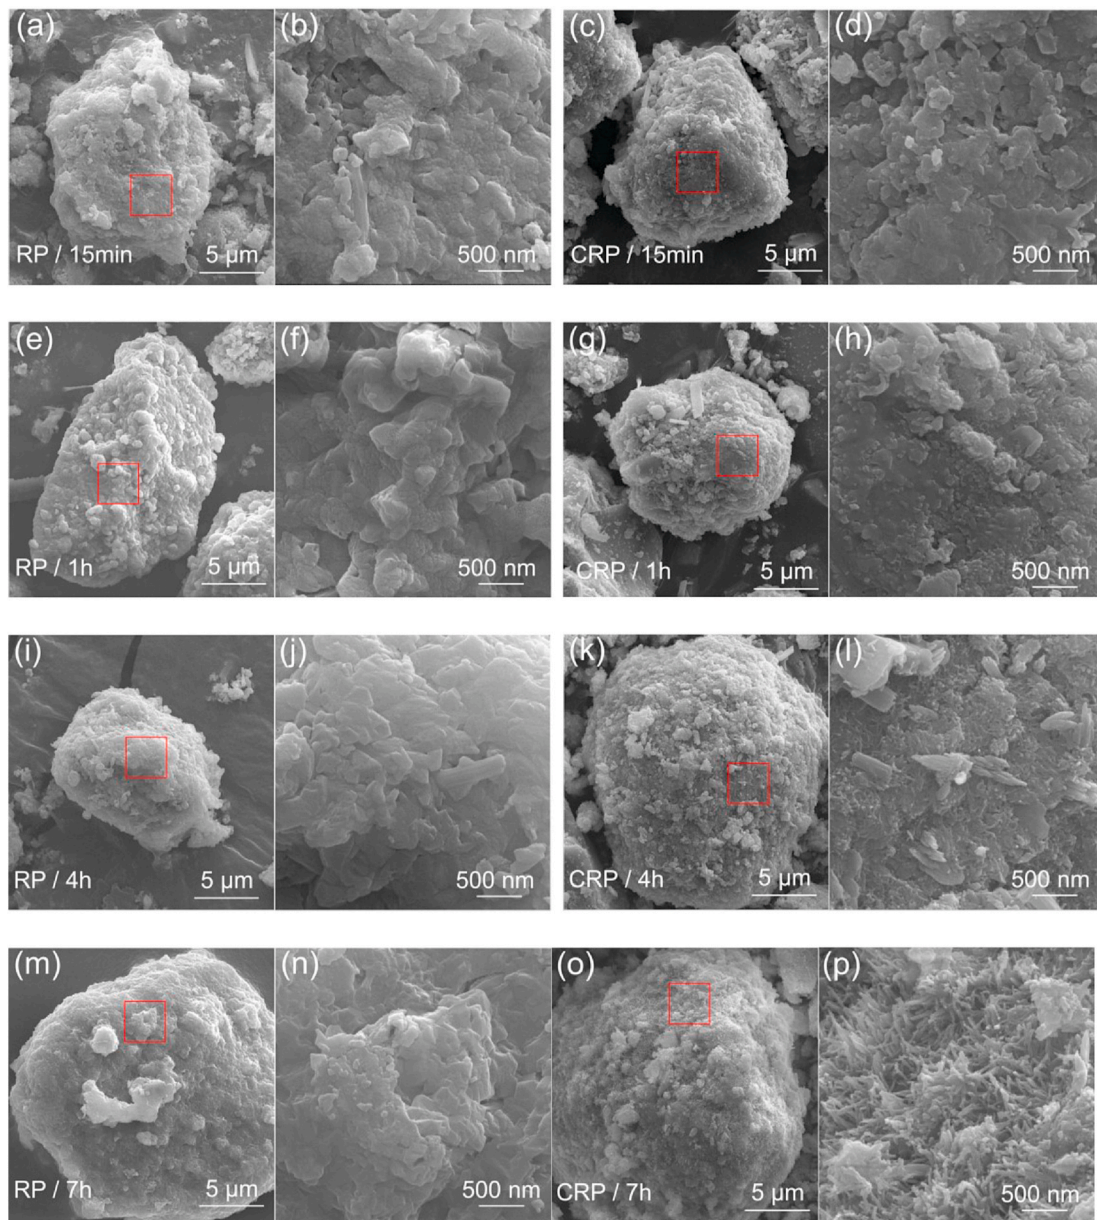

**Fig. 8.** Morphology of hydration products on the surface of RP particle at 15min (a, b), 1 h (e, f), 4 h (i, j) and 7 h (m, n), and CRP particle at 15min (c, d), 1 h (g, h), 4 h (k, l) and 7 h (o, p).


provides a nucleation site for C–S–H.

### 3.4. Crack characterization

The differences in crack propagation originate from the interface properties. According to the previous studies [39–41], the crack propagations in the cement paste are governed by weak interfaces and local stress distribution. The weak interface has a high probability to crack. To understand the effect of carbonation treatment of recycled hardened cement paste powder on the strength development of cement paste, the bond strength between RP or CRP and hydration products was evaluated by characterizing the crack propagation in the cement pastes subjected to compressive loading. Based on the microscopic observation by SEM, crack propagations in cement pastes at the curing ages of 7, 28, 96 and 120 d are illustrated in Figs. 9–12, respectively. The red boxes in these figures are used to mark the crack propagated alongside the RP or CRP particles corresponding to the weak bonding; The yellow boxes are used to mark the crack passed through the RP or CRP particles.

Figs. 9a, 10a and 11a and 12a show the cracks in the cement paste with 30% RP at the curing age of 7, 28, 96 and 120 d, respectively. As can be seen from these figures, the number of cracks tend to propagate along with the RP particles decreases as increasing curing age but not obvious. Moreover, the cracks propagating around the RP particles can be seen regardless of curing age. It indicates that the strength of the interface between matrix and RP particle is weak and further hydration cannot enhance the interface even though the overall strength of the paste increased.

Whereas, even at the curing age of 7 d, there are few cracks propagated along with the CRP particles (Fig. 9b). At the curing age of 28, 96 and 120 d, it is hard to find crack propagated through the interface between matrix and CRP particles, as shown in Figs. 10b, 11b and 12b. The cracks in the cement paste have an increasing tendency to propagate through the CRP particle as increasing curing age. It illustrates that CRP has a much stronger interface with hydration products than RP.

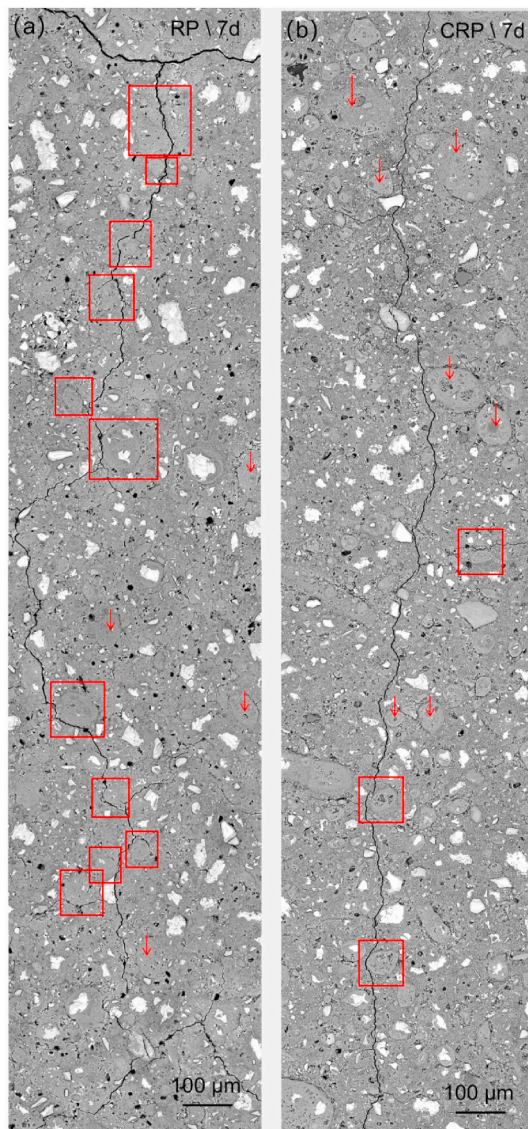


**Fig. 9.** Crack propagation in cement paste incorporating 30% RP (a), and 30% CRP (b) at 7 days (The red boxes mark the crack propagated alongside the RP or CRP particles and the red arrows indicate the RP or CRP particles). (For interpretation of the references to colour in this figure legend, the reader is referred to the Web version of this article.)

#### 4. Discussion

**Fig. 13** shows an overview of the effect of the carbonation treatment on the performance of the recycled cement paste powder as a cement replacement in terms of the rheology, hydration and strength development:

- (a) **Materials characterization.** The analysis of XRD, TGA and NMR showed that during the carbonation, most of the C–S–H, CH and anhydrous phases in RP had reacted with  $\text{CO}_2$  to form  $\text{CaCO}_3$  and silica gel. Besides, the zeta potential measurement indicated that the surface of CRP was covered by silica-rich materials. It is supposed to be the silica gel resulted from carbonation reactions of  $\text{CO}_2$  with CH and C–S–H gel. Furthermore, based on the observation of the C–S–H nucleation and growth on CRP's surface, it showed that the CRP's surface was covered by the perpendicular needle C–S–H after hydration for 7 h (Fig. 8o). It is indicated that underneath of the silica gel is  $\text{CaCO}_3$  since the

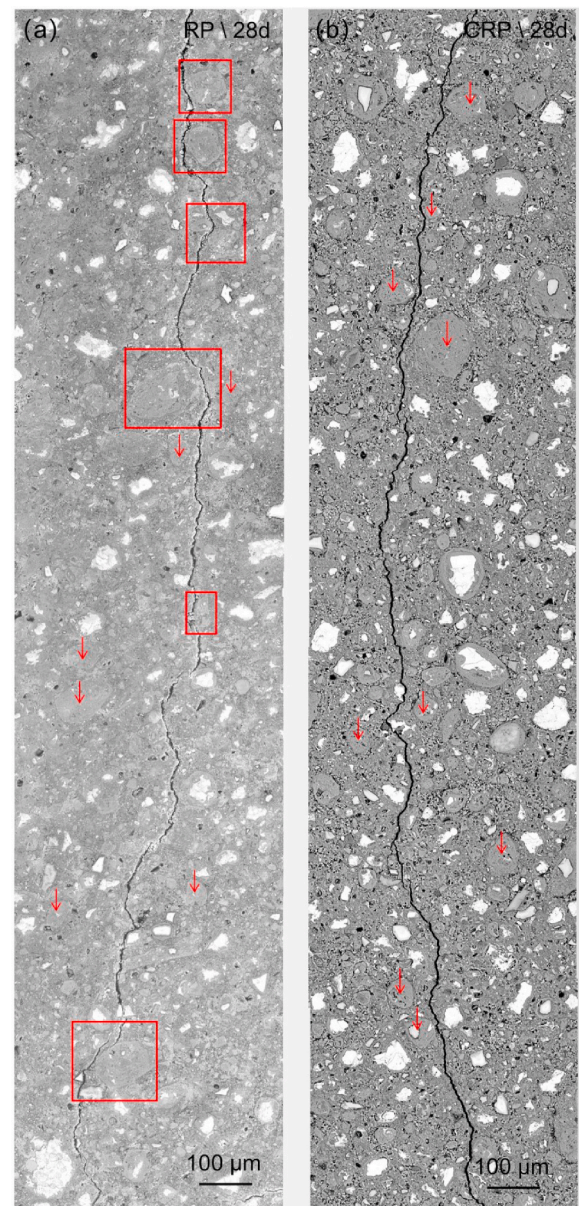


**Fig. 10.** Crack propagation in cement paste incorporating 30% RP (a), and 30% CRP (b) at 28 days (The red boxes mark the crack propagated alongside the RP or CRP particles and the red arrows indicate the RP or CRP particles). (For interpretation of the references to colour in this figure legend, the reader is referred to the Web version of this article.)


strong chemical interactions between  $\text{CaCO}_3$  and C–S–H enable the C–S–H to grow perpendicularly and uniformly on its surface. It is concluded that in this investigation the carbonated recycled cement paste particle was covered by a large amount of silica gel, underneath of it is  $\text{CaCO}_3$ , as shown in **Fig. 13a**. This conclusion is the key to understand the effect of carbonation treatment on the performance of the recycled cement paste powder as a cement replacement. As mentioned, the surface chemical properties of the particles determine the interactions with  $\text{H}_2\text{O}$  and ions in the solution of cement paste. These interactions play a crucial role in the C–S–H nucleation and growth on the particles [25], the strength of the interface between the particles and hydrates [27] and rheology of the blended cement paste [28].

- (b) **Effect on rheology.** From the materials characterization, it is concluded that the surface of CRP was covered with a layer of amorphous silica gel. As is well known, the silica gel has a strong



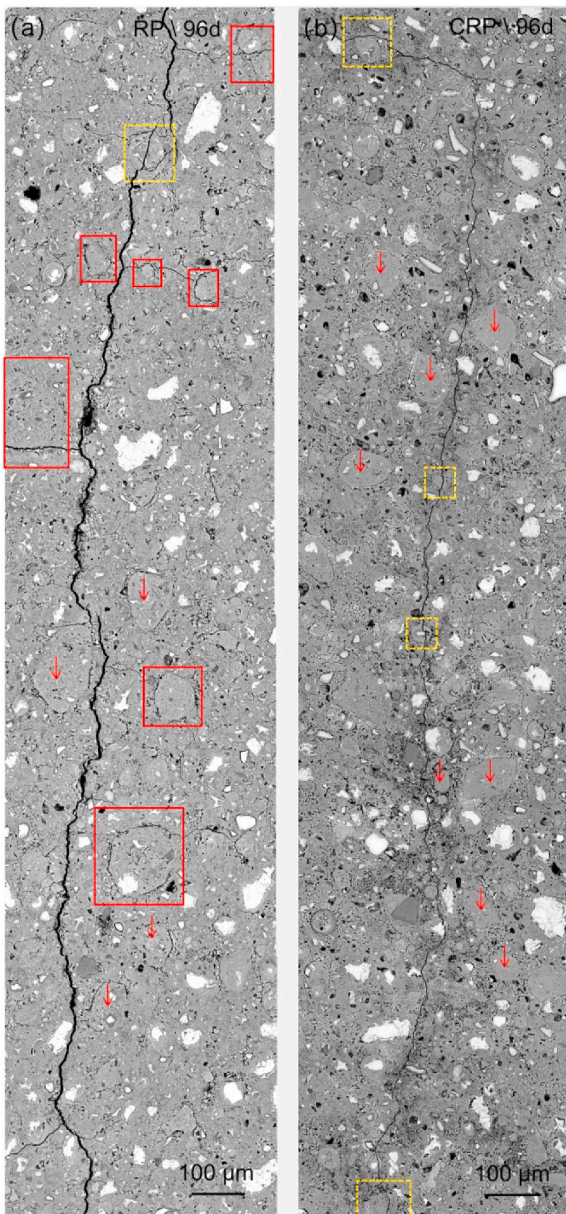

**Fig. 11.** Crack propagation in cement paste incorporating 30% RP (a), and 30% CRP (b) at 96 days (The red boxes mark the crack propagated alongside the RP or CRP particles, the yellow boxes refer to the crack passed through the RP or CRP particles, and the red arrows indicate the RP or CRP particles). (For interpretation of the references to colour in this figure legend, the reader is referred to the Web version of this article.)

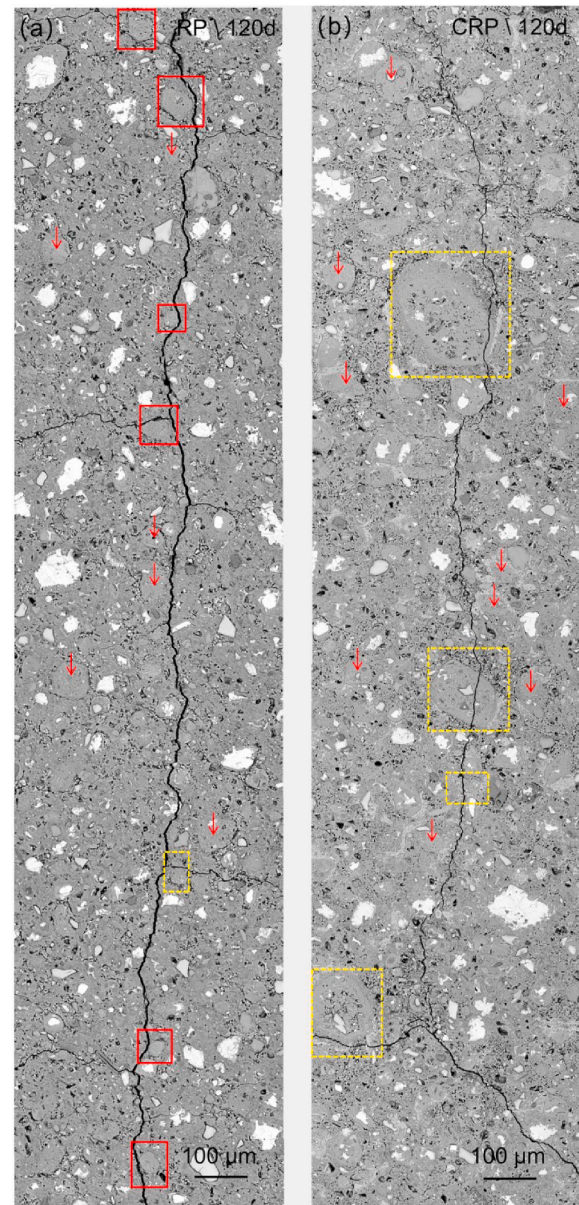

**Fig. 12.** Crack propagation in cement paste incorporating 30% RP (a), and 30% CRP (b) at 120 days (The red boxes mark the crack propagated alongside the RP or CRP particles, the yellow boxes refer to the crack passed through the RP or CRP particles, and the red arrows indicate the RP or CRP particles). (For interpretation of the references to colour in this figure legend, the reader is referred to the Web version of this article.)

affinity for  $H_2O$ . As a result, once the CRP mixed with water, a larger amount of water was absorbed on the surface of CRP particles, as shown in Fig. 13b. It is adverse to the flowability of the blended cement paste. Therefore, CRP-cement paste has much higher shear stress than the RP-cement paste despite that CRP has a larger particle size and lower surface area.

- (c) Effect on hydration. The morphology of the hydrates on the surface of RP and CRP particles (Fig. 8) indicates that during the early hydration of cement, the silica gel layer on the surface of CRP particles dissolved and made  $CaCO_3$  exposed to provide a nucleation site for C–S–H. The surface of  $CaCO_3$  possesses a very high affinity for  $Ca^{2+}$ . As demonstrated in the previous study [25], the driving force of adsorbing  $Ca^{2+}$  ions on the  $CaCO_3$  surface is a strong acid-base interaction. This chemical

interaction facilitates the nucleation of C–S–H nuclei and stabilizes the C–S–H phase. As a result, the C–S–H grew uniformly and perpendicularly on the surface, as shown in Fig. 13c. In the case of RP particles, their surface is covered by the C–S–H phase since the CH on the surface dissolved during the hydration. As shown in the previous study [25], the C–S–H has no affinity for  $Ca^{2+}$ . The driving force of adsorbing  $Ca^{2+}$  ions on the C–S–H surface is the relatively weak electrostatic interaction. Consequently, less  $Ca^{2+}$  ions are adsorbed onto the surfaces of RP. It made the C–S–H hard to nucleate and grow on the surface of RP, so few C–S–H nuclei can be observed in Fig. 8.

- (d) Effect on strength development. In general, the surface chemical properties of particles have a strong correlation with the interface bonding strength. Chemically adsorbed  $Ca^{2+}$  onto the  $CaCO_3$  surface results in the formation of a very strong bond between

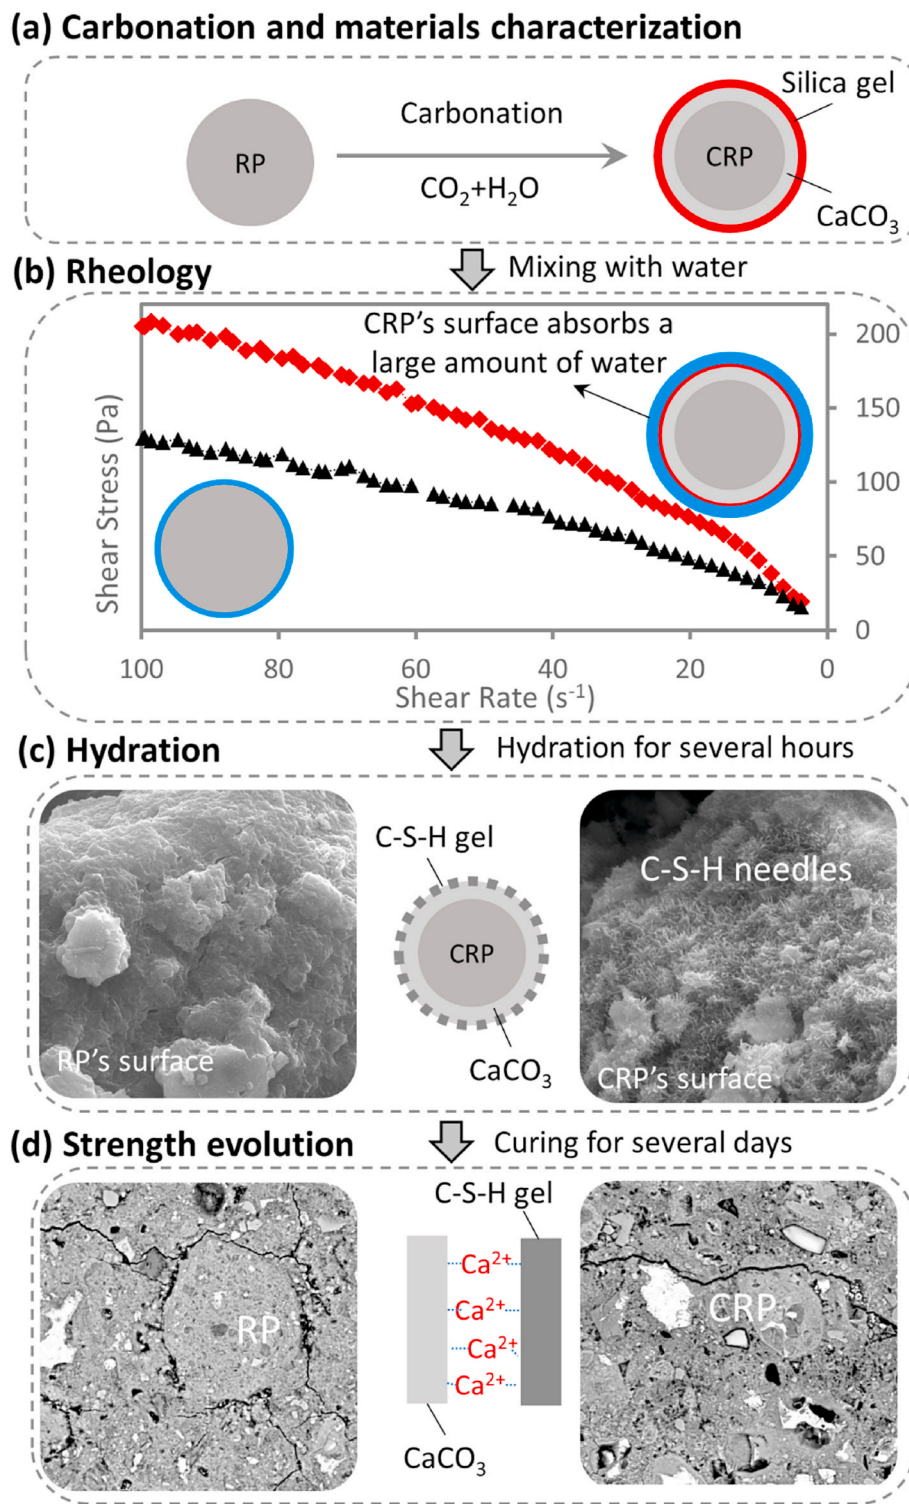


Fig. 13. Schematic diagram of the effect of carbonation treatment of recycled cement paste powder on the rheology, hydration and strength development.

CaCO<sub>3</sub> and C-S-H, while C-S-H particle is bonded to silica particle by relatively weak electrostatic forces [27]. The surface of the CRP turned into a calcite phase after hydration for several hours, while the surface of the RP was still silica phase (C-S-H). Therefore, the interface between CRP and hydrates was much stronger than that between RP and hydrates. The silica gel on the surface of CRP reacts with CH to form C-S-H, as inferred from Fig. 8, leading to a denser interface between CRP and matrix, also improved the interface strength.

### 5. Conclusions

In this paper, the surface properties of the carbonated recycled cement paste powder were elucidated. The effect of carbonation treatment on the performance of the recycled cement paste powder as a cement replacement in terms of the rheology, hydration and strength development was investigated. Based on the results obtained in this study, the conclusions can be drawn as follows:

1. During the carbonation, the CRP's surface is believed to be covered by a layer of amorphous silica gel. The generated  $\text{CaCO}_3$  was wrapped by the silica gel and seldom exposed.
2. CRP-cement paste showed a higher flowability than the RP-cement paste despite that CRP has a larger particle size and lower surface area. It is due to that the silica gel on the surface of CRP has a strong affinity for  $\text{H}_2\text{O}$ .
3. During the very early hydration, the C-S-H grew uniformly and perpendicularly on the surface of CRP, but there were few hydration products on the surface of RP. This is because after silica gel on the surface dissolved  $\text{CaCO}_3$  exposed which facilitated nucleation of C-S-H.
4. CRP has a much stronger interface with hydration products than RP, due to the stronger bond formed between  $\text{CaCO}_3$  and C-S-H, and increased C-S-H resulted from the reactions of silica gel with CH at the interface.

### Declaration of competing interest

The authors declare that they have no known competing financial interests or personal relationships that could have appeared to influence the work reported in this paper.

### Acknowledgments

The authors thank the Natural Science Foundation of Guangdong Province (Grant No. 2019A1515110799) and the Guangzhou Municipal Science and Technology Project (Grant No. 201904010290) for funding this work.

### References

- [1] i.L.B. Topçu, N.F. Günçan, Using waste concrete as aggregate, *Cement Concr. Res.* 25 (7) (1995) 1385–1390.
- [2] C.S. Poon, Z.H. Shui, L. Lam, H. Fok, S.C. Kou, Influence of moisture states of natural and recycled aggregates on the slump and compressive strength of concrete, *Cement Concr. Res.* 34 (1) (2004) 31–36.
- [3] Z.H. Duan, C.S. Poon, Properties of recycled aggregate concrete made with recycled aggregates with different amounts of old adhered mortars, *Mater. Des.* 58 (2014) 19–29.
- [4] J. Xiao, J. Li, C. Zhang, Mechanical properties of recycled aggregate concrete under uniaxial loading, *Cement Concr. Res.* 35 (6) (2005) 1187–1194.
- [5] C. Shi, Y. Li, J. Zhang, W. Li, L. Chong, Z. Xie, Performance enhancement of recycled concrete aggregate—a review, *J. Clean. Prod.* 112 (2016) 466–472.
- [6] D. Xuan, B. Zhan, C.S. Poon, Assessment of mechanical properties of concrete incorporating carbonated recycled concrete aggregates, *Cement Concr. Compos.* 65 (2016) 67–74.
- [7] J. Zhang, C. Shi, Y. Li, X. Pan, C.-S. Poon, Z. Xie, Influence of carbonated recycled concrete aggregate on properties of cement mortar, *Construct. Build. Mater.* 98 (2015) 1–7.
- [8] B. Zhan, C. Poon, C. Shi, CO<sub>2</sub> curing for improving the properties of concrete blocks containing recycled aggregates, *Cement Concr. Compos.* 42 (2013) 1–8.
- [9] L. Li, C.S. Poon, J. Xiao, D. Xuan, Effect of carbonated recycled coarse aggregate on the dynamic compressive behavior of recycled aggregate concrete, *Construct. Build. Mater.* 151 (2017) 52–62.
- [10] B. Zhan, C.S. Poon, Q. Liu, S. Kou, C. Shi, Experimental study on CO<sub>2</sub> curing for enhancement of recycled aggregate properties, *Construct. Build. Mater.* 67 (2014) 3–7.
- [11] J. Zhang, C. Shi, Y. Li, X. Pan, C.-S. Poon, Z. Xie, Performance enhancement of recycled concrete aggregates through carbonation, *J. Mater. Civ. Eng.* 27 (11) (2015), 04015029.
- [12] M. Zajac, J. Skocek, P. Durdzinski, F. Bullerjahn, J. Skibsted, M.B. Haha, Effect of carbonated cement paste on composite cement hydration and performance, *Cement Concr. Res.* 134 (2020) 106090.
- [13] S. Kashaf-Haghighi, Y. Shao, S. Ghoshal, Mathematical modeling of CO<sub>2</sub> uptake by concrete during accelerated carbonation curing, *Cement Concr. Res.* 67 (2015) 1–10.
- [14] A. Morandea, M. Thiery, P. Dangla, Investigation of the carbonation mechanism of CH and CSH in terms of kinetics, microstructure changes and moisture properties, *Cement Concr. Res.* 56 (2014) 153–170.
- [15] B. Wu, G. Ye, Development of porosity of cement paste blended with supplementary cementitious materials after carbonation, *Construct. Build. Mater.* 145 (2017) 52–61.
- [16] B. Lu, C. Shi, J. Zhang, J. Wang, Effects of carbonated hardened cement paste powder on hydration and microstructure of Portland cement, *Construct. Build. Mater.* 186 (2018) 699–708.
- [17] Z. Šauman, Carbonization of porous concrete and its main binding components, *Cement Concr. Res.* 1 (6) (1971) 645–662.
- [18] T.F. Sevelsted, J. Skibsted, Carbonation of C-S-H and C-A-S-H samples studied by <sup>13</sup>C, <sup>27</sup>Al and <sup>29</sup>Si MAS NMR spectroscopy, *Cement Concr. Res.* 71 (2015) 56–65.
- [19] M. Zajac, J. Skibsted, J. Skocek, P. Durdzinski, F. Bullerjahn, M.B. Haha, Phase assemblage and microstructure of cement paste subjected to enforced, wet carbonation, *Cement Concr. Res.* 130 (2020) 105990.
- [20] M. Thiery, G. Villain, P. Dangla, G. Platret, Investigation of the carbonation front shape on cementitious materials: effects of the chemical kinetics, *Cement Concr. Res.* 37 (7) (2007) 1047–1058.
- [21] P.A. Slegers, P.G. Rouxhet, Carbonation of the hydration products of tricalcium silicate, *Cement Concr. Res.* 6 (3) (1976) 381–388.
- [22] L. Li, J. Xiao, D. Xuan, C.S. Poon, Effect of carbonation of modeled recycled coarse aggregate on the mechanical properties of modeled recycled aggregate concrete, *Cement Concr. Compos.* 89 (2018) 169–180.
- [23] C. Liang, B. Pan, Z. Ma, Z. He, Z. Duan, Utilization of CO<sub>2</sub> curing to enhance the properties of recycled aggregate and prepared concrete: a review, *Cement Concr. Compos.* 105 (2020) 103446.
- [24] J. Visser, Influence of the carbon dioxide concentration on the resistance to carbonation of concrete, *Construct. Build. Mater.* 67 (2014) 8–13.
- [25] X. Ouyang, D.A. Koleva, G. Ye, K. Van Breugel, Insights into the mechanisms of nucleation and growth of C-S-H on fillers, *Mater. Struct.* 50 (5) (2017) 213.
- [26] D. Hou, Z. Li, T. Zhao, P. Zhang, Water transport in the nano-pore of the calcium silicate phase: reactivity, structure and dynamics, *Physical Chemistry Chemical Physics* 17 (2) (2014) 1411–1423.
- [27] X. Ouyang, D.A. Koleva, G. Ye, K. van Breugel, Understanding the adhesion mechanisms between CSH and fillers, *Cement Concr. Res.* 100 (2017) 275–283.
- [28] D.P. Bentz, C.F. Ferraris, S.Z. Jones, D. Lootens, F. Zunino, Limestone and silica powder replacements for cement: early-age performance, *Cement Concr. Compos.* 78 (2017) 43–56.
- [29] K. Scrivener, A. Ouzia, P. Juilland, A.K. Mohamed, Advances in understanding cement hydration mechanisms, *Cement Concr. Res.* 124 (2019) 105823.
- [30] A. Standard, C305, Standard Practice for Mechanical Mixing of Hydraulic Cement Pastes and Mortars of Plastic Consistency, Annual book of ASTM standards, 2006.
- [31] S. Masse, H. Zanni, J. Lecourtier, J.-C. Roussel, A. Rivereau, <sup>29</sup>Si solid state NMR study of tricalcium silicate and cement hydration at high temperature, *Cement Concr. Res.* 23 (5) (1993) 1169–1177.
- [32] E. Pustovgar, R.P. Sangodkar, A.S. Andreev, M. Palacios, B.F. Chmelka, R.J. Flatt, J. B. d'Espinose de Lacaillerie, Understanding silicate hydration from quantitative analyses of hydrating tricalcium silicates, *Nat. Commun.* 7 (2016) 10952.
- [33] D. Hou, T. Li, P. Wang, Molecular Dynamics Study on the Structure and Dynamics of NaCl Solution Transport in the Nanometer Channel of CASH Gel, *ACS Sustainable Chemistry & Engineering*, 2018 accschemeng.8b02126.
- [34] H. Hou, J. Zhang, W. Pan, Y. Zhang, Z. Zhang, Nanoscale mechanism of ions immobilized by the geopolymer: a molecular dynamics study, *J. Nucl. Mater.* 528 (2020) 151841.
- [35] G.W. Groves, A. Brough, I.G. Richardson, C.M. Dobson, Progressive changes in the structure of hardened C3S cement pastes due to carbonation, *J. Am. Ceram. Soc.* 74 (11) (1991) 2891–2896.
- [36] Y. Ikeda, Y. Yasuike, M. Kumagai, Y.-Y. Park, M. Harada, H. Tomiyasu, Y. Takashima, <sup>29</sup>Si MAS NMR study on structural change of silicate anions with carbonation of synthetic 11Å tobermorite, *J. Ceram. Soc. Jpn.* 100 (1165) (1992) 1098–1102.
- [37] H. Viallis-Terrisse, A. Nonat, J.-C. Petit, Zeta-potential study of calcium silicate hydrates interacting with alkaline cations, *J. Colloid Interface Sci.* 244 (1) (2001) 58–65.
- [38] B.J. Zhan, D.X. Xuan, C.S. Poon, Enhancement of recycled aggregate properties by accelerated CO<sub>2</sub> curing coupled with limewater soaking process, *Cement Concr. Compos.* 89 (2018) 230–237.
- [39] M. Luković, E. Schlangen, G. Ye, Combined experimental and numerical study of fracture behaviour of cement paste at the microlevel, *Cement Concr. Res.* 73 (2015) 123–135, 0.
- [40] J.M. van Mier, Multi-scale interaction potentials (F –r) for describing fracture of brittle disordered materials like cement and concrete, *Int. J. Fract.* 143 (1) (2007) 41–78.
- [41] X. Ouyang, G. Ye, K. van Breugel, Experimental and numerical evaluation of mechanical properties of interface between filler and hydration products, *Construct. Build. Mater.* 135 (2017) 538–549.