

ENCAPSULATION OF SACRIFICIAL SILICON CONTAINING PARTICLES FOR SH OXIDE CERAMICS VIA A BOEHMITE PRECURSOR ROUTE

A. L. Carabat ¹, S. van der Zwaag ² and W. G. Sloof ¹

¹ Department of Materials Science and Engineering, TU Delft, Mekelweg 2, 2628 CD Delft, The Netherlands – e-mail: a.l.carabat@tudelft.nl; w.g.sloof@tudelft.nl;

² Delft Center for Materials, TU Delft, Kluyverweg 1, 2629 HS Delft, The Netherlands – e-mail: s.vanderzwaag@tudelft.nl

Keywords: ceramic coatings, self-healing particles, encapsulation, alumina shell

ABSTRACT

Easy crack propagation in oxide ceramic coatings limits their application in high temperature environment (e.g. such as engines and gas turbine components) [1]. In order to overcome this problem, incorporation of sacrificial particles into an oxide ceramic coating may be a viable option. Particles of silicon compounds, such as: Si₃N₄, SiC, MoSi₂, TaSi₂ and WSi₂ are attractive due to their unique features of producing a reaction product (i.e. SiO₂) which fills the crack and bonds well to the surrounding matrix and exhibit, a relatively low density and melting point above that of the matrix [2]. To achieve a better control of the self-healing process with silicon compound particles a gas tight encapsulation procedure of these particles is a crucial prerequisite in order to avoid premature oxidation in the absence of a local crack. One possible route is the encapsulation of these particles by a sol-gel method [3, 4]. The dispersed healing particles were coated by Al₂O₃ layer prepared from boehmite sols, using two different alumina precursors (salt and alkoxide precursors). The resulted embedded sols were annealed in reducing atmosphere at temperatures above 1200 °C in order to achieve a dense α-Al₂O₃ microcapsule shell wall. The morphology, structure and composition of the encapsulation are determined with advanced analysis techniques. The thermal stability of the encapsulated healing particles is studied by high temperature exposure in air.

1. INTRODUCTION

Oxide ceramic coatings are promising materials for technological applications which require high temperatures, oxidation resistance and long term stability. The most important factor in the development of these types of materials is the improvement of their mechanical behaviour. The lifetime of oxide ceramic coatings is strongly affected by the crack propagation which limits their application in high-temperature environments (e.g. furnace heating elements, engines and gas turbine components) [1]. A possible route to overcome this critical issue is the incorporation of sacrificial particles into an oxide ceramic coating. Intermetallic particles based on silicon compounds, such as Si₃N₄, SiC, MoSi₂, TaSi₂ and WSi₂ are attractive due to their unique features of forming a reaction product, mainly SiO₂, which fills the crack and bonds well with the surrounding matrix [2].

To have a better control of the self-healing process with silicon based intermetallic compounds an encapsulation process is prerequisite in order to avoid the premature oxidation in the absence of any local crack. One possible way to achieve this is via

inorganic encapsulation of these particles using soft-chemical methods (precipitation or sol-gel).

In this work, an encapsulation process of MoSi_2 particles via boehmite precursor route has been developed.

2. MATERIALS AND METHODS

Aluminium chloride hexahydrate ($\text{AlCl}_3 \cdot 6\text{H}_2\text{O}$, 99% purity, Sigma Aldrich), ammonium hydroxide (NH_4OH , aqueous solution 25%, J.T. Baker Chemical Co) and molybdenum disilicide (MoSi_2 99.5% purity, average particle size $20 \mu\text{m}$, ChemPur) were used as starting materials.

The encapsulation process was performed at room temperature. MoSi_2 particles were firstly dispersed in $\text{AlCl}_3 \cdot 6\text{H}_2\text{O}$ aqueous solution. The obtained suspensions were stirred and ultrasonicated for 30 minutes to break up the agglomerates and to avoid the particles sedimentation. Subsequently, the mixture was hydrolysed by slow addition of NH_4OH under continuous stirring, at room temperature, until the reaction mixture attained a pH value between 5.0 – 6.0. The concentration of $\text{AlCl}_3 \cdot 6\text{H}_2\text{O}$ varied from 0.5 M, 2 M, 3.5 M to 5 M and the molar ratio $\text{AlOOH}/\text{MoSi}_2$ was fixed at 10 : 1. The obtained precipitates were separated by filtration, washed of free chloride and ammonium ions with hot bi-distilled water and dried at $100 \text{ }^\circ\text{C}$ for 2h. The as synthesized samples were then annealed at $1300 \text{ }^\circ\text{C}$ for 2 hours, in a reducing atmosphere (10% H_2 and 90% N_2). The flowchart of the encapsulation process of MoSi_2 particles is shown in Figure 1.

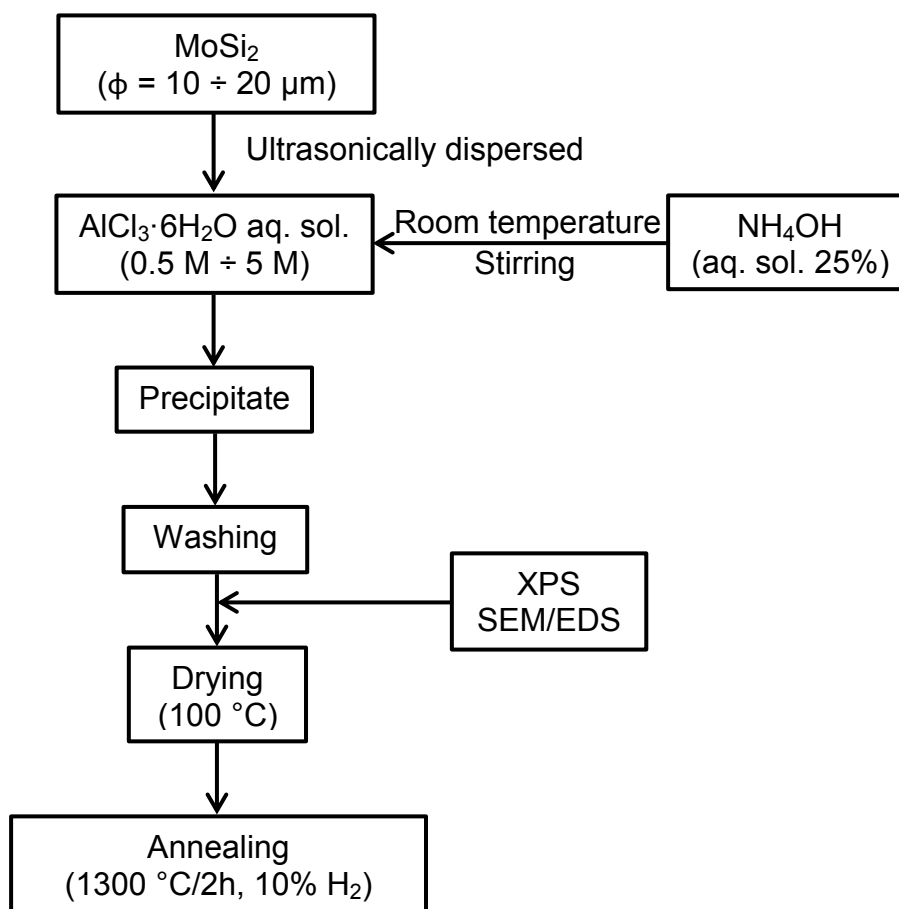


Figure 1: Flowchart of MoSi_2 encapsulation with AlOOH .

3. RESULTS AND DISCUSSION

The morphology of the MoSi₂ healing particles before and after encapsulation was observed by means of scanning electron microscopy (SEM); see Figure 2. The MoSi₂ particles are of irregular shape with sizes in the range of 10 to 20 μm; see Figure 2a. The precipitation of boehmite in a AlCl₃·6H₂O 0.5 M aqueous solution completely covered the surface of MoSi₂ particles; see Figure 2b. Similar observations were made for the other suspensions prepared by using more concentrated solutions of AlCl₃·6H₂O (2 M, 3.5 M and 5 M, respectively).

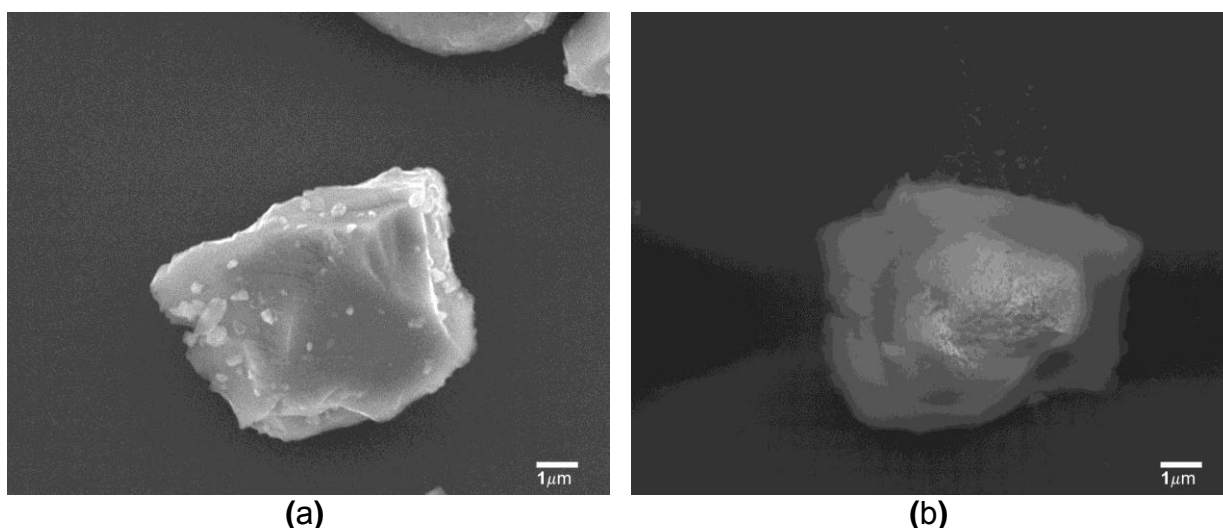


Figure 2: SEM images of uncoated and coated MoSi₂ particles: (a) as received MoSi₂ particles and (b) boehmite coated MoSi₂ particles prepared by using AlCl₃·6H₂O 0.5 M aqueous solution.

Another evidence of boehmite shell formation on the surface of MoSi₂ particles is given by X-ray Photoelectron Spectroscopy (XPS). For all the layers deposited onto the MoSi₂ particles, the O 1s peaks can be described precisely by two components corresponding to OH⁻ and O²⁻, respectively. The curve fitting of the O 1s photoelectron peak was performed using a Gaussian-Lorentzian fitting curve in the binding energy region of 526–538 eV after subtraction of the Shirley type background. The binding energies corresponding to the resolved OH⁻, O²⁻ components of O 1s and Al 2p are summarized in Table 1.

Table 1: Binding energies corresponding to O²⁻, OH⁻ and Al 2p components of the Boehmite shells obtained from the curve fitting of the XPS spectra.

Concentration AlCl ₃ solution	O ²⁻ BE (eV)	OH ⁻ BE (eV)	Al 2p BE (eV)
0.5 M	531.0	532.6	74.0
2.0 M	530.9	532.9	74.0
3.5 M	530.8	532.2	73.9
5.0 M	530.8	532.1	74.0

The binding energies of both components, O²⁻ and OH⁻ present narrow ranges: 530.8 – 531.0 eV and 532.1 – 532.9 eV, respectively. These values for O 1s components are in agreement with the results presented in the literature [5].

As already observed with SEM and confirmed with XPS, the MoSi₂ healing particles are fully covered with boehmite, since no photoelectron peaks corresponding to Mo or Si were detected.

The MoSi₂ particles remained intact during the encapsulation process, as evidenced by X-ray diffraction patterns of the particles before and after encapsulation.

After annealing the boehmite encapsulated MoSi₂ particles in reducing atmosphere (10% H₂ and 90% N₂) at 1300 °C analysis suggests that the boehmite is transformed to the desired α -Al₂O₃ phase.

4. CONCLUSION

MoSi₂ healing particles were successfully encapsulated with boehmite using a soft-chemical method. A closed shell of aluminium oxyhydroxide layer was formed on the surface of MoSi₂ particles after the precipitation process. Annealing the encapsulated particles in a gas mixture of 10% H₂ and 90% N₂ at 1300 °C transformed the boehmite into α -Al₂O₃, while the MoSi₂ core remained intact.

ACKNOWLEDGEMENTS

Financial support from Delft Centre for Materials of Delft University of Technology – DCMat (www.dcmat.tudelft.nl) gratefully acknowledged. The authors are indebted to Ing. R. W. A. Hendrix for the X-ray diffraction analysis, to Ing. J. C. Brouwer for assistance with XPS analysis and annealing experiments, and to Ing. C. Kwakernaak for his advice on the soft-chemical method.

REFERENCES

- [1] M. Backhaus-Ricoult, V. Guerin, A. M. Huntz, V. S. Urbanovich, High-temperature oxidation behavior of high-purity α -, β -, and mixed silicon nitride ceramics, *Journal of the American Ceramic Society*, 85-2 (2002) 385-392.
- [2] X. Fei, Y. Niu, H. Ji, L. Huang, X. Zheng, Oxidation behavior of ZrO₂ reinforced MoSi₂ composite coatings fabricated by vacuum plasma spraying technology, *Journal of Thermal Spray Technology*, 19-5 (2010) 1074-1080.
- [3] A. Taavoni-Gilan, E. Taheri-Nassaj, R. Naghizadeh, H. Akhondi, Properties of sol-gel derived Al₂O₃-15 wt.% ZrO₂ (3 mol% Y₂O₃) nanopowders using two different precursors, *Ceramics International*, 36-3 (2010) 1147-1153.
- [4] X. Lu, M. Zhong, W. Shu, Q. Yu, X. Xiong, R. Wang, Alumina encapsulated SrAl₂O₄:Eu²⁺, Dy³⁺ phosphors, *Powder Technology*, 177-2 (2007) 83-86.
- [5] J. van den Brand, W. G. Sloof, H. Terryn, J. H. W. de Wit, Correlation between hydroxyl fraction and O/Al atomic ratio as determined from XPS spectra of aluminium oxide layers, *Surface and Interface Analysis*, 36-1(2004) 81-88.