

## Tuning electron transfer by crystal facet engineering of BiVO<sub>4</sub> for boosting visible-light driven photocatalytic reduction of bromate

Liu, Guoshuai; Zhu, Yukun; Yan, Qun; Wang, Han; Wu, Peng; Shen, Yaoliang; Doekhi-Bennani, Yasmina

### DOI

[10.1016/j.scitotenv.2020.143086](https://doi.org/10.1016/j.scitotenv.2020.143086)

### Publication date

2021

### Document Version

Accepted author manuscript

### Published in

Science of the Total Environment

### Citation (APA)

Liu, G., Zhu, Y., Yan, Q., Wang, H., Wu, P., Shen, Y., & Doekhi-Bennani, Y. (2021). Tuning electron transfer by crystal facet engineering of BiVO<sub>4</sub> for boosting visible-light driven photocatalytic reduction of bromate. *Science of the Total Environment*, 762, Article 143086. <https://doi.org/10.1016/j.scitotenv.2020.143086>

### Important note

To cite this publication, please use the final published version (if applicable).  
Please check the document version above.

### Copyright

Other than for strictly personal use, it is not permitted to download, forward or distribute the text or part of it, without the consent of the author(s) and/or copyright holder(s), unless the work is under an open content license such as Creative Commons.

### Takedown policy

Please contact us and provide details if you believe this document breaches copyrights.  
We will remove access to the work immediately and investigate your claim.

Manuscript for: *Science of the Total Environment*  
Submission date: 12-10-2020

**Tuning Electron Transfer by Crystal Facet Engineering of BiVO<sub>4</sub> for Boosting  
Visible-Light Driven Photocatalytic Reduction of Bromate**

Guoshuai Liu<sup>a,†</sup>, Yukun Zhu<sup>b,†</sup>, Qun Yan<sup>a,c,\*</sup>, Han Wang<sup>a</sup>, Peng Wu<sup>c</sup>, Yaoliang Shen<sup>c</sup>, and Yasmina  
Doekhi-Bennani<sup>d</sup>

<sup>a</sup> School of Environmental and Civil Engineering, Jiangnan University, Wuxi 214122, China

<sup>b</sup> School of Environmental Science and Engineering, State Key Laboratory of Bio-fibers and  
Eco-textiles, Qingdao University, Qingdao 266071, China

<sup>c</sup> Jiangsu Collaborative Innovation Center of Technology and Material of Water Treatment, Suzhou  
215011, China

<sup>d</sup> Department of Water Management, Section Sanitary Engineering, Delft University of Technology,  
PO Box 5048, 2600 GA Delft, The Netherlands

<sup>†</sup> The authors contribute equally to this work.

**Corresponding author:**

\* Qun Yan  
School of Environmental and Civil Engineering, Jiangnan University, Wuxi 214122, China.  
E-mail: yanqun@jiangnan.edu.cn (Q. Yan).

**ABSTRACT:**

Removal of bromate ( $\text{BrO}_3^-$ ) has gained increasing attention in drinking water treatment process. Photocatalysis technology is an effective strategy for bromate removal. During the photocatalytic reduction of bromate process, the photo-generated electrons are reductive species toward bromate reduction and photo-generated holes responsible for water oxidation. In this study, the monoclinic bismuth vanadate ( $\text{BiVO}_4$ ) single crystal was developed as a visible photocatalyst for the effective removal of bromate. The as-synthesized  $\text{BiVO}_4$  photocatalyst with optimized  $\{010\}$  and  $\{110\}$  facets ratio could achieve almost 100% removal efficiency of  $\text{BrO}_3^-$  driven by visible light with a first-order kinetic constant of  $0.0368 \text{ min}^{-1}$ . As demonstrated by the electron scavenger experiment and density functional theory (DFT) calculations, the exposed facets of  $\text{BiVO}_4$  should account for the high photocatalytic reduction efficiency. Under visible light illumination, the photo-generated electron and holes were spatially transferred to  $\{010\}$  facets and  $\{110\}$  facets, respectively. The  $\text{BiVO}_4$  single crystal photocatalyst may serve as an attractive photocatalyst by virtue of its response to the visible light, spatially charge transfer and separation as well as high photocatalytic activity, which will make the removal of  $\text{BrO}_3^-$  in water much easier, more economical and more sustainable.

*Keywords:* bromate; bismuth vanadate; photocatalysis; crystal engineering

## INTRODUCTION

Bromate ( $\text{BrO}_3^-$ ) originated from the chlorination or ozonation process in bromide-containing water has attracted the attention of many researchers (Bouland et al., 2005; Chen et al., 2016; Parker et al., 2014, Zhu et al., ). The drinking water standard of  $\text{BrO}_3^-$  in the European Union and the U.S. Environmental Protection Agency is less than 10  $\mu\text{g/L}$  (Shen et al., 2017; Weinberg et al., 2003; Wu et al., 2013). To overcome this obstacle, considerable progress has been made regarding the transformation of  $\text{BrO}_3^-$  to  $\text{Br}^-$  by using various technologies, such as electrochemical reductive treatment (Xie and Shang, 2007), zero-valent iron (Wang et al., 2009; Zhang et al., 2015) and  $\text{FeOOH}$  catalytic reduction (Nie et al., 2014). Although these already established technologies can remove  $\text{BrO}_3^-$  effectively, they may suffer from various problems such as high cost, operational complexity, as well as the potential secondary pollution risk induced by metal leaching (Ayoubi-Feiz et al., 2015; Lin et al., 2016; Noguchi et al., 2003).

Recently, photocatalysis process was regarded as a superior technology to remove  $\text{BrO}_3^-$  (Noguchi et al., 2002). Compared with the conventional removal methods mentioned above, photocatalysis shows fascinating potential for bromate removal systems due to its high efficiency, low-cost and environmental benignity (Ayoubi-Feiz et al., 2015; Lin et al., 2016; Noguchi et al., 2003). As the widely used photocatalyst,  $\text{TiO}_2$  based photocatalysts had been extensively employed in bromate removal by UV-light driven photocatalysis, whereas the efficient conversion of  $\text{BrO}_3^-$  to  $\text{Br}^-$  was contributed to the photo-generated electrons at conduction band (CB) (Li et al., 2016; Liu et al., 2016; Zhang et al., 2005).

However, the photocatalytic systems based on  $\text{TiO}_2$ -photocatalysis still suffer from some problems for bromate removal: (i) The wide bandgap ( $E_g = 3.2 \text{ eV}$ ) of  $\text{TiO}_2$  can only be responsively under UV light irradiation (UV, 3% ratio of solar light). This may cause inconvenience in practical applications (Perry et al., 2009; Williams et al., 2008; Yang et al., 2020a; Yang et al., 2020b). (ii) The reducing agent in the photocatalytic system is photo-generated electrons. It is important to improve the

quantum efficiency of photoelectrons to participate in the bromate reduction reaction (Pan and Zhu, 2010; Wang et al., 2020a; Yang et al., 2019; Zhu et al., 2020c; Wang et al., 2020b; Wang et al., 2019). (iii) As a redox couple in the reaction depends on generated-electrons and holes, the photocatalytic reduction half-reaction is interdependent to the oxidation half-reaction mediated by photo-generated holes at the valence band (VB). Therefore, there is a growing interest in developing high overall efficiency visible light driving photocatalysts (Zhang et al., 2019; Zhu et al., 2019; Zhu et al., 2020a).

In the  $\text{BrO}_3^-$  reduction system,  $\text{BrO}_3^-$  acts as an electron acceptor, and the reduction reaction ( $1\text{ e}^-$  process) is not considered as a limiting step for the overall photocatalytic redox reaction. On the other hand, the oxidation of water ( $4\text{ e}^-$  process) is observed as a bottleneck or the rate-determining step (Zhu et al., 2020b). Based on the above-mentioned points, the premise for effective  $\text{BrO}_3^-$  reduction is to find a visible photocatalyst with high reductive activity, high selectivity and water oxidation ability.

Monoclinic  $\text{BiVO}_4$  has been widely used in photocatalysis or photoelectrochemical process for the water oxidation to produce oxygen due to its efficient and active visible light photocatalytic properties (Nakabayashi et al., 2017; Saison et al., 2015). Therefore, the oxidation reaction would not hamper the reductive half-reaction (bromate reduction reaction). On the premise that  $\text{BiVO}_4$  can efficiently oxidize water, the major water oxidation products are oxygen rather than hydroxyl radicals (Nakabayashi et al., 2017; Saison et al., 2015). This can mitigate the problem of the re-oxidation of bromine ions by hydroxyl radicals. Recent associated studies on the preparation of single crystal  $\text{BiVO}_4$  photocatalysts have shown that photo-generated carriers could be transferred to different exposed crystal facets (Li et al., 2013; Zhu et al., 2017), the reduction and oxidation reactions were spatially separated with a high reaction extent. Learned from these experiences, the reduction surface (photo-generated electron rich surface) of  $\text{BiVO}_4$  can be made by the crystal facet engineering, thus improving the quantum efficiency of photo-generated electrons involved in the

bromate reduction reaction.

Herein, three kinds of  $\text{BiVO}_4$  crystals (BVO-a, b and c) with different exposed facets were prepared and applied to the photocatalytic reduction of bromate under visible light. Additionally, the structure and morphology of  $\text{BiVO}_4$  single crystals were characterized using X-ray diffraction (XRD) and field emission scanning electron microscopy (FESEM). Furthermore, the  $\text{BrO}_3^-$  reduction performance was evaluated by calculating the conversion of  $\text{BrO}_3^-$  to  $\text{Br}^-$ . Lastly, the optical properties and electron configuration were estimated using density functional theory (DFT), and the bandgap, band position, and effective electron mass were also taken into consideration. The possible photocatalytic reduction mechanisms of  $\text{BrO}_3^-$  by  $\text{BiVO}_4$  crystals were proposed.

## EXPERIMENTAL SECTION

**Synthesis of the photocatalyst.**  $\text{BiVO}_4$  powders were prepared by liquid-solid state reaction. 5 mmol of  $\text{V}_2\text{O}_5$  and 10 mmol of  $\text{Bi}(\text{NO}_3)_3 \cdot 5\text{H}_2\text{O}$  were added in 60 mL of DI water. The precursor solution was stirred until a yellow solution was formed. The pH of the solution was regulated to 1.0, 0.5 and 0.1 by ammonia solution or dilute nitric acid solution, and then the solution was vigorously stirred at room temperature for 5 days. The obtained  $\text{BiVO}_4$  powder was separated by centrifugation, washed with DI water and dried at 60 °C. Moreover, the obtained  $\text{BiVO}_4$  powders synthesized at different pH values of 1.0, 0.5 and 0.1 were labeled as  $\text{BiVO}_4\text{-a}$ ,  $\text{BiVO}_4\text{-b}$  and  $\text{BiVO}_4\text{-c}$ .

**Characterization.** The powder X-ray diffraction (XRD) characterization was conducted on an X-ray diffractometer (Bruker D8 Adv., Germany). The crystalline phase and morphology of the as-prepared  $\text{BiVO}_4$  samples were characterized by an X-ray diffractometer (Bruker D8 Adv., Germany) and a field emission scanning electron microscope (FESEM, Type-4800, Hitachi, Japan), respectively. A spectrophotometer (Type-UV2550, Shimadzu, Japan) recorded the UV-vis diffuse reflectance spectroscopy (DRS) of the powders. The photoelectrochemical measurements were conducted using a CHI760E electrochemical workstation. The photocurrent measurements were carried out under visible light irradiation (300 W Xenon lamp).

**Theoretical Calculations.** The optimization of the unit cell of monoclinic scheelite  $\text{BiVO}_4$  was performed using the CASTEP code with the projector augmented wave (PAW) pseudopotentials (Liu et al., 2017), and the parameter was set according to the reference (Long et al., 2008). The angle  $b$  of monoclinic scheelite  $\text{BiVO}_4$  was set to  $134.9^\circ$  for simplification, the detailed parameters can be found in Table S1. The stable crystal configuration of the bulk and the cleavage surface with the optimized lowest energy are shown in Figure S1.

**Experimental Setup and Procedures.** The  $\text{BrO}_3^-$  ions removal performance was tested according to the previous method reported by our team (Liu et al., 2019). Both  $\text{BrO}_3^-$  and  $\text{Br}^-$  ions were determined by an ion chromatograph analyzer (LC-10A, Shimadzu, Japan).

## RESULTS AND DISCUSSION

**Characterization of  $\text{BiVO}_4$  Photocatalysts.** The XRD patterns of three types of as-synthesized  $\text{BiVO}_4$  photocatalysts are presented in Figure 1A. All diffraction patterns of samples ( $\text{BiVO}_4$ -a, b and c) showed sharp diffraction peaks and all typical peaks were attributed to monoclinic scheelite  $\text{BiVO}_4$  crystal phase (JCPDS No. 14-0688, space group:  $C2/c$ ), evidently suggesting that the  $\text{BiVO}_4$  photocatalysts have high crystallinity (Liu et al., 2014). Considering the phenomenon that the (121) peak was the highest peak for separated  $\text{BiVO}_4$ -a, b and c, the (121) peak was selected as the benchmark to evaluate the possible exposed surface in  $\text{BiVO}_4$  crystal qualitatively, i.e., the intensity ratios of the diffraction peak of (040) and (110) compared with (121). The intensity of (040) diffraction peak followed the order of  $\text{BiVO}_4\text{-a} > \text{BiVO}_4\text{-b} > \text{BiVO}_4\text{-c}$ , while that of (110) diffraction peak showed a reverse order, i.e.,  $\text{BiVO}_4\text{-c} > \text{BiVO}_4\text{-b} > \text{BiVO}_4\text{-a}$ . However, the intensity of (110) diffraction peak of  $\text{BiVO}_4\text{-c}$  was stronger than that of  $\text{BiVO}_4\text{-b}$  and a ( $\text{BiVO}_4\text{-c} > \text{BiVO}_4\text{-b} > \text{BiVO}_4\text{-a}$ ). According to Wang's study, this intensity difference in XRD pattern indicated that the (040) diffraction peak was the dominant peak for  $\text{BiVO}_4\text{-a}$ , and that for  $\text{BiVO}_4\text{-c}$  was (110) (Wang et al., 2011). The FESEM image of  $\text{BiVO}_4\text{-a}$  exhibited a sheet-like geometry with a length of 1.5  $\mu\text{m}$ , width of 400-nm, and thickness of 150-nm, respectively (Figure 1B). The  $\text{BiVO}_4\text{-b}$  sample exhibited

a polyhedral box shape (Figure 1C) with an average size of about 1.5  $\mu\text{m}$ . In addition, the  $\text{BiVO}_4\text{-c}$  with an octahedral shape of about 2  $\mu\text{m}$  was observed in Figure 1D. To further identify the exposed crystal faces, the corresponding HRTEM image for  $\text{BiVO}_4\text{-a}$  is given in Figure 1E.

The corresponding selected area electron diffraction (SAED) pattern in Figure 1F (inset picture) is taken from the sheet-like  $\text{BiVO}_4\text{-a}$  sample (Figure 1E), revealing the growth orientation in accordance with the results of XRD measurements. As determined by XRD result, and with different b axis orientations for different sheets, the d spacings measured from SAED (zone axis [010]) were 2.61 Å, which agreed well with the lattice spacings of (200) monoclinic  $\text{BiVO}_4$  (Wang et al., 2011). The growth direction was along the (040) facet, i.e., {010} crystal planes; therefore, the sheet-like  $\text{BiVO}_4\text{-a}$  grew along the b axis as seen in the HRTEM images (Figure 1F). Based on these analyses and calculations, a simple schematic illustration of the exposed crystal surface is presented in the insets in Figure 1B, C and D according to the XRD and HRTEM analysis. The XPS spectra of Bi 4f, V 2p and O 1s are illustrated in Figure S2. The Bi 4f consisted of two peaks at the binding energy of 156.3 and 161.5 eV, while the V 2p spectra showed two peaks of 514.0 eV and 521.7 eV, respectively. Moreover, the O 1s spectra was detected at the binding energy of 527.1 eV.

### **Figure 1 (A-F)**

**Photocatalytic Reduction of  $\text{BrO}_3^-$  by  $\text{BiVO}_4$  Photocatalysts.** The feasibility of photocatalytic reduction of  $\text{BrO}_3^-$  using  $\text{BiVO}_4$  photocatalysts under visible light irradiation were examined by photocatalytic experiment. No  $\text{BrO}_3^-$  reduction was observed in the absence of photocatalysts, which excluded the direct visible light driven photolysis of  $\text{BrO}_3^-$  reduction. As illustrated in Figure 2A, the concentration of  $\text{BrO}_3^-$  decreased from initial 1000 to 0  $\mu\text{g L}^{-1}$  (below the detection limit) for  $\text{BiVO}_4\text{-b}$  after 150 minutes of reaction, which exhibited almost 100%  $\text{BrO}_3^-$  removal efficiency. However,  $\text{BiVO}_4\text{-a}$  and  $\text{BiVO}_4\text{-c}$  reduced the initial  $\text{BrO}_3^-$  concentration (1000

$\mu\text{g L}^{-1}$ ) to 130 and 230  $\mu\text{g L}^{-1}$ , respectively. The  $\text{BrO}_3^-$  removal performance can be well indexed to the first-order reaction  $k = 0.0368 \text{ min}^{-1}$  for  $\text{BiVO}_4\text{-b}$  (Figure 2B), which was 2.08 and 3.94 times higher than that of  $\text{BiVO}_4\text{-a}$  ( $0.0177 \text{ min}^{-1}$ ) and  $\text{BiVO}_4\text{-c}$  ( $0.0094 \text{ min}^{-1}$ ), respectively. (Table S2). These results demonstrated that the  $\text{BiVO}_4\text{-b}$  sample showed superior photocatalytic bromate removal performance than that of  $\text{BiVO}_4\text{-a}$  and  $\text{-c}$  samples which might be benefited from the facet effect of  $\text{BiVO}_4$  crystal. Moreover, the stability of the  $\text{BiVO}_4$  photocatalysts was also evaluated and the result can be seen in Figure S3. during the recycling process, the photocatalytic performance of  $\text{BiVO}_4$  was with high stability, amount to 3% activity loss after five-cycles. During the recycling process, the photocatalytic performance of  $\text{BiVO}_4$  was of high stability with the activity loss amounting to 3% activity loss after five-cycles

### **Figure 2 (A and B)**

**Mechanisms Insight.** To further understand the  $\text{BrO}_3^-$  reduction mechanism by  $\text{BiVO}_4$  photocatalyst, the electron scavenger experiments were implemented by adding  $\text{S}_2\text{O}_8^{2-}$  (Romão et al., 2015). As a typical electron scavenger, the degradation performance of  $\text{BrO}_3^-$  was decreased obviously after the introduction of  $\text{S}_2\text{O}_8^{2-}$  (Figure S4 and Table S3). Notably, the bromate removal nearly disappeared when 5 mmol of  $\text{K}_2\text{S}_2\text{O}_8$  was added. Thus, it could be concluded that the photo-generated electrons were the reactive species during the  $\text{BrO}_3^-$  photocatalytic reduction process.

As we know, for semiconductor photocatalysis, the optical properties are directly related to the intrinsic electron configuration and thus influence the photocatalytic performance. Figure 3A shows the DRS spectra of  $\text{BiVO}_4$  samples with different exposed surfaces. The adsorption properties of the obtained three types of  $\text{BiVO}_4$  were all typical visible light-driven photocatalysts with an absorption edge at approximately 536 nm ( $E_g = 2.31 \text{ eV}$ ), which was in line with the previous report (Su et al.,

2011). The DFT calculation regarding optical properties was conducted to better understand the relationship of light absorption with exposed surface. As shown in Figure 3B, there was no obvious difference in the absorption threshold for polycrystal, {010} and {110} facets BiVO<sub>4</sub>, respectively, which was in accordance with the DRS results. Based on the above DRS and DFT calculation results, it can be concluded that the optical properties of BiVO<sub>4</sub> samples may not be the major reasons for the great difference in the photocatalytic removal of bromate.

### Figure 3 (A and B)

$$E_{\text{VB}} = \chi - E^e + \frac{E_{\text{g}}}{2} \quad (1)$$

$$E_{\text{CB}} = E_{\text{VB}} - E_{\text{g}} \quad (2)$$

Furthermore, the theoretical positions of energy band position of BiVO<sub>4</sub> at pH = pH<sub>pzc</sub> were calculated using the following conventional eqn. 1 and 2 (Xu and Schoonen, 2000).  $E^e$  is the free electron energy (4.5 V),  $E_{\text{g}}$  is the measured band gap. By substituting these absolute electronegativities of Bi, V and O to eqn. 1 and 2, the  $E_{\text{VB}}$  of 2.80 V and  $E_{\text{CB}}$  of 0.49 V (SHE) were obtained (Cooper et al., 2014). Although the valence band position of BiVO<sub>4</sub> was suitable for hydroxyl radicals generation, according to the previous literature, BiVO<sub>4</sub> was generally considered as a highly efficient photocatalyst for water oxidation to produce oxygen rather than hydroxyl radicals, thus making the reduction of BrO<sub>3</sub><sup>−</sup> more efficient towards Br<sup>−</sup> conversion (Nakabayashi et al., 2017; Saison et al., 2015).

As shown in Figure S1, VO<sub>4</sub><sup>3−</sup> was a stretched tetrahedron. In the stretched BiO<sub>8</sub> dodecahedron, Bi atoms were surrounded by 8 O atoms, and the four bond lengths were different (2.467, 2.466, 2.471, and 2.528 Å) (Stoltzfus et al., 2007; Yang et al., 2013). As we know, the dipole moments played an important role in photocatalysis, especially on the effective separation of carriers. A big dipole

moment always means a high driving force makes efficient photo-generated carriers transfer (Li et al., 2014). In this regard, the absolute numerical value of dipole moment is calculated to be 0.79 and 0.68 D on {010} and {110} facets, respectively. The larger dipole moment of the BiO polyhedrons for {010} facet demonstrates greater distortion of the {110} surface layer, hence leading to a larger internal polarization which is conducive to the charge separation and higher activity for the photocatalytic reduction of  $\text{BrO}_3^-$ .

**Table 1**

To further understand the electronic configuration of the two exposed crystal facets, the band structure of  $\text{BiVO}_4$  is plotted in Figure 4A. Considering the symmetry of the monoclinic system, the path selected from the Brillouin zone was along  $Z \rightarrow G \rightarrow Y \rightarrow A \rightarrow B \rightarrow D \rightarrow E \rightarrow C$ . The DFT calculated  $E_g$  for  $\text{BiVO}_4$  was 2.12 eV, close to the experimental value (2.31 eV). The highest band energy level and lowest energy level were located at different K-points, which indicated the typical indirect band gap property. Furthermore, we can calculate the effective carrier masses of {010} and {110} facets based on the curvatures of the bands in the corresponding directions by fitting parabolic functions to the conduction band minimum (CBM) and valence band maximum (VBM) of  $\text{BiVO}_4$ . According to the Eq. (3) (Li et al., 2014), the effective electron masses can be estimated, where  $k$  is the wave vector, and  $E_k$  is the energy corresponding to the wave vector  $k$ .

$$m^* = \pm h^2 \left( \frac{d^2 E_k}{dk^2} \right)^{-1} \quad (3)$$

The calculated results are summarized in Table 1. The effective electron masses were approximately 0.13  $m_0$  and 0.30  $m_0$ , and the effective hole masses are estimated to be approximately 0.18  $m_0$  and 0.57  $m_0$  for {010} and {110} surfaces, respectively. In the photocatalytic process, lower effective mass means higher drift velocity, and the photo-generated hole/electron pairs could be transferred to the surface of photocatalyst (Li et al., 2014). Therefore, the effective electron mass of {010} was

0.13 m<sub>0</sub>, obviously lower than that of {110} facets making it favorable for the photocatalytic bromate reduction process.

#### **Figure 4 (A and B)**

According to the dipole moment and charge transport calculation, the presence of {010} facet exposed BiVO<sub>4</sub> was beneficial for the charge separation. As revealed from the photocurrent of BiVO<sub>4</sub>-a, BiVO<sub>4</sub>-b and BiVO<sub>4</sub>-c in Figure 4B, BiVO<sub>4</sub>-b possessed a much higher photocurrent than BiVO<sub>4</sub>-a and BiVO<sub>4</sub>-c. The intense photocurrent generally means a higher hole/electron pairs separation efficiency (Li et al.). As shown in Figure 4B, the BiVO<sub>4</sub>-b sample with {010} facet exposed maintained a high separation efficiency of hole/electron pairs, which was in well agreement with the result of dipole moment calculations.

The intrinsic reason for the separation of photo-generated carriers on the {010} and {110} of BiVO<sub>4</sub> crystal facets was evaluated by the DFT calculation method (Pan et al., 2011). Figure 5A shows the density of states (DOS) calculation results (where Fermi energy was set as 0 eV). We can ascertain the conduction band edge and valence band edge from Figure 5A, where the conduction band edge for {110} facets was 1.33 eV, and that for {010} was 2.15 eV. Thus, the energy differences for conduction bands ( $\Delta_{CB}$ ) between {010} and {110} facets was about 0.82 eV. Similarly, we could calculate the  $\Delta_{VB}$  by analyzing the DOS curves and the result is about 0.20 eV between {010} and {110} facets. The existed difference well demonstrated that the transfer trend of photo-generated electron was from {110} to {010} facets in the thermodynamic view. Within this context, the electrons were accumulated on {010} facets, whereas the holes were enriched on {110} facets. Based on the calculated results obtained in Figure 5A, the schematic diagram of spatial photo-generated carriers separation between {110} and {010} facets is schematic shown in Figure 5B. Furthermore, the Work function (W) calculation results are shown in Figure 5C and 5D. The W of {010} and {110}

facets was 6.2 eV and 4.5 eV, respectively. The W value of {010} facets is obvious bigger than that of {110} facets, which makes the {010} facets have a higher electron capture ability (Gao et al., 2011). The results were in line with the density of state (DOS) analysis, where the photo-generated electrons were separated spatially with the photo-generated holes during photocatalytic process to form electron-rich {010} facets and hole-rich {110} facets.

### **Figure 5 (A, B, C and D)**

For a practical photocatalytic reaction, reduction reactions were accompanied by oxidation reactions. To achieve a high photocatalytic efficiency (in this study, is photocatalytic reduction of bromate), high oxidation reactions involved by photo-generated holes must be considered. To clarify the mechanism deeply, the test of BiVO<sub>4</sub> photocatalyst utilized in water oxidation under visible light irradiation of O<sub>2</sub> evolution with BrO<sub>3</sub><sup>-</sup> as electron sacrificial agent (NaBrO<sub>3</sub>, 0.1 mol L<sup>-1</sup>) was conducted, and the photocatalytic O<sub>2</sub> evolution performance is shown in Table S4. As shown in Table S4, the BiVO<sub>4</sub>-b exhibited the highest oxygen production with the rate of 11.70 μmol h<sup>-1</sup>, and the order of oxygen production rate was BiVO<sub>4</sub>-b (11.70 μmol h<sup>-1</sup>) >> BiVO<sub>4</sub>-a (2.30 μmol h<sup>-1</sup>) > BiVO<sub>4</sub>-c (1.50 μmol h<sup>-1</sup>). The results evidently confirmed that the BiVO<sub>4</sub>-b showed the highest water oxidation, as an overall reaction, the photo-reduction performance was correlated with the oxidation ability. Therefore, the BiVO<sub>4</sub>-b sample with an optimized exposure ratio of the {010} and {110} surfaces exhibited the highest photocatalytic bromate reduction activity. The conceivable intrinsic mechanisms are schematically showed in Figure 6. Under the irradiation of visible light, photo-generated carriers were separated toward different surfaces for the polyhedral box shape BiVO<sub>4</sub> photocatalyst, i.e., the photo-generated electrons (thermodynamic potential of 0.49 V, SHE) and photo-generated holes (2.80 V, SHE) were transferred to different facets of BiVO<sub>4</sub> crystal. As shown in Figure 6, the {010} facets were the electron-rich surfaces, whereas the holes were

accumulated on the {110} surfaces. The electron with a redox potential of 0.49 V was a robust reductive for bromate reduction ( $\text{BrO}_3^- + 6\text{H}^+ + 6\text{e}^- \rightarrow \text{Br}^- + 3\text{H}_2\text{O}$ ,  $E^\circ = 1.423 \text{ V}$ ). And photo-generated hole with a high redox potential of 2.80 V could decompose  $\text{H}_2\text{O}$  to produce oxygen efficiently ( $2\text{H}_2\text{O} - 4\text{e}^- \rightarrow \text{O}_2 + 4\text{H}^+$ ,  $E^\circ = 1.23 \text{ V}$ ). In this manner,  $\text{BrO}_3^-$  could be regarded as the electron acceptor and *in-situ* reduced at {010} facets, while the water oxidation reaction was occurred at {110} surfaces to produce  $\text{O}_2$ . The photo-generated electron-hole pairs were spatially separated, and the oxidation and reduction reactions occurred at different crystal facets; thus, a high bromate reduction efficiency and selectivity on  $\text{BiVO}_4$  single crystal with optimized {010} and {110} ratio could be achieved. Besides, a systemic comparison with conventional photocatalyst of  $\text{TiO}_2$ , traditional bulk  $\text{BiVO}_4$  or  $\text{Bi}_2\text{MoO}_6$  documented from literature is summarized in Table S5. The  $\text{BiVO}_4$ -b sample with active exposed facets ratio could remove almost 100% of  $\text{BrO}_3^-$ , whose kinetic constant was significantly higher than that of other conventional photocatalysts.

### **Figure 6**

**Conclusions.** To achieve efficient removal of  $\text{BrO}_3^-$ , we herein developed single crystal photocatalysts  $\text{BiVO}_4$  with different exposed facets. The {010} facets are exposed electron-rich surfaces with a higher dipole moment and a lower effective mass of electrons/holes, which is more favorable for the photocatalytic bromate reduction reaction. Under visible light illumination, the photo-generated reductive electrons and oxidative photo-generated holes are spatially transported to {010} and {110} facets, respectively. During the bromate photocatalytic removal process, water acts as an electron donor, thus avoiding the risk of secondary pollution, making the  $\text{BrO}_3^-$  removal of high efficiency. This investigation provides a simple and effective strategy for enhanced degradation of bromate without complicated preparation procedure, which makes the bromate removal more efficient and sustainable, and also gives a guideline for the development of single crystal

photocatalyst for bromate photocatalytic reduction.

## ACKNOWLEDGEMENTS

National Key Research and Development Program of China (2017YFE9133400), Pre-research Fund of Jiangsu Collaborative Innovation Center of Technology and Material of Water Treatment (XTCXSZ2020-3).

## REFERENCES

- Ayoubi-Feiz B, Aber S, Sheydaei M. Effect of oxidants on photoelectrocatalytic decolourization using  $\alpha$ -Fe<sub>2</sub>O<sub>3</sub>/TiO<sub>2</sub>/activated charcoal plate nanocomposite under visible light. *RSC Adv.* 2015; 5: 19368-19378.
- Boulard S, Duguet J-P, Montiel A. Evaluation of bromate ions level introduced by sodium hypochlorite during post-disinfection of drinking water. *Environ. Technol.* 2005; 26: 121-126.
- Chen F, Yang Q, Zhong Y, An H, Zhao J, Xie T, et al. Photo-reduction of bromate in drinking water by metallic Ag and reduced graphene oxide (RGO) jointly modified BiVO<sub>4</sub> under visible light irradiation. *Water Res.* 2016; 101: 555-563.
- Cooper JK, Gul S, Toma FM, Le C, Glans PA, Guo J, et al. Electronic structure of monoclinic BiVO<sub>4</sub>. *Chem. Mater.* 2014; 26: 5365-5373.
- Gao E, Wang W, Shang M, Xu J. Synthesis and enhanced photocatalytic performance of graphene-Bi<sub>2</sub>WO<sub>6</sub> composite. *Phys. Chem. Chem. Phys.* 2011; 13: 2887-2893.
- Li R, Zhang F, Wang D, Yang J, Li M, Zhu J, et al. Spatial separation of photogenerated electrons and holes among {010} and {110} crystal facets of BiVO<sub>4</sub>. *Nat. Commun.* 2013; 4: 1432-1439.
- Li X, Pi Y, Xia Q, Li Z, Xiao J. TiO<sub>2</sub> encapsulated in Salicylaldehyde-NH<sub>2</sub>-MIL-101 (Cr) for enhanced visible light-driven photodegradation of MB. *Appl. Catal. B-Environ.* 2016; 191: 192-201.
- Li Y, Jiang Y, Ruan Z, Lin K, Yu Z, Zheng Z, et al. Simulation-guided synthesis of graphitic carbon nitride beads with 3D interconnected and continuous meso/macropore channels for enhanced light absorption and photo-catalytic performance. *J. Mater. Chem. A.* 2017; 5: 21300-21312.
- Li Z, Dai Y, Ma X, Zhu Y, Baibiao H. Tuning photocatalytic performance of the near-infrared-driven photocatalyst Cu<sub>2</sub>(OH)PO<sub>4</sub> based on effective mass and dipole moment. *Phys. Chem. Chem. Phys.* 2014; 16: 3267-3273.
- Lin K-YA, Lin C-H, Chen S-Y, Yang H. Enhanced photocatalytic reduction of concentrated bromate in the presence of alcohols. *Chem. Eng. J.* 2016; 303: 596-603.
- Liu G, Liu S, Lu Q, Sun H, Xu F, Zhao G. Synthesis of monoclinic BiVO<sub>4</sub> microribbons by sol-gel combined with electrospinning process and photocatalytic degradation performances. *J. Sol-gel Sci. Technol.* 2014; 70: 24-32.
- Liu G, You S, Ma M, Huang H, Ren N. Removal of nitrate by photocatalytic denitrification using nonlinear optical material. *Environ. Sci. Technol.* 2016; 50: 11218-11225.
- Liu G, You S, Tan Y, Ren N. In situ photochemical activation of sulfate for enhanced degradation of organic pollutants in water. *Environ. Sci. Technol.* 2017; 51: 2339-2346.
- Liu G, You S, Zhang Y, Huang H, Spanjers H. Conjugated donor-acceptor (D-A) supramolecule catalyst for visible-light-driven photocatalytic removal of bromate in water. *J. Colloid Interf. Sci.* 2019; 553: 666-673.
- Long M, Cai W, Kisch H. Visible light induced photoelectrochemical properties of n-BiVO<sub>4</sub> and n-BiVO<sub>4</sub>/p-Co<sub>3</sub>O<sub>4</sub>. *J.*


- Phys. Chem. C 2008; 112: 548-554.
- Nakabayashi Y, Nishikawa M, Saito N, Terashima C, Fujishima A. Significance of hydroxyl radical in photoinduced oxygen evolution in water on monoclinic bismuth vanadate. *J. Phys. Chem. C* 2017; 121: 25624-25631.
- Nie Y, Hu C, Li N, Yang L, Qu J. Inhibition of bromate formation by surface reduction in catalytic ozonation of organic pollutants over  $\beta$ -FeOOH/Al<sub>2</sub>O<sub>3</sub>. *Appl. Catal. B-Environ.* 2014; 147: 287-292.
- Noguchi H, Nakajima A, Watanabe T, Hashimoto K. Removal of bromate ion from water using TiO<sub>2</sub> and alumina-loaded TiO<sub>2</sub> photocatalysts. *Water Sci. Technol.* 2002; 46: 27-31.
- Noguchi H, Nakajima A, Watanabe T, Hashimoto K. Design of a photocatalyst for bromate decomposition: Surface modification of TiO<sub>2</sub> by pseudo-boehmite. *Environ. Sci. Technol.* 2003; 37: 153-157.
- Pan C, Zhu Y. New type of BiPO<sub>4</sub> oxy-acid salt photocatalyst with high photocatalytic activity on degradation of dye. *Environ. Sci. Technol.* 2010; 44: 5570-5574.
- Pan J, Liu G, Lu GQ, Cheng HM. On the true photoreactivity order of {001}, {010}, and {101} facets of anatase TiO<sub>2</sub> crystals. *Angew. Chem. Int. Edit.* 2011; 50: 2133.
- Parker KM, Zeng T, Harkness J, Vengosh A, Mitch WA. Enhanced formation of disinfection byproducts in shale gas wastewater-impacted drinking water supplies. *Environ. Sci. Technol.* 2014; 48: 11161-9.
- Perry IV JJ, Perman JA, Zaworotko MJ. Design and synthesis of metal-organic frameworks using metal-organic polyhedra as supermolecular building blocks. *Chem. Soc. Rev.* 2009; 38: 1400-1417.
- Romão JS, Hamdy MS, Mul G, Baltrusaitis J. Photocatalytic decomposition of cortisone acetate in aqueous solution. *J. Hazard. Mater.* 2015; 282: 208-215.
- Saison T, Chemin N, Chanéac C, Durupthy O, Mariey L, Maugé Fo, et al. New insights into BiVO<sub>4</sub> properties as visible light photocatalyst. *J. Phys. Chem. C* 2015; 119: 12967-12977.
- Shen W, Lin F, Jiang X, Li H, Ai Z, Zhang L. Efficient removal of bromate with core-shell Fe@Fe<sub>2</sub>O<sub>3</sub> nanowires. *Chem. Eng. J.* 2017; 308: 880-888.
- Stoltzfus MW, Woodward PM, Ram S, Jae-Hyun K, Bruce B. Structure and bonding in SnWO<sub>4</sub>, PbWO<sub>4</sub>, and BiVO<sub>4</sub>: lone pairs vs inert pairs. *Inorg. Chem.* 2007; 46: 3839-50.
- Su J, Guo L, Bao N, Grimes CA. Nanostructured WO<sub>3</sub>/BiVO<sub>4</sub> Heterojunction films for efficient photoelectrochemical water splitting. *Nano Lett.* 2011; 11: 1928-1933.
- Wang D, Jiang H, Zong X, Xu Q, Ma Y, Li G, et al. Crystal facet dependence of water oxidation on BiVO<sub>4</sub> sheets under visible light irradiation. *Chem. Eur. J.* 2011; 17: 1275-1282.
- Wang Q, Snyder S, Kim J, Choi H. Aqueous ethanol modified nanoscale zerovalent iron in bromate reduction: synthesis, characterization, and reactivity. *Environ. Sci. Technol.* 2009; 43: 3292-3299.
- Wang W, Han Q, Zhu Z, Zhang L, Zhong S, Liu B. Enhanced photocatalytic degradation performance of organic contaminants by heterojunction photocatalyst BiVO<sub>4</sub>/TiO<sub>2</sub>/RGO and its compatibility on four different tetracycline antibiotics. *Adv. Powder Technol.* 2019; 30: 1882-1896.
- Wang Y, Ding K, Xu R, Yu D, Wang W, Gao P, et al. Fabrication of BiVO<sub>4</sub>/BiPO<sub>4</sub>/GO composite photocatalytic material for the visible light-driven degradation. *J. Clean. Prod.* 2020a; 247: 119108.
- Wang Y, Yu D, Wang W, Gao P, Zhong S, Zhang L, et al. Synthesizing Co<sub>3</sub>O<sub>4</sub>-BiVO<sub>4</sub>/g-C<sub>3</sub>N<sub>4</sub> heterojunction composites for superior photocatalytic redox activity. *Sep. Purif. Technol.* 2020b; 239: 116562.
- Weinberg HS, Delcomyn CA, Unnam V. Bromate in chlorinated drinking waters: occurrence and implications for future regulation. *Environ. Sci. Technol.* 2003; 37: 3104-3110.
- Williams G, Seger B, Kamat PV. TiO<sub>2</sub>-graphene nanocomposites. UV-assisted photocatalytic reduction of graphene oxide. *ACS Nano* 2008; 2: 1487-1491.
- Wu X, Yang Q, Xu D, Zhong Y, Luo K, Li X, et al. Simultaneous adsorption/reduction of bromate by nanoscale zerovalent iron supported on modified activated carbon. *Ind. Eng. Chem. Res.* 2013; 52: 12574-12581.

- Xie L, Shang C. The effects of operational parameters and common anions on the reactivity of zero-valent iron in bromate reduction. *Chemosphere* 2007; 66: 1652-1659.
- Xu Y, Schoonen MAA. The absolute Energy position of conduction and valence bands of selected semiconducting minerals. *Am. Mineral.* 2000; 85: 543-556.
- Yang J, Wang D, Zhou X, Li C. A theoretical study on the mechanism of photocatalytic oxygen evolution on  $\text{BiVO}_4$  in aqueous solution. *Chem. Eur. J.* 2013; 19: 1320-1326.
- Yang R, Dong F, You X, Liu M, Zhong S, Zhang L, et al. Facile synthesis and characterization of interface charge transfer heterojunction of  $\text{Bi}_2\text{MoO}_6$  modified by Ag/AgCl photosensitive material with enhanced photocatalytic activity. *Mater. Lett.* 2019; 252: 272-276.
- Yang R, Zhong S, Zhang L, Liu B.  $\text{PW12/CN@Bi}_2\text{WO}_6$  composite photocatalyst prepared based on organic-inorganic hybrid system for removing pollutants in water. *Sep. Purif. Technol.* 2020a; 235: 116270.
- Yang R, Zhu Z, Hu C, Zhong S, Zhang L, Liu B, et al. One-step preparation (3D/2D/2D)  $\text{BiVO}_4/\text{FeVO}_4/\text{rGO}$  heterojunction composite photocatalyst for the removal of tetracycline and hexavalent chromium ions in water. *Chem. Eng. J.* 2020b; 390: 124522.
- Zhang F, Jin R, Chen J, Shao C, Gao W, Li L, et al. High photocatalytic activity and selectivity for nitrogen in nitrate reduction on Ag/ $\text{TiO}_2$  catalyst with fine silver clusters. *J. Catal.* 2005; 232: 424-431.
- Zhang H, Yu D, Wang W, Gao P, Zhang L, Zhong S, et al. Construction of a novel BON-Br-AgBr heterojunction photocatalysts as a direct Z-scheme system for efficient visible photocatalytic activity. *Appl. Surf. Sci.* 2019; 497: 143820.
- Zhang Y, Jing S, Liu H. Reactivity and mechanism of bromate reduction from aqueous solution using Zn-Fe(II)-Al layered double hydroxides. *Chem. Eng. J.* 2015; 266: 21-27.
- Zhu J, Pang S, Dittrich T, Gao Y, Nie W, Cui J, et al. Visualizing the nano cocatalyst aligned electric fields on single photocatalyst particles. *Nano Lett.* 2017; 17: 6735-6741.
- Zhu Y, Li J, Dong C, Ren J, Huang Y, Zhao D, et al. Red phosphorus decorated and doped  $\text{TiO}_2$  nanofibers for efficient photocatalytic hydrogen evolution from pure water. *Appl. Catal. B-Environ.* 2019; 255: 117764.
- Zhu Y, Lv C, Yin Z, Ren J, Yang D. A [001]- Oriented hitorf's phosphorus nanorods/polymeric carbon nitride heterostructure for boosting wide- spectrum- responsive photocatalytic hydrogen evolution from pure water. *Angew. Chem. Int. Edi.* 2020a; 59: 868-873.
- Zhu Y, Ren J, Zhang X, Yang D. Elemental red phosphorus-based materials for photocatalytic water purification and hydrogen production. *Nanoscale* 2020b, 12, 13297-13310
- Zhu Z, Wang C, Liang L, Yu D, Sun J, Zhang L, et al. Synthesis of novel ternary photocatalyst  $\text{Ag}_3\text{PO}_4/\text{Bi}_2\text{WO}_6/\text{multi-walled carbon nanotubes}$  and its enhanced visible-light photoactivity for photodegradation of norfloxacin. *J. Nanosci. Nano.* 2020c; 20: 2247-2258.


Table List

Table 1 Summary of the effective masses


|                             | {010}/m <sub>0</sub> | {110}/m <sub>0</sub> |
|-----------------------------|----------------------|----------------------|
| m <sub>h</sub> <sup>*</sup> | 0.18                 | 0.57                 |
| m <sub>e</sub> <sup>*</sup> | 0.13                 | 0.30                 |

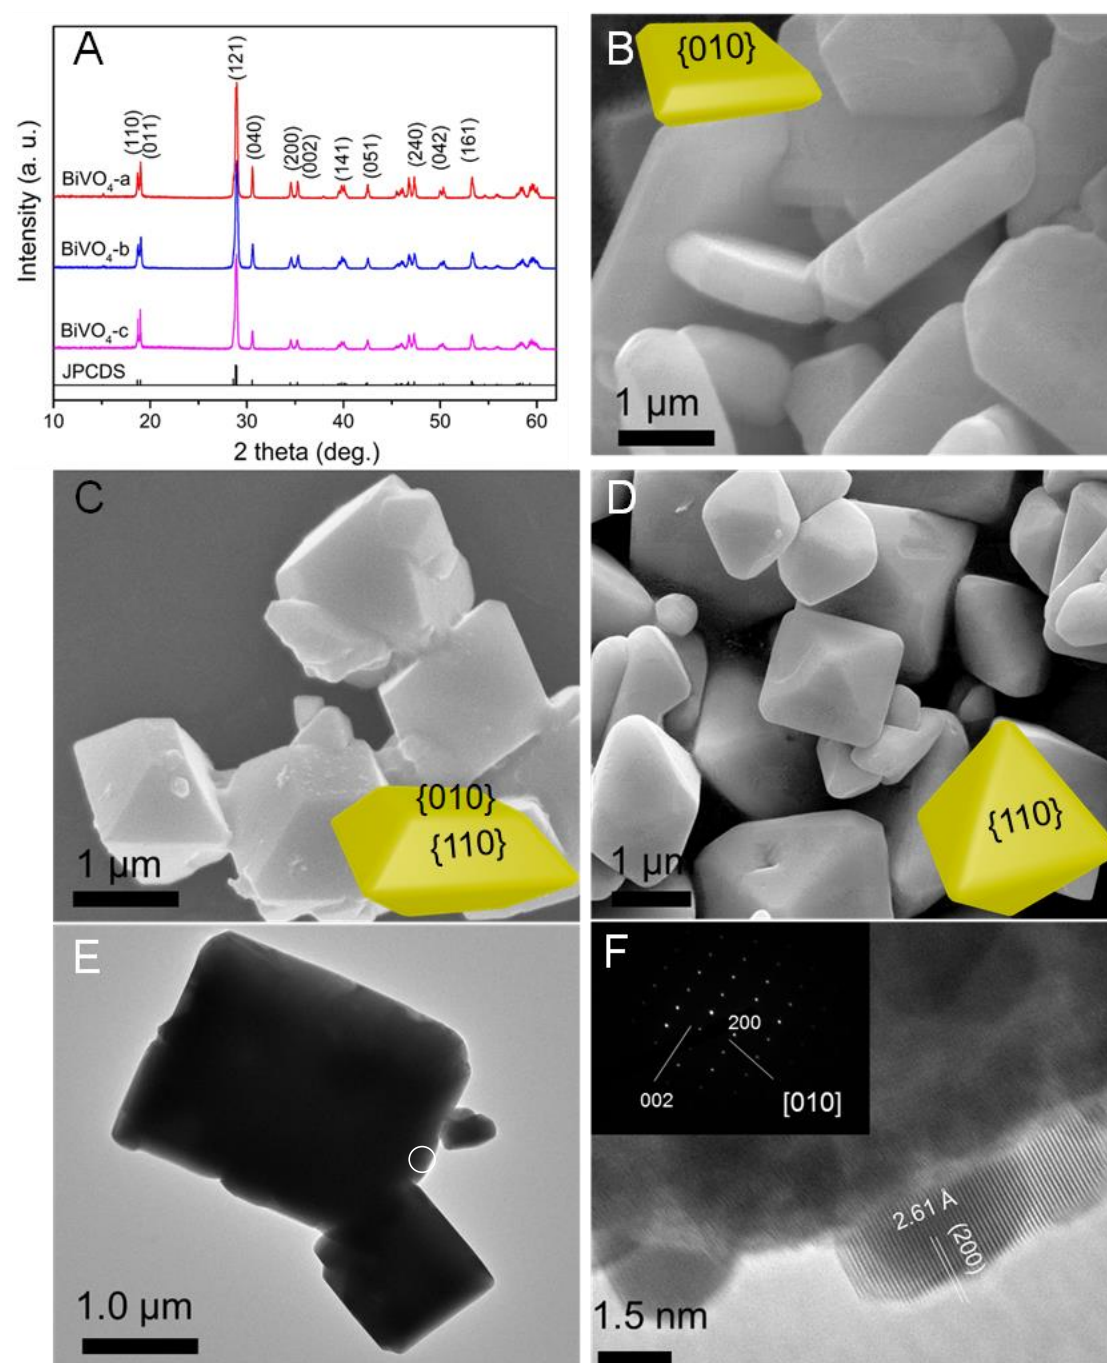


**Figure 1** XRD patterns of (A) BiVO<sub>4</sub> samples, SEM pictures of (B) BiVO<sub>4</sub>-a, (C) BiVO<sub>4</sub>-b, (D) BiVO<sub>4</sub>-c, (E) TEM and HRTEM (F) pictures of BiVO<sub>4</sub>-a.

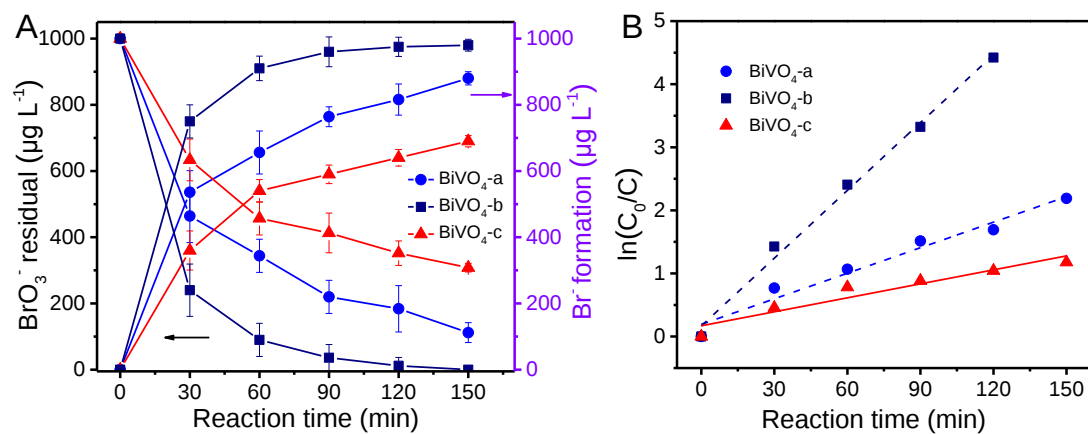


**Figure 2** Time course of (A) photocatalytic reduction of  $\text{BrO}_3^-$  by  $\text{BiVO}_4$  photocatalysts under visible light irradiation at pH  $7.1 \pm 0.4$ , (B) the corresponding kinetics rate constants derived from A.

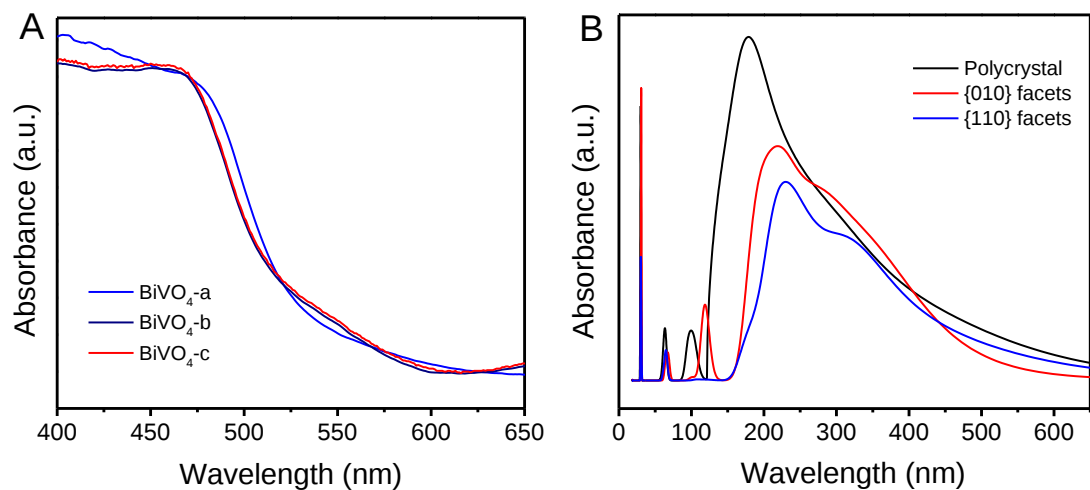


**Figure 3** (A) The experimental diffuse reflectance spectra of BiVO<sub>4</sub> samples, (B) calculated absorption coefficient of polycrystal BiVO<sub>4</sub>, {010} and {110} facets exposed BiVO<sub>4</sub>.

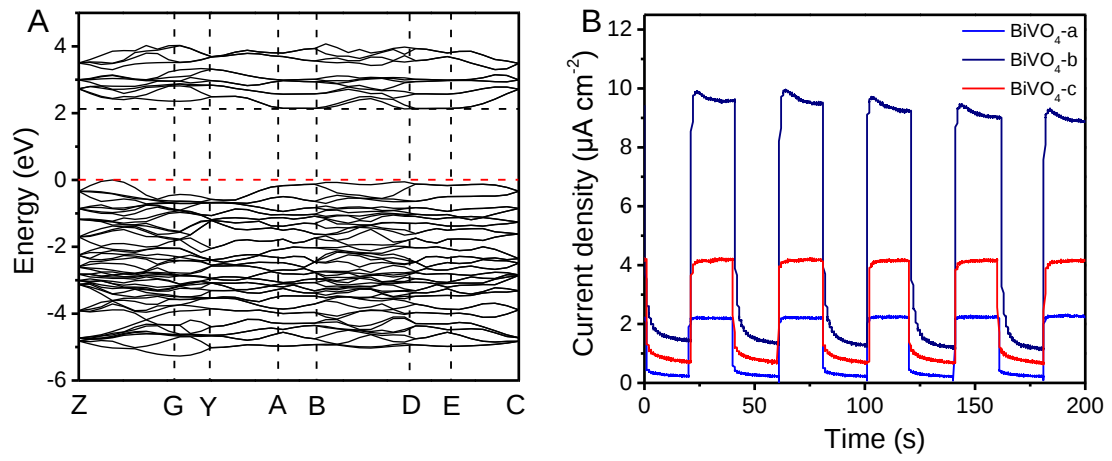

**Figure 4** The band structure (A) of BiVO<sub>4</sub> crystal and (B) photocurrent-time curve of BiVO<sub>4</sub> samples.

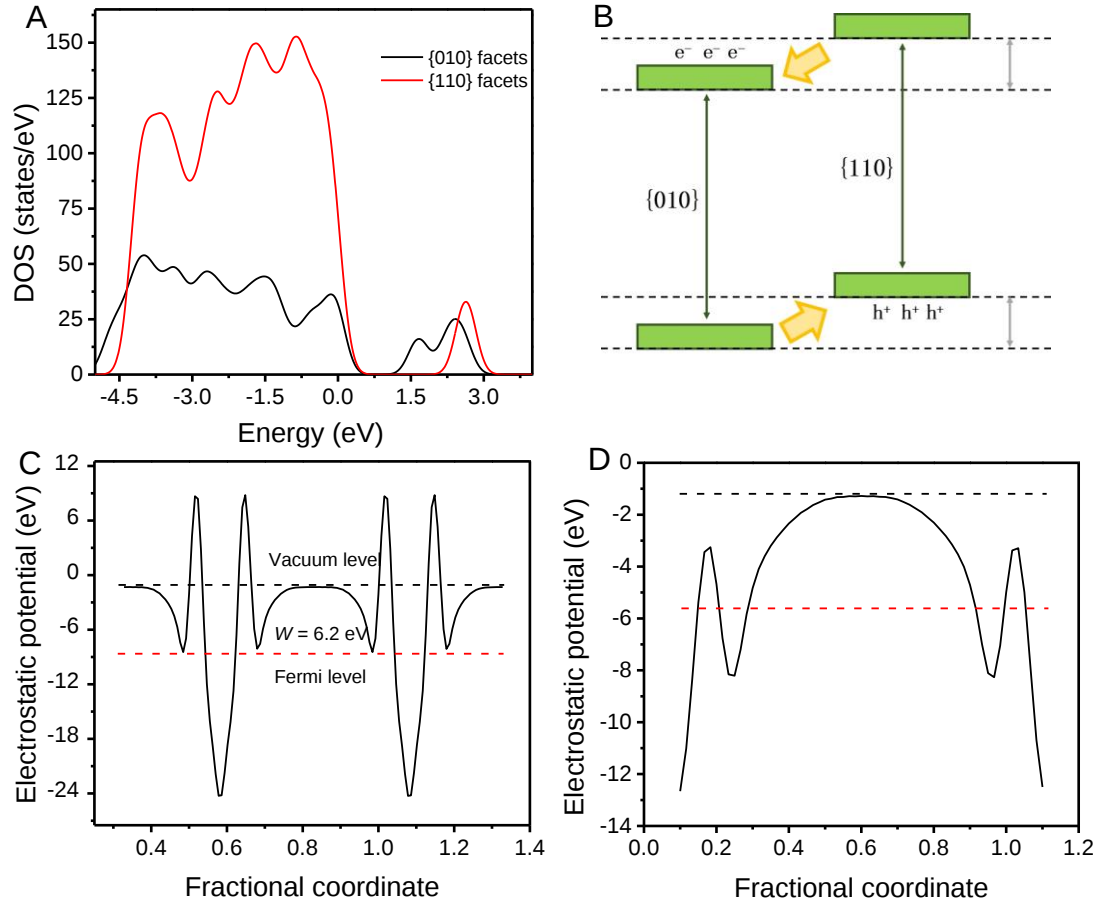

**Figure 5** (A) The differences of the energy levels in conduction bands ( $\Delta_{CB}$ ) for {010} and {110} facets, (B) the scheme of carrier separation between {010} and {110} facets, (C) the workfunction ( $W$ ) of {010} surface and (D) {110} surface.

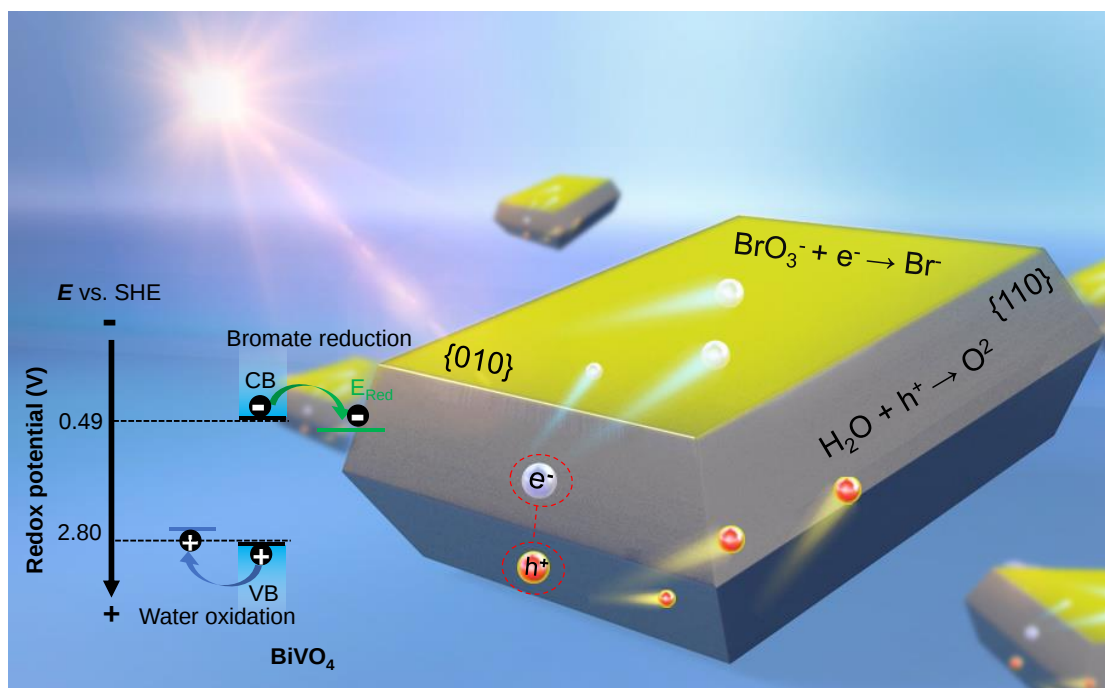

**Figure 6** Schematic illustration of photocatalytic reduction of  $\text{BrO}_3^-$  by  $\text{BiVO}_4$ -b.