

Shearography non-destructive testing of a composite ship hull section subjected to multiple impacts

Tao, N.; Anisimov, A.; Elenbaas, Marcel ; Groves, R.M.

Publication date

2022

Document Version

Final published version

Published in

Proceedings of the 20th European Conference on Composite Materials: Composites Meet Sustainability

Citation (APA)

Tao, N., Anisimov, A., Elenbaas, M., & Groves, R. M. (2022). Shearography non-destructive testing of a composite ship hull section subjected to multiple impacts. In A. P. Vassilopoulos , & V. Michaud (Eds.), *Proceedings of the 20th European Conference on Composite Materials: Composites Meet Sustainability: Vol 3 – Characterization* (pp. 469-474). EPFL Lausanne, Composite Construction Laboratory.

Important note

To cite this publication, please use the final published version (if applicable).
Please check the document version above.

Copyright

Other than for strictly personal use, it is not permitted to download, forward or distribute the text or part of it, without the consent of the author(s) and/or copyright holder(s), unless the work is under an open content license such as Creative Commons.

Takedown policy

Please contact us and provide details if you believe this document breaches copyrights.
We will remove access to the work immediately and investigate your claim.

ECCM
20
26-30 JUNE
2022
LAUSANNE
SWITZERLAND



Proceedings of the 20th European Conference on Composite Materials

COMPOSITES MEET SUSTAINABILITY

Vol 3 – Characterization

Editors : Anastasios P. Vassilopoulos, Véronique Michaud

Organized by :

EPFL

Under the patronage of :

CCLAB
Composite
Construction
Laboratory

LPAC
Laboratory for Processing
of Advanced Composites

ESCM
EUROPEAN SOCIETY
FOR COMPOSITE MATERIALS



**Proceedings of the 20th
European Conference on Composite Materials
ECCM20
26-30 June 2022,
EPFL Lausanne Switzerland**

Edited By :

Prof. Anastasios P. Vassilopoulos, CCLab/EPFL
Prof. Véronique Michaud, LPAC/EPFL

Organized by:

Composite Construction Laboratory (CCLab)
Laboratory for Processing of Advanced Composites (LPAC)
Ecole Polytechnique Fédérale de Lausanne (EPFL)

ISBN: 978-2-9701614-0-0

DOI: http://dx.doi.org/10.5075/epfl-298799_978-2-9701614-0-0

Published by :

Composite Construction Laboratory (CCLab)
Ecole Polytechnique Fédérale de Lausanne (EPFL)
BP 2225 (Bâtiment BP), Station 16
1015, Lausanne, Switzerland

<https://cclab.epfl.ch>

Laboratory for Processing of Advanced Composites (LPAC)
Ecole Polytechnique Fédérale de Lausanne (EPFL)
MXG 139 (Bâtiment MXG), Station 12
1015, Lausanne, Switzerland

<https://lpac.epfl.ch>

Cover:

Swiss Tech Convention Center
© Edouard Venceslau - CompuWeb SA

Cover Design:

Composite Construction Laboratory (CCLab)
Ecole Polytechnique Fédérale de Lausanne (EPFL)
Lausanne, Switzerland

©2022 ECCM20/The publishers

The Proceedings are published under the CC BY-NC 4.0 license in electronic format only, by the Publishers.

The CC BY-NC 4.0 license permits non-commercial reuse, transformation, distribution, and reproduction in any medium, provided the original work is properly cited. For commercial reuse, please contact the authors. For further details please read the full legal code at <http://creativecommons.org/licenses/by-nc/4.0/legalcode>

The Authors retain every other right, including the right to publish or republish the article, in all forms and media, to reuse all or part of the article in future works of their own, such as lectures, press releases, reviews, and books for both commercial and non-commercial purposes.

Disclaimer:

The ECCM20 organizing committee and the Editors of these proceedings assume no responsibility or liability for the content, statements and opinions expressed by the authors in their corresponding publication.

SHEAROGRAPHY NON-DESTRUCTIVE TESTING OF A COMPOSITE SHIP HULL SECTION SUBJECTED TO MULTIPLE IMPACTS

Nan Tao^{a*}, Andrei G. Anisimov^a, Marcel Elenbaas^b, Roger M. Groves^a

a: TU Delft Structural Integrity & Composites

b: Damen Shipyards

*n.tao@tudelft.nl

Abstract: *The use of thick composites and sandwich structures is increasing rapidly in diverse industries. Nevertheless, due to extreme loads such as impact and blast, various defects tend to occur in thick composites that can degrade the structural integrity severely. Hence, it is important to advance non-destructive testing (NDT) towards composite structures of significant thickness. The objective of this study is to perform shearography NDT of a composite ship hull section which has been multiple impacts in the RAMSSES project. In this paper, experimental results on the inspection of the large-scale composite structure are reported. Different loading scenarios including step heating and mechanical loading were performed for shearography NDT. A comparison between thermal loading and mechanical loading on thick composite inspection with shearography is presented. Here we aim at bringing the shearography technique out of the laboratory and extending its applications to composites with a thickness of more than 50 mm.*

Keywords: thick composite inspection; shearography NDT; composite ship hull section; multiple impacts; thermal and mechanical loading

1. Introduction

Owing to the remarkable advantages of lightweight and superior material properties, composite materials are seeing widespread applications in various industrial sectors [1–4]. Initially, these materials were mainly used in thin structures, but in recent years the use of thick composites and sandwich structures has increased rapidly in the marine sector (e.g. decks and hulls) [1] and in wind energy (e.g. wind turbine blades) [3,4]. Particularly, sandwich structures consisting of glass-fiber laminate skins bonded to a foam core are attractive in the marine sector due to their resistance to corrosion and underwater shocks and cost-effectiveness [5]. Those marine composites tend to have significant thicknesses (e.g. 50-200 mm) and to be large-scale (e.g. up to 85 m in length). Nevertheless, they are susceptible to extreme loads such as impacts or blasts that can result in various defects including delaminations, core debonding, and fiber breakage. The presence of those defects can degrade material properties and structural integrity severely. Hence, it is important to advance non-destructive testing (NDT) towards composite structures of significant thickness.

Some well-known NDT techniques, including ultrasonic testing and thermography, are difficult to be implemented for thick composite inspection. For ultrasonic testing, the problems of attenuation [3,4] and practical coupling issues with high surface roughness are significant. For thermography, it is difficult to heat evenly a large structure and to avoid rapid heat dissipation in thick composites [3,4]. Among the various NDT methods, shearography [6,7] is an optical NDT method that offers many advantages such as full-field and non-contact measurement. It reveals

defects by comparing two states of deformation of a test object. By applying a suitable loading, the defects can be revealed by looking for defect-induced anomalies in fringe maps or phase maps that can be related to surface strain components. It is possible to improve the sensitivity of shearography for defect detection by selecting suitable loading methods [8]. In shearography NDT, thermal loading is commonly used because of the advantages of versatility, non-contact, and low cost. Nevertheless, studies on the efficacy of mechanical loading on defect detection are rarely reported [9]. Our previous work with a 51 mm thick marine laminate [10] showed that defects at 5 to 20 mm depth can be detected successfully using shearography with thermal loading. Here we aim at bringing this technique out of the laboratory and extending shearography applications to large-scale composites with a thickness of more than 50 mm.

The objective of this study is to perform shearography NDT of a large-scale thick composite structure, specifically a composite ship hull section which had been subjected to multiple impacts. Different loading scenarios including step heating as well as mechanical loading were performed for shearography NDT. Section 2 describes the tested composite hull section and the shearography inspection system. Section 3 presents experimental inspection results of the large-scale composite structure. A comparison between thermal loading and mechanical loading on thick composite inspection with shearography is given in section 3 as well. The conclusions are given in section 4.

2. Shearography inspection system for the composite ship hull section

An overview of the composite ship hull section is shown in Fig. 1. The dimensions are about 6 meters in height and 2.3 meters in width. The structure is made from FRP laminate skins and foam cores. The composite ship hull section is a RAMSSES demonstrator [11,12] at Damen Shipyards. Before shearography inspection, multiple impact tests (<https://vimeo.com/522716506>) surpassing helicopter emergency landing loads have been performed on the hull shell and its composite helicopter deck for proving the resilience of composites to harsh marine environments. The impacted area on the hull shell is shown in Fig. 1(c).

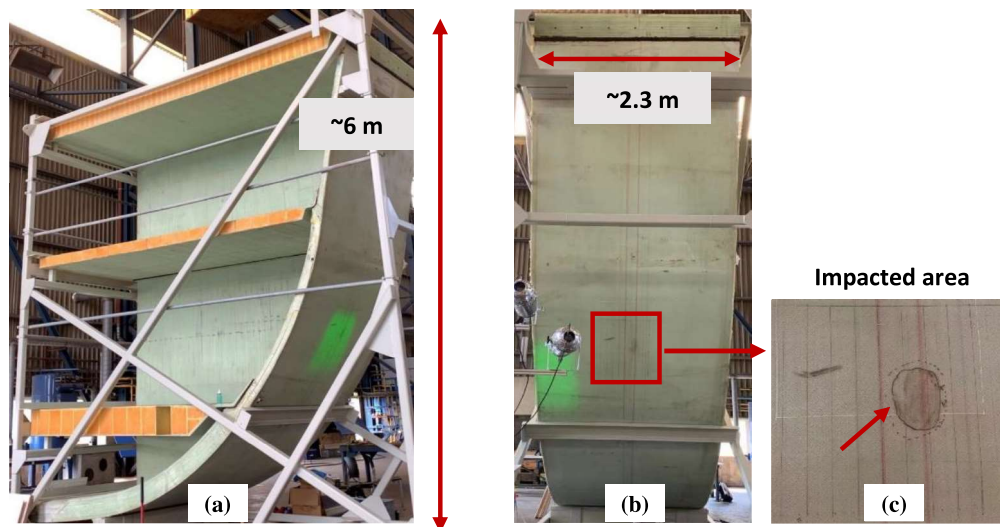


Figure 1 The composite ship hull section at Damen Shipyards: (a) Overall view. (b) Front view. (c) The area with multiple impacts on the hull shell.

In this study, shearography was used to perform NDT of the large-scale composite ship hull section. Its theory and operation principle are well reported in [6,7,9]. For this experiment, the shearography instrument [Fig. 2(a)] was adopted to measure the out-of-plane displacement derivative in a location where defect-induced deformation is expected to be high. Both thermal and mechanical loadings were applied for shearography NDT to evaluate their corresponding efficacies in defect detection.

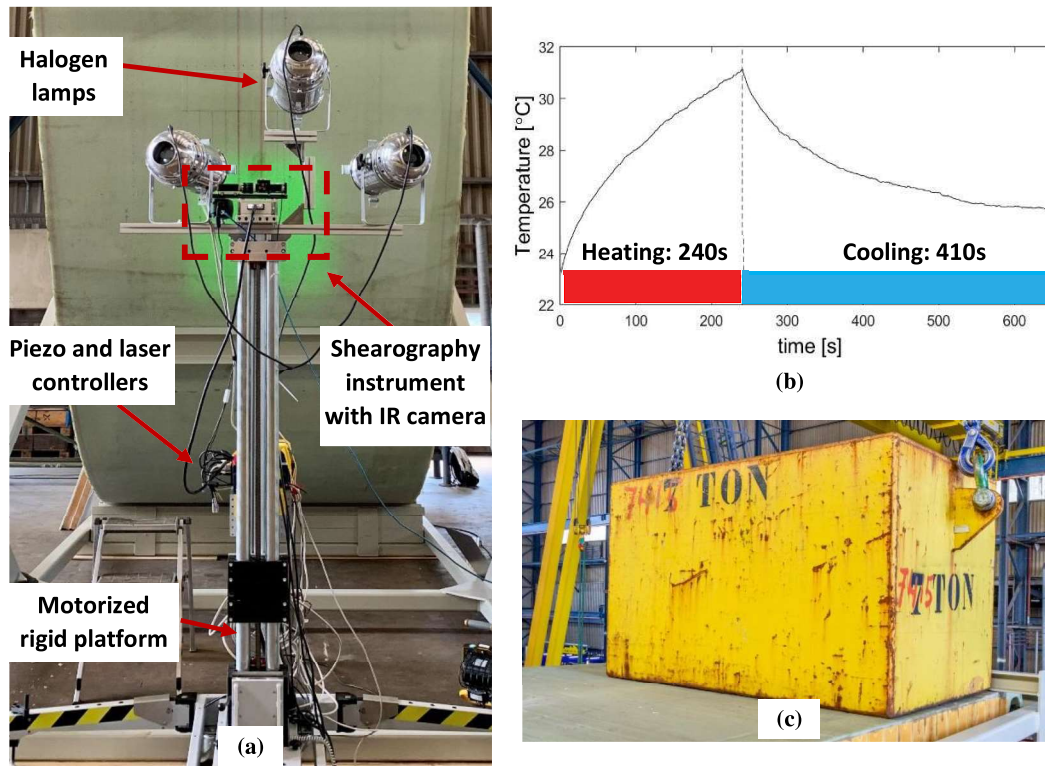


Figure 2 Testing campaign at Damen Shipyards: (a) Experimental inspection system. (b) Average temperature profile from thermal loading. (c) Applying mechanical loading.

The hull shell was illuminated with a Torus 532 laser source (optical power of 500 mW and wavelength of 532 nm) through a beam expander [Fig. 2(a)]. The formed speckle image was captured by a Pilot piA2400 camera with Linos MeVis-C 1.6/25 imaging lens and a Thorlabs bandpass filter through a Michelson interferometer. A piezo-electric actuator PSH 4z from Piezosystem Jena was used to enable temporal phase-shifting (three-step, 2.8 s per phase-shifting cycle). The shearing distance is about 9 mm (~34 pixels) in the vertical direction, which was determined experimentally to produce reliable phase maps for defect detection. During the testing, the shearography instrument was fixed on a motorized rigid platform. By adjusting the rigid platform, scanning in both horizontal and vertical directions can be achieved, enabling a large-area inspection.

Thermal loading was performed by three halogen lamps, each operating at full electrical power (1000W) [Fig. 2(a)]. During heating and cooling, the surface temperature of the hull shell was monitored with a FLIR A655 thermal infrared (IR) camera. The fields of view (FOVs) were inspected by repeating the same thermal loading [Fig. 2(b), 240s of heating], while the average temperature increase of the heated area was about 8 °C. Mechanical loading was done by

placing a 7-ton metal block on the structure [Fig.2(c)], which corresponds to the landing of a medium-sized helicopter.

3. Results and discussions

3.1 Shearography inspection results

The experimental results with thermal loading are shown in Fig. 3. A total area of about $1500 \times 900 \text{ mm}^2$ was inspected by stitching six FOVs of $600 \times 600 \text{ mm}^2$ [Fig. 3(a), 2 in the vertical direction by 3 in the horizontal with about 20% overlap for stitching]. Phase-shifted sets of speckle images were captured continuously during cooling. All sets of the recorded images were analyzed and stitched together to produce built-up phase maps of the whole area [Fig. 3(b)] that represent the evolution of the surface out-of-plane strain during cooling. The resultant phase map was further processed to obtain the compensated phase map [Fig. 3(c)], where the defect-induced deformation was extracted [10]. This compensated phase map reports the presence of damage in the structure. The stitching process can be further improved by considering the shape of the surface, the positions of the camera and the laser [13]. The damage in the impacted region is not obvious, this can be because its position is close to the edge of the FOVs no.5 and no.6, which makes it difficult to extract actual defect deformation.

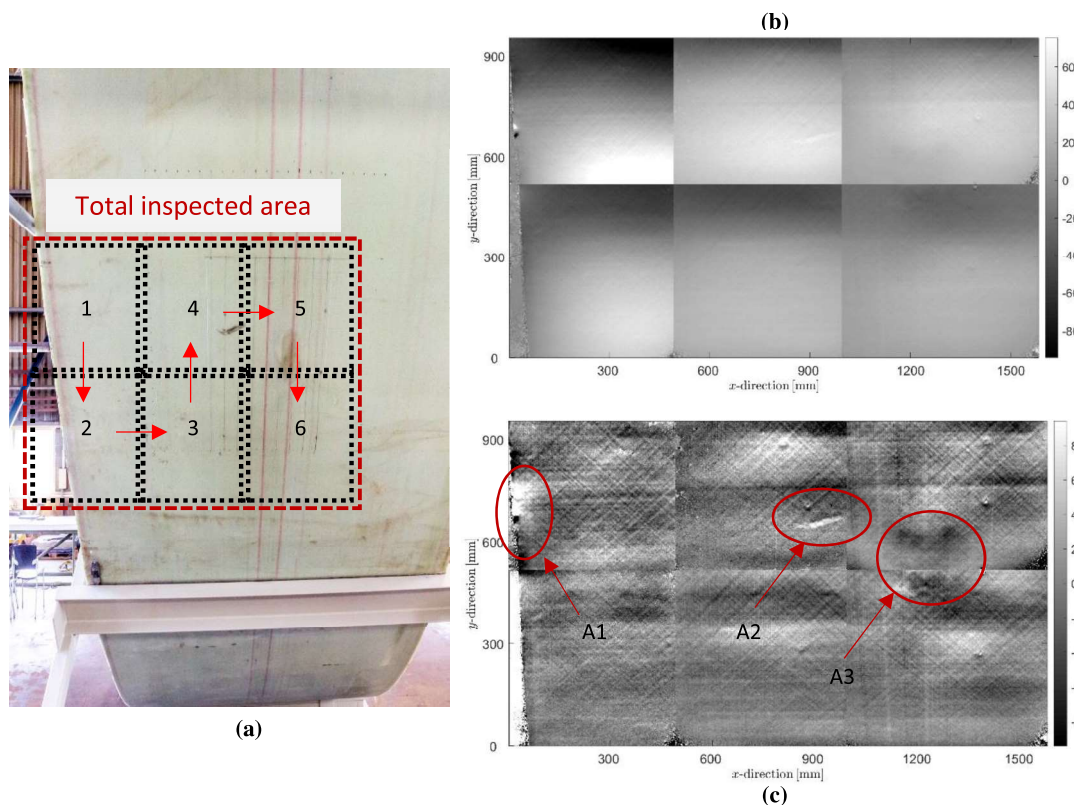


Figure 3 Stitched inspection results for six FOVs with thermal loading: (a) Total inspected area (FOVs no. 1-6). (b) Origin phase map. (c) Compensated phase map, A1 - skin-to-core debonding, A2 - heat damage, A3 - impact damage of interest. [Unit of phase is radian]

The results of the detailed inspection of the impacted area are shown in Fig. 4. Both thermal loading and mechanical loading were applied for shearography NDT. The compensated phase maps with thermal and mechanical loadings are shown in Figs. 4(b) and 4(c), respectively. The

impact damage (shown as strain anomalies in compensated phase maps) was detected successfully from both thermal and mechanical loadings in the same region, which indicates the reliability of shearography. These strain anomalies are expected to be due to delaminations and potential skin-to-core debonding in the thick structure.

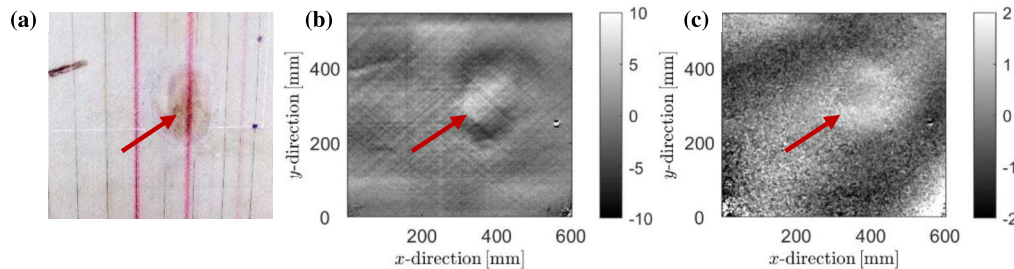


Figure 4 Detailed inspection of the impact region (a) The inspection area with multiple impacts. (b) The compensated phase map with thermal loading. (c) The compensated phase map with mechanical loading. [Unit of phase is radian]

3.2 Discussion

The principle of shearography NDT relies on deformation changes of the test object surface. Therefore developing shearography NDT operation eventually becomes developing a suitable method of loading to deform the object that can reveal defects [9].

For thermal loading, it is easy to apply, and loading parameters such as intensity and time of heating are easy to control. Uniform heating can be useful to inspect a large structure. Nevertheless when inspecting deep defects, e.g. deeper than 20 mm, more time is required for heat to propagate (tens of minutes). It can be noted that heating lamps can cause hot airflow during heating and cooling which should be treated carefully in experiments.

For mechanical loading, it is possible to reveal critical defects only and to avoid trivial defects if the test object is loaded in a similar stress state to the actual working load in-service [9]. One possible advantage can be fast measurement time as heat propagation is not needed. However, the deformation of the test object is difficult to estimate in experiments. Suitable loading increments need to be determined for shearography. The loading process usually introduces large rigid body movements that may cause unfavorable speckle decorrelation in shearography. This was observed during the inspection. The unloading process is found to be acceptable in experiments for producing reliable phase maps. The challenge is to develop an adequate mechanical loading scenario to obtain the detectable defect-induced strain. For this, prior numerical modelling can be done to give an estimation of the needed load for expected critical defects.

4. Conclusions

This experimental study of the composite hull section demonstrates that shearography can be a suitable NDT technique for large-scale composite structures of significant thickness up to 50 to 200 mm. Both thermal and mechanical loadings were evaluated for shearography NDT. Compensated phase maps from the two loadings both identified the presence of impact damage successfully. Uniform heating can be useful for inspecting a large structure with shearography, however significant time, e.g., 10 to 20 minutes, can be needed for heat to propagate when inspecting deep defects. Mechanical loading is possible to reveal critical defects directly and fast

in speed, nevertheless, one precaution is to avoid excessive rigid body movements. Future work can be to determine suitable mechanical loading increments for shearography and to study the detection capability of shearography with mechanical loading.

Acknowledgements

Access to the composite ship hull section subjected to multiple impacts is provided by the partners of the European Innovation Action RAMSSES project. This research was supported by the Operationeel Programma Zuid-Nederland (Op-Zuid) Project as part of the Dutch Composite Maintenance Centre (DCMC), supported by the Europees Fonds voor Regionale Ontwikkeling (EFRO) and the North Brabant province of the Netherlands.

5. References

1. Greene E. Inspection techniques for marine composite construction and NDE. Report No SSC-463, United States Ship Structure Committee, Washington, DC 2012.
2. Groves RM. Inspection and Monitoring of Composite Aircraft Structures. In: Beaumont PWR, Zweben CH, editors. *Comprehensive Composite Materials II*, Oxford: Elsevier; 2018, p. 300–11.
3. Ibrahim ME. Nondestructive evaluation of thick-section composites and sandwich structures: A review. *Composites Part A: Applied Science and Manufacturing* 2014;64:36–48.
4. Nsengiyumva W, Zhong S, Lin J, Zhang Q, Zhong J, Huang Y. Advances, limitations and prospects of nondestructive testing and evaluation of thick composites and sandwich structures: A state-of-the-art review. *Composite Structures* 2021;256:112951.
5. Tran P, Ghazlan A, Nguyen TP, Gravina R. Experimental and theoretical damage assessment in advanced marine composites. In: Pemberton R, Summerscales J, Graham-Jones J, editors. *Marine Composites*, Woodhead Publishing; 2019, p. 55–84.
6. Steinchen W, Yang L. Digital shearography: theory and application of digital speckle pattern shearing interferometry. vol. 100. CCH; 2003.
7. Francis D, Tatam RP, Groves RM. Shearography technology and applications: a review. *Measurement Science and Technology* 2010;21:102001.
8. Jiang H, Ma Y, Dai M, Dai X, Yang F, He X. Panoramic dual-directional shearography assisted by a bi-mirror. *Appl Opt* 2020;59:5812–20.
9. Hung YY. Shearography for non-destructive evaluation of composite structures. *Optics and Lasers in Engineering* 1996;24:161–82.
10. Tao N, Anisimov AG, Groves RM. Shearography non-destructive testing of thick GFRP laminates: Numerical and experimental study on defect detection with thermal loading. *Composite Structures* 2022;282:115008.
11. Cau C, Krause M, Roland F. RAMSSES--Realisation and Demonstration of Advanced Material Solutions for Sustainable and Efficient Ships. *Proceedings of 7th Transport Research Arena TRA 2018* 2018.
12. Paboeuf S, de Bruijn A, Evegren F, Krause M, Elenbaas M. A “Fast Track to Approval” Process for Innovative Maritime Solutions. In: Okada T, Suzuki K, Kawamura Y, editors. *Practical Design of Ships and Other Floating Structures*, Singapore: Springer Singapore; 2021, p. 51–63.
13. Anisimov AG, Serikova MG, Groves RM. 3D shape shearography technique for surface strain measurement of free-form objects. *Appl Opt* 2019;58:498–508.