

RSC Advances



This article can be cited before page numbers have been issued, to do this please use: H. Al Kutubi, L. Rassaei, W. Olthuis, G. Nelson, J. S. Foord, P. Holdway, M. Carta, R. Malpass-Evans, N. B. McKeown, E. Tsang, R. Castaing, T. Forder, M. D. Jones, D. He and F. Marken, *RSC Adv.*, 2015, DOI: 10.1039/C5RA15131G.



This is an *Accepted Manuscript*, which has been through the Royal Society of Chemistry peer review process and has been accepted for publication.

Accepted Manuscripts are published online shortly after acceptance, before technical editing, formatting and proof reading. Using this free service, authors can make their results available to the community, in citable form, before we publish the edited article. This *Accepted Manuscript* will be replaced by the edited, formatted and paginated article as soon as this is available.

You can find more information about *Accepted Manuscripts* in the [Information for Authors](#).

Please note that technical editing may introduce minor changes to the text and/or graphics, which may alter content. The journal's standard [Terms & Conditions](#) and the [Ethical guidelines](#) still apply. In no event shall the Royal Society of Chemistry be held responsible for any errors or omissions in this *Accepted Manuscript* or any consequences arising from the use of any information it contains.



COMMUNICATION

Polymers of Intrinsic Microporosity as High Temperature Templates for the Formation of Nanofibrous Oxides

H. Al Kutubi,^{a,b} L. Rassaei,^b W. Olthuis,^c G. W. Nelson,^d J. S. Foord,^e P. Holdway,^f M. Carta,^g R. Malpass-Evans,^g N. B. McKeown,^g S. C. Tsang,^h R. Castaing,^a T. R. Forder,^a M. D. Jones,^a D. He,^a and F. Marken^{*a}

Received 00th January 20xx,
Accepted 00th January 20xx

DOI: 10.1039/x0xx00000x

www.rsc.org/

The highly rigid molecular structure of Polymers of Intrinsic Microporosity (PIM) – associated with a high thermolysis threshold – combined with the possibility to fill intrinsic micropores allows the direct “one-step” templated conversion of metal nitrates into nano-structured metal oxides. This is demonstrated here with PIM-EA-TB and with PIM-1 for the conversion of $\text{Pr}(\text{NO}_3)_3$ to Pr_6O_{11} .

Nano-templating offers rapid access to novel nano-structured materials and interfaces¹ in particular for technologies where high surface area inorganic architectures are desirable.² Template hosts such as regular opaloid structures,³ surfactant-based nano-structures,⁴ or novel MOF structures⁵ have been proposed. Here, polymers of intrinsic microporosity (PIM)⁶ are introduced as “high temperature templates” for “one-step” metal oxide nano-structure growth as demonstrated for the case of Pr_6O_{11} .

Polymers of intrinsic microporosity represent a novel group of polymers with a rigid backbone (see structures in Figure 1) that prevents them from collapsing into a close-packed conformation even when heated up. Space is created within the polymer, allowing for permanent microporosity and leading to a surface area as high as $900 \text{ m}^2 \text{ g}^{-1}$ for PIM-1⁷ and $1027 \text{ m}^2 \text{ g}^{-1}$ for PIM-EA-TB.⁸ PIM

materials are readily casted from solution into films and have been investigated for applications in gas separation membranes, catalysis, and gas storage.⁹ From thermogravimetric data[†] (TGA, see Figure 1) it is clear that these rigid polymer structures also show considerable high temperature stability (after some initial weight loss due to water desorption below 100°C , decomposition onset occurs for PIM-EA-TB at 310°C and for PIM-1 at 480°C , both with charring). Therefore, in this study we contrast the ability of PIM-EA-TB and PIM-1 to function as template hosts for high temperature metal oxide nanostructure synthesis. A suitable model nano-structured metal oxide with promise for application in sensors¹⁰ and in catalysis¹¹ is Pr_6O_{11} .

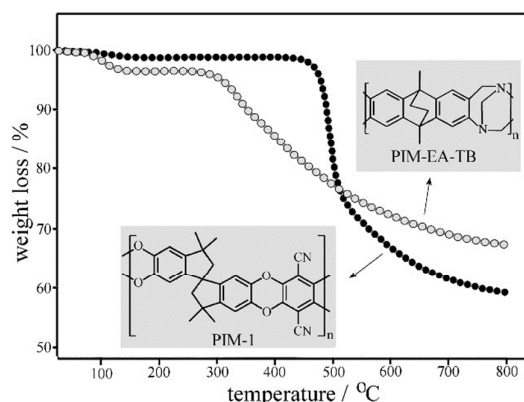


Figure 1. Thermogravimetric data and molecular structures for PIM-EA-TB and PIM-1.

The synthesis of praseodymium oxides has been carried out previously by chemical vapour deposition,¹² calcination of praseodymium hydroxide ($\text{Pr}(\text{OH})_3$),^{13,14} electro-deposition,¹⁵ or by thermal transformation of a praseodymium-containing precursor compound.¹⁶ The products obtained through thermal oxidation depend on both the precursor as well as oxidation conditions such

^a Remi Castaing, Dr. Thomas R. Forder, Dr. Matthew D. Jones, Dr. Daping He, Prof. Frank Marken, Department of Chemistry, University of Bath, Claverton Down, Bath BA2 7AY, UK. Email f.marken@bath.ac.uk.

^b Hanan Al Kutubi, Dr. Liza Rassaei, Department of Chemical Engineering, Delft University of Technology, Delft, The Netherlands.

^c Dr. Wouter Olthuis, BIOS/Lab-on-a-Chip group, University of Twente, PO Box 217, 7500 Enschede, The Netherlands.

^d Dr. Geoffrey W. Nelson, Imperial College London, Department of Materials, Royal School of Mines, Exhibition Road, London, SW7 2AZ, UK.

^e Prof. John S. Foord, Chemistry Research Laboratories, Oxford University, South Parks Road, Oxford OX1 3TA, UK.

^f Dr. Philip Holdway, Department of Materials, Begbroke Science Park, Sandy Lane, Yarnton, Oxford, OX5 1PF, UK.

^g Dr. Mariolino Carta, Richard Malpass-Evans, Prof. Neil B. McKeown, School of Chemistry, University of Edinburgh, West Mains Road, Edinburgh, EH9 3JJ, UK.

^h Prof. Shik Chi Tsang, Inorganic Chemistry Laboratory, University of Oxford, South Parks Road, Oxford OX1 3QR, UK.

[†] Electronic Supplementary Information (ESI) available: additional scanning electron microscopy data and EDX data. See DOI: 10.1039/x0xx00000x



as temperature and oxygen partial pressure. The oxygen deficient Pr_6O_{11} phase can be formed as dominant phase at temperatures higher than 465 °C.¹⁷ Bäumer and coworkers^{11b} investigated the formation of nanostructured praseodymium oxide via thermal decomposition of praseodymium nitrate with and without carbon-based templates. Here, we report the formation of praseodymium oxide structures not in bulk, but directly at the surface of tin-doped indium oxide (ITO) electrodes.

When the PIM host solution (1 mg/mL in chloroform) and $\text{Pr}(\text{NO}_3)_3$ solution (1 mg/mL in DMF) are mixed in 1:1 weight ratio and deposited onto ITO, calcination at 500 °C in air affords a thin film of oxide materials on ITO (see Experimental, Figure 2).

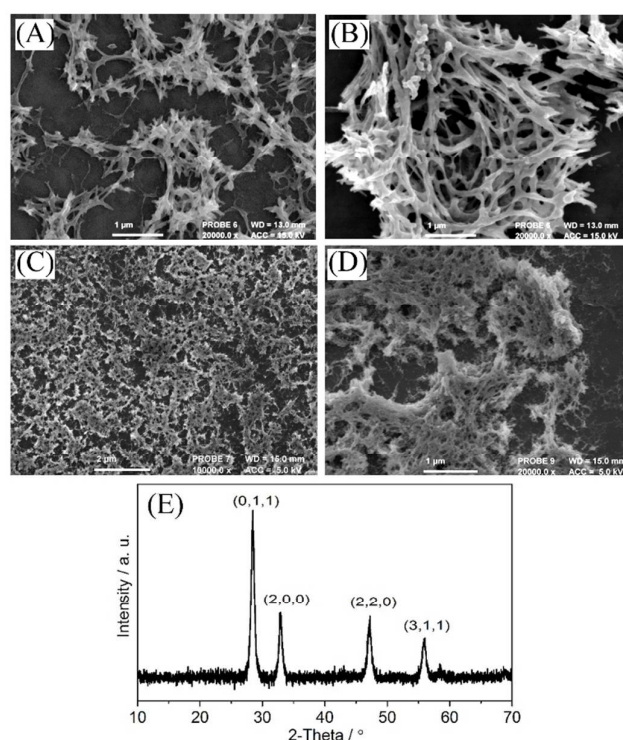


Figure 2. Electron micrographs of (A) a 10-layer PIM-EA-TB – $\text{Pr}(\text{NO}_3)_3$ (1:1) film after calcination, (B) a 20-layer PIM-EA-TB – $\text{Pr}(\text{NO}_3)_3$ (1:1) film after calcination, (C) a 10-layer PIM-1 – $\text{Pr}(\text{NO}_3)_3$ (1:1) film after calcination and (D) a higher resolution image of the same sample. (E) XRD analysis.

The presence of praseodymium oxide is confirmed by EDX (see Figure SI1D) and by XRD (Figure 2E, with characteristic lines^{15,11b}). Electron micrographs show fibrous deposits of Pr_6O_{11} on the ITO substrate (Figure 2). With PIM-EA-TB as host template “leaf-like” nano-structures are seen. Doubling the amount of precursor deposit resulted in slightly coarser structures, which must reflect the pore geometry of the precursor at the point when solidification of the oxide precursor occurs. Changing the ratio of PIM-EA-TB to $\text{Pr}(\text{NO}_3)_3$ resulted in similar structures (see Figure SI1A,B,C). When investigating the PIM-1 template (see Figure 2C,D) it became

apparent that a much finer nano-structure with filaments down to 20 nm or less are formed. BET-based pore size data for PIM-EA-TB polymer (12 – 40 Å¹⁸) and for PIM-1 polymer (5 to 15 Å¹⁹) suggest that in both the parent polymers only comparably smaller pores are present. The feature size in the Pr_6O_{11} deposits appear considerably bigger for PIM-EA-TB but more similar to the original pore size for PIM-1. Therefore the feature size could be linked to the behaviour of the polymer template at elevated temperature. TGA data in Figure 1 clearly show the higher thermal stability of PIM-1, which is likely to result in a finer oxide nano-structure that more closely reflects the original PIM-1 template pores.

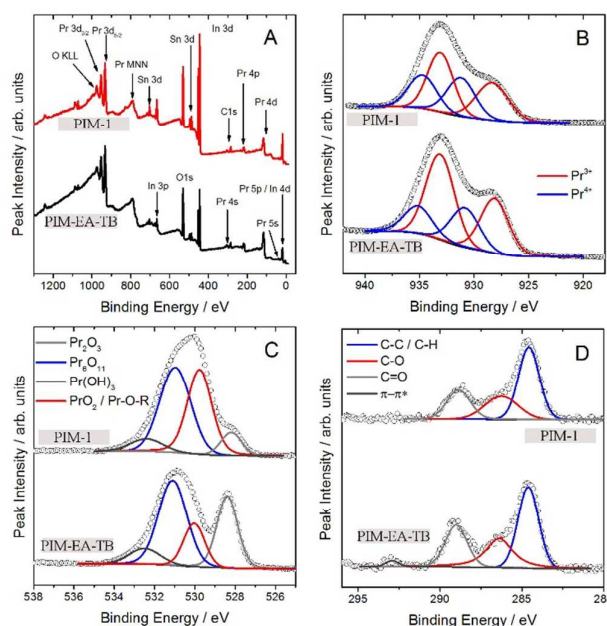


Figure 3. XPS survey spectra (A) of PIM-EA-TB and PIM-1 and core level data for (B) $\text{Pr}3d_{5/2}$ (with red and blue curve fits for Pr^{3+} and Pr^{4+} species, respectively), (C) $\text{O}1s$, (D) $\text{C}1s$.

In order to demonstrate the absence of polymer remnants, further surface analysis has been performed with XPS (Figure 3). Apart from the underlying ITO surface elements clear evidence for Pr, C, and O is observed in the survey scan. Carbon signals are very low and assigned to adventitious surface-adsorbed molecules (or possibly remnants of the template). Oxygen signals are assigned predominantly to Pr_6O_{11} , but with some other species present at the surface. Wolfrum *et al.*²⁰ have studied thin Pr_xO_y films made from Pr_6O_{11} targets and their work is the primary basis for fitting the $\text{O}1s$ spectra here. Four peaks were required to curve fit the $\text{O}1s$ spectra. The two main component at ≈ 528.5 eV and ≈ 531 eV most likely belong to Pr_2O_3 and Pr_6O_{11} , respectively. Lukehoff *et al.*²¹ indicated that the signal at ≈ 532 eV can be ascribed to Pr-based hydroxides, such as $\text{Pr}(\text{OH})_3$. These would be expected from the breakdown of Pr_6O_{11} in the presence of surface water (eventually leading to PrO_2 formation).²¹ The feature at ≈ 529.5 eV could be



either indicative of the presence of PrO_2 ²² or be related to surface adsorbates in the form of Pr-O-R ,^{23,21} both species have O1s signal known to overlap with the Pr_6O_{11} O1s signal. As seen in Table 1, the Pr_6O_{11} and Pr-hydroxide content at surfaces seem independent of the method of preparation. However, use of PIM-EA-TB favours the additional formation of Pr_2O_3 (Pr^{3+}), whilst use of PIM-1 favours the formation of PrO_2 (Pr^{4+}) and surface adsorbates. The chemical reasons for this difference are currently not fully understood.

Table 1. Oxygen composition data from XPS in as-prepared Pr_6O_{11} .
% O1s Composition

Species	PIM-EA-TB	PIM-1
Pr_2O_3	29.2	8.2
PrO_2 /adsorbates	16.7	39.2
Pr_6O_{11}	45.3	45.8
Hydroxides	8.8	6.9

Wolfram *et al.*²³ note that unambiguous fitting of the Pr3d core levels is difficult and remains controversial. Again using the above reference as a model, four chemical environments were curve fitted. The line pair at higher binding energy (≈ 931 eV and ≈ 935 eV) are ascribed to Pr^{4+} species (e.g. Pr_6O_{11} and PrO_2). Assuming that they reflect chemical environments at the surface and are not satellites.^{23,25} The line pair at lower binding energy (≈ 928 eV and ≈ 933 eV) originate from Pr^{3+} (e.g. Pr_2O_3 and Pr(OH)_3). The ratio between Pr^{3+} : Pr^{4+} species is approximately 2:1 and 4:3 for PIM-EA-TB and PIM-1, respectively. Notwithstanding the different chemical states, the surface O/Pr ratio is 4.6 and 2.6 for PIM-EA-TB and PIM-1, respectively. These ratios are quite high - the stoichiometric and expected O/Pr ratio for Pr_2O_3 (Pr^{3+}) and Pr_6O_{11} (Pr^{4+}) is 1.5 and 1.8, respectively. This may indicate that the O1s signal is influenced by other sources of surface oxygen, other than the Pr-oxides (e.g. hydroxides, water, the underlying substrate, etc.). One expects an O/Pr ratio $< 2:1$ for the Pr-based oxides.²³ It is clear from Table 2 that PIM-EA-TB has a higher Pr^{3+} component than PIM-1, and vice versa in the case of the Pr^{4+} species. In future, bulk elemental analytical methods have to be employed to further investigate bulk phase purity and possible impurities from the thermolysis process in the resulting products as a function of thermolysis time and temperature.

Table 2. $\text{Pr}^{3+}/\text{Pr}^{4+}$ composition data from XPS in as-prepared Pr_6O_{11} .

	Pr3d _{5/2} Binding Energy (eV)				Pr3d composition (%)	
	928	931	933	935	Pr^{3+}	Pr^{4+}
PIM-EA-TB	27.0	19.2	39.8	14.0	66.8	33.2
PIM-1	25.9	23.1	31.5	19.5	57.4	42.6

Electrochemical testing of Pr_6O_{11} nano-structures was performed in aqueous 0.1 M KNO_3 (Figure 4). Nyquist plots (Figure 4A) and Bode plots (not shown) suggest a high frequency switch from resistive to capacitive behaviour associated with the ITO substrate time constant (for bare ITO $110 \Omega \times 15 \mu\text{F} = 1.65$ ms, Figure 4D). With Pr_6O_{11} films deposited an additional resistive component, R_{et} is observed associated with charging of the nano-structured deposit. The impedance for this charging decreases from a calcined 10-layer PIM-EA-TB – $\text{Pr(NO}_3)_3$ deposit to calcined 20-layer PIM-EA-TB – $\text{Pr(NO}_3)_3$ and again to calcined 10-layer PIM-1 – $\text{Pr(NO}_3)_3$. This result indicates an increase in oxide surface area in this sequence.

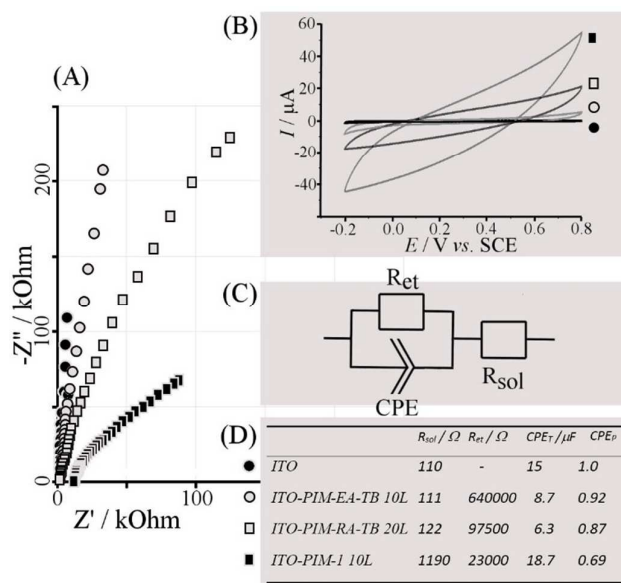


Figure 4. (A) Nyquist plots (1 Hz to 128 kHz) with impedance data for bare ITO, PIM-EA-TB 10-layer, PIM-EA-TB 20-layer, and PIM-1 10-layer deposits biased at 0.3 V vs. SCE in 0.1 M KNO_3 . (B) Cyclic voltammograms (scan rate 200 mVs^{-1}) under the same conditions. (C) Equivalent circuit and (D) summary of data.

Complementary cyclic voltammetry data (Figure 4B) also demonstrate the decrease in impedance as an increase in charging current. Full charging and therefore full capacitive characteristics would require more time (or a higher conductivity of the oxide). The electrochemical properties are consistent with those reported previously for Pr_6O_{11} with potential applications in charge storage and sensing. However, the methodology for oxide nano-structure formation in PIM templates will be applicable for a much wider range of oxides and mixed oxides.

Conclusions



Praseodymium oxide nano-structures have been formed in a convenient and novel "one-step" process using a high temperature template based on polymers of intrinsic microporosity. The resulting structures differ from those obtained through simple calcination and show a leaf-like or nano-fibrous structures. Finer structures are formed with the more thermally stable PIM-1 template. The results indicate that this methodology could be used beneficially for the rapid formation of a wider range of nano-structured metal oxide as well as mixed metal oxides with future applications in electronic, sensor, or solar cell components.

Notes and references

† Experimental

Chemical Reagents. Praseodymium nitrate hexa-hydrate, N,N-dimethylformamide (DMF) and chloroform were obtained from Sigma-Aldrich and used without further purification. Polymers with intrinsic microporosity PIM-EA-TB⁸ and PIM-1²³ were prepared following literature procedures. Tin-doped indium oxide glass plates (ITO) with a resistivity of 15 Ω /square were obtained from Image Optics Components Ltd. (Basildon, UK). A KCl-saturated calomel (SCE) reference electrode was obtained from Radiometer.

Instrumentation. The morphology of the samples was analysed using a JEOL FESEM6301F field emission scanning electron microscopy (FE-SEM). XPS experiments were conducted using a Thermo K Alpha (Thermo Scientific) spectrometer (operating at $\approx 10^{-8}$ – 10^{-9} Torr) with a 180° double focusing hemispherical analyser running in constant analyser energy (CAE) mode and a 128-channel detector. A mono-chromated Al K α radiation source (1486.7 eV) was used. Peak fitting was conducted using XPS Peak Fit (v. 4.1) software using Shirley background subtraction. Peaks were referenced to the adventitious carbon C1s peak (284.6 eV) and peak areas were normalized to the photoelectron cross-section of the F1s photoelectron signal using atomic sensitivity factors.²⁴ An Elite Thermal Systems Ltd. tube furnace was used to remove the possible organic contamination on the ITO electrodes and for calcination of metal oxides. Electrochemical testing was performed using an Ecochemie Autolab PGSTAT12 potentiostat system. TGA data were collected on a Setaram Setsys Evolution TGA instrument. The samples were heated under Ar from 20 °C until 800 °C at 10 K per minute.

Procedure for nano-Pr₆O₁₁ Film Deposition. Tin-doped indium oxide (ITO) coated glass slides were cut into 1 cm × 3 cm strips and cleaned by rinsing with water and ethanol, followed by calcination at 500 °C for one hour. A solution of 1 mg/mL PIM in chloroform was mixed with a solution of 1 mg/mL Pr(NO₃)₃ · 6H₂O in DMF in the desired ratio. From the resulting mixture, 25 μ L was deposited onto a clean ITO plate covering approximately 1 cm² and dried in an oven at 100 °C for 15 minutes. This deposition process was repeated for a desired number of layers and finally followed by calcination in a tube furnace at 500 °C for 1 hour.

- [1] I.W. Hamley, *Nanotechnology*, 2003, **14**, R39.
- [2] P.V. Braun, P. Osenar, V. Tohver, S.B. Kennedy and S.I. Stupp, *J. Amer. Chem. Soc.*, 1999, **121**, 7302.
- [3] A. Stein, *Microporous Mesoporous Mater.*, 2001, **44**, 227.
- [4] G.J.D. Soler-illia, C. Sanchez, B. Lebeau and J. Patarin, *Chem. Rev.*, 2002, **102**, 4093.
- [5] X. Xu, R. Cao, S. Jeong and J. Cho, *Nano Lett.*, 2012, **12**, 4988.
- [6] N.B. McKeown and P.M. Budd, *Chem. Soc. Rev.*, 2006, **35**, 675.
- [7] P.M. Budd, B.S. Ghanem, S. Makhseed, N.B. McKeown, K.J. Msayib and C.E. Tattershall, *Chem. Commun.*, 2004, 230.
- [8] M. Carta, R. Malpass-Evans, M. Croad, Y. Rogan, J.C. Jansen, P. Bernardo, F. Bazzarelli and N.B. McKeown, *Science*, 2013, **339**, 303.
- [9] N.B. McKeown and P.M. Budd, *Macromolecules*, 2010, **43**, 5163.
- [10] (a) X.S. Liang, Y.H. He, F.M. Liu, B. Wang, T.G. Zhong, B. Quan and G. Lu, *Sens. Actuators B-Chem.*, 2007, **125**, 544. (b) S. Shrestha, C.M.Y. Yeung, C.E. Mills, J. Lewington and S.C. Tsang, *Angew. Chem. Internat. Ed.*, 2007, **46**, 3855.
- [11] (a) E.S. Putna, J.M. Vohs, R.J. Gorte and G.W. Graham, *Catal. Lett.*, 1998, **54**, 17. (b) Y. Borchert, P. Sonstrom, M. Wilhelm, H. Borchert and M. Bäumer, *J. Phys. Chem. C*, 2008, **112**, 3054.
- [12] H.C. Aspinall, J. Gaskell, P.A. Williams, A.C. Jones, P.R. Chalker, P.A. Marshall, J.F. Bickley, L.M. Smith and G.W. Critchlow, *Chem. Vapor Dep.*, 2003, **9**, 235.
- [13] X.W. Ouyang, S.S. Yuan, Q.B. Qiu, W.W. Zeng, G.A. Hope and H.H. Li, *Inorg. Chem. Commun.*, 2014, **46**, 21.
- [14] S. Shrestha, C.M.Y. Yeung, F. Marken, C.E. Mills and S.C. Tsang, *Sens. Actuators B Chem.*, 2007, **123**, 400.
- [15] S. Shrestha, F. Marken, J. Elliott, C.M.Y. Yeung, C.E. Mills and S.C. Tsang, *J. Electrochem. Soc.*, 2006, **153**, C517.
- [16] S. Zinatloo-Ajabshir and M. Salavati-Niasari, *New J. Chem.*, 2015, **39**, 3948.
- [17] G.A.M. Hussein, B.A.A. Balboul, M.A.A. Warith and A.G.M. Othman, *Thermochim. Acta*, 2001, **369**, 59.
- [18] E. Madrid, Y.Y. Rong, M. Carta, N.B. McKeown, R. Malpass-Evans, G.A. Attard, T.J. Clarke, S.H. Taylor, Y.T.



- Long and F. Marken, *Angew. Chem. Internat. Ed.*, 2014, **53**, 10751.
- [19] M. Heuchel, D. Fritsch, P.M. Budd, N.B. McKeown and D. Hofmann, *J. Membrane Sci.*, 2008, **318**, 84.
- [20] D. Wolfram, M. Ratzke, M. Kappa, M.J. Montenegro, M. Döbeli, Th. Lippert and J. Reif, *Mater. Sci. Engineer. B*, 2004, **109**, 24.
- [21] S. Lutkehoff, M. Neumann, A. Slebarski, *Phys. Rev. B*, 1995, **52**, 13808.
- [22] M. Sawangphruk and J.S. Foord, *Diam. Rel. Mater.*, 2010, **19**, 885.
- [23] (a) P.M. Budd, K.J. Msayib, C.E. Tattershall, B.S. Ghanem, K.J. Reynolds, N.B. McKeown and D. Fritsch, *J. Mem. Sci.*, 2005, **251**, 263. (b) P.M. Budd, E.S. Elabas, B.S. Ghanem, S. Makhseed, N.B. McKeown, K.J. Msayib, C.E. Tattershall and D. Wang, *Adv. Mater.*, 2004, **16**, 456.
- [24] C.D. Wagner, L.E. Davis, M.V. Zeller, J.A. Taylor, R.M. Raymond and L.H. Gale, *Surf. Interface Anal.*, 1981, **3**, 211.

Graphical Abstract

Highly rigid polymers of intrinsic microporosity (PIM) offer novel high temperature template materials for the formation of nanostructured metal oxides. Electroactive nanostructured Pr_6O_{11} films are prepared on tin-doped indium oxide substrates in a “one-step” process by calcination of $\text{Pr}(\text{NO}_3)_3$ embedded in a PIM template.

Keywords: sensor; nanostructure; oxide; catalysis; energy storage

