

Synthesis of severe lattice distorted MoS_2 coupled with hetero-bonds as anode for superior lithium-ion batteries

Liu, Yanyan; Zhang, Long; Wang, Hongqiang; Yu, Chuang; Yan, Xinlin; Liu, Qiunan; Xu, Bo; Wang, Li min

DOI

[10.1016/j.electacta.2018.01.023](https://doi.org/10.1016/j.electacta.2018.01.023)

Publication date

2018

Document Version

Accepted author manuscript

Published in

Electrochimica Acta

Citation (APA)

Liu, Y., Zhang, L., Wang, H., Yu, C., Yan, X., Liu, Q., Xu, B., & Wang, L. M. (2018). Synthesis of severe lattice distorted MoS_2 coupled with hetero-bonds as anode for superior lithium-ion batteries. *Electrochimica Acta*, 262, 162-172. <https://doi.org/10.1016/j.electacta.2018.01.023>

Important note

To cite this publication, please use the final published version (if applicable).
Please check the document version above.

Copyright

Other than for strictly personal use, it is not permitted to download, forward or distribute the text or part of it, without the consent of the author(s) and/or copyright holder(s), unless the work is under an open content license such as Creative Commons.

Takedown policy

Please contact us and provide details if you believe this document breaches copyrights.
We will remove access to the work immediately and investigate your claim.



Synthesis of severe lattice distorted MoS₂ coupled with hetero-bonds as anode for superior lithium-ion batteries

Yanyan Liu^a, Long Zhang^{a,*}, Hongqiang Wang^b, Chuang Yu^c, Xinlin Yan^d, Qiunan Liu^a, Bo Xu^a, Li-min Wang^a

^a State Key Laboratory of Metastable Materials Science and Technology, Yanshan University, Qinhuangdao, Hebei 066004, China

^b College of Chemistry & Environmental Science, Hebei University, Baoding, Hebei 071000, China

^c Department of Radiation Science and Technology, Delft University of Technology, Mekelweg 15, Delft 2629 JB, The Netherlands

^d Institute of Solid State Physics, Vienna University of Technology, Wiedner Hauptstr. 8-10, 1040 Vienna, Austria



ARTICLE INFO

Article history:

Received 16 November 2017

Received in revised form

29 December 2017

Accepted 4 January 2018

Available online 4 January 2018

Keywords:

MoS₂

Polyethylene glycol

Oxygen-containing groups

Lattice distortion

Lithium-ion batteries

ABSTRACT

Exploration of advanced anode materials is a highly relevant research topic for next generation lithium-ion batteries. Here, we report severe lattice distorted MoS₂ nanosheets with a flower-like morphology prepared with PEG400 as additive, which acts not only as surfactant but importantly, also as reactant. Notably, in the absence of a carbon-related incorporation/decoration, it demonstrates superior electrochemical performance with a high reversible capacity, a good cycling stability, and an excellent rate capability, originated from the advantages of synthesized MoS₂ including enlarged interlayer spacing, 1T-like metallic behavior, and coupling of Mo–O–C (and Mo–O) hetero-bonds. PEG-assisted synthesis is believed applicable to other anode materials with a layered structure for lithium-ion batteries.

© 2018 Elsevier Ltd. All rights reserved.

1. Introduction

Lithium ion batteries (LIBs) have been the most promising power source for electronic devices. With the intense development of smart devices and electric vehicles, further improvements of energy density, cycling life, and ability of fast charging/discharging are anticipated [1–3]. Graphitized carbon is currently served as a commercial negative electrode, but the low theoretical capacity (372 mAh g^{−1}) and the poor rate performance restrict its application in many fields [4,5]. Transition-metal sulfides have attracted tremendous attention to be used in LIBs because of their high theoretical capacity and relatively good electrochemical performance [6]. Among these materials, molybdenum disulfide (MoS₂) has been intensively investigated as one of the most promising next-generation anode materials for LIBs because of several advantages including [7–12]: (1) a high theoretical capacity of 670 mAh g^{−1}; (2) a layered structure with a large interlayer spacing of 0.62 nm and thus weak van der Waals forces between the S–Mo–S neighboring layers, which is beneficial to the intercalation of Li⁺;

(3) existence of 1T-like structure leading to metallic behavior to enhance the electrical conductivity; and (4) a low cost and easy fabrications.

However, there are also challenges in the development of MoS₂ anode toward high electrochemical performance such as a poor cycling stability and inferior rate capability, which can be accounted for the low intrinsic electrical conductivity between the S–Mo–S layers and structural deterioration due to the large volume expansion upon cycling [13]. So far lots of works have been focused on solving these issues [14–17]. One of the effective ways is to enlarge interlayer spacing of MoS₂ because it can not only accommodate more Li atoms to increase the specific capacity but also tolerate the larger volume expansion in the intercalation/deintercalation process so as to improve the structural stability [18]. The interlayer spacing can be expanded via intercalating or trapping foreign species for example, the cationic groups, the functional groups, and the polymer chains [7,9,18].

An environmental friendly nonionic surfactant polyethylene glycol (PEG) has been reported to be used as a surface dispersant agent and play a crucial role in the formation of nanostructure because of the binding effect. Abundant active oxygen atoms of PEG lead to a strong interaction between PEG chains and metal ions [19,20]. Therefore, PEG-assisted synthesis methods are widely used

* Corresponding author.

E-mail address: lzhang@ysu.edu.cn (L. Zhang).

for such as biomedical materials and solar cells [21–23]. To the best of our knowledge, so far there is no report on PEG-assisted synthesized MoS_2 as anode for LIBs. However, it is found that PEG accelerates the dispersion of precursors and prevents the agglomeration of MoS_2 nanoparticles during desulphurizing [24]. On the other hand, because of the interaction effect, oxygen-containing groups in PEG may insert into the interlayer spacing of MoS_2 . This is beneficial to a high reversible capacity and excellent rate capability because the oxygen-containing groups may serve as a bridge between the S-Mo-S layers to facilitate the electron transfer, provide active sites for the reaction with Li^+ , and play a supporting role to maintain the structural stability [25]. Therefore, it is highly motivated to synthesize MoS_2 as anode for LIBs using the PEG-assisted method.

In this work, an interlayer enlarged MoS_2 was prepared by a facile hydrothermal method using water plus the PEG400 additive as hydrothermal solvent. In addition to act as a surfactant to form flower-like MoS_2 nanosheets, the PEG400 additive has several advantages due to incorporation of oxygen- and carbon-containing groups: (1) Evaluated from X-ray powder diffraction (XRD) and transmission electron microscope (TEM) measurements, the interlayer spacing was enlarged as wide as 1.0 nm. This value is significantly larger than that of bulk MoS_2 (0.62 nm). (2) Observed from the Fourier transform infrared spectra (FTIR) and X-ray photoelectron spectroscopy (XPS) data, Mo–O–C (and Mo–O) hetero-bonds were formed during hydrothermal processes. (3) Observed from Raman spectrum, MoS_2 nanosheets contain only few layers, thus demonstrating 1T-like metallic behavior. All these advantages enable MoS_2 prepared with PEG400 additive demonstrating superior electrochemical performance compared to that prepared completely using water as solvent. Additionally, these advantages vanished after annealing MoS_2 at 550 °C, verifying the key role of the hetero-bonds incorporation on performance enhancements.

2. Experimental section

2.1. Synthesis of MoS_2 nanosheets

The MoS_2 nanosheets were prepared by a hydrothermal method. All the chemicals were used as received without further purification. First, 1.2 g sodium molybdate hexahydrate ($\text{Na}_2\text{MoO}_4 \cdot 2\text{H}_2\text{O}$, 99.95%, Aladdin) and 1.9 g thiourea ($\text{CH}_4\text{N}_2\text{S}$, 99%, Alfa Aesar) were dissolved in 60 mL distilled water (sample designated as $\text{MoS}_2\text{-H}_2\text{O}$) or in a mixture of 30 mL distilled water and 30 mL PEG400 (purchased from Alfa Aesar; sample designated as $\text{MoS}_2\text{-PEG}$) under magnetic stirring to form a homogenous solution. Then, the solution was transferred into a 100 mL Teflon-lined stainless-steel autoclave and maintained at 190 °C for 24 h. After the autoclave cooled to room temperature naturally, the products were collected by centrifugation, washed with distilled water, ethanol and acetone for several times and dried at 80 °C under vacuum. For comparison, $\text{MoS}_2\text{-PEG}$ was annealed at 550 °C for 3 h under Ar flow (designated as $\text{MoS}_2\text{-PEG-A}$) to restore the ordered structure and remove the hetero-bonds.

2.2. Materials characterization

XRD was performed using a Rigaku D/MAX-2500/PC (Cu K α , 40 kV 200 mA) from 5° to 70°. Morphological characterizations were taken with a scanning electron microscope (SEM, Hitachi S-4800 II FESEM) equipped with an energy dispersive spectrometry (EDS) instrument. TEM images were taken on a FEI Titan ETM microscope. The XPS spectra were recorded by using a spectrometer with Al K α radiation (ESCALAB 250 XI). The binding energy

value of each element was corrected by $\text{C1s} = 284.6$ eV. Raman scattering measurements were performed using a Renishaw inVia system with a 532 nm excitation source. FTIR spectra were recorded in an E55 + FRA106 instrument (NICOLET-5700) at ambient temperature in the range from 4000 to 400 cm^{-1} . Differential scanning calorimetry (DSC) and thermogravimetric analysis (TGA) measurements were carried out on a Netzsch STA thermoanalyzer in an argon atmosphere.

2.3. Electrochemical characterization

The electrochemical performance of the MoS_2 electrodes was measured in CR2032 coin cells. The working electrode consists of active material ($\text{MoS}_2\text{-PEG}$, $\text{MoS}_2\text{-PEG-A}$, $\text{MoS}_2\text{-H}_2\text{O}$), acetylene black and Poly(vinylidene fluoride) (PVDF) with a mass ratio of 80:10:10, dissolved in N-methylpyrrolidinone (NMP). The resulting slurry was painted on a Cu foil and dried at 110 °C for 12 h under vacuum, and then cut into disks of 12 mm diameter. Li foil was used as the counter/reference electrode. 1 M LiPF₆ dissolved in a mixture of ethylene carbonate (EC), ethyl methyl carbonate (EMC), and dimethyl carbonate (DMC) (1:1:1) was used as electrolyte with FEC (5 wt%) as additive, and Celgard 2400 was used as the separator film. Finally, the cells were assembled in an Ar-filled glovebox. The galvanostatic charge and discharge measurements and rates performance were performed on an Arbin BT2000 system in a voltage range of 3 to 0.01 V at ambient temperature.

The specific capacity was calculated based on the weight of the active material, as much as 80 wt% weight of the electrode. Cyclic voltammetry (CV) measurements were tested on a Princeton P4000 electrochemical workstation at 0.1 mV s^{-1} in the voltage range from 3 to 0.01 V. Electrochemical impedance spectroscopy (EIS) was carried out on a Princeton P4000 electrochemical workstation in the frequency range of 100 KHz to 0.01 Hz at by applying a potential of 5 mV.

3. Results and discussion

3.1. Structural and physical properties

Fig. 1 shows the XRD profiles of MoS_2 using PEG400 as solvent before ($\text{MoS}_2\text{-PEG}$) and after ($\text{MoS}_2\text{-PEG-A}$) annealing and compared with that using H_2O ($\text{MoS}_2\text{-H}_2\text{O}$) as solvent. $\text{MoS}_2\text{-PEG}$ demonstrates two specific new peaks at $2\theta = 8.7^\circ$ (#1) and

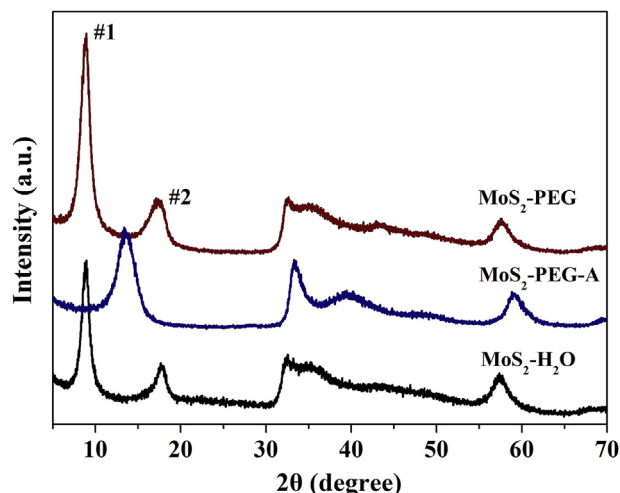


Fig. 1. XRD profiles of $\text{MoS}_2\text{-PEG}$ before and after annealing at 550 °C and $\text{MoS}_2\text{-H}_2\text{O}$.

$2\theta = 17.4^\circ$ (#2) corresponding to the (00 l) reflections, similar to 2H-MoS₂ but absence of the characteristic peak of 2H-MoS₂ at $2\theta = 14.4^\circ$ for (002) reflection, indicating the formation of a new graphene-like 2D structure, differing from 2H-MoS₂ [26]. Calculated from the Bragg equation with $d = 0.5\lambda/\sin(\theta)$, the interlayer distances of these two new peaks are *ca.* 1.0 and 0.5 nm, respectively. Compared with the d-spacing of 0.62 nm corresponding to the (002) plane of 2H-MoS₂, the enlarged d-spacing for the new peak at $2\theta = 8.7^\circ$ can be assigned to the intercalation of foreign atoms and/or functional groups into the spacing between the Mo-S layers. The peak at $2\theta = 17.4^\circ$ may represent the interlayer spacing between the MoS₂ layer and the foreign atom layer. The disappearance of (002) reflections indicates that the structure of such 2D MoS₂ contains only a few MoS₂ layers [27]. This result is verified by the microstructure observation from TEM (Fig. 2). A typical cluster of flower-like MoS₂ is shown in Fig. 2a. It can be obviously seen that the “petals” (nanosheets) are very thin since the electron beam can penetrate them despite of the overlap of the “petals”. The nanosheet contains only a few MoS₂ layers with a distance of 0.97 nm (Fig. 2b) corresponding to the (00 l) crystal plane. Moreover, a large amount of defects/distortions induced by the severe lattice distortion are observed, which is beneficial to stabilize the ultrathin MoS₂ nanosheets and generates more active unsaturated atoms because of the lowered surface energy [28]. The lattice spacing perpendicular to the (00 l) plane is 0.27 nm, which is assigned to the (100) crystal plane. These results are in good agreement with the XRD results. After annealing at 550 °C two observations can be made. First, the two new peaks (the #1 and #2 peaks) vanished while the peak of the (002) reflections appears at $2\theta = 14.4^\circ$ with a calculated $d = 0.6$ nm. Second, regarding the (100) and (103) reflections, the relative peak intensity increases and the peak width becomes narrow. This indicates the dissociation of the intercalated atoms from the MoS₂ interlayer and restacking of the MoS₂ layers. MoS₂-H₂O demonstrates the similar XRD profile as MoS₂-PEG. However, the #1 and #2 peaks are at $2\theta = 9.0^\circ$ and $2\theta = 18.0^\circ$, respectively, demonstrating a “red-shift” behavior to high angles compared to those of MoS₂-PEG. In addition, the ratios of the peak intensity for $I_{\#1}/I_{(100)}$ and $I_{\#2}/I_{(100)}$ are 2.43 and 0.91 for MoS₂-H₂O, which are obviously lower than the values of 3.74 and 1.02 for MoS₂-PEG. Therefore, MoS₂-PEG achieves larger (00 l) interlayer spacing and probably a thinner nanosheet than MoS₂-H₂O. Such a microstructure is favorable for the intercalation of Li ions and can alleviate the volume expansion for LIBs during cycling.

The SEM images for MoS₂-H₂O and MoS₂-PEG before and after

annealing are displayed in Fig. 3. The low magnification images clearly illustrate the different MoS₂ morphologies. The sample using H₂O (Fig. 3a) as solvent is dominated with agglomerated particles with large dimensions, while that using PEG (Fig. 3c) as solvent is dominated with spherical shapes of diameters about 2 μ m. Compared these two samples at high magnification, the latter is more porous than the former, which is favorable for permeation of electrolyte, though the structures of these two samples are both composed by nanosheets. The dimension has not significantly changed after annealing, but lots of extra particles are observed under high magnification (Fig. 3f). These particles show irregular shapes with a size of 1–2 μ m. This may be the reason why the XRD peaks regarding the (100) and (103) reflections become sharp and narrow.

Fig. 4 schematically illustrates the formation of the severe lattice distorted spherical MoS₂ nanosheets. During the process of hydrothermal reaction, Mo (VI) in MoO₄²⁻ was reduced by H₂S generated from the hydrolysis of thiourea and forms MoS₂ nanosheets [29,30]. The chemical reaction formula is displayed in Fig. 4. PEG chains contain a large amount of active –O– when dispersed in water, leading to a strong interaction between PEG chains and the metallic ions [20]. PEG thus plays a key role as surfactant to absorb on MoS₂ surface to anchor the spherical morphology. On the other hand, the strong binding force between the active oxygen atoms and the metallic ions may: 1) facilitate the incorporation of PEG chains into the MoS₂ interlayer during forming the MoS₂ nanosheets; and 2) prevent the removal of these intercalated PEG chains from the MoS₂ interlayer when MoS₂-PEG was washed with distilled water, alcohol, and acetone for several times. The residual PEG chains and/or oxygen atoms inherited from the molybdate precursor may contribute to the severe lattice distortion as confirmed by the XRD and TEM characterization.

MoS₂ interlayers can be intercalated by atoms, ions, and polymers. Various characterization methods have been carried out to find out what the intercalated substance is. The FTIR spectra of MoS₂-PEG before and after annealing, MoS₂-H₂O, and PEG400 are compared in Fig. 5a. The vertical dotted lines are a guide for the eye. The two highest peaks for MoS₂-PEG and MoS₂-H₂O are at the same positions of 3430 and 1630 cm⁻¹, which are slightly shifted in contrast to those for PEG400 at 3375 (O–H stretching) and 1645 cm⁻¹ (H–O–H deformation), respectively. This indicates that the hydroxyl group is not originated from PEG but from the existence of the surface water, in accordance with the previous result [31]. Compared with MoS₂-H₂O, the additional FTIR peaks for

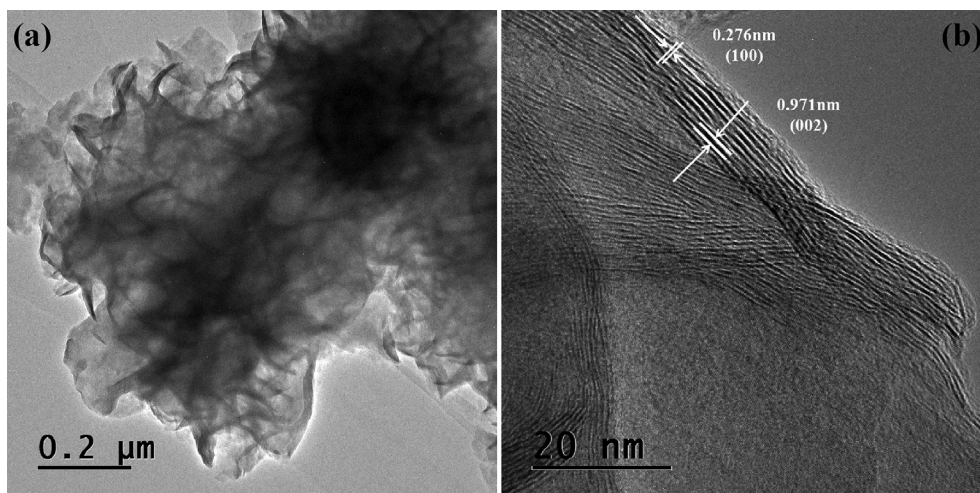


Fig. 2. TEM images for (a) a MoS₂-PEG “flower” and (b) its magnification to see the “petal” containing a few MoS₂ layers.

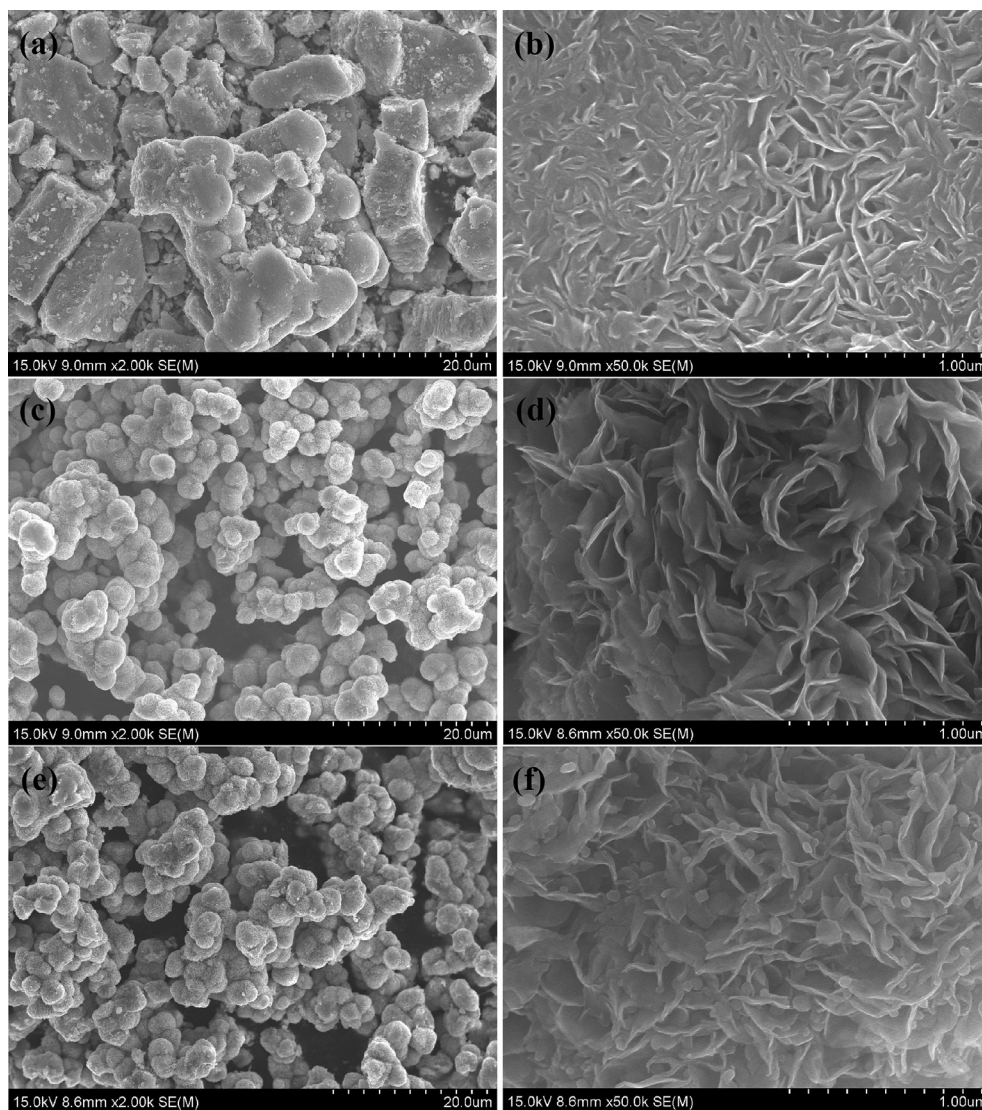


Fig. 3. SEM images with low and high magnifications for MoS₂-H₂O (a,b), MoS₂-PEG (c,d), and MoS₂-PEG-A (e,f).

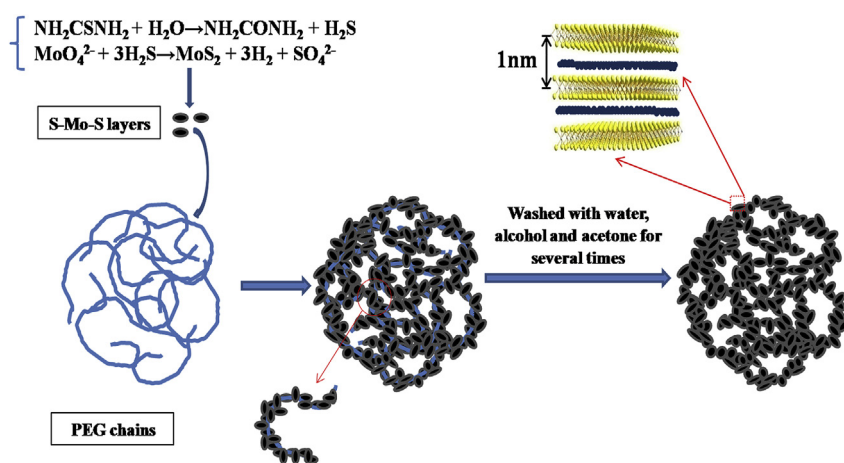


Fig. 4. Schematic representations of the formation of severe lattice distorted spherical MoS₂ nanosheets.

MoS₂-PEG at 1593, 1460, 1260, and 858 cm⁻¹ may be ascribed to the PEG chains and/or the oxygen-containing groups inserted into the

S-Mo-S interlayers [25,31]. After annealing at 550 °C (MoS₂-PEG-A), most of the FTIR peaks vanished except those at 1624 cm⁻¹ and

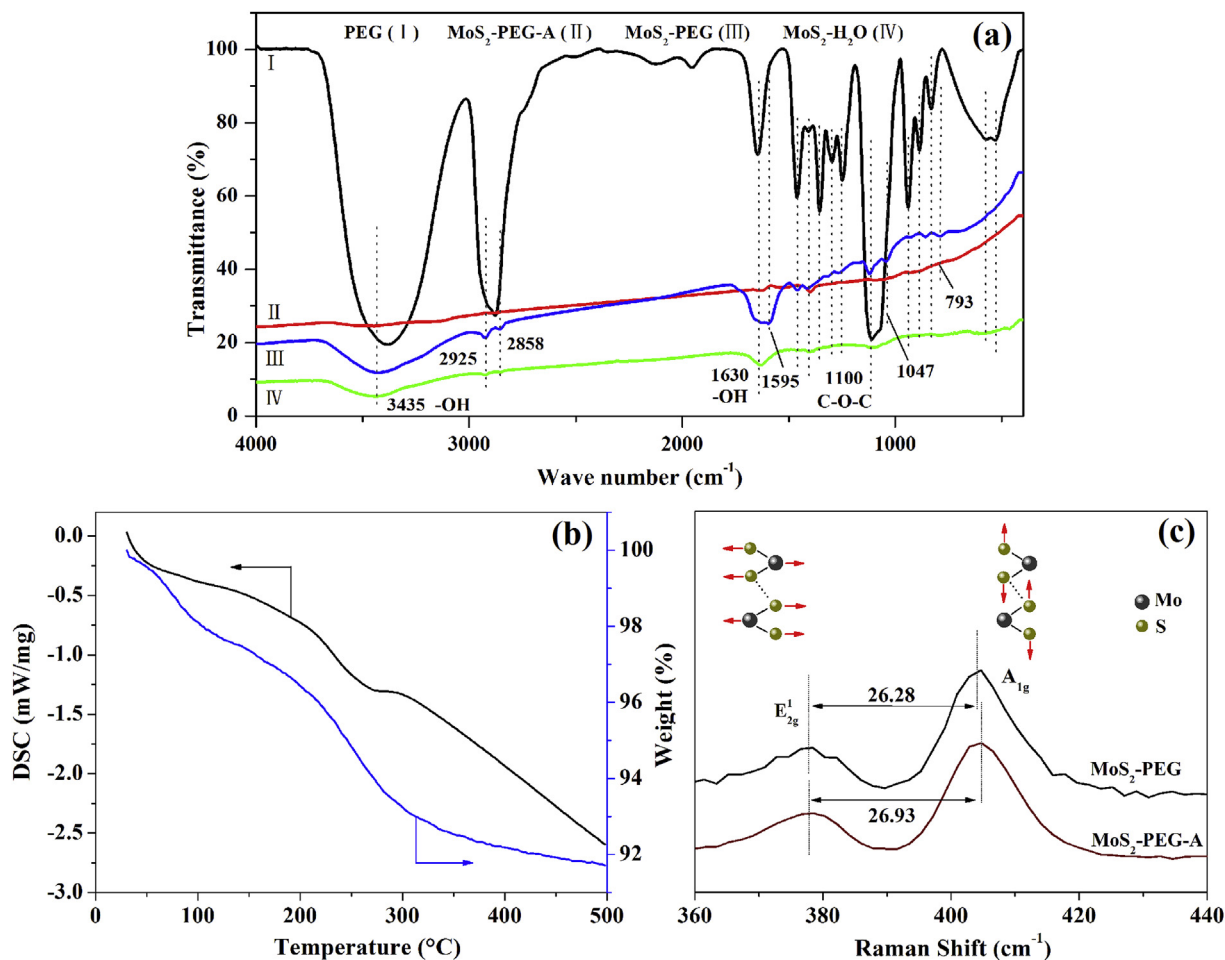


Fig. 5. (a) FTIR spectra of MoS₂-PEG before and after annealing, MoS₂-H₂O, and PEG400 for comparison. (b) DSC/TG curves of MoS₂-PEG. (c) Raman spectra of MoS₂-PEG before and after annealing.

1395 cm⁻¹, and a broad peak from 1126 to 950 cm⁻¹, though the intensities of these remaining peaks are significantly suppressed in contrast to those before annealing. Since these remaining peaks also appear in MoS₂-H₂O, they may come from the molybdate and thiourea precursors. Although the samples were washed for several times, the weak characteristic peaks of PEG400 can still be observed from MoS₂-PEG, indicating a slight incorporation of PEG or its related functional groups in the final product. The DSC/TG curves for MoS₂-PEG (Fig. 5b) illustrate two endothermic peaks at about 90 °C and 300 °C. Based on the FTIR results and the results previously reported [31], we believe that the former is related to the evaporation of the adsorbate such as the surface water and the latter may be induced by dissociation/decomposition of the intercalated PEG.

The EDS measurements (Table 1) also show that after annealing the amount of C and O decrease from 16.10 wt% and 7.49 wt% to 10.24 wt% and 2.71 wt%, respectively. On the other hand, the atomic ratio of Mo:S after annealing changes from 1:2.35 to 1:1.96, indicating a variation from a S-rich composition to a nearly stoichiometric composition. High degree of unsaturated sulfur atoms for MoS₂-PEG further confirms a severe distorted structure [28,32].

The Raman spectra of MoS₂ before and after annealing are shown in Fig. 5c. For both samples, two typical stretching modes of MoS₂ are observed corresponding to the out-of-plane A_{1g} mode and the in-plane E_{2g} mode, which can be ascribed to the vibration of S atoms in the opposite direction along c-axis and an opposite vibration of the Mo atom with respect to two S atoms perpendicular

Table 1
Elemental Analyses of MoS₂ before and after annealing.

	wt%				atomic ratio normalized to Mo			
	Mo	S	O	C	Mo	S	O	C
MoS ₂ -PEG	42.83	33.58	7.49	16.1	1	2.35	1.05	3.00
MoS ₂ -PEG-A	52.5	34.56	2.71	10.24	1	1.96	0.31	1.56

to c-axis [33], respectively. After annealing, the A_{1g} vibration stiffens with a blue shift from 403.93 cm⁻¹–404.68 cm⁻¹ while the E_{2g} vibration shows a negligible red shift from 377.65 cm⁻¹–377.75 cm⁻¹. This behavior is in agreement with that for few-layer MoS₂ that restacking has a weak perturbation on the in-plane E_{2g} vibration [33], but partially different from that for a single-layer MoS₂ [34]. Revealed by that paper [34], when a single-layer MoS₂ restacks to form bulk MoS₂, the interlayer van der Waals force not only enhances the out-of-plane A_{1g} vibration but also softens the E_{2g} vibration. Additionally, the difference of the Raman frequencies between the A_{1g} and E_{2g} modes (Δ) is regarded as an indicator of the layer thickness for MoS₂ [34]. After annealing, the difference of the two modes for MoS₂-PEG expands from $\Delta = 26.28$ cm⁻¹ to $\Delta = 26.93$ cm⁻¹, indicating an increased thickness of the nanosheets after annealing. In view of these results of Raman spectra, MoS₂-PEG is composed by the ultrathin MoS₂ nanosheets with only few layers, in line with the observation from

TEM (Fig. 2b). When the samples subjected to high temperature heat treatment, the layer becomes thicker because of the dissociation of the intercalated atoms.

Since the MoS_2 nanosheets contain only a few S–Mo–S layers, XPS is very suitable for evaluating their interfacial nature and chemical species. Fig. 6a compares the XPS spectra for MoS_2 -PEG before and after annealing. Both samples are composed of Mo, S, O and C elements. However, the relative intensities of O and C after

annealing are significantly reduced while those of Mo and S are by contrast increased, indicating removal of C and O with heat treatment. The high-resolution XPS peaks of Mo 3d (Fig. 6b) show two doublet bands assigned to Mo 3d_{3/2} and Mo 3d_{5/2}. These two peaks for the samples before and after annealing are obviously different. The spectrum of MoS_2 -PEG can be deconvoluted into four peaks belonging to the 1T and 2H phases of MoS_2 [27,35], indicating a mixture structural type of MoS_2 -PEG. The quantitative analysis of

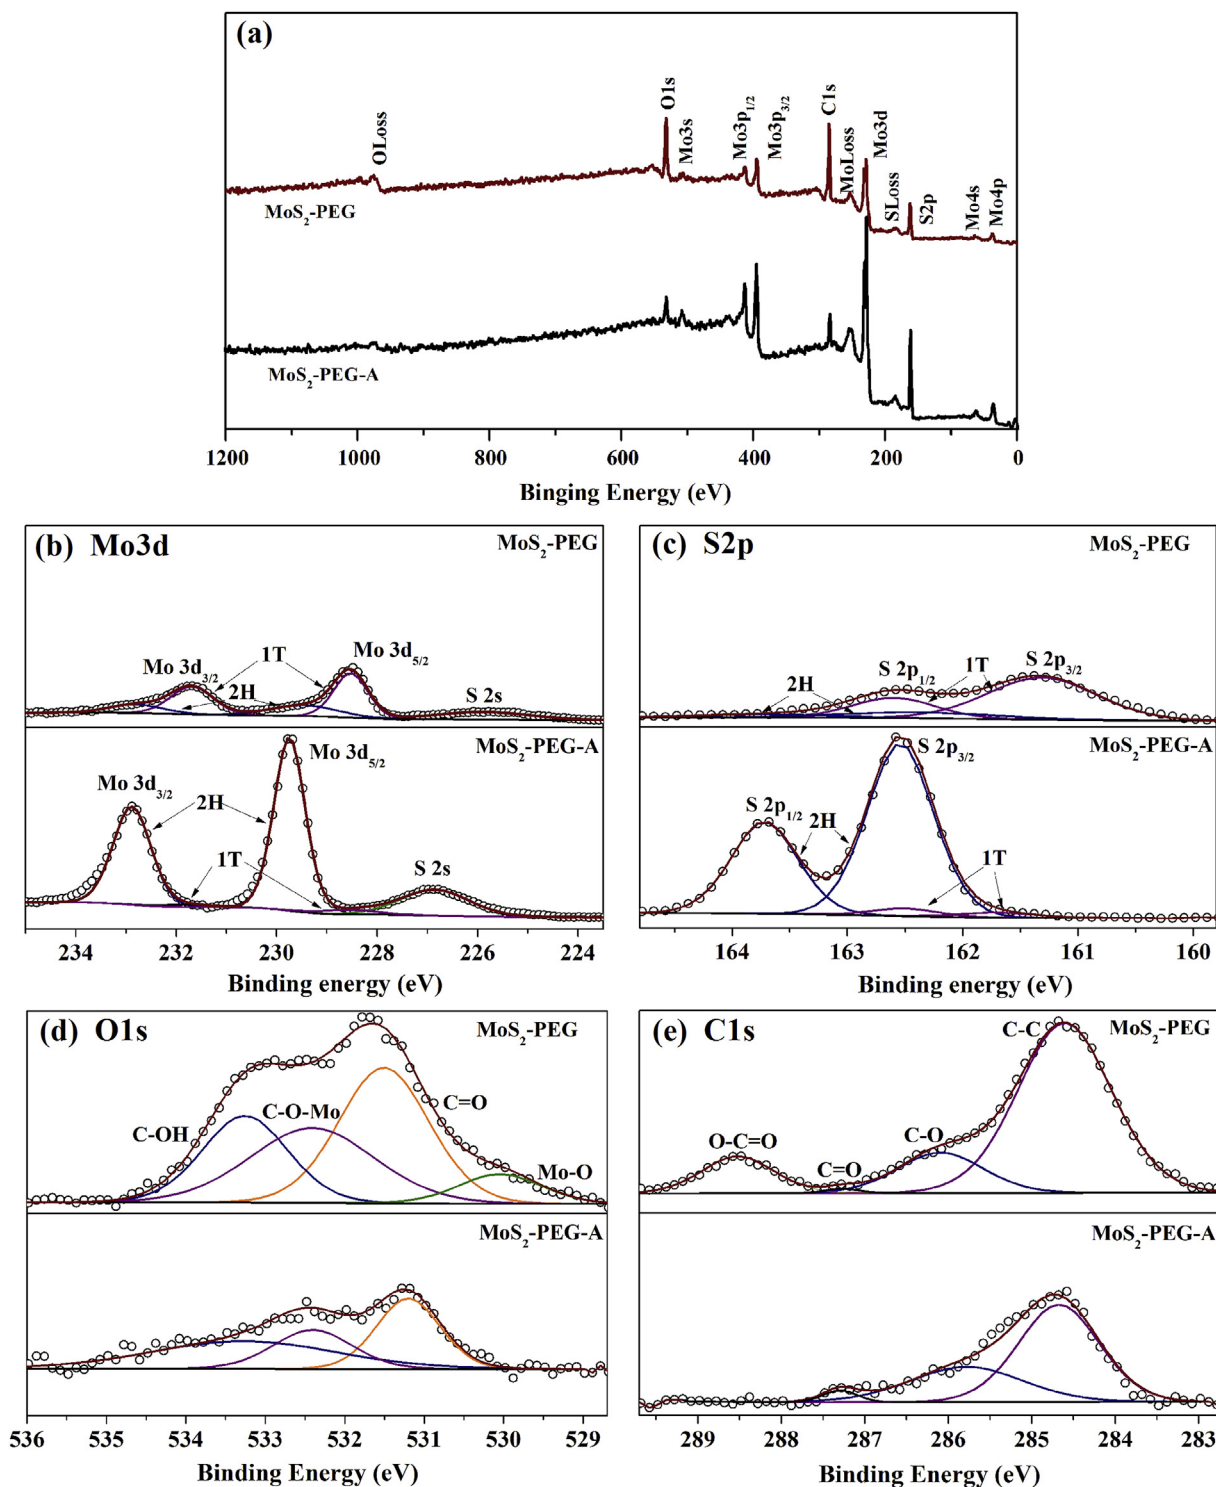


Fig. 6. XPS spectra of MoS_2 -PEG and MoS_2 -PEG-A. (a) Survey spectra, and high resolution XPS spectra of Mo3d (b), S2p (c), O1s (d), and C1s (e).

Table 2

Binding energy (BE) and elemental analysis of Mo 3d and S 2p for MoS₂-PEG and MoS₂-PEG-A.

			MoS ₂ -PEG		MoS ₂ -PEG-A	
			BE (eV)	at%	BE (eV)	at%
Mo	1T	3d _{3/2}	231.69	30.35	231.59	2.82
		3d _{5/2}	228.53	38.91	228.53	1.69
	2H	3d _{3/2}	232.81	12.06	232.88	38.98
		3d _{5/2}	229.46	18.68	229.75	56.50
S	1T	2p _{3/2}	161.31	59.88	161.7	1.88
		2p _{1/2}	162.60	21.89	162.5	2.26
	2H	2p _{3/2}	162.38	12.57	162.54	62.5
		2p _{1/2}	163.69	5.39	163.72	33.13

the 1T and 2H phases can be obtained by curve fitting. The results are listed in Table 2. MoS₂-PEG is composed by 69 at% of the 1T phase and 31 at% of the 2H phase. The metallic 1T phase is favorable for both higher electrical conductivity and faster ion motility compared to the semiconducting 2H phase [7,8]. However, the 1T phase almost fully converts to the 2H phase after annealing as MoS₂-PEG-A is composed by 96 at% of the 2H phase and only 4 at% of the 1T phase. The high-resolution XPS peaks of S 2p (Fig. 6c), assigned to 2p_{1/2} and 2p_{3/2}, show the similar changes before and after annealing as those of Mo3d.

The XPS survey spectra of O 1s and C 1s for the samples before and after annealing are also different, as illustrated in Fig. 6d–e. Deconvolution of the complicated O 1s region of MoS₂-PEG

indicates the existence of C=O, Mo–O–C, C–OH, and Mo–O bonds [25,36]. On the other hand, deconvolution of the C 1s region indicates the existence of C–C, C–O, C=O, and O–C=O bonds [25]. This further confirms that the expanded interlayer spacing of MoS₂-PEG is induced by intercalation of the C and O atoms. By contrast, the peaks for Mo–O and O–C=O bonds disappear and the relative intensities of the other peaks decrease after annealing. These results are in good agreement with the FTIR, EDS, and Raman results above mentioned, confirming the partial removal of C and O after heat treatment. Metal-oxygen bonds were found to play an important role to enhance the electron transport in the results previously reported [37,38]. The theoretical study reveals a strong oxygen bridge in C–O–Ni linkage, which contains a large electron charge overlap providing a short diffusion pathway for lithium ions and electrons among the sheet-like structure [38]. Therefore, the covalent Mo–O–C (and Mo–O) bonding between the S–Mo–S layers is favorable for the structural stability and the rate capability, thus a good electrochemical performance for MoS₂-PEG is anticipated.

3.2. Electrochemical performances

Fig. 7a shows the cyclic voltammogram (CV) curves of MoS₂-PEG during the first four cycles at 0.2 mV s^{−1} in the voltage range of 0.01–3 V. In the first cathodic scan, there appears a broadened reduction peak at 1.5 V and a sharp reduction peak at 0.41 V. The peak at 1.5 V corresponds to the intercalation of Li ions into MoS₂

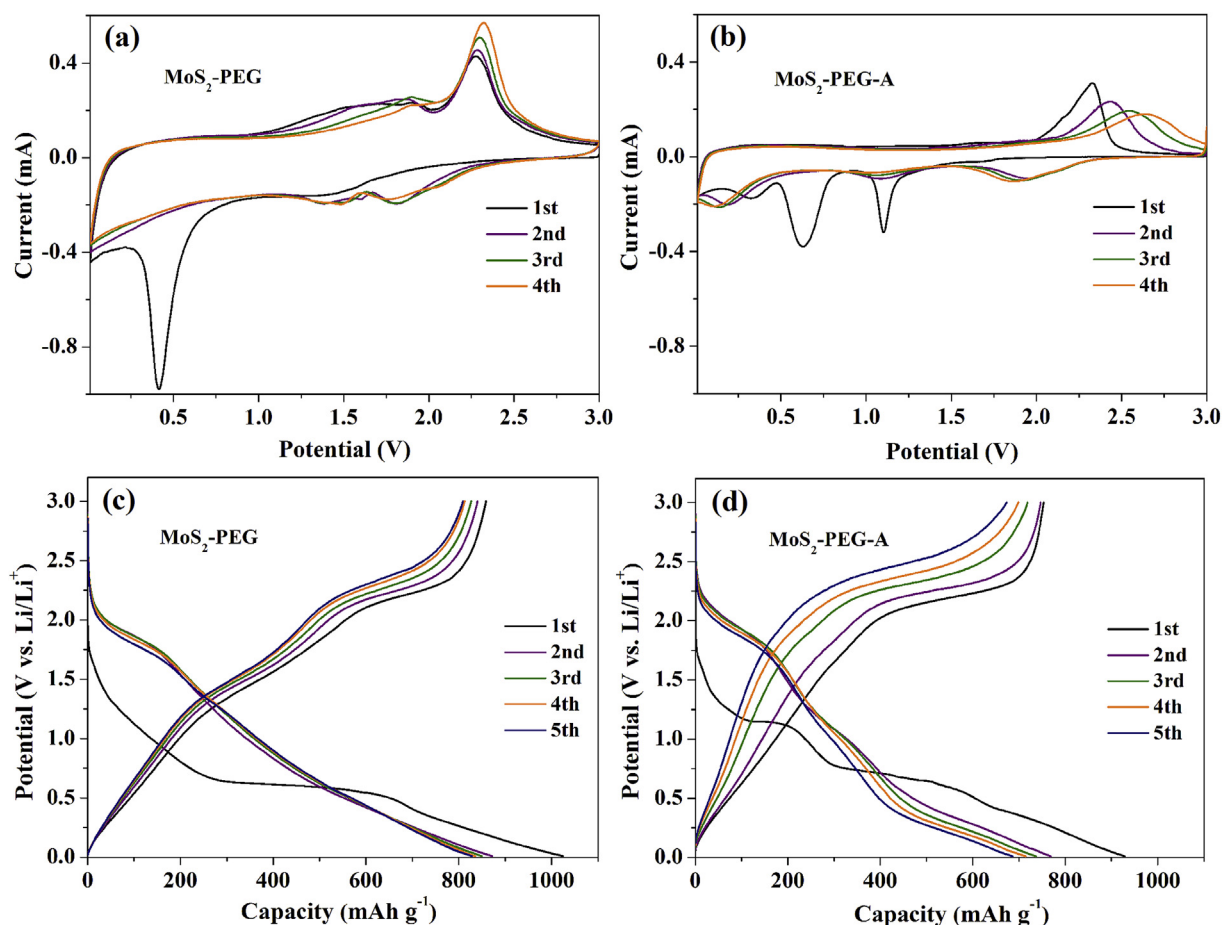


Fig. 7. Cyclic voltammograms of MoS₂-PEG (a) and MoS₂-PEG-A (b) at a scan rate of 0.1 mV s^{−1}. The charging-discharging curves of MoS₂-PEG (c) and MoS₂-PEG-A (d) at a current density of 0.1 A g^{−1}.

layers to form Li_xMoS_2 , which normally appears at 1.0 V for MoS_2 with unexpanded interlayer spacing. This variation is originated from the different electronic environment and different sites or quantity of defects in the MoS_2 due to its interlayer expanded by intercalation of foreign atoms [39–41]. The peak at 0.41 V may be attributed to the conversion of Li_xMoS_2 to metallic Mo and Li_2S . In the following anodic scan, there appears two oxidation peaks at about 1.7 V and 2.3 V, which are associated to the oxidation of Mo to MoS_2 because of the inhomogeneous delithiation induced by the defect sites and the formation of MoS_2 , respectively [42]. In the second cathodic scan, the peaks at 0.41 V and 1.5 V disappeared, and there appears another two peaks at about 1.8 V and 1.37 V, which are attributed to the conversion reaction of S to Li_2S and the association of Li and Mo, respectively [28]. In contrast, $\text{MoS}_2\text{-PEG-A}$ shows a different CV profile, as displayed in Fig. 7b. The peak regarding formation of Li_xMoS_2 appears at 1.1 V instead of at 1.5 V for $\text{MoS}_2\text{-PEG}$, indicating a higher crystal structure and a lower quantity of defects. This is also confirmed by the following anodic scan with a missing peak at 1.7 V compared to $\text{MoS}_2\text{-PEG}$. Moreover, the oxidation peak shown in $\text{MoS}_2\text{-PEG-A}$ more obviously shifts to a higher voltage in contrast to that shown in $\text{MoS}_2\text{-PEG}$, indicating a larger polarization. This polarization can also be observed from the discharge/charge curves shown in Fig. 7d.

Fig. 7c and d respectively show the first five discharge/charge curves for $\text{MoS}_2\text{-PEG}$ and $\text{MoS}_2\text{-PEG-A}$ at a current density of

100 mA g^{-1} from 0.01 to 3 V. The potential plateaus shown in both of the cells are in accordance with the CV results. The initial discharge capacities for $\text{MoS}_2\text{-PEG}$ and $\text{MoS}_2\text{-PEG-A}$ are 1082.5 and 928.5 mAh g^{-1} , respectively. The irreversible capacity-losses between the first discharge and charge process for these two cells are 20% and 19%, respectively, which is mainly due to the formation of SEI film by the decomposition of the electrolyte and the Li incorporation into SEI. Additionally, $\text{MoS}_2\text{-PEG}$ demonstrates a better reversibility than $\text{MoS}_2\text{-PEG-A}$. Therefore, comparing $\text{MoS}_2\text{-PEG}$ with $\text{MoS}_2\text{-PEG-A}$ and considering the recovered distortion and a reduced defect concentration after annealing, one can conclude that distortion/defects are beneficial to enhance the electrochemical performance but have negligible influence on the irreversible capacity-loss.

The cycling performance and Coulombic efficiency for $\text{MoS}_2\text{-PEG}$, $\text{MoS}_2\text{-H}_2\text{O}$ and $\text{MoS}_2\text{-PEG-A}$ are compared between 0.01 and 3 V at a current rate of 0.2 A g^{-1} , as shown in Fig. 8a. The initial capacities for these specimens are comparable with the values of 1038.2 , 972.0 , and $1028.5 \text{ mAh g}^{-1}$, respectively. Although the initial Coulombic efficiency is only 78% due to the formation of SEI film by the decomposition of the electrolyte and Li incorporation into SEI, the specimens show excellent reversibility with a Coulombic efficiency approaching 100% after the second cycle, indicating a facile insertion/extraction of Li ion process [43]. All three compounds exhibit a capacity climbing after fading for a

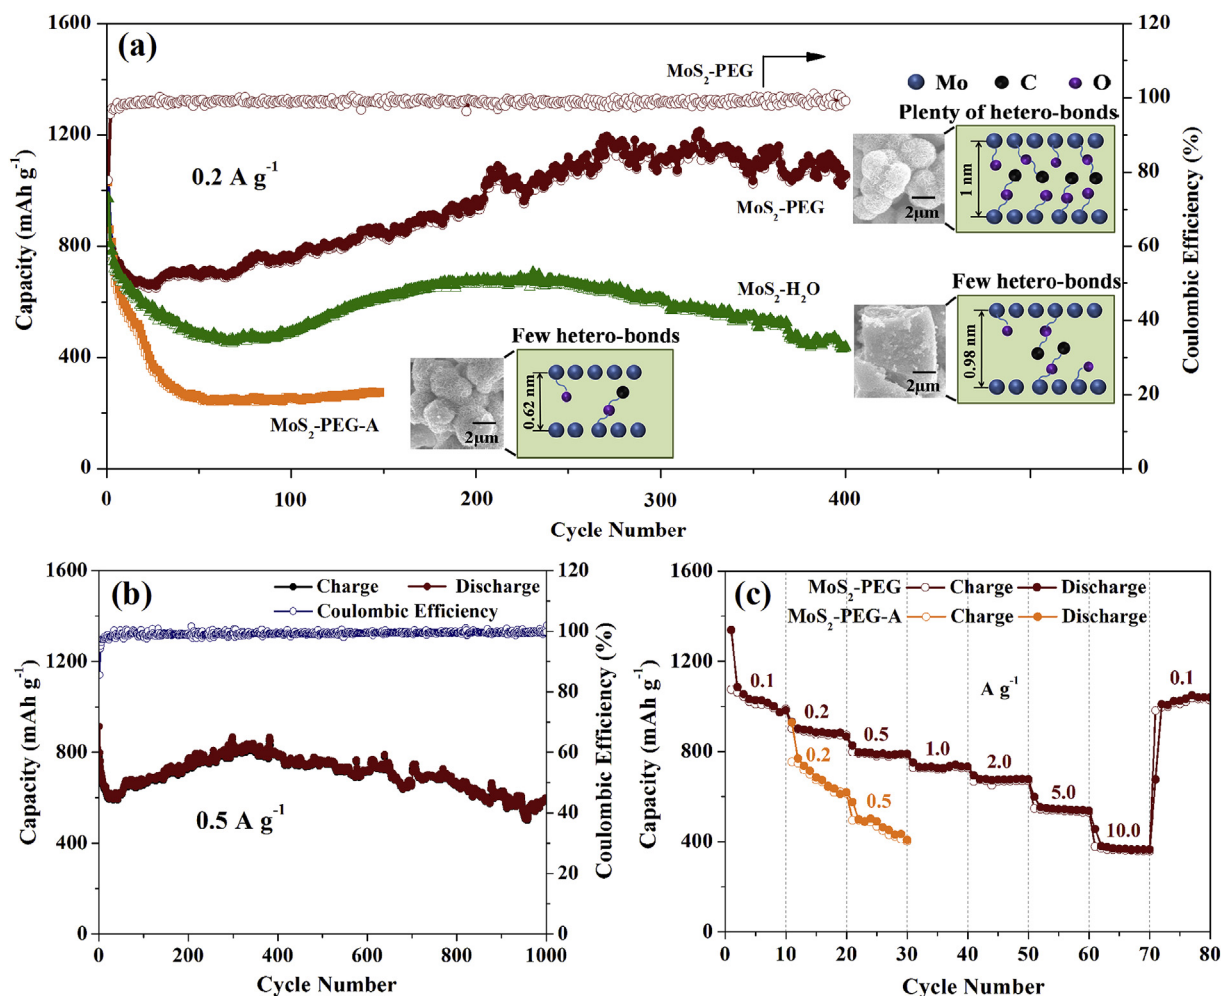


Fig. 8. (a) Cycling performance and Coulombic efficiency of $\text{MoS}_2\text{-PEG}$, $\text{MoS}_2\text{-PEG-A}$, and $\text{MoS}_2\text{-H}_2\text{O}$ electrodes at a current rate of 0.2 A g^{-1} . (b) Cycling performance and Coulombic efficiency of $\text{MoS}_2\text{-PEG}$ at a current rate of 0.5 A g^{-1} . (c) Rate capability of $\text{MoS}_2\text{-PEG}$ and $\text{MoS}_2\text{-PEG-A}$.

number of cycles. The continuous capacity increase can be attributed to several points including: (1) interlayer expansion and electrochemical delamination of the layered nanostructure after several cycles [25,42,44–46] and, (2) the formation of electrochemical active sites after cycling due to gradual extension of the defects/vacancies [42]. EIS measurements were performed after 400 cycles, as shown in Figure S1 and Table S1 in Supplementary Information. Compared the capacitance C_2 before cycling, the value is one order of magnitude higher after 400 cycles, indicating an increase of electrochemical surface area on the electrode. This capacity climbing effect may be mitigated by incorporating buffer layer such as graphene or carbon nanotube. Among these three specimens, MoS₂-PEG demonstrates the best cycling performance and the highest capacity up to 1200 mAh g⁻¹. Compared with MoS₂-PEG-A, MoS₂-PEG contains expanded interlayer spacing as well as a plenty of Mo–O–C (and Mo–O) hetero-bonds and defects. On the other hand, compared with MoS₂-H₂O composed of agglomerated bulk, MoS₂-PEG is composed of “flowers” with small particle sizes (~2 μm). Therefore, both expanded interlayer spacing and Mo–O–C (and Mo–O) hetero-bonds make great contributions to the excellent cycling performance and the high capacity. The advantages including expanded interlayer spacing, hetero-bonds, and flower-like morphology ensure MoS₂-PEG possessing the superior ability for buffering the mechanical stress and the huge volume change during Li⁺ insertion and extraction [39]. Our future work is to increase the amount of the hetero-bonds and defects in MoS₂ and to investigate their status after cycling by using Raman and/or XPS. Prolonged cycling tests (Fig. 8b) were performed on MoS₂-PEG at a current rate of 0.5 A g⁻¹. The discharge capacity still maintains at over 600 mAh g⁻¹ after 1000 cycles with a Coulombic efficiency of 99.9%. The discharge capacity values of MoS₂-PEG and part of recently reported MoS₂-based anodes with their interlayer distances are summarized in Table 3. Obviously, MoS₂-PEG exhibits a moderate reversible capacity with an excellent cycling stability among MoS₂-based anodes. It is notable that none carbon-related incorporation/decoration is performed on MoS₂-PEG, otherwise a higher reversible capacity and better cycling performance are expected. The final gradual capacity fading can be explained by the microstructural damages (pulverization) induced by volume changes. The SEM and HRTEM images and ex situ XRD profile of the positive electrode after 800 cycles are shown in Figure S2 and S3 in Supplementary Information. The SEM images show that the flower-like MoS₂ nanosheets were partially pulverized and became thicker after cycling in contrast to the pristine electrode. Both the HRTEM image and the ex situ XRD result reveal that the pristine MoS₂

nanosheets disappear while amorphous phase and nanocrystalline appear after cycling, which cause the capacity decay.

In addition to the cycling stability, a good rate capability is important for practical application. Fig. 8c shows the rate capability of MoS₂-PEG electrode compared with MoS₂-PEG-A. The reversible capacity is about 982 mAh g⁻¹ at the current density of 0.1 A g⁻¹. The reversible capacities of MoS₂-PEG maintain at 866, 790, 733, 676, 537, and 364 mAh g⁻¹ at current densities of 0.2, 0.5, 1.0, 2.0, 5.0 and 10.0 A g⁻¹, respectively. When the current density turns back from 10 to 0.1 A g⁻¹, the discharge capacity recovers to 1010 mAh g⁻¹, indicating a high cycle stability. By contrast, the capacity of MoS₂-PEG-A shows a fast capacity fading with increasing current density. The capacity rapidly decays from 768 to 499 mAh g⁻¹ as current density increases from 0.2 to 0.5 A g⁻¹. The superior rate capability of MoS₂-PEG over MoS₂-PEG-A is attributed to the enlarged interlayer spacing favorable to lithiation/delithiation [47]. Coupling of the Mo–O–C (and Mo–O) hetero-bonds facilitates an effective electron transfer path between the S–Mo–S layers as well as enhances the structural stability [25,48], and the 1T-like behavior is favorable to enhance lithium storage capability and rate capability [49,50]. Although 1T-like MoS₂ is reconstructed to the other nano phases after cycling, the initial 1T-like structure is previously reported to provide a special structure with expanded interlayer spacing as well as a high concentration of active sites to achieve prominent electrochemical properties [49,50]. The comparison of the electrodes cut from the center with that cut from the edge is shown in Figure S4. The former shows a rapid capacity fading until stabilizing at a low capacity, either for the cycling tests or for the rate capability test. However, the electrode cut from the edge part demonstrates a stable shoulder before 35 cycles and after that decreases to the same specific capacity as those cut from the center part. The thickness and the loading mass of the electrodes significantly affect the behavior of electrochemical performance. Figure S5 shows the galvanostatic charge-discharge properties of LiFePO₄/MoS₂-PEG full-cells. The initial charge and discharge capacities are 1290.0 and 948.7 mAh g⁻¹, respectively, in good agreement with the values based on MoS₂-PEG half-cells. The discharge specific capacity maintains at 920.6 mAh g⁻¹ with a coulombic efficiency of 97.1% in the following several cycles, indicating good electrochemical performance of the MoS₂-PEG anode in full-cells.

EIS measurements were performed to further understand the rate capability difference for MoS₂-PEG before and after annealing. The Nyquist plots of the impedance at room temperature for MoS₂-

Table 3
The discharge capacities of MoS₂-PEG compared with recently reported MoS₂-based anode materials in lithium ion batteries.

MoS ₂ type	Interlayer spacing (nm)	Discharge capacity (mAh g ⁻¹)	Current density (A g ⁻¹)	Cycles
MoS ₂ -PEG (TW)	0.97	1150	0.2	400
		600	0.5	1000
MoO ₂ @MoS ₂ [48]	0.62	1016	0.1	200
MoS ₂ -46.8%/SRGO [53]	0.629	724.2	0.05	200
Fe ₃ O ₄ /Fe _{1-x} S@C@MoS ₂ [54]	0.63	1003	0.2	100
Tremella-like MoS ₂ [55]	0.647	693	0.039	50
MoS ₂ @f-graphene [56]	0.652	1064	0.1	100
GODs/MoS ₂ [57]	0.78–0.80	1031	0.1	80
MoS ₂ -AC-RGO-0.1 [58]	0.98	910	0.2	120
MoS ₂ /G [37]	0.63	1077	0.1	150
N-C@MoS ₂ [59]	0.65	1050	0.15	300
MoS ₂ /Ti ₃ C ₂ MXene@C [60]	0.64	1130	1.0	700
MoS ₂ /PANI [61]	1.08	1207	0.2	100
Bubble MoS ₂ -C [46]	0.62	1500–2000	0.5	600

TW: This work, without any carbon-related decoration/incorporation.

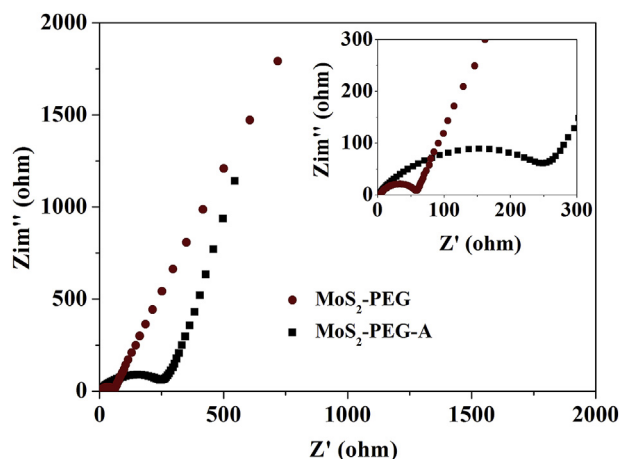


Fig. 9. Nyquist plots of MoS₂-PEG and MoS₂-PEG-A. The insert magnifies the Nyquist plots at high and medium frequency regions.

PEG and MoS₂-PEG-A are shown in Fig. 9. The impedance spectrum can be separated into an intercept of the Z' axis at high frequency region, a high and a medium frequency semicircle, and a long tail at low frequency region. These parts from high to low frequencies are ascribed to the bulk resistance, the resistance of SEI film, the charge transfer resistance on the electrode/electrolyte interface, and the Warburg impedance related to the Li⁺ diffusion in the electrode materials [51,52]. The semicircle of MoS₂-PEG is significantly smaller than that of MoS₂-PEG-A, indicating a higher conductivity of the former attributed to its 1T-like metallic behavior and the special structure (expanded interlayer spacing, hetero-bonds, and extended active sites). The high conductivity of MoS₂-PEG is beneficial to enhance charge transfer kinetics.

4. Conclusions

In summary, a facile synthesis approach toward severe lattice distorted MoS₂ nanosheets was discovered by a PEG-assisted hydrothermal synthesis. Compared with pure water as solvent, the PEG400 additive not only acts as surfactant to form flower-like morphology, but, more importantly, also modifies the microstructure of MoS₂, which enlarges the interlayer spacing and reduces nanosheet layers, and thus giving rise to a 1T-like metallic behavior with a high conductivity. Furthermore, the incorporation of oxygen- and carbon-containing groups into MoS₂ interlayers leads to the coupling of Mo–O–C (and Mo–O) hetero-bonds, which facilitates the electron transport rate and the structural stability of MoS₂. This special structure enables MoS₂ to achieve superior electrochemical performance, independent of carbon coating/supporting. Prepared via a PEG-assisted synthesis route, MoS₂ maintains the reversible capacity up to 1200 (600) mAh g^{−1} over 400 (1000) cycles at a current density of 0.2 (0.5) A g^{−1} and 364 mAh g^{−1} at a current density of 10 A g^{−1}. Future work is to further enhance the electrochemical performance of MoS₂-PEG through a carbon-related incorporation/decoration.

Acknowledgments

This work was supported by the National Science Foundation of China (51525205), and the Foundation of Higher Education of Hebei (ZD2016033).

Appendix A. Supplementary data

Supplementary data related to this article can be found at <https://doi.org/10.1016/j.electacta.2018.01.023>.

References

- [1] Y. Yao, N. Xu, D. Guan, J. Li, Z. Zhuang, L. Zhou, C. Shi, X. Liu, L. Mai, Facet-selective deposition of FeOx on alpha-MoO₃ nanobelts for lithium storage, *ACS Appl. Mater. Interfaces* 9 (2017) 39425–39431.
- [2] L. Zhou, Z. Zhuang, H. Zhao, M. Lin, D. Zhao, L. Mai, Intricate hollow structures: controlled synthesis and applications in energy storage and conversion, *Adv. Mater.* 29 (2017) 1602914.
- [3] K.A. Owusu, L. Qu, J. Li, Z. Wang, K. Zhao, C. Yang, K.M. Hercule, C. Lin, C. Shi, Q. Wei, L. Zhou, L. Mai, Low-crystalline iron oxide hydroxide nanoparticle anode for high-performance supercapacitors, *Nat. Commun.* 8 (2017) 14264.
- [4] E.S. Pampal, E. Stojanovska, B. Simon, A. Kilic, A review of nanofibrous structures in lithium ion batteries, *J. Power Sources* 300 (2015) 199–215.
- [5] X.L. Wu, Y.G. Guo, L.J. Wan, Rational design of anode materials based on Group IVA elements (Si, Ge, and Sn) for lithium-ion batteries, *Chem. Asian J.* 8 (2013) 1948–1958.
- [6] X. Chia, A.Y. Eng, A. Ambrosi, S.M. Tan, M. Pumera, Electrochemistry of nanostructured layered transition-metal dichalcogenides, *Chem. Rev.* 115 (2015) 11941–11966.
- [7] X. Cao, C. Tan, X. Zhang, W. Zhao, H. Zhang, Solution-processed two-dimensional metal dichalcogenide-based nanomaterials for energy storage and conversion, *Adv. Mater.* 28 (2016) 6167–6196.
- [8] X. Hu, W. Zhang, X. Liu, Y. Mei, Y. Huang, Nanostructured Mo-based electrode materials for electrochemical energy storage, *Chem. Soc. Rev.* 44 (2015) 2376–2404.
- [9] X. Wang, W. Xing, X. Feng, L. Song, Y. Hu, MoS₂/Polymer nanocomposites: preparation, properties, and applications, *Polym. Rev.* 57 (2017) 440–466.
- [10] L. Huang, Q. Wei, X. Xu, C. Shi, X. Liu, L. Zhou, L. Mai, Methyl-functionalized MoS₂ nanosheets with reduced lattice breathing for enhanced pseudocapacitive sodium storage, *Phys. Chem. Chem. Phys.* 19 (2017) 13696–13702.
- [11] Y. Yan, B. Xia, Z. Xu, X. Wang, Recent development of molybdenum sulfides as advanced electrocatalysts for hydrogen evolution reaction, *ACS Catal.* 4 (2014) 1693–1705.
- [12] M.Q. Wen, T. Xiong, Z.G. Zang, W. Wei, X.S. Tang, F. Dong, Synthesis of MoS₂/g-C₃N₄ nanocomposites with enhanced visible-light photocatalytic activity for the removal of nitric oxide (NO), *Optic Express* 24 (2016) 10205–10212.
- [13] X. Zhou, L.J. Wan, Y.G. Guo, Facile synthesis of MoS₂@CMK-3 nanocomposite as an improved anode material for lithium-ion batteries, *Nanoscale* 4 (2012) 5868–5871.
- [14] X. Wang, Q. Weng, Y. Yang, Y. Bando, D. Golberg, Hybrid two-dimensional materials in rechargeable battery applications and their microscopic mechanisms, *Chem. Soc. Rev.* 45 (2016) 4042–4073.
- [15] G. Chen, L. Yan, H. Luo, S. Guo, Nanoscale engineering of heterostructured anode materials for boosting lithium-ion storage, *Adv. Mater.* 28 (2016) 7580–7602.
- [16] A. Sajedi-Moghaddam, E. Saievar-Iranizad, M. Pumera, Two-dimensional transition metal dichalcogenide/conducting polymer composites: synthesis and applications, *Nanoscale* 9 (2017) 8052–8065.
- [17] X.-Y. Yu, L. Yu, X.W.D. Lou, Metal sulfide hollow nanostructures for electrochemical energy storage, *Adv. Energy Mater.* 6 (2016) 1501333.
- [18] K.D. Rasamani, F. Alimohammadi, Y. Sun, Interlayer-expanded MoS₂, *Mater. Today* 20 (2017) 83–91.
- [19] X.L. Gou, F.Y. Cheng, Y.H. Shi, L. Zhang, S.J. Peng, J. Chen, P.W. Shen, Shape-controlled synthesis of ternary chalcogenide ZnIn₂S₄ and CuIn(S,Se)₂ nano/microstructures via facile solution route, *J. Am. Chem. Soc.* 128 (2006) 7222–7229.
- [20] X. Shi, L. Pan, S. Chen, Y. Xiao, Q. Liu, L. Yuan, J. Sun, L. Cai, Zn(II)-PEG 300 globules as soft template for the synthesis of hexagonal ZnO microns by the hydrothermal reaction method, *Langmuir* 25 (2009) 5940–5948.
- [21] Z. Wu, D. Wang, A. Sun, Surfactant-assisted fabrication of MoS₂ nanospheres, *J. Mater. Sci.* 45 (2010) 182–187.
- [22] W. Liu, S. He, Y. Wang, Y. Dou, D. Pan, Y. Feng, G. Qian, J. Xu, S. Miao, PEG-assisted synthesis of homogeneous carbon nanotubes-MoS₂-carbon as a counter electrode for dye-sensitized solar cells, *Electrochim. Acta* 144 (2014) 119–126.
- [23] T. Liu, C. Wang, X. Gu, H. Gong, L. Cheng, X. Shi, L. Feng, B. Sun, Z. Liu, Drug delivery with PEGylated MoS₂ nano-sheets for combined photothermal and chemotherapy of cancer, *Adv. Mater.* 26 (2014) 3433–3440.
- [24] T.Z. Zou, J.P. Tu, H.D. Huang, D.M. Lai, L.L. Zhang, D.N. He, Preparation and tribological properties of inorganic fullerene-like MoS₂, *Adv. Eng. Mater.* 8 (2006) 289–293.
- [25] Y. Teng, H. Zhao, Z. Zhang, Z. Li, Q. Xia, Y. Zhang, L. Zhao, X. Du, Z. Du, P. Lv, K. Swierczek, MoS₂ nanosheets vertically grown on graphene sheets for lithium-ion battery anodes, *ACS Nano* 10 (2016) 8526–8535.
- [26] M.R. Gao, M.K. Chan, Y. Sun, ge-terminated molybdenum disulfide with a 9.4-Å interlayer spacing for electrochemical hydrogen production, *Nat. Commun.* 6 (2015) 7493.
- [27] M. Acerce, D. Voiry, M. Chhowalla, Metallic 1T phase MoS₂ nanosheets as supercapacitor electrode materials, *Nat. Nanotechnol.* 10 (2015) 313–318.
- [28] Z. Wu, B. Li, Y. Xue, J. Li, Y. Zhang, F. Gao, Fabrication of defect-rich MoS₂ ultrathin nanosheets for application in lithium-ion batteries and supercapacitors, *J. Mater. Chem.* 3 (2015) 19445–19454.
- [29] S. Wang, G. Li, G. Du, X. Jiang, C. Feng, Z. Guo, S.-J. Kim, Hydrothermal synthesis of molybdenum disulfide for lithium ion battery applications, *Chin. J. Chem. Eng.* 18 (2010) 910–913.
- [30] J. Wang, J. Liu, J. Luo, P. Liang, D. Chao, L. Lai, J. Lin, Z. Shen, MoS₂ architectures supported on graphene foam/carbon nanotube hybrid films: highly integrated frameworks with ideal contact for superior lithium storage, *J. Mater. Chem.* 3 (2015) 17534–17543.
- [31] D. Wang, X. Zhang, S. Bao, Z. Zhang, H. Fei, Z. Wu, Phase engineering of a multiphase 1T/2H MoS₂ catalyst for highly efficient hydrogen evolution, *J. Mater. Chem.* 5 (2017) 2681–2688.
- [32] J. Xie, H. Zhang, S. Li, R. Wang, X. Sun, M. Zhou, J. Zhou, X.W. Lou, Y. Xie, Defect-rich MoS₂ ultrathin nanosheets with additional active edge sites for enhanced electrocatalytic hydrogen evolution, *Adv. Mater.* 25 (2013) 5807–5813.
- [33] S. Zhang, B.V.R. Chowdary, Z. Wen, J. Jin, J. Yang, Constructing highly oriented configuration by few-layer MoS₂: toward high-performance lithium-ion batteries and hydrogen evolution reactions, *ACS Nano* 9 (2015) 12464–12472.
- [34] C. Lee, H. Yan, L.E. Brus, T.F. Heinz, J. Hone, S. Ryu, Anomalous lattice vibrations of single- and few-layer MoS₂, *ACS Nano* 4 (2010) 2695–2700.
- [35] Z. Chen, K. Leng, X. Zhao, S. Malkhandi, W. Tang, B. Tian, L. Dong, L. Zheng, M. Lin, B.S. Yeo, K.P. Loh, Interface confined hydrogen evolution reaction in zero valent metal nanoparticles-intercalated molybdenum disulfide, *Nat. Commun.* 8 (2017) 14548.
- [36] J. Xie, J. Zhang, S. Li, F. Grote, X. Zhang, H. Zhang, R. Wang, Y. Lei, B. Pan, Y. Xie, Controllable disorder engineering in oxygen-incorporated MoS₂ ultrathin nanosheets for efficient hydrogen evolution, *J. Am. Chem. Soc.* 135 (2013)

- 17881–17888.
- [37] Y. Teng, H. Zhao, Z. Zhang, Z. Li, Q. Xia, Y. Zhang, L. Zhao, X. Du, Z. Du, P. Lv, K. Swierczek, MoS₂ nanosheets vertically grown on graphene sheets for lithium-ion battery anodes, *ACS Nano* 10 (2016) 8526–8535.
 - [38] G.M. Zhou, D.W. Wang, L.C. Yin, N. Li, F. Li, H.M. Chen, Oxygen bridges between NiO nanosheets and graphene for improvement of lithium storage, *ACS Nano* 6 (2012) 3214–3223.
 - [39] Y. Lu, X. Yao, J. Yin, G. Peng, P. Cui, X. Xu, MoS₂ nanoflowers consisting of nanosheets with a controllable interlayer distance as high-performance lithium ion battery anodes, *RSC Adv* 5 (2015) 7938–7943.
 - [40] K. Chang, W. Chen, In situ synthesis of MoS₂/graphene nanosheet composites with extraordinarily high electrochemical performance for lithium ion batteries, *Chem. Commun.* 47 (2011) 4252–4254.
 - [41] U.K. Sen, S. Mitra, High-rate and high-energy-density lithium-ion battery anode containing 2D MoS₂ nanowall and cellulose binder, *ACS Appl. Mater. Interfaces* 5 (2013) 1240–1247.
 - [42] K. Chang, D. Geng, X. Li, J. Yang, Y. Tang, M. Cai, R. Li, X. Sun, Ultrathin MoS₂/nitrogen-doped graphene nanosheets with highly reversible lithium storage, *Adv. Energy Mater.* 3 (2013) 839–844.
 - [43] L. Zhang, L. Lu, D. Zhang, W. Hu, N. Wang, B. Xu, Y. Li, H. Zeng, Dual-buffered SnSe@CNFs as negative electrode with outstanding lithium storage performance, *Electrochim. Acta* 209 (2016) 423–429.
 - [44] J. Xu, J. Zhu, X. Yang, S. Cao, J. Yu, M. Shalom, M. Antonietti, Synthesis of organized layered carbon by self-templating of dithioxamide, *Adv. Mater.* 28 (2016) 6727–6733.
 - [45] Y. Zheng, T. Zhou, X. Zhao, W.K. Pang, H. Gao, S. Li, Z. Zhou, H. Liu, Z. Guo, Atomic interface engineering and electric-field effect in ultrathin Bi₂MoO₆ nanosheets for superior lithium ion storage, *Adv. Mater.* 29 (2017) 1700396.
 - [46] P. Wang, J. Tian, J. Hu, X. Zhou, C. Li, Supernormal conversion anode consisting of high-density MoS₂ bubbles wrapped in thin carbon network by self-sulfuration of polyoxometalate complex, *ACS Nano* 11 (2017) 7390–7400.
 - [47] T.S. Sahu, S. Mitra, Exfoliated MoS₂ sheets and reduced graphene oxide—an excellent and fast anode for sodium-ion battery, *Sci. Rep.* 5 (2015) 12571.
 - [48] Z. Xu, T. Wang, L. Kong, K. Yao, H. Fu, K. Li, L. Cao, J. Huang, Q. Zhang, MoO₂@MoS₂ nanoarchitectures for high-loading advanced lithium-ion battery anodes, *Part. Part. Syst. Char.* 34 (2017) 1600223.
 - [49] T. Xiang, Q. Fang, H. Xie, C. Wu, C. Wang, Y. Zhou, D. Liu, S. Chen, A. Khalil, S. Tao, Q. Liu, L. Song, Vertical 1T-MoS₂ nanosheets with expanded interlayer spacing edged on a graphene frame for high rate lithium-ion batteries, *Nanoscale* 9 (2017) 6975–6983.
 - [50] K. Leng, Z. Chen, X. Zhao, W. Tang, B. Tian, C.T. Nai, W. Zhou, K.P. Loh, Phase restructuring in transition metal dichalcogenides for highly stable energy storage, *ACS Nano* 10 (2016) 9208–9215.
 - [51] K. Chang, W. Chen, Single-layer MoS₂/graphene dispersed in amorphous carbon: towards high electrochemical performances in rechargeable lithium ion batteries, *J. Mater. Chem.* 21 (2011) 17175–17184.
 - [52] L. Lu, L. Zhang, H. Zeng, B. Xu, L. Wang, Y. Li, Enhanced cycling performance of Se-doped SnS carbon nanofibers as negative electrode for lithium-ion batteries, *J. Alloy. Comp.* 695 (2017) 1294–1300.
 - [53] M. Choi, S.K. Koppala, D. Yoon, J. Hwang, S.M. Kim, J. Kim, A route to synthesis molybdenum disulfide-reduced graphene oxide (MoS₂-RGO) composites using supercritical methanol and their enhanced electrochemical performance for Li-ion batteries, *J. Power Sources* 309 (2016) 202–211.
 - [54] Q. Pan, F. Zheng, X. Ou, C. Yang, X. Xiong, Z. Tang, L. Zhao, M. Liu, MoS₂ decorated Fe₃O₄/Fe₁-xS@C nanosheets as high-performance anode materials for lithium ion and sodium ion batteries, *ACS sustainable chem, Eng. Times* 5 (2017) 4739–4745.
 - [55] G. Qu, J. Cheng, Z. Wang, B. Wang, S. Ye, Self-templated formation of tremella-like MoS₂ with expanded spacing of (002) crystal planes for Li-ion batteries, *J. Mater. Sci.* 51 (2016) 4739–4747.
 - [56] B. Wang, Y. Zhang, J. Zhang, R. Xia, Y. Chu, J. Zhou, X. Yang, J. Huang, Facile synthesis of a MoS₂ and functionalized graphene heterostructure for enhanced lithium-storage performance, *ACS Appl. Mater. Interfaces* 9 (2017) 12907–12913.
 - [57] J. Guo, H. Zhu, Y. Sun, L. Tang, X. Zhang, Boosting the lithium storage performance of MoS₂ with graphene quantum dots, *J. Mater. Chem.* 4 (2016) 4783–4789.
 - [58] J. Liu, A. Fu, Y. Wang, P. Guo, H. Feng, H. Li, X.S. Zhao, Spraying coagulation-assisted hydrothermal synthesis of MoS₂/carbon/graphene composite microspheres for lithium-ion battery applications, *ChemElectroChem* 4 (2017) 2027–2036.
 - [59] D. Xie, X. Xia, Y. Wang, D. Wang, Y. Zhong, W. Tang, X. Wang, J. Tu, Nitrogen-Doped carbon embedded MoS₂ microspheres as advanced anodes for lithium- and sodium-ion batteries, *Chemistry* 22 (2016) 11617–11623.
 - [60] X. Wu, Z. Wang, M. Yu, L. Xiu, J. Qiu, Stabilizing the MXenes by carbon nanoplating for developing hierarchical nanohybrids with efficient lithium storage and hydrogen evolution capability, *Adv. Mater.* 29 (2017) 1607017.
 - [61] H. Wang, H. Jiang, Y. Hu, N. Li, X. Zhao, C. Li, 2D MoS₂/polyaniline heterostructures with enlarged interlayer spacing for superior lithium and sodium storage, *J. Mater. Chem.* 5 (2017) 5383–5389.