

The Glass Transition Temperature of Heterogeneous Biopolymer Systems

Espíndola, Suellen Pereira; Norder, Ben; Koper, Ger J.M.; Picken, Stephen J.

DOI

[10.1021/acs.biomac.2c01356](https://doi.org/10.1021/acs.biomac.2c01356)

Publication date

2023

Document Version

Final published version

Published in

Biomacromolecules

Citation (APA)

Espíndola, S. P., Norder, B., Koper, G. J. M., & Picken, S. J. (2023). The Glass Transition Temperature of Heterogeneous Biopolymer Systems. *Biomacromolecules*, 24(4), 1627-1637. <https://doi.org/10.1021/acs.biomac.2c01356>

Important note

To cite this publication, please use the final published version (if applicable). Please check the document version above.

Copyright

Other than for strictly personal use, it is not permitted to download, forward or distribute the text or part of it, without the consent of the author(s) and/or copyright holder(s), unless the work is under an open content license such as Creative Commons.

Takedown policy

Please contact us and provide details if you believe this document breaches copyrights. We will remove access to the work immediately and investigate your claim.

The Glass Transition Temperature of Heterogeneous Biopolymer Systems

Suellen Pereira Espíndola,* Ben Norder, Ger J. M. Koper, and Stephen J. Picken*



Cite This: *Biomacromolecules* 2023, 24, 1627–1637



Read Online

ACCESS |



Metrics & More





Article Recommendations



Supporting Information

ABSTRACT: Biopolymers are abundant, renewable, and biodegradable resources. However, bio-based materials often require toughening additives, like (co)polymers or small plasticizing molecules. Plasticization is monitored via the glass transition temperature versus diluent content. To describe this, several thermodynamic models exist; nevertheless, most expressions are phenomenological and lead to over-parametrization. They also fail to describe the influence of sample history and the degree of miscibility via structure–property relationships. We propose a new model to deal with semi-compatible systems: the generalized mean model, which can classify diluent segregation or partitioning. When the constant k_{GM} is below unity, the addition of plasticizers has hardly any effect, and in some cases, even anti-plasticization is observed. On the other hand, when the k_{GM} is above unity, the system is highly plasticized even for a small addition of the plasticizer compound, which indicates that the plasticizer locally has a higher concentration. To showcase the model, we studied Na-alginate films with increasing sizes of sugar alcohols. Our k_{GM} analysis showed that blends have properties that depend on specific polymer interactions and morphological size effects. Finally, we also modeled other plasticized (bio)polymer systems from the literature, concluding that they all tend to have a heterogeneous nature.

Heterogeneity factor

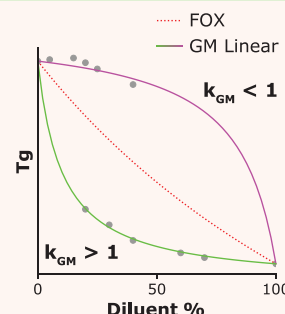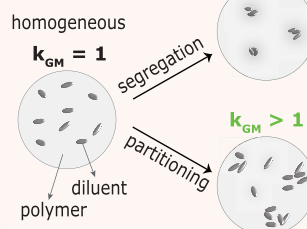

INTRODUCTION

Global concerns over climate change, plastic pollution, and scarcity of resources have made several industries actively look for alternative and sustainable material sources. Biopolymers are a great alternative with many applications already developed in food, agriculture, biomedical, and composite fields.^{1–3} However, solid-state materials consisting of polysaccharides and proteins are often too brittle and not workable.⁴ This is a classical materials design dilemma, where films are either (too) stiff and brittle or tough and (too) ductile. A common alternative for toughening polymeric materials is blending them with a diluent.^{5–7} This includes both (co)polymers and small non-volatile molecules, which can be added to decrease the polymer's glass transition temperature (T_g). Therefore, further exploring our understanding of polymer–polymer and polymer–diluent systems is fundamental for developing improved biodegradable and sustainable biopolymer-based applications.

Biopolymer blends are frequently required because they can combine the specific properties of different materials in one. Often, small molecules are applied to plasticize the biopolymer, which provides better toughness and avoids catastrophic brittle failure. The ideal plasticizer for such biopolymer-based materials must be non-toxic, biodegradable, and preferably derived from natural sources.⁴ For instance, there are many reports of materials composed of polyols, oligosaccharides,

citrates, lactates, vegetable oils, and tannins as natural additives.^{8–10} Even though the literature using bio-based materials and plasticizer agents is growing, their application is often investigated by trial and error. Furthermore, very few research studies exist on how to select a plasticizer, with most of them being phenomenological and case-specific. In addition, sample history, miscibility, and the extent of (local) phase separation are ignored. Therefore, how component compatibility affects the barrier, thermal, and mechanical properties of biopolymers is poorly addressed. As a side note, it is probably fair to say that living tissues, materials in nature with structural and mechanical functions, such as teeth, bones, wood, wool, and silk, obtain their sometimes excellent properties by virtue of components that bring about the required amount of mobility.

Glass Transition Model Proposal. Polymer blend miscibility is often studied via the determination of T_g , in which a single measured transition temperature identifies

Received: November 14, 2022

Revised: February 22, 2023

Published: March 8, 2023





Chart 1. Morphology Classification of Polymer Systems We Propose for Glass Transition (T_g) Modeling Based on the Degree of Miscibility^a

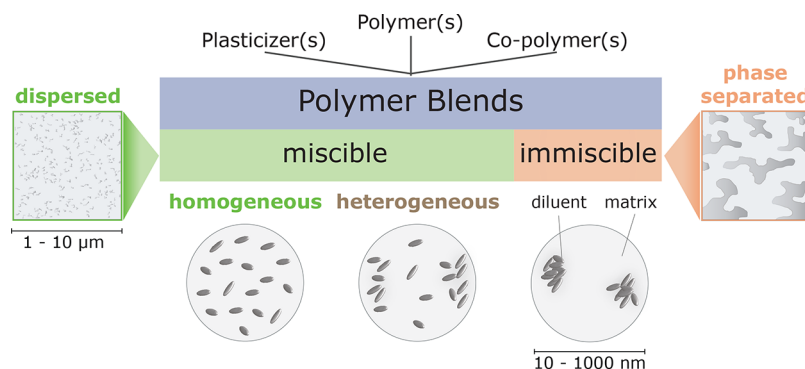

^aImages inside boxes and circles relate to the microscale and nanoscale, respectively.

compatible systems.¹¹ In truth, due to chain connectivity, even in miscible systems, the components will effectively experience distinct levels of mobility or relaxation times associated to a glass transition.¹² For binary systems, several thermodynamical models for predicting the averaged T_g have been proposed, for instance, using the Gordon–Taylor and Couchman–Karasz expressions.^{7,13–15} In product engineering, the Fox equation⁶ is frequently applied, which also appears as a limiting form of the Couchman–Karasz expression. Nevertheless, it is seldom mentioned that these theories are only intended for the case of full compatibility. This is far from the general case of (bio)polymer mixtures, which may have a complex chemical composition and might show multiple conformations and variable levels of polydispersity. Due to this molecular complexity, the nanostructures that evolve from mixing biomacromolecules and diluents are expected to be locally heterogeneous in composition. On a supramolecular scale, there is local organization of mixed components, i.e., a certain level of segregation or partitioning may be recognized (Chart 1). Experimentally, the T_g of such heterogeneous blends is identified by one broad transition. The prediction of the T_g , even in binary systems, will also be difficult due to possible component interactions.¹⁶ As a result of concentration fluctuations¹⁷ and specific interactions, data can show negative or positive deviations from the usual rule of mixing for T_g .

Not surprisingly, there have been plenty of reports on how models based on the Couchman–Karasz expression fail to describe systems lacking true miscibility.^{15,18,19} Consequently, data from inhomogeneous mixtures are usually fitted by including additional correction terms to these equations. This leads to phenomenological expressions and over-parameterization. To work with semi-compatible systems, we propose an alternative working model, the generalized mean (linear) or $GM(L)$ model. Within this framework, the conventional Fox equation becomes a particular case of our model, that of a homogeneous miscible system. It is based on the rather obvious idea that T_g is connected to interactions (enthalpy) and degrees of freedom (entropy) using a second-order phase transition-like framework, where the enthalpy and entropy type terms are averaged as a function of composition.

Model Case Study with Alginate-Polyols. To showcase the use of the $GM(L)$ model, we have performed a systematic study on the general plasticization effects of Na-Alginate with polyols. We have selected sugar alcohols as polyols because they provide a series of increasing H-bonded interactions and

sizes. Then, we investigated if a single master curve of plasticization occurs based on a plasticizer's mass fraction or molar density of the interacting functional group. Additionally, we used this system to investigate the interactions and the degree of miscibility based on our T_g modeling.

Finally, we demonstrate how the $GM(L)$ model can be applied to an extensive list of T_g datasets from the literature. We explore the general understanding of static heterogeneity in (bio)polymer mixtures by evaluating the model's constant k_{GM} . Special attention is given to complex, multicomponent biopolymer systems since we believe the current theoretical background on T_g for this class of materials has yet to be adequately addressed.

EXPERIMENTAL SECTION

Materials. Sodium alginate (high ratio of mannuronic:guluronic acid, $M_w \approx 12$ –40 kDa), ethylene glycol, glycerol, meso-erythritol, D-(+)-arabitol, D-mannitol, and D-sorbitol were purchased from Sigma–Aldrich.

Methods for Na-Alginate-(Sugar Alcohol) Films. Plasticization and Film Casting. The alginate-polyol films were prepared by the solution-casting method. Different sugar alcohols ((CHOH)_nH₂, where n is varying) with increasing chain length were tested to investigate the plasticizing effect on the developed films. Namely, ethylene glycol (C₂), glycerol (C₃), erythritol (C₄), arabitol (C₅), sorbitol (C₆), and mannitol (C₆) were used as plasticizers. The film preparation procedure is described as follows: a 5 wt % stock solution of Na-alginate in demineralized water was prepared. Afterward, an appropriate amount of dissolved plasticizer (5 wt %, in demineralized water) was added into separate film-forming solutions at a final dry mass of 0 to 50 wt % plasticizer (alginate basis, pH 8). The film-forming solutions with different plasticizer content were carefully homogenized with a glass rod, avoiding bubble formation until uniformly blended, and cast into polystyrene Petri dishes. The exact weight was calculated separately for each plasticizer to result in films with a thickness of about 0.15 mm. The freshly cast films were placed in ambient conditions (at 50 RH and RT), and different drying environments were tested. After around 3 to 5 days of drying, the free-standing films were peeled from the casting surfaces for analysis. Water is a natural plasticizer for hygroscopic alginate films, and sorption/desorption phenomena occur depending on the ambient conditions. Hence, to evaluate only the effects of polyol addition to the films, the cut film specimens were vacuum dried for 1 day at 40 °C and kept in a desiccator containing silica gel until immediately before analysis. For glycerol and sorbitol, the humid films (ambient, ~50% RH) were also analyzed for comparison (Supporting Information, Figure S12 and Table S1).

Thermogravimetric Analysis. It was possible to add C₂ to alginate and cast thin films. However, vacuum drying also removed part of this

plasticizer from the matrix since it is too volatile. Hence, to measure the exact C_2 content in the dried films, thermogravimetric analysis (TGA) was carried out on a PerkinElmer TGA 8000. The measurements were performed on samples of about 5 mg placed in a corundum crucible from 30–300 °C at a heating rate of 5 °C min^{−1} under a nitrogen atmosphere with an isothermal step at 90 °C for 30 min. TGA was also used for determining the water content in films of C_3 and C_6 equilibrated to ambient relative humidity using similar scans. TGA results can be found in the Supporting Information, Figure S5 and Table S1.

Dynamic Mechanical Thermal Analysis. Dynamic mechanical thermal analysis (DMTA) was performed on a PerkinElmer DMA-7e. DMTA experiments on the plasticized films were performed in tensile mode at a frequency of 1 Hz, a −100 to 180 °C temperature range, and a heat rate of 5 °C min^{−1} with film dimensions of roughly 20.0 mm × 3.0 mm × 0.1 mm. The thickness of the films was measured with the aid of a digital micrometer. The resulting glass transition was observed by the abrupt change in storage modulus slope and corresponding loss modulus maximum. This event is often called a polymer's alpha relaxation. When possible, the T_g was estimated from duplicate measurements.

Glass Transition Modeling. To this experimental data, models were applied based on a T_g rule of mixing of polymer and plasticizer contributions. For convention, T_{g1} and T_{g2} are expressed as polymer and diluent components, respectively, with high and low T_g values. We chose to fit the often-applied Fox model:⁶

$$\frac{1}{T_g} = \frac{x_1}{T_{g1}} + \frac{x_2}{T_{g2}} \quad (1)$$

where x_i and T_{gi} denote the molar fraction and glass transition of components 1 and 2, respectively.

Further, we also fitted our model of interest, the generalized mean linear (GM(L)):

$$\frac{1}{T_g} = \frac{\frac{\phi_1}{T_{g1}} + \frac{\phi_2 k_{GM}}{T_{g2}}}{\phi_1 + \phi_2 k_{GM}} \quad (2)$$

where ϕ_i and T_{gi} denote the volume fraction and glass transition of components 1 and 2, respectively, and k_{GM} denotes the model constant. A full description of the Fox model and the GM(L) models we propose here can be found in Appendix A (Supporting Information). Curve fitting using nonlinear least squares was performed for all the studied plasticizers using a Python code and the function `scipy.optimize.curve_fit`, which employs a trust region reflective algorithm.²⁰ The T_g values for alginate-polyol were optimized case by case but allowed to range from −200 to 200 °C. In addition, the T_g of alginate was not initially constrained to be the same in all systems. No initialization values were given. The goodness-of-fit of models was evaluated by the total sum of squares (TSS), p -value, and standard error of the regression S .

Modeling (Bio)polymer Mixtures from Literature. Fox and GM(L) models, eqs 1 and 2, were also tested to an extended dataset of (bio)polymer blends carefully gathered from the literature. For completion, the full GM model was also investigated with alpha and beta values set to be positive (Supporting Information, Figure S15, and Table S3), as this constraint on the exponents is required to ensure convergence.

RESULTS AND DISCUSSION

Blends of Na-Alginate-(Sugar Alcohol). The glass transition temperature is a dynamic property with great current interest, since it is tied to thermal, mechanical, and vibrational properties. For instance, it is used not only to determine operational and processing temperature ranges but also influences mechanical properties like stiffness, tensile strength, toughness, hardness, and impact resistance.^{4,5} Besides standard thermomechanical factors, it has been related to materials' adhesive and healing mechanisms.^{21–23} Indirectly,

T_g will also affect electrical, optical, diffusion, and barrier properties, physical aging, and environmental stability. The T_g of polymers can conventionally be assessed through thermal analysis, i.e., evaluating the dependence of a specific volume, jump in heat capacity, or change in modulus on temperature.

We chose to study the T_g of alginate-polyols by DMTA due to the high sensitivity of this method to polymer relaxations. The onset of the primary relaxation (alpha) corresponds to the mobility of the main chain, which happens only at T_g . Figure 1

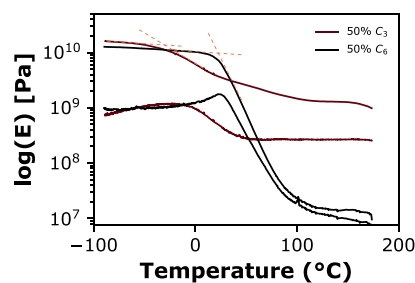


Figure 1. DMTA analysis of Na-alginate-(sugar alcohol) films containing 50 wt % glycerol (C_3) or sorbitol (C_6). The higher and lower curves respectively show the temperature dependence of the storage (E') and loss (E'') moduli. The dashed lines demonstrate how to estimate the temperature of a glass transition relaxation on a logarithmic modulus scale.

shows examples of alpha relaxation identification from highly plasticized alginate films. In a polymer blend, the presence of one major relaxation is a sign of miscibility. DMTA showed primarily one main relaxation for dried samples, while samples left to ambient relative humidity resulted in the appearance of additional relaxations. This phenomenon is further explained in Supporting Information (Figures S6 to S12). After the T_g event, the magnitude of the rubber plateau in alginate blends varied with the type and size of added sugar alcohol.

In Figure 2, the obtained T_g values of dry blends are plotted against the diluent's mass or equivalent molar fractions. Irrespective of the way the plasticizer content is evaluated, one cannot find a master curve of T_g versus plasticizer. This is surprising since sugar alcohols have the same generic chemical formula: $(\text{CHOH})_n\text{H}_2$. Even if we reduce all polyol concentrations to $[\text{CHOH}]$ equivalents, as shown in the inset graph of Figure 2B, there is no obvious universal T_g pattern. This strong argument supports that even though they are miscible, the sugar alcohols do not interact in the same way with the alginate chains. Similar findings of a plasticizer-dependent interaction and compatibility limit have previously been reported for the systems of alginate and C_3 and C_6 polyols.^{24,25}

We have performed model curve fitting to evaluate this T_g data (Figure 3). The widely applied Fox model is a simple harmonic mean of T_g contributions. We observe that this model does not fit the data of most sugar alcohol mixtures well. Even though the data fit for C_3 and C_5 are statistically accurate ($p < 0.05$, $S < 31$ °C), the values of T_g are poorly predicted (Table 1). Alternatively, the linearization of the generalized mean model, GML, shows an excellent prediction of datasets ($p < 0.01$, $S < 15$ °C). In addition, the GML goodness-of-fit is equivalent to that obtained via the analogous Gordon–Taylor equation. However, when possible, the T_g of individual components should also be experimentally obtained prior to model fitting. Hence, Table 1 values are to be taken as a

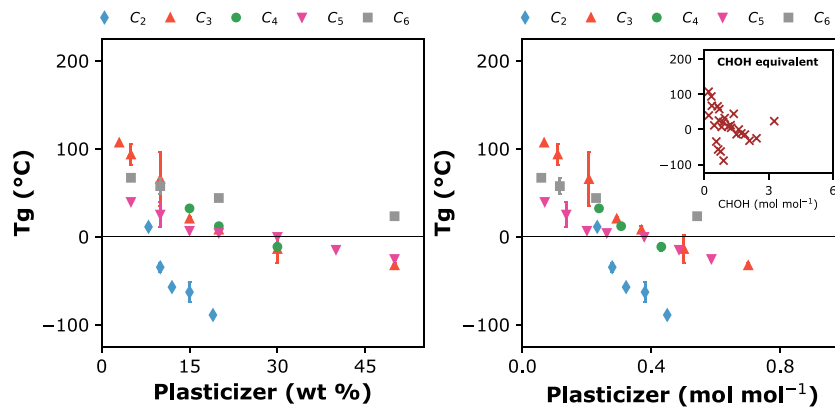


Figure 2. Glass transition temperature (T_g) of mixtures of Na-alginate and sugar alcohol plasticizers in mass (A) or molar (B) fractions. The sugar alcohols are depicted from C_2 to C_6 , based on the general formula $(CHOH)_nH_2$. Inset: T_g over plasticizer fractions translated to CHOH molar equivalents. Error bars indicate standard deviation.

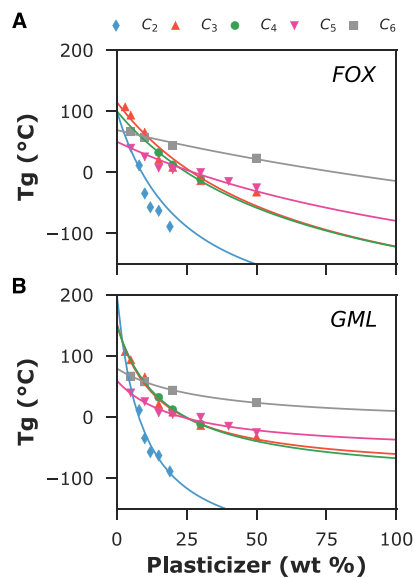


Figure 3. Experimental and calculated values of glass transition temperature (T_g) for Na-alginate-(sugar alcohols). (A) Fox model (FOX); (B) generalized mean linear model (GML). Curve-fitting was allowed using appropriate boundary values for the individual T_g parameters.

likelihood of T_g within the mixture. We also note that setting appropriate boundary conditions for the individual T_g contributions was necessary for a good-quality GML fit.

Another advantage of the T_g models is that they can be used to indirectly determine the (virtual) transition of a glassy polymer by extrapolation to zero diluent concentration. Like many biopolymers,²⁶ the T_g of pristine Na-alginate cannot be determined since thermal decomposition is observed before the transition. From Figure 3, all alginate-polyol datasets point toward a virtual Na-alginate T_g or T_{g1} , between 60 to 180 °C. Russo et al.²⁷ have previously reported a T_g of 133 °C for Na-alginate based on differential scanning calorimetry of relatively dry specimens. This seems like a reasonable estimate of M-rich alginate with the remaining tightly bound water. We can use this as a unified value for the Na-alginate-(sugar alcohol) data and retrofit it to the GML model (Figure 4). The approximated value of 133 °C does seem to fit well with most datasets except for C_6 ($p > 0.05$). That can be explained by the fact that the estimated T_g of Na-alginate is not an actual material property but an apparent one, with a plasticizer changing the internal structure. For C_5 and C_6 polyols, both studied models result in a lower T_g estimated for the neat alginate. It might be that the addition of a larger H-bonding plasticizer partially disrupted the semi-crystallinity of this block-copolymer. Evidence of semi-crystallinity was also found in powder XRD, haziness of alginate-polyol films, and a high modulus rubber plateau in the DMTA results (Supporting

Table 1. Glass Transition Parameters and Statistics Obtained from Curve-Fitting Fox or Generalized Mean Linear (GML) Models to Na-Alginate-(Sugar Alcohol) Datasets^a

polyol	model	T_{g1} (°C)	T_{g2} (°C)	model constant, k (fit \pm st. error)	TSS	p value	S (°C)
C_2	Fox	100*	−200*	1	7781	0.0173	31.27
	GML	200*	−196	1.93 ± 8.08	5665	0.0071	14.64
C_3	Fox	115	−122	1	17,436	0.0006	16.30
	GML	153	−61	3.92 ± 1.31	17,432	0.0002	8.31
C_4	Fox	100*	−122	1	954	0.0374	4.25
	GML	150*	−67	$3.30 \pm N/A$	954	N/A	N/A
C_5	Fox	50*	−80	1	2944	0.0009	8.10
	GML	60	−37	3.75 ± 2.01	2944	0.0008	5.19
C_6	Fox	69	−14	1	1077	0.0252	4.12
	GML	79	10	3.32 ± 0.00	1077	1.96×10^{-14}	6.62×10^{-13}

^aTSS: total sum of squares from the regression model; S : standard error of regression coefficient; N/A: not applicable due to zero degree of freedom. *Values corresponded to the used boundaries for the parameter.

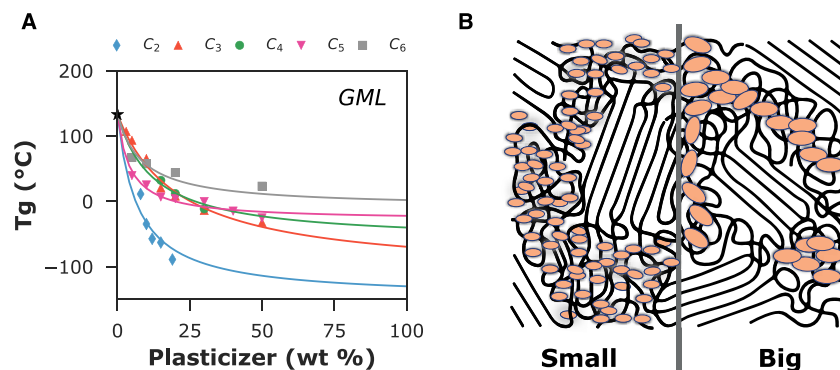


Figure 4. (A) Experimental and calculated values of glass transition temperature (T_g) for Na-alginate-(sugar alcohols). The generalized mean linear (GML) model was fitted by assuming a fixed glassy polymer T_g (star) and appropriate boundary values for the plasticizer T_g . (B) Illustration showing the difference in steric partitioning of a small or big plasticizer in a semi-crystalline polymer.

Table 2. Glass Transition Parameters and Statistics Obtained after Curve Fitting Generalized Mean Linear (GML) Model on Na-Alginate-(Sugar Alcohol) Datasets Using a Unified T_g for the Glassy Polymer^a

polyol	T_{g1} (°C)	T_{g2} (°C)	boundaries T_{g2} (°C)	k_{GM} (fit \pm st. error)	TSS	p value	S (°C)
C ₂	133*	−130	−100 \pm 30	5.37 \pm 42.85	5675	0.0432	24.96
C ₃	133*	−70	−79 \pm 30	2.83 \pm 1.23	17,439	0.0005	10.06
C ₄	133*	−40	−10 \pm 30	5.19 \pm N/A	956	N/A	N/A
C ₅	133*	−22	−22 \pm 30	14.90 \pm 14.65	2945	0.0003	7.89
C ₆	133*	2	−28 \pm 30	8.71 \pm 20.26	1109	0.2949	20.84

^aTSS: total sum of squares from the regression model; S: standard error of regression coefficient; N/A: not applicable due to zero degree of freedom; * Assumed value for neat Na-alginate as found by Russo and co-workers.²⁷

Information, Figures S1, S4, and S6–S11). Additionally, the plasticizer itself also showed a tendency to crystallize, as in the case of films with high content of C₄ or another C₆ compound (mannitol) (Supporting Information, Figures S2–S4).

Nevertheless, the new GML fits described all datasets well as a physical model ($S < 25$ °C) (Table 2). The fit values obtained for polyol T_g were in good agreement with the literature (Supporting Information, Table S2). The retrofit allows us to appropriately compare the alginate T_g over the increasing plasticizer fraction. For small-size polyols, C₂ and C₃, the T_g of the blend decreases rapidly with more polyol until a plateau is reached. For larger polyols, C₅ and C₆, we observe a T_g plateau already at a relatively lower polyol fraction. The GML model introduces a new constant, k_{GM} , which can be interpreted to arise from the static partitioning of the polymer/plasticizer fractions. From Table 2, the positive k_{GM} values for all Na-alginate-(sugar alcohols) indicate a substantial deviation from the case of miscibility ($k_{GM} = 1$, analogous to the Fox model). This k_{GM} value of >1 means that the effective plasticizer concentration appears to be higher than expected, resulting in a lower T_g at lower plasticizer content due to partitioning. The most significant deviations were observed for C₅ and C₆ alcohols, which might be explained by their size, causing substantial steric interaction-driven partitioning in a semi-crystalline matrix. We envision that a smaller plasticizer, such as C₂ polyol, would better penetrate and fill the free volume of the amorphous domains in contrast to C₅ and C₆ (Figure 4B), which would not be able to penetrate into the amorphous phase adjacent to the crystalline regions. In fact, it should be noticed that a certain level of semi-crystallinity will always result in $k_{GM} > 1$ as the concentration of diluent in the amorphous matrix regions will effectively be higher than expected from the overall composition because the crystalline regions are not (or much less) available.


The actual extent of semi-crystalline/amorphous fractions and domain sizes is experimentally challenging to be obtained. In theory, it might have been resolved by X-ray scattering and analysis of the crystalline peak width using the Scherrer equation. For the case of alginate semi-crystallinity, the measured crystalline degree would also serve to estimate the amorphous phase that is available for the plasticizer. Thus, this amorphous space would be equivalent to the length of heterogeneity. This rationale obviously assumes the plasticizer to be amorphous in the resulting mixture. Nevertheless, getting good information on this from scattering techniques is very challenging and would constitute an entire additional study. One advantage of the GML model is that the quantification of any crystalline or immobile fraction is not necessary to fit T_g data over composition and identify levels of heterogeneity, therefore, it might serve to better determine heterogeneity from structural analysis as it provides an expectation value.

Indeed, only the GML model resulted in good descriptive curves for the T_g of alginate-(sugar alcohols). We believe that this can only be due to partial miscibility or, to put it in another way, local heterogeneity of polymer and plasticizer distribution in such blends. In some cases, the components' specific interactions might cause this phenomenon, i.e., semi-crystallinity, H-bonding, and chirality. In fact, H-bonds are well known to affect the final semi-crystallinity of polymers.^{28–30} Another influence might be the chirality of C₄ to C₆ sugar alcohols, causing preferential sites in the plasticizer distribution. In general, the case of alginate blends is a good example that specific interaction contributions and partitioning need to be considered. The Fox model neglects such interactions as it is based solely on the entropic contributions of components in a fully miscible blend. However, fully and partially miscible blends can be described with GML, where the constant k_{GM} acts as a factor representing the heterogeneity. Regarding

thermodynamics, k_{GM} can also be interpreted as a convoluted factor of both (second order) enthalpic and entropic contributions.

Heterogeneity Constant. Other situations can cause static heterogeneity ($k_{GM} \neq 1$) of a diluent distribution within a glassy polymer matrix. A link to the T_g property can easily be interpreted if coupled with the free volume theory. For comparison purposes, one could classify heterogeneous blends resulting in k_{GM} below or above unity, as illustrated in Chart 2.

Chart 2. Illustrations of a Homogeneously Distributed ($k_{GM} = 1$) or Partitioned Diluent ($k_{GM} \neq 1$) in a Glassy Polymer Host^a

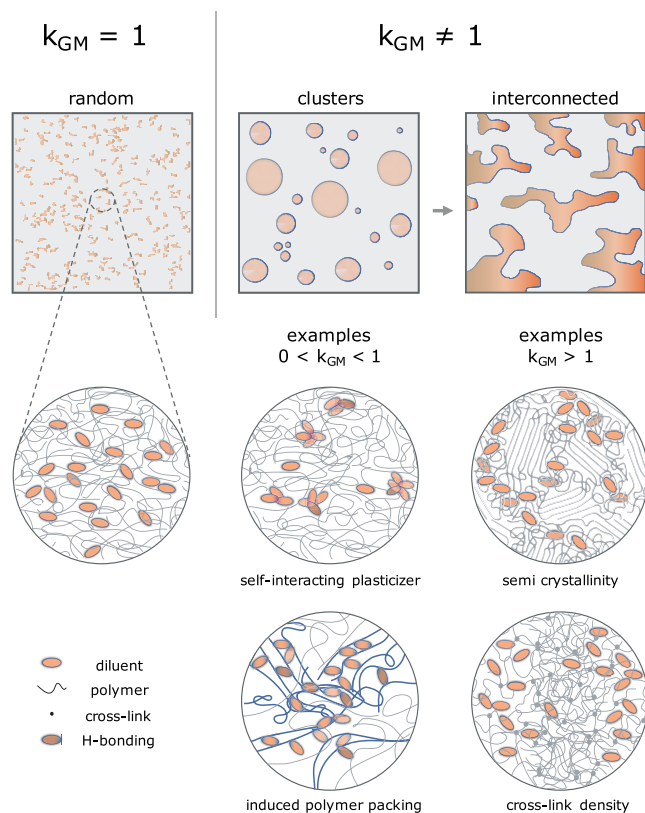

^aBoxes: microscale; circles: nanoscale.

Both semi-crystallinity and crosslinking density variations can result in T_g values lower than predicted by the Fox model ($k_{GM} > 1$). In the first case, as shown here with alginate-(polyols), steric partitioning effects can happen if the glassy matrix forms some crystalline or densely packed domains. With regards to cross-linking, a densely packed polymer–polymer network can also effectively create irregular boundaries to plasticizer clusters,⁷ even though cross-linking generically increases T_g , the plasticizer would be at a higher concentration in the available regions (Chart 2).

A few examples, usually in a low diluent content regime, can lead to T_g values higher than predicted by the Fox model ($0 < k_{GM} < 1$). For instance, often at lower volume fractions, a plasticizer with a tendency for segregation can result in the free volume cavities of the polymer being filled with plasticizer, e.g., the anti-plasticization effect. It can also happen that interactions between the diluent/plasticizer and stiff polymer chains will enhance the level of polymer packing.³¹ This is analogous to the anti-solvent polymer packing effect.³²

In both cases, further diluent clustering will frequently lead to microscopic phase separation of a blend, which is often observed in the form of opacity and coarsening of the phase-separated structure. Further, the diluent phase will either exudate out of the solid matrix, forming a binary or ternary-phased system, or even locally crystallize, thereby removing the plasticizer from the polymer matrix entirely. These two events are macroscopic. From a thermodynamic perspective, the k_{GM} factor can also characterize blends from miscible to immiscible states as it deviates away from unity.

It is interesting to note that the proposed local heterogeneity is not necessarily an undesirable phenomenon on a micro- or nanoscopic level. Heterogeneous plasticization will create zones of local plasticization and lubrication of amorphous polymer chains, resulting in mobility, pliability, and increased toughness. Simultaneously, the material's structural integrity or tenacity is still provided by the regions of low plasticizer content, preventing creep and flow. In other words, good plasticizers should not be too compatible with the polymer. It should be enough to mobilize without solubilizing the whole system.

Within the context of binary polymer blends, it might be helpful to consider the self-concentration approach proposed by Lodge and McLeish (2000) for blends with large T_g difference.¹² The theory states that the average composition of the local environment around a certain component must be enriched by itself because of chain connectivity. Therefore, even for homogeneous blends, each polymer will effectively experience its own composition dependent dynamics and effective T_g . This unavoidable segregation happens at the level of the chain Kuhn length and can get further exacerbated by the abovementioned specific interactions and clustering/segregation phenomena. The k_{GM} constant is obtained assuming a mixture's single or averaged T_g , where the product $k_{GM}\phi_2$ is an estimation of the (anti)plasticizer phase. Therefore, k_{GM} is also a convoluted expression of local heterogeneity from multiple length scales: at chain segment and cluster levels. A theoretical relationship between the effective self-concentrations of a polymer/diluent in a blend and the $GM(L)$ model constant is still lacking, which shall be considered in future work.

General Application to Heterogeneous Mixtures. In this section, we demonstrate the versatility of the $GM(L)$ model for polymer blends of synthetic and biological origin. The goal is to show via partitioning factor k_{GM} how easily systems fall outside true miscibility and simple rule-of-mixing theory, especially when biopolymers are used. These peculiar states of miscibility can arise from strong specific molecular interactions, steric effects, and conformational changes (morphology), depending strongly on sample history. It also makes sense to present this data compilation to connect our current work to general plasticization and anti-plasticization phenomena.

Figure 5 displays datasets with a greater decrease of T_g with diluent content ($k_{GM} > 1$) in contrast to what was predicted by Fox's theory. We can interpret those results with the main rationale that the effective diluent volumetric fraction in a polymer matrix is higher than initially expected. In Figure 5A, the synthetic polymer blend of Phenoxy resin or poly(hydroxy ether of bisphenol-A), with an aliphatic polyester of succinate (PDPS), shows decreased T_g values in comparison with those predicted by entropic contributions (Fox theory).³¹ It is common knowledge in polymer processing that a physical

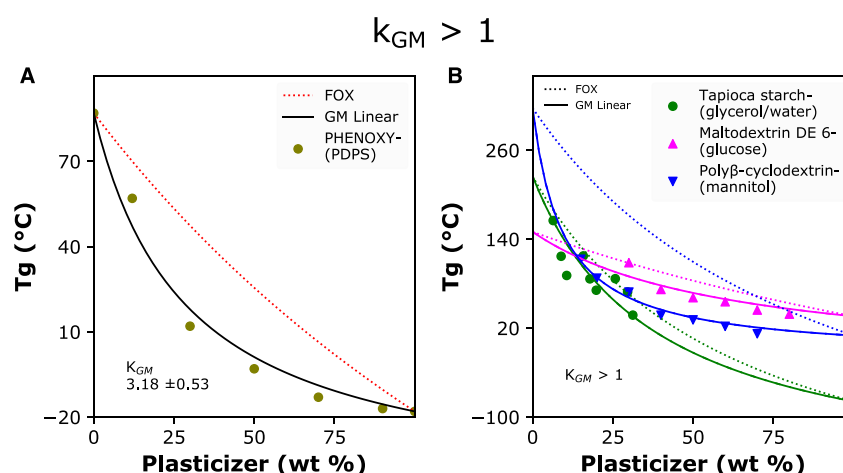


Figure 5. Experimental and calculated values of glass transition temperature (T_g) for several datasets displaying a greater-than-expected decrease with a plasticizer (or $k_{GM} > 1$). (A) Synthetic polymer blend of the polyhydroxyether of bisphenol A (PHENOXY) and poly(2,2-dimethyl-1,3-propylene succinate) (PDPS). (B) Biopolymer-(plasticizer) mixtures. FOX: Fox model (dotted lines); GM Linear: generalized mean linear model (solid lines). Curve-fitting was performed using fixed values for the individual T_g parameters for demonstrative purposes. Data from Schneider, 1997;³¹ Chang, 2006;³³ Linnenkugel et al, 2021;¹⁵ and Tabary et al, 2016.³⁷

Table 3. Glass Transition Parameters and Statistics Obtained from Curve Fitting Fox and Generalized Mean Linear (GM(L)) Model for Datasets Showing Deviations from the Rule of Mixing^a

system	T_{g1} (°C)	T_{g2} (°C)	model	model constant, k (fit \pm st. error)	TSS	p value	S (°C)	references
Phenoxy-(PDPS)	87*	-18*	Fox	1	11,167	N/A	18.92	Schneider, 1997 ³¹
			GML	3.18 ± 0.53	10,183	2.52×10^{-6}	5.31	
tapioca starch-(glycerol/water)	225* *	-79* *	Fox	1	15,759	N/A	28.57	Chang, 2006 ³³
			GML	1.41 ± 0.19	10,615	0.0009	24.24	
maltodextrin DE 6-(glucose)	150* *	36*	Fox	1	5107	N/A	13.07	Linnenkugel et al, 2021 ¹⁵
			GML	1.91 ± 0.72	3779	0.0024	9.44	
poly-cyclodextrin-(mannitol)	317*	10*	Fox	1	61,190	N/A	67.79	Tabary et al., 2016 ³⁷
			GML	5.60 ± 0.57	9984	6.95×10^{-7}	5.56	
PBIAz-(ULTEM)	427*	217*	Fox	1	112,615	N/A	30.08	Schneider 1997 ³¹
			GML	0.38 ± 0.04	98,908	6.04×10^{-13}	12.88	
sugar palm starch-(glycerol)	238*	-79* *	Fox	1	41,787	N/A	96.51	Sahari et al., 2013 ³⁸
			GML	0.14 ± 0.01	2526	0.0005	4.96	
chitosan-(polyols)	125*	-79* *	Fox	1	8196	N/A	54.83	Ma et al., 2019 ⁴⁰
			GML	0.09 ± 48.92	1124	0.7109	18.82	
corn starch/chitosan-(glycerol/water)	90* *	-79* *	Fox	1	10,514	N/A	52.92	Liu et al, 2013 ⁴⁵
			GML	0.11 ± 0.19	250	0.3069	11.35	

^a*Values used to fit models were extracted from the original data source; **Values used to fit models were absent and, thus, estimated by this study for illustrative purposes.

blending of polymers needs strong specific interactions to result in miscibility. In this case, H-bonding between carbonyl groups of succinate ester and hydroxyl of Phenoxy should overcome intramolecular cohesion and favor miscibility. However, the T_g curve gives us additional information that there must be competing energetic interactions since $k_{GM} > 1$. We speculate that this makes sense, since while Phenoxy is a blocky and amphiphilic polymer, the succinate polyester is polar, which might cause a more loosely packed structure, thus affecting the free volume of the blend.

The plasticized mixture of tapioca starch-(glycerol/water) also follows a $k_{GM} > 1$ trend (Figure 5). The difference between Fox and GML curves is subtle, as seen in Table 3. However, this becomes relevant if we know that the films formed a semi-crystalline matrix upon drying,³³ possibly resulting in plasticizer partitioning. In starches, the recrystallization of amylose and sometimes amylopectin can funda-

mentally influence properties, e.g., water vapor permeability and toughness. Water from moisture can further change T_g considerably.^{34,35} Consequently, the effect of water in crystalline biopolymer blends should always be evaluated or excluded.

Continuing on Figure 5B, the system of maltodextrin-glucose¹⁵ is interesting because the polymer is a polydisperse derivative of starch. The maltodextrin analyzed did not show crystallite sites; nevertheless, again, we find that $k_{GM} > 1$. This can maybe be explained by the strong H-bonding interactions between glucose and maltodextrin, creating plasticizer-polymer and polymer-polymer domains with possible steric effects.¹⁵ One could consider evaluating the extent of blending steric effects by systematically increasing the plasticizer size, for instance, from smaller polyols to different-chain length polyethylene glycols.³⁶

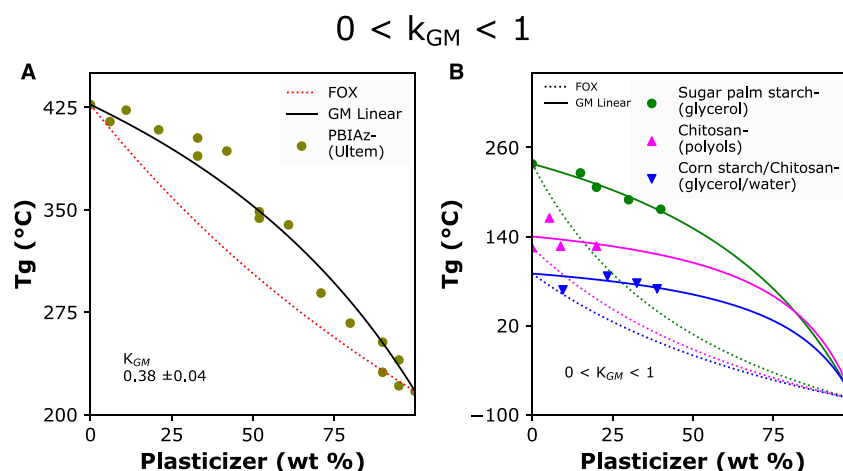


Figure 6. Experimental and calculated values of glass transition temperature (T_g) for several datasets displaying lower than expected decrease with a plasticizer (or $0 < k_{GM} < 1$). (A) Synthetic polymer blend of polybenzimidazole (PBIaz) and Ultem polyetherimide (Ultem). (B) Biopolymer-(plasticizer) mixtures. FOX: Fox model (dotted lines); GM Linear: generalized mean linear model (solid lines). Curve-fitting was performed using fixed values for the individual T_g parameters for demonstration purposes. Data from Schneider 1997;³¹ Sahari et al., 2013;³⁸ Ma et al., 2019;⁴⁰ and Liu et al., 2013.⁴⁵

Complexes of guest–host chemistry and cross-linking will also impact T_g values and trends. In Figure 5B, a blend between a methylated polymer of β -cyclodextrin (poly- β -cyclodextrin) and mannitol³⁷ shows a significant divergence from Fox's prediction. The polymer cyclodextrin can form hydrophobic-core inclusion complexes for drug delivery. The degree of di-ester cross-linking of the polymer with citrate is also essential to this application and T_g determination. The 36 wt % cross-linked and plasticized material was produced via a melting process. We could relate the T_g divergence from the ideal rule of mixing theory to the increased free volume of heterogeneous cross-linking of the sample, influencing molecular packing, along with mannitol's resistance to filling in the hydrophilic core of cyclodextrin inclusions.

A good plasticizer will result in pliable and durable materials that are easy to process by increasing the mixture's free volume or lowering the T_g . In turn, the mixed material should be tougher than the initial glassy polymer. In Figure 6, datasets show an increase of T_g with polymer or plasticizer content. This increase deviates completely from the Fox theory; for GM(L), it represents the case of $0 < k_{GM} < 1$ (Table 3). In fact, the synthetic blend of polybenzimidazole with commercial polyetherimide (Ultem)³¹ resulted in anti-plasticization. This phenomenon happens when we observe an increase in overall specific density with diluent addition.⁵ In extreme cases, even phase separation can occur. Within the partial miscibility region, anti-plasticization can be desired if a material's performance needs to be improved. However, a slowly decreasing T_g or even a plateau with increasing diluent content often seems counterintuitive. Polybenzimidazoles (PBIaz) are high-performance engineering thermoplastics with very stiff aromatic polymer cores and high T_g values (> 400 °C). In Figure 6A, we propose that the strong H-bonding interaction of PBIaz with Ultem via amine groups may cause additional stiffness via chain confinement. Hence, in this case, the favorable interactions between the chains cause the T_g to hardly decrease, giving rise to anti-plasticization.

For sugar palm starch-(glycerol) plasticized films (data in Figure 6B), strong H-bonding interactions between glycerol and amylose/amylopectin resulted in high T_g values.^{38,39} In particular, for starches, processing can be crucial. Starch

samples often must be gelatinized at high temperatures (> 130 °C) to obtain thermoplastic behavior. This could result in the plasticizer affecting the formation of crystalline domains from starch moieties. Similarly, systems of chitosan-polyols can also show significantly different properties depending on the strength of H-bonding interaction with the polymer backbone and overall moisture content (Figure 6). The chitosan data is shown with respect to the hydroxyl groups of sugar alcohols.⁴⁰ It is important to note that with further diluent addition, aging, or the increment of water from moisture, systems can dramatically move from the anti-plasticized to the plasticized regime.^{41–43} This can be observed both in T_g and in mechanical performance. The plasticization shift will depend on how strong the energetic interactions (enthalpy-driven) are and how favorable the increase of free volume (entropy-driven) is. In polymer blends and plasticized systems with large ΔT_g , this has been early on reported as a break (or cusp) in T_g -composition curves.^{11,44} The phenomena have mostly been attributed to a critical temperature, where a change in (strong) specific interactions with diluent fraction is observed.

Trends in multicomponent systems can also be interpreted similarly via k_{GM} . A 1:1 starch/chitosan blend was produced by microfluidization.⁴⁵ This blend was plasticized by glycerol and water, showing high anti-plasticization ($0 < k_{GM} < 1$) through strong H-bonding between the plasticizer and macromolecules. Previous works have only presented explicit thermodynamic solutions for multicomponent systems of polysaccharides, polyols, and water^{8,15} by working with Flory Huggins's free volume theory and extending the Couchman–Karasz expression for T_g .

Locally heterogeneous mixtures are ubiquitous in materials based on (bio)polymers, showing complex thermodynamic behavior. We have observed that k_{GM} can be a helpful tool to investigate (bio)polymer-diluent miscibility and possibly derive insights into structure–property relationships. We note that the linearized GML model is intended only for systems in a continuum, i.e., with no phase separation, crystallization, or phase inversion. Alternatively, the original GM model can adopt complex shapes (Supporting Information, Figure S15). Yet, we do not recommend modeling immiscible systems instead of splitting the developed phases. Overall, this study is

another example that the topic of glass transition is a complicated part of polymer science.⁴⁸ For example, it is often very challenging to determine the T_g of neat and biopolymer mixtures because the thermal transitions are found above degradation, increasing with the strength of electrostatic interactions, cross-links, and branching. Nowadays, this topic has become even more relevant with the rapid pursuit of tailored biodegradable and sustainable materials.

SUMMARY AND CONCLUSIONS

The generalized mean linear model, *GML*, works as a versatile model for studying the glass transition of polymer blends and plasticized systems. The model can be seen as a natural extension of the widely used Fox model (1956). In *GML*, if the constant k_{GM} is not 1, the system is not fully homogeneous—or Fox-like—and there is obvious evidence of heterogeneity or local demixing on a nanoscale. This can be explored via systematic studies to reveal the structure–property relationships of blends and elect a suitable and stable plasticizer for a specific application. To deal with strong interactions and heterogeneity, previous models have been proposed and modified, like Couchman–Karasz equations. However, the adopted solutions are often case-specific, phenomenological, and lead to over-parametrization, thus failing to describe the overall picture of (partial) miscibility.

This study showcases our *GML* model applied to predict the T_g of Na-alginate and polyols as plasticizing molecules. The experimental data on T_g clearly does not follow the Fox equation, while only the *GML* model can fit the results. This indicates that heterogeneity is important in alginate-polyol, as is also substantiated by the observed size effect of the type of polyol on T_g curves. This proposed heterogeneity indeed becomes apparent at higher plasticizer content from the overall sample appearance and via microscopy. Hence, sample processing history also becomes important. This heterogeneous plasticizer distribution is presumably caused by regio-specific interactions in the alginate-polyol system, such as the semi-crystallinity of the polymer matrix and steric effects in amorphous domains, as is apparent from our results. In addition, the *GML* model can easily describe the heterogeneity present in a wide range of diverse (bio)polymer blends, demonstrating its utility in analyzing complex polymer materials and even anti-plasticization phenomena.

Based on the above and considering the heterogeneous nature of biopolymers, research on bio-based systems can benefit from the *GML* approach. Living organisms produce biopolymers that are designed to be complex in structure and interactions, containing chiral macromolecular arrangements taking the form of helices and sheets or even showing semi-crystallinity. The already-present structural heterogeneity is often amplified by extraction and (re)processing conditions. In the case of solvent-based processes, the scale of heterogeneity can be large, especially if elevated temperatures are used. The chemical structure, therefore, is not so well-controlled. In addition, electrostatic interactions are nearly always present, which adds additional specific interactions not customarily found in fossil-based polymers. In summary, one could say that the molecular morphology of materials based on biopolymers and natural plasticizers is intrinsically heterogeneous. Hence, such systems should nearly always fall outside the commonly used rules of mixing for the thermal properties of polymer blends.

ASSOCIATED CONTENT

Supporting Information

The Supporting Information is available free of charge at <https://pubs.acs.org/doi/10.1021/acs.biomac.2c01356>.

Appendix A (derivation generalized mean model); Experimental design; powder XRD of Na-Alginates; photographs of thin films of alginate-polyol, also under different drying conditions; optical microscopy of thin films of alginate-polyol; TGA curves of alginate-polyols for C_2 plasticizer final concentration; DMTA curves of alginate-polyols under dry and humid conditions used for obtaining T_g ; residual plot for Fox and *GM(L)* models for alginate-polyols; sugar alcohol T_g ; *GM(L)* model applied to complex datasets from literature (PDF)

AUTHOR INFORMATION

Corresponding Authors

Suellen Pereira Espindola — Advanced Soft Matter, Department of Chemical Engineering, Faculty of Applied Sciences, Delft University of Technology, 2629 HZ Delft, The Netherlands; orcid.org/0000-0002-3135-3760; Email: S.PereiraEspindola-1@tudelft.nl

Stephen J. Picken — Advanced Soft Matter, Department of Chemical Engineering, Faculty of Applied Sciences, Delft University of Technology, 2629 HZ Delft, The Netherlands; orcid.org/0000-0002-6003-518X; Email: S.J.Picken@tudelft.nl

Authors

Ben Norder — Advanced Soft Matter, Department of Chemical Engineering, Faculty of Applied Sciences, Delft University of Technology, 2629 HZ Delft, The Netherlands

Ger J. M. Koper — Advanced Soft Matter, Department of Chemical Engineering, Faculty of Applied Sciences, Delft University of Technology, 2629 HZ Delft, The Netherlands

Complete contact information is available at: <https://pubs.acs.org/10.1021/acs.biomac.2c01356>

Author Contributions

The manuscript was written with the contributions of all authors. All authors have approved the final version of the manuscript.

Funding

This work was financed by the Netherlands Organization for Scientific Research (NWO), Earth and Life Sciences Division (grant number ALW GK.2016.025).

Notes

The authors declare no competing financial interest.

ACKNOWLEDGMENTS

We thank the Netherlands Organization for Scientific Research (NWO) for financing this study. We are also thankful to Dr. Jure Zlopaša for data curation and meaningful discussions on plasticization.

ABBREVIATIONS

C_2 , ethylene glycol; C_3 , glycerol; C_4 , erythritol; C_5 , arabitol; C_6 , sorbitol; TGA, thermogravimetric analysis; DMTA, dynamic mechanical thermal analysis; *GM*, generalized mean model;

GML, generalized mean linear model; k_{GM} constant of the generalized mean linear model

REFERENCES

- (1) Zhang, Y.; Han, J. H. Mechanical and Thermal Characteristics of Pea Starch Films Plasticized with Monosaccharides and Polyols. *J. Food Sci.* **2006**, *71*, E109–E118.
- (2) Tavassoli-Kafrani, E.; Shekarchizadeh, H.; Masoudpour-Behabadi, M. Development of Edible Films and Coatings from Alginates and Carrageenans. *Carbohydr. Polym.* **2016**, *137*, 360–374.
- (3) Area, M. R.; Montero, B.; Rico, M.; Barral, L.; Bouza, R.; López, J. Isosorbide Plasticized Corn Starch Filled with Poly(3-Hydroxybutyrate-Co-3-Hydroxyvalerate) Microparticles: Properties and Behavior under Environmental Factors. *Int. J. Biol. Macromol.* **2022**, *202*, 345–353.
- (4) Vieira, M. G. A.; da Silva, M. A.; dos Santos, L. O.; Beppu, M. M. Natural-Based Plasticizers and Biopolymer Films: A Review. *Eur. Polym. J.* **2011**, *47*, 254–263.
- (5) Stukalin, E. B.; Douglas, J. F.; Freed, K. F. Plasticization and Antiplasticization of Polymer Melts Diluted by Low Molar Mass Species. *J. Chem. Phys.* **2010**, *132*, No. 084504.
- (6) Fox, T. G. Influence of Diluent and of Copolymer Composition on the Glass Temperature of a Polymer System. *Bull. Am. Phys. Soc.* **1956**, *1*, 123.
- (7) Ten Brinke, G.; Karasz, F. E.; Ellis, T. S. Depression of Glass Transition Temperatures of Polymer Networks by Diluents. *Macromolecules* **1983**, *16*, 244–249.
- (8) van der Sman, R. G. M. Phase Separation, Antiplasticization and Moisture Sorption in Ternary Systems Containing Polysaccharides and Polyols. *Food Hydrocolloids* **2019**, *87*, 360–370.
- (9) Bocqué, M.; Voirin, C.; Lapinte, V.; Caillol, S.; Robin, J. J. Petro-Based and Bio-Based Plasticizers: Chemical Structures to Plasticizing Properties. *J. Polym. Sci., Part A: Polym. Chem.* **2016**, *54*, 11–33.
- (10) Wang, N.; Feng, X.; Pei, J.; Cui, Q.; Li, Y.; Liu, H.; Zhang, X. Biobased Reversible Cross-Linking Enables Self-Healing and Reprocessing of Epoxy Resins. *ACS Sustainable Chem. Eng.* **2022**, *10*, 3604–3613.
- (11) Prud'Homme, R. E. Polymeric Plasticizers for PVC. *J. Vinyl Technol.* **1989**, *11*, 6–8.
- (12) Lodge, T. P.; McLeish, T. C. B. Self-Concentrations and Effective Glass Transition Temperatures in Polymer Blends. *Macromolecules* **2000**, *33*, 5278–5284.
- (13) Couchman, P. R.; Karasz, F. E. A Classical Thermodynamic Discussion of the Effect of Composition on Glass-Transition Temperatures. *Macromolecules* **1978**, *11*, 117–119.
- (14) Gordon, M.; Taylor, J. S. Ideal Copolymers and the Second-Order Transitions of Synthetic Rubbers. I. Noncrystalline Copolymers. *Rubber Chem. Technol.* **1953**, *26*, 323–335.
- (15) Linnenkugel, S.; Paterson, A. H. J.; Huffman, L. M.; Bronlund, J. E. Prediction of the Glass Transition Temperature of Low Molecular Weight Components and Polysaccharide Mixtures. *J. Food Eng.* **2021**, *292*, No. 110345.
- (16) Huang, C. C.; Du, M. X.; Zhang, B. Q.; Liu, C. Y. Glass Transition Temperatures of Copolymers: Molecular Origins of Deviation from the Linear Relation. *Macromolecules* **2022**, *55*, 3189–3200.
- (17) Zetsche, A.; Fischer, E. W. Dielectric Studies of the A-relaxation in Miscible Polymer Blends and Its Relation to Concentration Fluctuations. *Acta Polym.* **1994**, *45*, 168–175.
- (18) Mayhew, E. J.; Neal, C. H.; Lee, S. Y.; Schmidt, S. J. Glass Transition Prediction Strategies Based on the Couchman-Karasz Equation in Model Confectionary Systems. *J. Food Eng.* **2017**, *214*, 287–302.
- (19) Pinal, R. Entropy of Mixing and the Glass Transition of Amorphous Mixtures. *Entropy* **2008**, *10*, 207–223.
- (20) Virtanen, P.; Gommers, R.; Oliphant, T. E.; Haberland, M.; Reddy, T.; Cournapeau, D.; Burovski, E.; Peterson, P.; Weckesser, W.; Bright, J.; van der Walt, S. J.; Brett, M.; Wilson, J.; Millman, K. J.; Mayorov, N.; Nelson, A. R. J.; Jones, E.; Kern, R.; Larson, E.; Carey, C. J.; Polat, İ.; Feng, Y.; Moore, E. W.; VanderPlas, J.; Laxalde, D.; Perktold, J.; Cimrman, R.; Henriksen, I.; Quintero, E. A.; Harris, C. R.; Archibald, A. M.; Ribeiro, A. H.; Pedregosa, F.; van Mulbregt, P.; SciPy 1.0 Contributors. SciPy 1.0: Fundamental Algorithms for Scientific Computing in Python. *Nat. Methods* **2020**, *17*, 261–272.
- (21) Boiko, Y. M.; Guérin, G.; Marikhin, V. A.; Prud'homme, R. E. Healing of Interfaces of Amorphous and Semi-Crystalline Poly (Ethylene Terephthalate) in the Vicinity of the Glass Transition Temperature. *Polymer* **2001**, *42*, 8695–8702.
- (22) Ji, G.; Zhang, P.; Nji, J.; John, M.; Li, G. Shape Memory Polymer-Based Self-Healing Composites. In *Recent Advances in Smart Self-healing Polymers and Composites*; Elsevier Ltd.; 2015; pp. 293–363, DOI: 10.1016/B978-1-78242-280-8.00011-X.
- (23) Gately, T. J.; Li, W.; Mostafavi, S. H.; Bardeen, C. J. Reversible Adhesion Switching Using Spiropyran Photoisomerization in a High Glass Transition Temperature Polymer. *Macromolecules* **2021**, *54*, 9319–9326.
- (24) Gao, C.; Pollet, E.; Avérous, L. Innovative Plasticized Alginate Obtained by Thermo-Mechanical Mixing: Effect of Different Biobased Polyols Systems. *Carbohydr. Polym.* **2017**, *157*, 669–676.
- (25) Gao, C.; Pollet, E.; Avérous, L. Properties of Glycerol-Plasticized Alginate Films Obtained by Thermo-Mechanical Mixing. *Food Hydrocolloids* **2017**, *63*, 414–420.
- (26) Gatsiou, C. A.; Bick, A.; Krokidis, X.; Economou, I. G. Atomistic and Coarse-Grained Simulations of Bulk Amorphous Amylose above and below the Glass Transition. *Macromolecules* **2022**, *55*, 2999–3010.
- (27) Russo, R.; Malinconico, M.; Santagata, G. Effect of Cross-Linking with Calcium Ions on the Physical Properties of Alginate Films. *Biomacromolecules* **2007**, *8*, 3193–3197.
- (28) Domján, A.; Bajdik, J.; Pintye-Hódi, K. Understanding of the Plasticizing Effects of Glycerol and PEG 400 on Chitosan Films Using Solid-State NMR Spectroscopy. *Macromolecules* **2009**, *42*, 4667–4673.
- (29) Anglès, M. N.; Dufresne, A. Plasticized Starch/Tunicin Whiskers Nanocomposite Materials. 2: Mechanical Behavior. *Macromolecules* **2001**, *34*, 2921–2931.
- (30) Decroix, C.; Chalame, Y.; Sudre, G.; Caroll, V. Thermo-Mechanical Properties and Blend Behaviour of Cellulose Acetate/Lactates and Acid Systems: Natural-Based Plasticizers. *Carbohydr. Polym.* **2020**, *237*, No. 116072.
- (31) Schneider, H. A. Conformational Entropy Contributions to the Glass Temperature of Blends of Miscible Polymers. *J. Res. Natl. Inst. Stand. Technol.* **1997**, *102*, 229.
- (32) Flory, P. J. *Principles of Polymer Chemistry*; Cornell university press, 1953.
- (33) Chang, Y. P.; Abd Karim, A.; Seow, C. C. Interactive Plasticizing-Antiplasticizing Effects of Water and Glycerol on the Tensile Properties of Tapioca Starch Films. *Food Hydrocolloids* **2006**, *20*, 1–8.
- (34) Li, W.; Yun, L.; Zhao, Y.; Zhi, Z.; Muhindo, E. M.; Geng, X.; Liu, R.; Wu, T.; Sui, W.; Zhang, M. Effect of Water Sorption on Glass Transition and Microstructural Variation of Dextran & Sugar Mixtures. *Carbohydr. Polym.* **2022**, *290*, No. 119505.
- (35) Stępień, A.; Grzyb, K. Comparison of Critical Storage Parameters of the Powders Containing Soy Protein Isolate and Inulin, Based on the Concepts: Water Activity and Temperature of Glass Transition. *Int. J. Biol. Macromol.* **2023**, *230*, No. 123174.
- (36) Pasini Cabello, S. D.; Takara, E. A.; Marchese, J.; Ochoa, N. A. Influence of Plasticizers in Pectin Films: Microstructural Changes. *Mater. Chem. Phys.* **2015**, *162*, 491–497.
- (37) Tabary, N.; Garcia-Fernandez, M. J.; Danède, F.; Descamps, M.; Martel, B.; Willart, J. F. Determination of the Glass Transition Temperature of Cyclodextrin Polymers. *Carbohydr. Polym.* **2016**, *148*, 172–180.
- (38) Sahari, J.; Sapuan, S. M.; Zainudin, E. S.; Maleque, M. A. Thermo-Mechanical Behaviors of Thermoplastic Starch Derived from Sugar Palm Tree (*Arenga Pinnata*). *Carbohydr. Polym.* **2013**, *92*, 1711–1716.

- (39) Sanyang, M. L.; Sapuan, S. M.; Jawaid, M.; Ishak, M. R.; Sahari, J. Effect of Plasticizer Type and Concentration on Tensile, Thermal and Barrier Properties of Biodegradable Films Based on Sugar Palm (Arenga Pinnata) Starch. *Polymers (Basel, Switz.)* **2015**, *7*, 1106–1124.
- (40) Ma, X.; Qiao, C.; Wang, X.; Yao, J.; Xu, J. Structural Characterization and Properties of Polyols Plasticized Chitosan Films. *Int. J. Biol. Macromol.* **2019**, *135*, 240–245.
- (41) Zhao, Y.; Liu, J.; Li, X.; Lu, Y.; Wang, S. Q. How and Why Polymer Glasses Lose Their Ductility Due to Plasticizers. *Macromolecules* **2017**, *50*, 2024–2032.
- (42) Lourdin, D.; Bizot, H.; Colonna, P. “Antiplasticization” in Starch-Glycerol Films? *J. Appl. Polym. Sci.* **1997**, *63*, 1047–1053.
- (43) Mascia, L.; Kouparitsas, Y.; Nocita, D.; Bao, X. Antiplasticization of Polymer Materials: Structural Aspects and Effects on Mechanical and Diffusion-Controlled Properties. *Polymers (Basel, Switz.)* **2020**, *12*, 769.
- (44) Aubin, M.; Prud'homme, R. E. Analysis of the Glass Transition Temperature of Miscible Polymer Blends. *Macromolecules* **1988**, *21*, 2945–2949.
- (45) Liu, H.; Adhikari, R.; Guo, Q.; Adhikari, B. Preparation and Characterization of Glycerol Plasticized (High-Amylose) Starch-Chitosan Films. *J. Food Eng.* **2013**, *116*, 588–597.
- (46) Lapuk, S. E.; Ponomareva, M. A.; Galukhin, A. V.; Mukhametzyanov, T. A.; Schick, C.; Gerasimov, A. V. Glass Transition Kinetics and Physical Aging of Polyvinylpyrrolidones with Different Molecular Masses. *Macromolecules* **2022**, *55*, 4516–4522.

Recommended by ACS

Effect of Oligomers Derived from Biodegradable Polyesters on Eco- and Neurotoxicity

Naoto Yoshinaga, Keiji Numata, *et al.*

APRIL 21, 2023
BIOMACROMOLECULES

[READ !\[\]\(05be7c7a8995decd503647c99211f7c2_img.jpg\)](#)

Double-Network Protein Hydrogels as Flexible Pressure Sensors for Contactless Delivery

Anbo Zheng, Yanxu Chen, *et al.*

MARCH 03, 2023
ACS APPLIED POLYMER MATERIALS

[READ !\[\]\(fe3aebe81acea8d45108cd2768939da7_img.jpg\)](#)

Structural and Dynamical Properties of Elastin-Like Peptides near Their Lower Critical Solution Temperature

Tatiana I. Morozova, Jean-Louis Barrat, *et al.*

MARCH 06, 2023
BIOMACROMOLECULES

[READ !\[\]\(899d8b7697d64725bf017d3296cfcf1b_img.jpg\)](#)

Composition of Minor Ampullate Silk Makes Its Properties Different from Those of Major Ampullate Silk

Hiroyuki Nakamura, Kazuharu Arakawa, *et al.*

APRIL 01, 2023
BIOMACROMOLECULES

[READ !\[\]\(40770d9ed6ed4f1222ebf89a1396e8b2_img.jpg\)](#)

[Get More Suggestions >](#)