

Small-scale testing of water-saturated wooden discs for determining the strength properties of timber foundation piles

Pagella, Giorgio; Struik, Mark; Mirra, Michele; van de Kuilen, Jan Willem

DOI

[10.1080/17480272.2024.2426070](https://doi.org/10.1080/17480272.2024.2426070)

Publication date

2024

Document Version

Final published version

Published in

Wood Material Science and Engineering

Citation (APA)

Pagella, G., Struik, M., Mirra, M., & van de Kuilen, J. W. (2024). Small-scale testing of water-saturated wooden discs for determining the strength properties of timber foundation piles. *Wood Material Science and Engineering*, 20(3), 734-736. <https://doi.org/10.1080/17480272.2024.2426070>

Important note


To cite this publication, please use the final published version (if applicable). Please check the document version above.

Copyright

Other than for strictly personal use, it is not permitted to download, forward or distribute the text or part of it, without the consent of the author(s) and/or copyright holder(s), unless the work is under an open content license such as Creative Commons.

Takedown policy

Please contact us and provide details if you believe this document breaches copyrights. We will remove access to the work immediately and investigate your claim.

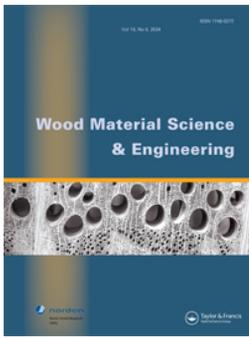

Small-scale testing of water-saturated wooden discs for determining the strength properties of timber foundation piles

Giorgio Pagella, Mark Struik, Michele Mirra & Jan Willem van de Kuilen

To cite this article: Giorgio Pagella, Mark Struik, Michele Mirra & Jan Willem van de Kuilen (17 Nov 2024): Small-scale testing of water-saturated wooden discs for determining the strength properties of timber foundation piles, Wood Material Science & Engineering, DOI: [10.1080/17480272.2024.2426070](https://doi.org/10.1080/17480272.2024.2426070)

To link to this article: <https://doi.org/10.1080/17480272.2024.2426070>



© 2024 The Author(s). Published by Informa UK Limited, trading as Taylor & Francis Group



Published online: 17 Nov 2024.



Submit your article to this journal [↗](#)



Article views: 89



View related articles [↗](#)



View Crossmark data [↗](#)

Small-scale testing of water-saturated wooden discs for determining the strength properties of timber foundation piles

Giorgio Pagella ^a, Mark Struik^a, Michele Mirra ^a and Jan Willem van de Kuilen ^{a,b}

^aFaculty of Civil Engineering and Geosciences, Biobased Structures and Materials, Delft University of Technology, Delft, The Netherlands; ^bSchool of Engineering and Design, Wood Technology, Technical University of Munich, München, Germany

ABSTRACT

The compressive strength properties of timber foundation piles in Amsterdam were characterised by small-scale compression tests on saturated round wooden discs. The discs were extracted from the head, middle, and tip of five spruce (*Picea abies*) piles dating back to 1727, 1886, 1922, and 2021. Several piles were subjected to underwater bacterial decay, causing a reduction of their load-carrying capacity over time. The amount of decay was determined with micro-drilling measurements. The results of small-scale tests were compared to large-scale axial compression tests to assess the feasibility of retrieving equivalent strength properties, considering the influence of diameters, decay, and wood knots.

ARTICLE HISTORY

Received 31 October 2024
Revised 2 November 2024
Accepted 2 November 2024

KEYWORDS

Wooden foundation piles; saturated strength properties; wood knots

1. Introduction

The bridges in the historic city centre of Amsterdam are supported by wooden foundation piles, mainly constructed between 100 and 300 years ago (Mirra *et al.* 2024). Nowadays, concerns regarding their potential safety issues have emerged. The piles remain entirely submerged below the water table, exposing them to bacterial decay in anaerobic conditions (Klaassen *et al.* 2005, Mirra *et al.* 2024). Piles degraded by bacteria in anoxic conditions can perform their function for centuries before showing a substantial reduction of the load-carrying capacity, as demonstrated in (Van de Kuilen 2007, Mirra *et al.* 2024, Pagella *et al.* 2024b). To characterise the remaining strength properties of the piles in Amsterdam in relation to bacterial degradation, a large-scale testing campaign was conducted in (Pagella *et al.* 2024b), involving a total of 201 pile segments that were retrieved from two bridges in Amsterdam. The research allowed to assess the remaining short-term compressive strength along the piles in relation to bacterial decay after three distinct periods of service time: 1727, 1886, and 1922. The micro-drilling technique enabled the estimation of the soft shell of each pile, which refers to the degraded outer layer of the cross-section with no remaining strength. Building on the previous works (Pagella *et al.* 2022, Pagella *et al.* 2024b), this paper explores the feasibility of conducting small-scale compression tests on approximately 150-mm-thick discs extracted from the piles. The objective is to determine whether testing wooden discs can reliably replicate the strength properties observed in larger pile segments. This approach aims to reduce the extensive experimental efforts and resources required for testing large-scale pile segments, especially focusing on the most influencing factors on the

strength: knots (Hoffmeyer 1987, Zobel and Van Buijtenen 1989, Pagella *et al.* 2022). Testing small sections with and without knots will examine the impact of knots on the strength properties, providing insights to streamline testing while ensuring accuracy in the results.

2. Materials and methods

The materials comprised six full-length tapered Norway spruce (*Picea abies*) piles. Four of these were retrieved from two bridges in Amsterdam, dating back to 1727 (2 piles), 1886 (2 piles), and 1922 (1 pile). One pile was a 'new' pile. The piles were ca. 12 meters long, with mean head diameter of 240 mm and a mean tip diameter of 170 mm. Severe decay was identified in the two piles from 1727 and in one pile from 1886, affecting 30–50% of their outer cross-sectional area consistently along each pile, as determined by micro-drilling analysis in (Pagella *et al.* 2024a, 2024b). Low decay was observed in the remaining two piles, one from 1992 and one from 1886, affecting less than 10% of their outer cross-sectional area. Each pile was divided into three parts (head, middle, and tip), from which a segment was extracted (Figure 1(a)) with a length equal to six times its most minor diameter (EN 14251 2003). Adjacent to this segment, two 150-mm-thick discs were sawn (Figure 1(b)): one from a knot cluster area (KW) and the other from a clear wood section (CW), with no knots. During handling and cutting procedures, the specimens were kept submerged in water tanks, aiming at a global moisture content (MC) higher than 60%, well above fibre saturation (EN 14251 2003). The short-term compressive strength ($f_{c,0,wet}$) was determined with large-scale compression tests for 20 saturated pile segments

CONTACT Giorgio Pagella  g.pagella@tudelft.nl  Faculty of Civil Engineering and Geosciences, Biobased Structures and Materials, Delft University of Technology, Delft 2628CN, The Netherlands

© 2024 The Author(s). Published by Informa UK Limited, trading as Taylor & Francis Group
This is an Open Access article distributed under the terms of the Creative Commons Attribution License (<http://creativecommons.org/licenses/by/4.0/>), which permits unrestricted use, distribution, and reproduction in any medium, provided the original work is properly cited. The terms on which this article has been published allow the posting of the Accepted Manuscript in a repository by the author(s) or with their consent.

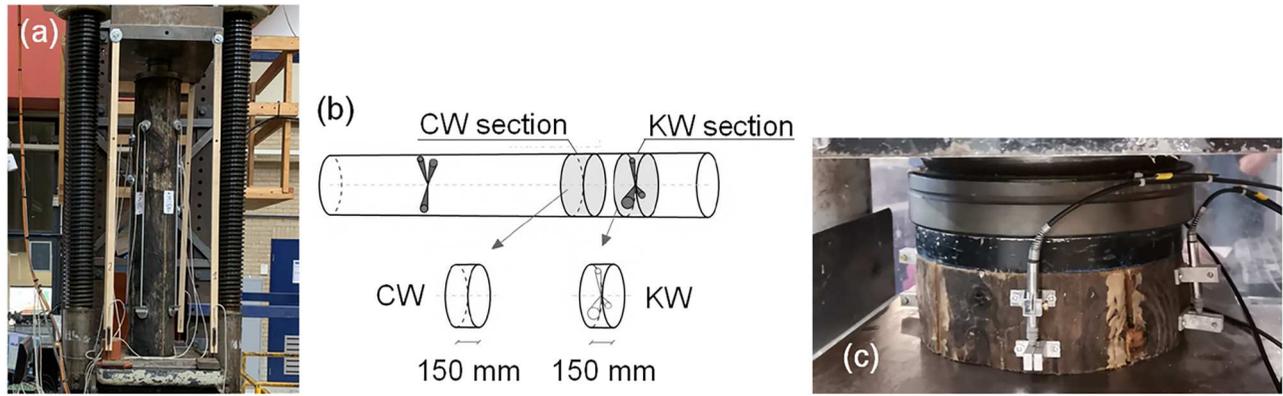


Figure 1. Test set-up: (a) compression test of large-scale pile segments, (b) extraction of 150 mm thick discs from a clear wood (CW) section and a section with knots (KW), and (c) small-scale compression test of a disc with knots.

(Figure 1(a)), explained in detail in (Pagella et al. 2024b), and with small-scale compression tests for 40 wooden discs (Figure 1(c)). The discs were loaded to failure within approximately 5 minutes, with a displacement-controlled set-up. The influence of the knots on $f_{c,0,wet}$ between the KW and CW discs, was studied considering an equivalent strength (EQ $f_{c,0,wet}$) of the discs, derived from the ratio between the maximum force reached in compression ($F_{c,0,test}$) and their average sound cross-sectional area (Pagella et al. 2024b), assuming that zero remaining strength is assigned to the degraded outer layer of the cross-section (Mirra et al. 2024, Pagella et al. 2024b). The presence of knots was calculated with the knot ratio (KR), i.e. the ratio between the sum of the knot diameters perpendicular to the longitudinal pile axis and the pile circumference.

3. Results

EQ $f_{c,0,wet}$ and KR for CW and KW discs were moderately correlated (Figure 2(a)). In particular, for $KR > 0.1$, the knots had an influence up to 30% on the compressive strength. For $KR < 0.1$, no significant difference was found between EQ $f_{c,0,wet}$ KW and CW discs. Considering this, the short-term strength of discs was very similar to that of larger pile segments (Figure 2(b)), independently of the amount of decay. Figure 2(c) shows the strong correlation between $f_{c,0,wet}$ of pile segments and discs, considering both CW and KW discs for $KR < 0.1$, and only KW discs for $KR > 0.1$.

4. Conclusions

This study conducted small-scale compression tests on 40 saturated wooden discs extracted from spruce foundation piles of varying service lives to determine their compressive strength relative to different knot ratios (KR). The results obtained from the wooden discs were compared with compression tests performed on full-scale pile segments. The compressive strength determined for the discs was very well aligned with that of the more significant pile segments. For $KR > 0.1$, the knots can influence the compressive strength by up to 30%. Thus, the strength properties of wooden piles can be accurately assessed using small-scale tests of wooden discs with knots (KW) extracted from the pile section with the highest KR. This method of small-scale testing of discs can be effectively adopted for characterising the strength properties of large-scale pile segments in Amsterdam, considering the presence of knots. This could considerably reduce the extensive experimental efforts of testing large-scale pile segments while providing accurate results for the short-term compressive strength of wooden foundation piles.

Acknowledgements

The Authors gratefully acknowledge the funder, municipality of Amsterdam, and Ruben Kunz, for his help during testing.

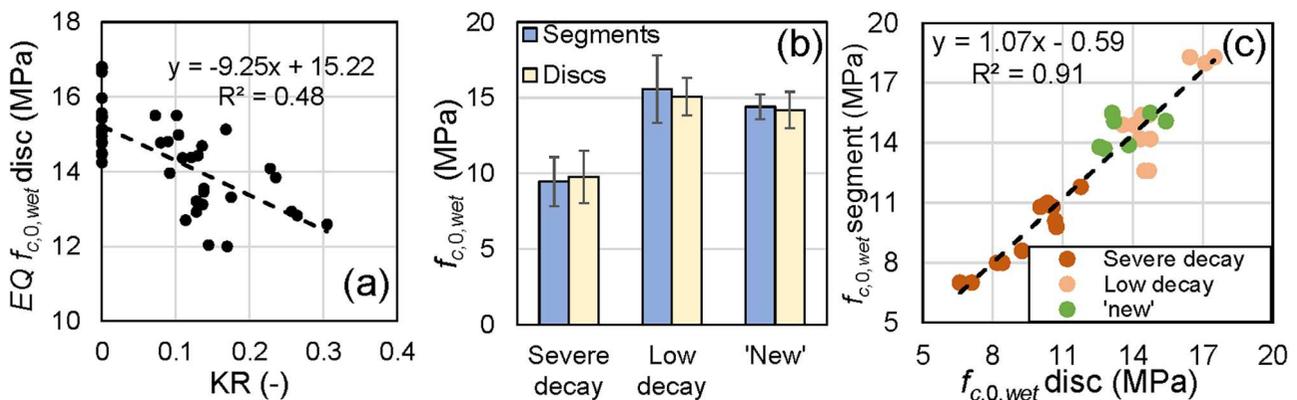


Figure 2. (a) relationship between EQ $f_{c,0,wet}$ discs and KR, (b) comparison between $f_{c,0,wet}$ of the pile segments and discs, and (c) relationship between $f_{c,0,wet}$ of the pile segments and discs for severe decay, low decay, and new wooden piles.

Disclosure statement

No potential conflict of interest was reported by the author(s).

Funding

This work was supported by Municipality of Amsterdam.

ORCID

Giorgio Pagella  <http://orcid.org/0000-0002-2552-4877>

Michele Mirra  <http://orcid.org/0000-0002-9898-8971>

Jan Willem van de Kuilen  <http://orcid.org/0000-0001-6974-3783>

References

- EN 14251, 2003. Structural round timber – Test methods. European Committee for Standardization (CEN).
- Hoffmeyer, P., 1987. The role of grain angle, knots, tension wood, compression wood, and other anomalies on the mechanical properties of wood. Technical University of Denmark. Byg Report No. TR-183.
- Klaassen, R.K.W.M., *et al.*, 2005. Preserving cultural heritage by preventing bacterial decay of wood in foundation poles and archaeological sites. Final report EVK4-CT-2001-00043. Wageningen.
- Mirra, M., *et al.*, 2024. Characterisation of bacterial decay effects on wooden foundation piles across various historical periods. *Construction and Building Materials*, 421, 135670. doi:10.1016/j.conbuildmat.2024.135670.
- Pagella, G., *et al.*, 2022. Influence of knots and density distribution on compressive strength of wooden foundation piles. Eighth International Conference on Structural Engineering, Mechanics and Computation, Cape Town, South Africa.
- Pagella, G., *et al.*, 2024a. Innovative application of micro-drilling for the assessment of decay and remaining mechanical properties of historic wooden foundation piles in Amsterdam. *Developments in the Built Environment*, 19, 100514. doi:10.1016/j.dibe.2024.100514.
- Pagella, G., *et al.*, 2024b. Characterization of the remaining material and mechanical properties of historic wooden foundation piles in Amsterdam. *Construction and Building Materials*, 450, 138616. doi:10.1016/j.conbuildmat.2024.
- Van de Kuilen, J.W.G., 2007. Service life modelling of timber structures. *Materials and Structures*, 40 (1), 151–161. doi:10.1617/s11527-006-9158-0.
- Zobel, B.J. and Van Buijtenen, J.P., 1989. *Wood variation: its causes and control*. 363. Berlin: Springer.