

Porous Metal-Organic Framework CUK-1 for Adsorption Heat Allocation toward Green Applications of Natural Refrigerant Water

Lee, Ji Sun; Yoon, Ji Woong; Mileo, Paulo G.M.; Cho, Kyung Ho; Park, Jaedeuk; Kim, Kiwoong; Kim, Hyungjun; de Lange, Martijn F.; Kapteijn, Freek; More Authors

DOI

[10.1021/acsami.9b02605](https://doi.org/10.1021/acsami.9b02605)

Publication date

2019

Document Version

Accepted author manuscript

Published in

ACS applied materials & interfaces

Citation (APA)

Lee, J. S., Yoon, J. W., Mileo, P. G. M., Cho, K. H., Park, J., Kim, K., Kim, H., de Lange, M. F., Kapteijn, F., & More Authors (2019). Porous Metal-Organic Framework CUK-1 for Adsorption Heat Allocation toward Green Applications of Natural Refrigerant Water. *ACS applied materials & interfaces*, 11(29), 25778-25789. <https://doi.org/10.1021/acsami.9b02605>

Important note

To cite this publication, please use the final published version (if applicable).
Please check the document version above.

Copyright

Other than for strictly personal use, it is not permitted to download, forward or distribute the text or part of it, without the consent of the author(s) and/or copyright holder(s), unless the work is under an open content license such as Creative Commons.

Takedown policy

Please contact us and provide details if you believe this document breaches copyrights.
We will remove access to the work immediately and investigate your claim.

The porous metal-organic framework CUK-1 for adsorption heat allocation toward green applications of natural refrigerant water

*Ji Sun Lee, ^a Ji Woong Yoon, ^a Paulo G. M. Mileo, ^b Kyung Ho Cho, ^a Jaedeuk Park, ^a Kiwoong Kim, ^a Hyungjun Kim, ^c Martijn F. deLange, ^d Freek Kapteijn, ^d Guillaume Maurin, ^b * Simon M. Humphrey ^e * and Jong-San Chang ^{a,f} **

^aResearch Group for Nanocatalyst and Chemical Safety Research Center, Korea Research Institute of Chemical Technology (KRICT), Gajeong-ro 141, Yuseong-gu, Daejeon 34114, South Korea, ^bInstitut Charles Gerhardt, Montpellier, UMR 5253 CNRS ENSCM UM, Université Montpellier, 34095 Montpellier, CEDEX 05, France, ^cGraduate School of Energy, Environment, Water and Sustainability, Korea Advanced Institute of Science and Technology (KAIST), Daehak-ro 291, Yuseong-gu, Daejeon 34141, South Korea, ^dCatalysis Engineering-Chemical Engineering Department, Delft University of Technology, Van der Maasweg 9, 2629 HZ Delft, The Netherlands, ^eDepartment of Chemistry, The University of Texas at Austin, 2.204 Welch Hall, 105 E. 24th St. Stop A5300, Austin, TX 78712, USA, ^fDepartment of Chemistry, Sungkyunkwan University, Suwon 440-476, South Korea

ABSTRACT: The development of new water adsorbents that are hydrothermally stable and can operate more efficiently than existing materials is essential for the advancement of water adsorption-driven chillers. Most of the existing benchmark materials and related systems in this field suffer from clear limitations that must be overcome to meet global requirements for sustainable and green energy production and utilization. Here, we report the energy-efficient water sorption properties of three isostructural metal-organic frameworks (MOFs) based on the simple ligand pyridine-2,4-dicarboxylate, named M-CUK-1 [$M_3(\mu_3\text{-OH})_2(2,4\text{-pdc})_2$] (where $M = \text{Co}^{2+}$, Ni^{2+} or Mg^{2+}). The highly hydrothermally-stable CUK-1 series feature step-like water adsorption isotherms, relatively high H_2O sorption capacities between $P/P_0 = 0.10\text{-}0.25$, stable cycling, facile regeneration, and most importantly, benchmark coefficient of performance (COP) values for cooling and heating at low driving temperature. Furthermore, these MOFs are prepared under green hydrothermal conditions in aqueous solutions. Our joint experimental-computational approach revealed that M-CUK-1 integrates several optimal features, resulting in promising materials as advanced water adsorbents for adsorption-driven cooling and heating applications.

1. INTRODUCTION

Recent advances in sustainable and green chemistry have focused on global issues such as climate change, energy production, availability of a safe and adequate water supply, and the use of water as a clean reaction/ synthesis medium.^{1,2} Water is one of the oldest refrigerants and an environmentally-friendly natural refrigerant that has attracted renewed interest because it is inherently benign, non-flammable, abundant and essentially cost-free.³ Therefore, the implementation of water as a refrigerant has been intensively considered in recent years for applications traditionally served by fluorocarbons.⁴ Global energy consumption for heating and

cooling in residential areas has increased steadily over the past few decades and it is forecasted to accelerate in the coming years, especially for cooling purposes.⁵ However, the current infrastructure relies primarily on non-sustainable energy resources; this is in misalignment with recent global agreements that aim to reduce our dependence on energy generation from fossil fuels.^{6,7}

When water evaporates under vacuum, it is cooled due to the substantial latent heat of evaporation (2500 kJ kg^{-1} or 40.7 kJ mol^{-1}). By exploiting this phenomenon, water has been touted as a ‘natural’ refrigerant fluid for adsorption-driven chiller/heat pump applications.⁸⁻¹³ The adsorption-driven chiller/heat pump technology features a two-step process comprising a working cycle and a regeneration cycle. The regeneration cycle of the adsorbent after the working cycle requires external work in the form of thermal energy input.

Ideally, the regeneration temperature should be as low as possible (below $80 \text{ }^\circ\text{C}$) to enable the use of low-grade and environmentally-sensitive heat sources (*e.g.*, industrial waste heat or solar energy). Such an arrangement could be considered to be a sustainable and more energy-efficient solution for both heating and cooling requirements.⁸ The implementation of this plan depends, in part, on the development of new materials that can act as green water adsorbents. Water adsorbents play a crucial role in ensuring energy-efficiency of adsorption chillers and heat pumps.⁸ Additionally, thermal energy storage by so-called ‘thermal batteries’, based on reversible adsorption/desorption of water as a working fluid rather than by conventional vapor compression, is a promising alternative to exploit waste thermal energy for heat re-allocation.⁸ A suitable water adsorbent needs to fulfil the following five criteria under specific working conditions: (i) have a high working capacity on a volumetric (or gravimetric) basis; (ii) have a high coefficient of performance (COP) values for cooling and heating which indicate thermal energy efficiency; (iii)

allow for rapid adsorption and desorption of water; (iv) permit regeneration at low temperature (< 80 °C); and (v) have sufficient chemical and mechanical robustness, particularly being resistant to degradation in hot water vapour (*i.e.*, steam).^{14,15} In addition to these criteria, the synthesis cost of the selected adsorbent is an important economical consideration for large-scale implementation.

Silica gel and aluminosilicate zeolites are currently the standard materials employed as water adsorbents. While these materials are relatively cheap and easy to prepare in large quantities, they suffer from distinct drawbacks for adsorption-chiller/heat pump applications, including weak hydrophilicity leading to water adsorption at rather high relative pressures (*e.g.*, silica gel), and very strong hydrophilic character that necessitates the need for high regeneration temperatures (often >150 °C; *e.g.*, aluminosilicate zeolites).¹⁶ As an alternative, the CHA-type silico-aluminophosphate material SAPO-34 has emerged as a commercially-viable adsorbent for adsorption-driven chillers due to its high water uptake at low relative pressure, combined with its very high durability and robustness.^{17,18} However, efforts to develop more advanced water adsorbents are both critical and timely since the working capacities of these commercial adsorbents at low pressure ($P/P_0 = 0.15-0.35$) are not large enough.

Metal-Organic Frameworks (MOFs) are a contemporary class of microporous materials that are characterized by having broadly-tunable structural and chemical properties, owing to an essentially unlimited combination of inorganic metal and organic linker components available for their synthesis.¹⁹⁻²¹ In the context of the water adsorption-driven chiller/heat pump applications, the richness of this family of materials leverages the ability to modulate the hydrophilic/hydrophobic environment of the micropores *via* synthetic design to an extent that is not possible for classical aluminosilicate materials. This can be achieved by incorporating particular functional groups within the MOF framework. In 2006, Chang and co-workers were the

first to report an energy-efficient sorption of water by MOF adsorbents exhibiting large water uptakes and easy regeneration at low temperature, *i.e.* below 80 °C.²² Specifically, we reported the energy-efficient dehumidification by the hydrothermally stable mesoporous metal(III) polycarboxylate MOFs, MIL-100 and MIL-101, which showed exceptional water sorption loading capacities and low associated regeneration energy penalties.²³ Subsequently, Henninger and Janiak proposed a heat transformation application using the MOF ISE-1 as a water adsorbent.²⁴ Since these pioneering reports, several more MOFs have been reported as promising candidates for water sorption applications.^{8,9,25-30} However, none of the MOFs studied so far have completely fulfilled all five of the criteria mentioned above, required for adsorption chiller and/or heat pump applications. Here we propose M-CUK-1 (CUK = Cambridge-University-KRICT), comprised of metal(II) cations and the di-anion of pyridine-2,4-dicarboxylic acid (2,4-pdcH₂)³¹ as viable candidates for cooling and heating at low driving temperatures, owing to their remarkable coefficients of performance under realistic working conditions, combined with their very high hydrothermal stability and ease of regeneration. The M-CUK-1 materials can also be easily tuned in terms of chemical modulation of the inorganic structural components, *i.e.*, by obtaining isostructural materials based on 3*s*- or 3*d*-metals, Mg²⁺, Co²⁺ or Ni²⁺.^{32,33} This assertion is demonstrated and confirmed by a combined experimental and computational investigation that integrates gravimetric sorption testing, thermodynamic calculations of cooling/heating performances and molecular simulations. This work equally aims to investigate the energy-efficient water sorption properties of M-CUK-1 materials that could be potentially applied to thermal energy storage as well as for adsorption-driven heating/cooling.

2. RESULTS AND DISCUSSION

2.1. Synthesis and characterization of M-CUK-1 (M = Mg, Co, Ni)

The Co(II)-based CUK-1 was the first phase reported in 2005;³⁴ This material was obtained by the hydrothermal reaction of pyridine-2,4- dicarboxylic acid (2,4-pdcH₂) and CoCl₂ with excess KOH in water at 200 °C for 15 h.³¹ In the reaction, sub-critical water under autogeneous pressure provides a highly solubilizing reaction medium, and the forcing reaction conditions yield porous Co-CUK-1, [Co₃(μ₃-OH)₂(2,4-pdc)₂]₂·9H₂O as a single, crystalline phase. Co-CUK-1 cannot be obtained by conventional solvothermal synthesis.

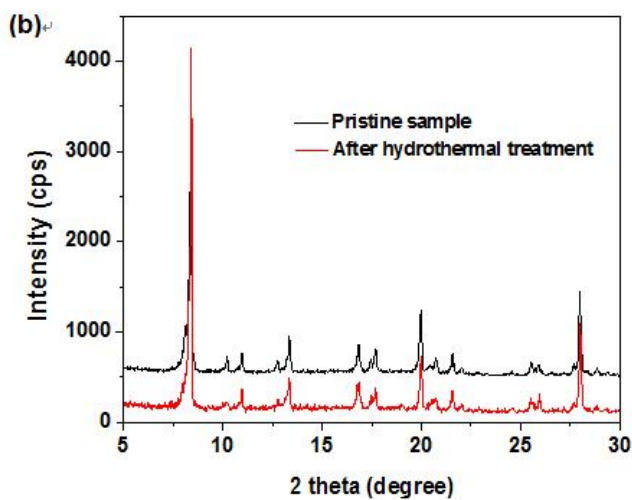
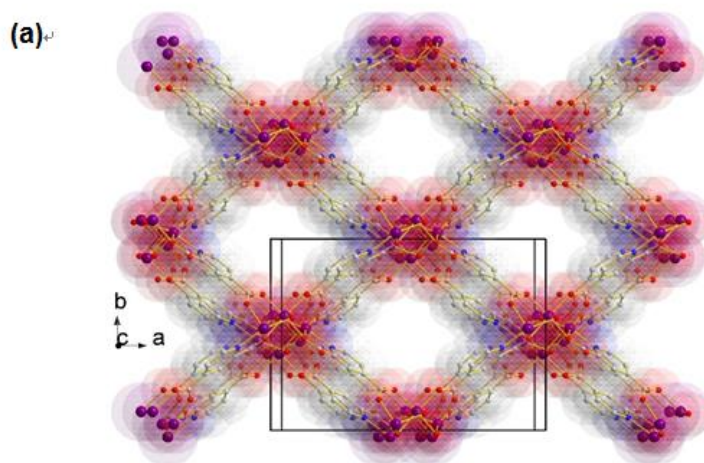


Figure 1. (a) The extended structure of desolvated Co-CUK-1 obtained by heating a single crystal to 100 °C in order to remove H₂O; The structural image of (a) shows the space-filling model and guest-accessible voids when viewed perpendicular to the direction of propagation of infinite 1-dimensional diamondoid channels.³⁰ (b) Powder X-ray diffraction (PXRD) patterns of Co-CUK-1 before and after hydrothermal treatment at 150°C for 3 days.

As illustrated in **Figure 1a**, Co-CUK-1 has an infinite 1-dimensional microchannel system supported by highly-connected 2,4-pdc ligands that are arranged in orthogonal fashion around edge- and vertex-sharing M₃(OH)₂ chains. The structural details of the CUK-1 materials are discussed in the previous papers.³¹⁻³³ The channels are filled with water molecules that can be fully removed by heating and/or under vacuum, without loss of crystallinity, as originally determined by single crystal X-ray diffraction (SCXRD) and bulk powder X-ray diffraction (PXRD) studies.³¹

Somewhat more recently, upon experimentation with other M(II) salts, two further analogues, Ni-CUK-1³² and Mg-CUK-1,³³ were also identified using NiCl₂ in a 3:2:9 molar ratio of NiCl₂:2,4-pdcH₂:KOH, or Mg(NO₃)₂ in a 3:2:8 molar ratio of Mg(NO₃)₂:2,4-pdcH₂:KOH, respectively, by analogous hydrothermal heating methods between 200-220 °C. Both the Ni and Mg materials are isostructural with the Co phase and the lattice connectivity is identical for the three frameworks. The space group of the as-synthesized Mg-CUK-1 was found to be of lower symmetry (*P2₁/c* in the Mg-analogue *versus* *C2/c* in the Co- and Ni-analogues) due to the positions of water molecules inside the pores, however Mg-CUK-1 reverts to a *C*-centered cell setting upon desolvation.³³ The PXRD patterns of three as-synthesized CUK-1 materials prepared in this work are actually concurrent with the simulated patterns obtained from the SCXRD structures.³¹ Thermogravimetric analysis (TGA) profiles of the freshly-prepared (hydrated) Co-CUK-1 and Ni-CUK-1 in a nitrogen carrier flow show close correlation in terms of their temperature-dependent mass loss behaviour (Supplementary Figure S1). There is a rapid loss of guest water molecules between 25-100 °C,

which conforms very closely to the mass loss that is expected for 9 H₂O per 3 M(II) ions (M = Co, Ni; observed mass loss = 22.4%; calculated = 21%) at which point the materials become resistant to any further mass loss due to a ligand-based decarboxylation until *ca.* 410 °C (Co-CUK-1) or 430 °C (Ni-CUK-1). The TGA for the hydrated Mg-CUK-1 confirmed a rapid 25% mass loss between 25 and 100 °C, after which there is a very large temperature window where Mg-CUK-1 remains thermally stable, until the onset of degradation *ca.* 510 °C.

The larger initial weight loss of Mg-CUK-1 compared to the two other CUK-1 is due to the significantly lower mass of Mg²⁺ (*i.e.*, Mg-CUK-1 is significantly less dense than the Co and Ni phases). Meanwhile, the higher thermal stability is attributed to the greater extent of electrostatic bonding between Mg²⁺ and the carboxylate-*O* donors. Overall, the TGA results evidenced that all M-CUK-1 are highly thermally robust, the Mg-version being more stable than the two 3*d*-metal analogues. CO₂ adsorption at -78.5 °C is commonly studied in the MOF literature, especially when cryogenic N₂ adsorption (at -196 °C) yields no information due to several possible limitations in terms of accessibility of the pores (case of ultra-small pore MOFs) or/and very slow kinetics of the adsorbates (case of strongly hindered environment of the porosity). Typically, CO₂ physisorption at -78.5 °C was used to estimate the BET area of the Ca-based MOF UTSA-280, which does not adsorb N₂ at -196 °C.³⁵ For M-CUK-1, the adsorption isotherms of CO₂ at -78.5 °C were used to evaluate the BET areas (Figure S2) since the N₂ physisorption isotherm of Co-CUK-1 at -196 °C was not correctly obtained due to the low temperature phase transformation of this solid.^{36,37} Fitting the BET equation to the resulting isotherms of CO₂ gives the following estimated BET areas: 510 m² g⁻¹ (Co-CUK-1); 520 m² g⁻¹ (Ni-CUK-1); 580 m² g⁻¹ (Mg-CUK-1). The micropore volumes of M-CUK-1 were obtained from the CO₂ adsorption at -77 °C, by applying the Dubinin-Radushkevich equation.³⁸ The micropore volumes of all three analogues are

similar: 0.26 mL g⁻¹ (Co-CUK-1); 0.26 mL g⁻¹ (Ni-CUK-1); and 0.28 mL g⁻¹ (Mg-CUK-1). Scanning electron microscopy (SEM) and optical microscopy analyses of the as-synthesized materials without grinding revealed average crystallite sizes of 180 × 80 μm, 15 × 15 μm, and 180 × 50 μm for Co-CUK-1, Ni-CUK-1, and Mg-CUK-1, respectively (Figure S3). Crystals of Co- and Mg-CUK-1 displayed distorted tetragonal-like morphology. Their sizes are significantly larger than that of Ni-CUK-1.

Since the hydrothermal stability of a porous solid is a prerequisite for heat transfer applications using water as a working fluid, the M-CUK-1 materials were exposed to boiling water. Co-CUK-1 and Ni-CUK-1 were found to maintain their crystal structures after hydrothermal treatment in water at 150 °C after 3 days (**Figure 1b** and Figure S4). In addition, the solids that had been subjected to this hydrothermal treatment maintained their water sorption properties upon isolation (Figure S5). Mg-CUK-1 was found to be less stable than the two 3d-metal analogues when exposed to harsh refluxing water conditions, however it is equally resistant to degradation under the lower-temperature (*ca.* 70 °C) working conditions required for adsorption cooling and dehumidification applications over prolonged periods. Indeed, **Figure 2** reveals the hydrolytic stability of Mg-CUK-1 under multiple cyclic conditions, as illustrated by the plots of the water adsorption at 30 °C with a 60% Relative Humidity (RH), and after water desorption at 70 °C and 8% RH. These results suggest that Mg-CUK-1 is kinetically stable under hydrothermal conditions at elevated temperatures, which is in-line with the highly electrostatic character of the Mg(II)-carboxylate-O bonds. Yaghi and co-workers emphasized difference in terms of thermodynamic and kinetic stabilities of water-adsorbent MOFs in the presence of water at elevated temperatures.³⁹ It is assumed that the kinetic stability of Mg-CUK-1 under hydrolytic conditions is ascribed to the

rigidity of its building node with high connectivity through triple bridging of Mg cations with two carboxylate bridges and a single-atom oxygen bridge.

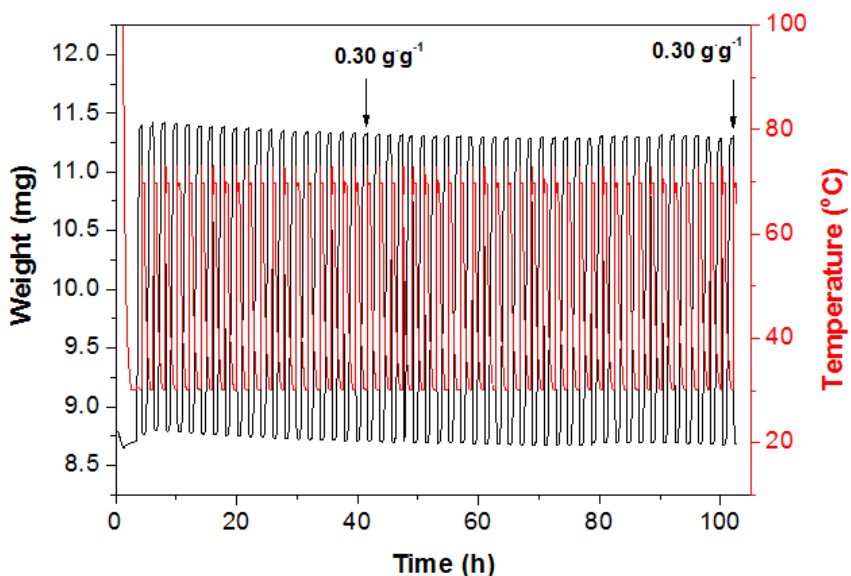


Figure 2. Hydrothermal stability of Mg-CUK-1 through TGA profile for 50 cycles of water adsorption-desorption. Test conditions: adsorption at 30 °C in humid nitrogen (60% RH) and desorption at 70 °C in N₂ gas with low humidity (8% RH). **In both conditions the absolute humidity is the same (~0.016 kg H₂O/kg dry air).** Prior to the multiple cycle experiment, the first cycle was carried out by a different condition such that Mg-CUK-1 is dehydrated at 150 °C for 1 h in dry N₂, hydrated at 30 °C in humid nitrogen (35% RH), and then dehydrated again at 70 °C in N₂ with low humidity (8% RH).

2.2. Water sorption properties of Co-CUK-1

Water sorption isotherms for Co-CUK-1 measured at three different temperatures are depicted in **Figure 3a**. The water sorption isotherms show a sigmoidal shape with a very steep adsorption step *ca.* $P/P_0 \sim 0.12$ (P_0 = saturation vapour pressure), indicating the presence of a uniform micropore. Most of the water uptake occurs at $P/P_0 < 0.25$. Considering a calculated crystal density of 1.46 g mL⁻¹, Co-CUK-1 exhibits a fairly high equilibrium water uptake of 0.28 g g⁻¹ (equivalent to 0.41

mL mL⁻¹) at 30 °C and $P/P_0 = 0.4$. The adsorption-desorption isotherms also portray fully reversible water sorption with only a small hysteresis, which is indicative of easy water cycling regeneration by the sample.

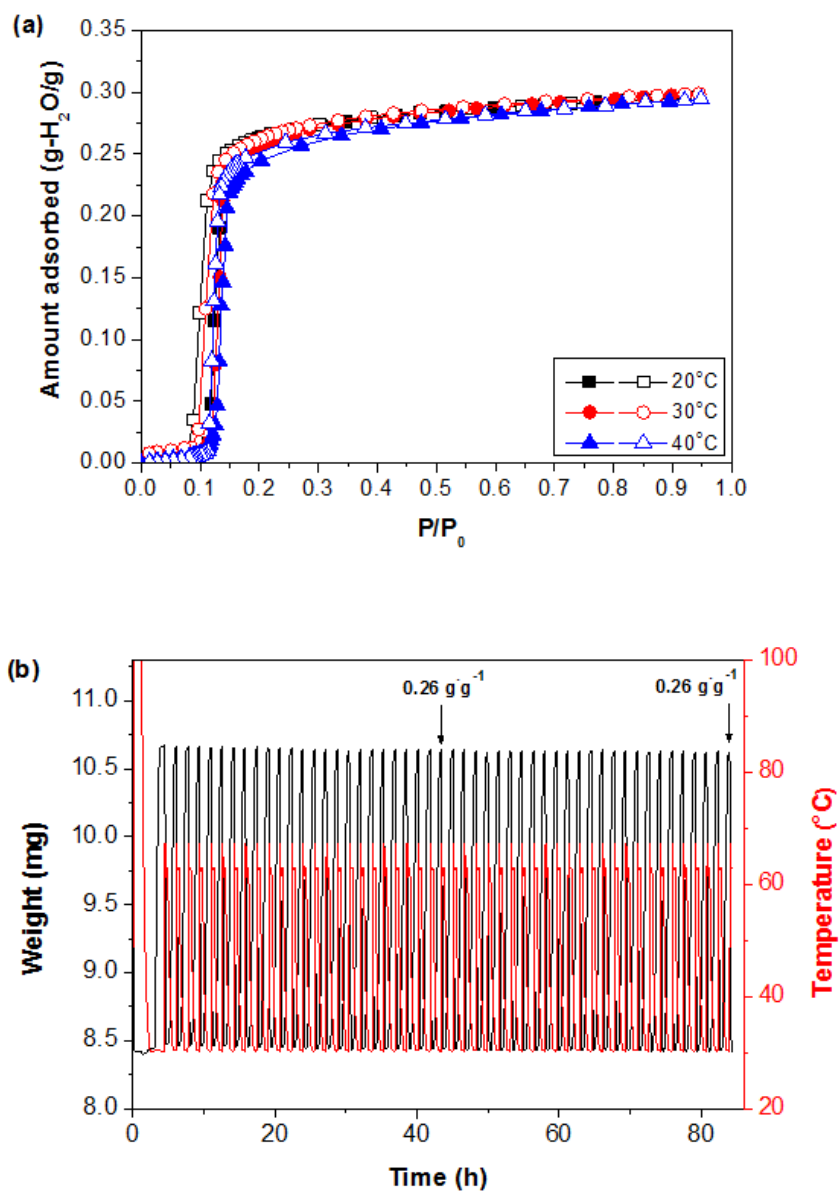


Figure 3. (a) Water sorption isotherms of Co-CUK-1 as a function of sorption temperatures (solid symbols: adsorption; open symbols: desorption); (b) TGA profile for 50 cycles of water adsorption-desorption of Co-CUK-1. Test conditions: adsorption at 30 °C in humid N₂ gas (35% RH) and desorption at 63 °C under N₂ with low humidity (6% RH). Absolute humidity in both

cases is ~ 0.009 kg H₂O/kg dry air. Prior to the multiple cycle experiment, the first cycle was carried out by a different condition such that Co-CUK-1 is dehydrated at 150 °C for 1 h in dry N₂, hydrated at 30 °C in humid N₂ (35% RH), and then dehydrated again at 63 °C in nitrogen with low humidity (6% RH). In the upper graph, solid symbols and open symbols denote adsorption and desorption, respectively.

The isosteric heat of water adsorption for Co-CUK-1 was calculated by applying the Clausius-Clapeyron equation for the adsorption isotherms collected at different temperatures.⁴⁰ The resulting isosteric heat of water adsorption was found to be 46.9 kJ mol⁻¹ up to 0.22 g g⁻¹ water uptake, which is above the evaporation enthalpy of water (40.7 kJ mol⁻¹) (Supplementary Figure S6). In order to check the reliability of this estimated heat of water adsorption, we also applied the virial equation⁴¹ to thermodynamic calculations of the adsorption isotherms (Supplementary Figure S21). It was confirmed that the isosteric heats of adsorption could be accurately reproduced using virial coefficient fitting.

To verify the low temperature desorption as well as the cycling stability of Co-CUK-1 between adsorption and desorption steps under working conditions in a hypothetical adsorption chiller, water sorption cycling experiments were then repeated 50 times: (i) each adsorption step was performed at 30 °C and 35% RH in N₂ gas; (ii) the desorption leg proceeded at 63 °C in N₂ gas with a lower RH = 6% (**Figure 3b**). The highly reversible cyclability test data shows a negligible difference in working capacity (0.26 ± 0.01 g g⁻¹) between consecutive cycles, indicating a very high cycling durability of Co-CUK-1. This result clearly highlights the energy-efficient water sorption properties of this MOF, which is suitable for facile dehydration below 70 °C.

2.3. Water adsorption mechanism in Co-CUK-1

A direct comparison of **Figure 4a** and **4b** shows that the experimental adsorption isotherm for Co-CUK-1 was accurately reproduced by Grand Canonical Monte Carlo (GCMC) simulations for Co-CUK-1. In particular, the onset of the pore-filling at $P/P_0 = 0.12$ is extremely well captured while the slight deviation between the experimental and predicted water uptake at saturation is most probably associated to extra-adsorption at the external surface of the materials. The hydrophobic behaviour of the MOF at the initial stage of the adsorption is also confirmed by the simulated adsorption enthalpy below the evaporation enthalpy of water (*i.e.*, below $P/P_0 = 0.12$; see Supplementary Figure S7) which gave an enthalpy of adsorption in the range of 45 to 60 kJ mol⁻¹ above $P/P_0 = 0.12$. This prediction is consistent with the experimental isosteric heat of adsorption discussed above (Figure S6). This observation validates the microscopic models employed to represent both MOF and water, as well as the force field parameters used to describe the interactions between Co-CUK-1 and H₂O. The water adsorption mechanism was further explored to shed light on the adsorption behaviour of Co-CUK-1 at the microscopic scale. We observed that at low coverage, the water molecules tend to interact preferentially with the hydroxyl groups (μ_3 -OH) of the MOF framework.

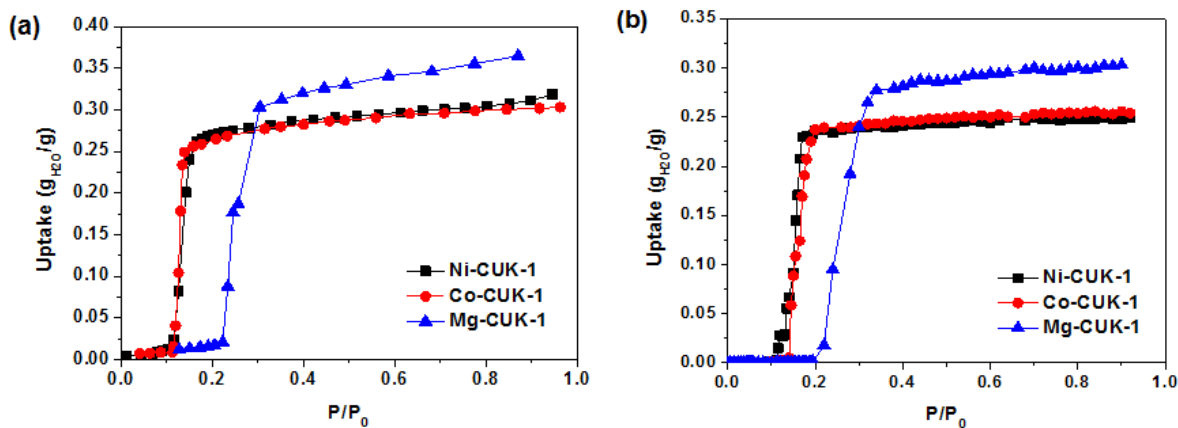


Figure 4. Comparison between (a) the experimental and (b) the GCMC simulated water adsorption isotherms at 30°C in the Co-CUK-1, Ni-CUK-1 and Mg-CUK-1.

As illustrated in **Figure 5**, there is a sharp peak in the radial distribution function (RDF) between the hydroxyl-*O* atoms and the oxygen of the water ‘*W*’, with a mean O_w - O_{OH} distance of *ca.* 2.8 Å. This distance corresponds to the formation of a relatively strong hydrogen bond between the two species. This conclusion is also supported by the analysis of the density distributions for the water molecules, calculated at low coverage, which revealed that the guest molecules are preferentially located in the vicinity of the hydroxyl groups (**Figure 5a**). Once the water molecules interact with these hydrophilic centres, they trigger the clustering of further water molecules, forming an extensive network of water until the channel is fully filled (Supplementary Figure S8).

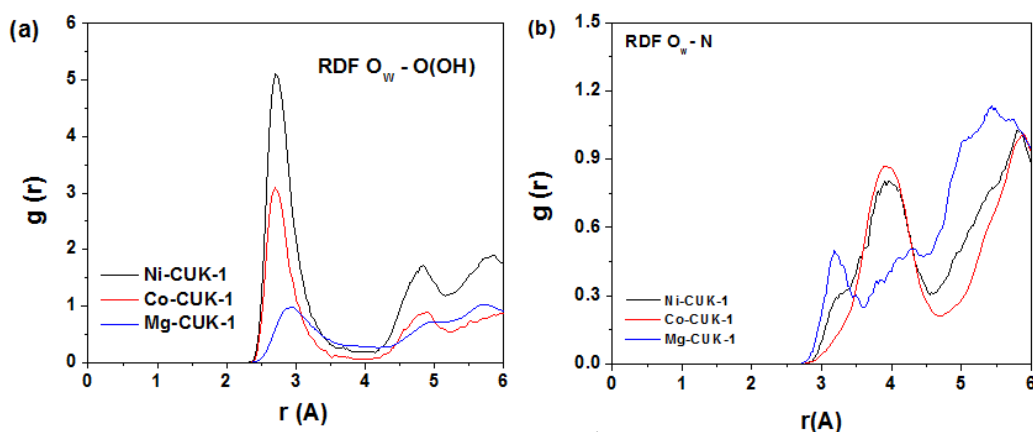


Figure 5. Radial distribution functions (RDFs) calculated at low coverage (1 water molecule per simulation box) between the oxygen of the water molecules (O_w) and (a) the oxygen of the hydroxyl groups [O(OH)] and (b) the nitrogen (N) atoms of all CUK-1. These data are averaged over the MC snapshots collected at 30°C.

The channel cross-sectional area (13.4 Å x 13.0 Å) in Co-CUK-1 is large enough to accommodate the formation of water clusters in cycles at saturation, which consist of between 4-7 molecules (see Supplementary Figure S9) that share common edges or are linked through single water molecules. Such a predicted geometry is in good agreement with the pentameric drums that were found experimentally by SCXRD previously.³³

2.4. Thermodynamic performance of Co-CUK-1/H₂O working pair

Evaluation of the achievable thermodynamic performance of adsorbent-water working pairs is crucial for the development of efficient adsorptive heat transformation systems (Figure S10). A full assessment and understanding of the ideal thermodynamic cycle between an adsorbent and water as an adsorbate is useful to choose working boundary conditions of adsorption chillers or heat pumps (Figure S11). This can be achieved experimentally through measurements of their main thermo-physical parameters, such as temperature (T), pressure (P), and water uptake (W).^[8] Figure S12 illustrates a typical adsorption-driven thermodynamic cooling cycle for Co-CUK-1 based on water adsorption isobars collected at three saturated vapour pressures, P , which correspond to specific temperatures, *i.e.*, 5 °C (0.9 kPa), 10 °C (1.2 kPa), and 30 °C (4.2 kPa), respectively. The cycle consists of four steps: two for adsorption and two for desorption, in the order, isosteric cooling (D-C), isobaric adsorption (C-A), isosteric heating (A-B) and isobaric desorption (B-D).⁸ During one such complete cycle, the adsorbed water as working fluid (W_{\max} - W_{\min}), the working capacity, has taken up energy from the environment at a low temperature in the evaporator by its evaporation (Q_{evap}), while releasing heat in the adsorber at an intermediate temperature level upon adsorption. According to the cycle in Figure S12, an effective water uptake (W_{\max} - W_{\min}) for Co-CUK-1 was found to be 0.24 g g⁻¹ (corresponding to 0.35 mL mL⁻¹) under the

boundary condition, 5 °C (T_{ev})/30 °C (T_{con})/70 °C (T_{des}). When the evaporation temperature is increased to 10 °C, the effective water uptake also increases to 0.26 g g⁻¹ (corresponding to 0.38 mL mL⁻¹).

As summarized in Table S1, the effective volumetric water uptake (0.35 mL mL⁻¹) of Co-CUK-1 at $T_{ev} = 5$ °C, $T_{con} = 30$ °C, and $T_{des} = 70$ °C is higher than that of benchmark adsorbents such as SAPO-34 (0.16 mL mL⁻¹), MIL-160 (0.12 mL mL⁻¹) and CAU-10-H (0.32 mL mL⁻¹). Clearly, Co-CUK-1 is therefore highly attractive as a water sorption medium and the discovery of these benchmark values encouraged us to further evaluate Co-CUK-1 for adsorptive chiller/heat pump applications under low driving temperatures. The choice of a driving temperature of 80 °C to regenerate the water-loaded adsorbent is directly in-line with what is required for solar cooling applications, since this level of temperature can be achieved by the use of standard flat-plate solar heat collectors.¹¹ Similarly, a slightly lower driving temperature of 70 °C enables the utilization of waste heat emitted from a co-generation plant.⁴² Kapteijn and co-workers have proposed standard conditions depending on the sorption temperature, water vapour pressure, and the evaporator and condenser temperatures in order to screen performances of water adsorbents envisaged for actual water adsorption chillers.⁸ For thermodynamic calculations of water sorption performances,⁸ we next considered two practical applications of M-CUK-1 for cooling and heat pump uses. First, it is useful to determine the thermodynamic efficiency, for which the coefficients of performance (COP_C or COP_H) for cooling or heat pump applications can be obtained, as standard indicator to make a direct comparison of performances with SAPO-34 and other MOFs (including MIL-160,⁹ CAU-10-H²⁵, and MIP-200³⁰). Two commonly-used benchmark MOFs, MIL-100(Fe) and Al fumarate each exhibit low adsorption at the evaporation temperature of 5 °C and hence their chilling performances are rather poor.⁸ At an evaporation temperature of 10 °C their performances

are improved, however they remain much lower than that observed for the CUK-1 samples. Therefore, these materials were not considered further in the COP comparisons described below.

The COP_C for cooling is defined as the useful energy output (Q_{evap}) that is withdrawn by the evaporator, divided by the energy required as an input (Q_{des}) to desorb water from the adsorbent (also known as regeneration).⁸ The alternative metric, COP_H , is applied to assess a material's performance in heat pump applications and it is defined as the summation of the useful energy output of Q_{evap} and Q_{ads} during the adsorption phase, divided by the energy input required for adsorbent regeneration (Q_{regen}).⁸ Note that by convention, the energy output is given as a negative value since energy is released from the adsorption cycle, while the energy needed to effect regeneration is a positive quantity.

The calculated COP graphs for chiller and heat pump applications depending on evaporator and condenser temperatures are given in **Figures 6 and 7**. The cooling efficiency, COP_C , of Co-CUK-1 is 0.83 at $T_{evap} = 5\text{ }^\circ\text{C}$, $T_{con} = 30\text{ }^\circ\text{C}$ and $T_{des} = 70\text{ }^\circ\text{C}$ (**Figure 6**). The efficiency is distinctively higher than that of benchmark porous solids at low driving temperatures between 70 and 100 $^\circ\text{C}$.

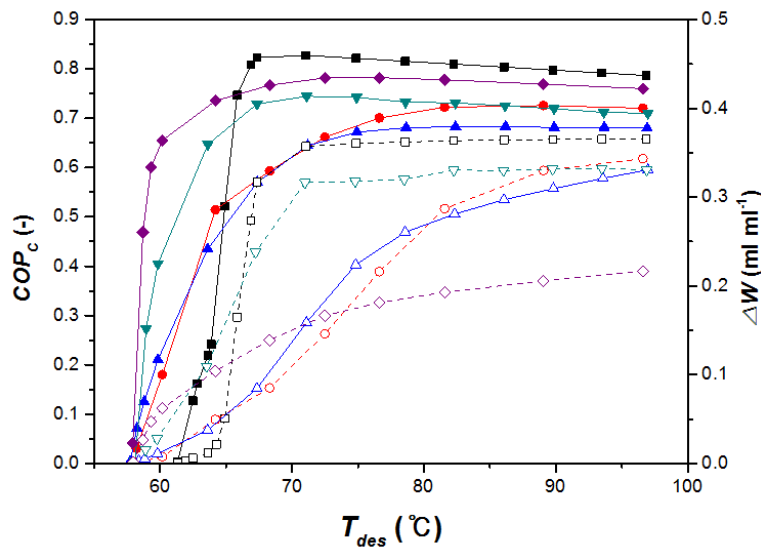


Figure 6. Coefficient of Performance (COP_C) plots for chiller conditions ($T_{ev} = 5\text{ }^\circ\text{C}$, $T_{ads} = 30\text{ }^\circ\text{C}$) as function of desorption temperature, T_{des} (closed symbols and full lines, left y-axis) and working capacity as volume of liquid water per volume of dry adsorbent, ΔW , as function of desorption temperature (open symbols, dashed lines, right y-axis) for Co-CUK-1 (■), MIL-160 (●),⁹ SAPO-34 (▲),^{8,9} CAU-10-H (▼),⁹ MIP-200 (◆).³⁰

The COP_C for Co-CUK-1 remains higher than other adsorbents even when T_{evap} is increased from $5\text{ }^\circ\text{C}$ to 10 and $15\text{ }^\circ\text{C}$ without changing T_{con} . This behaviour is in good agreement with the results of gravimetric and volumetric heat transferred from the evaporator in one cooling cycle as a function of the temperature lift at $T_{des} = 70\text{ }^\circ\text{C}$, as well as the storable energy capacity as a function of T_{des} when $T_{evap} = 10\text{ }^\circ\text{C}$ and $T_{con} = 30\text{ }^\circ\text{C}$ (Table S1).

In addition to its cooling properties, Co-CUK-1 shows a very high thermal efficiency on heating at $T_{evap} = 15\text{ }^\circ\text{C}$, $T_{con} = 45\text{ }^\circ\text{C}$, and $T_{des} = 85\text{-}100\text{ }^\circ\text{C}$ (**Figure 7**). These values confirm that Co-CUK-1 outperforms other MOFs as well as SAPO-34 for heat pump applications. As far as we are aware, Co-CUK-1 is one of the best MOFs reported so far in terms of both cooling and heating efficiencies for potential chiller and heat-pump applications. The small-pore alumino-phosphate AIPO-LTA (or AIPO-42) has been also reported to be an excellent material for water sorption-based heat allocation and storage, superior to SAPO-34.⁴³ This material was confirmed to show high COP_C values above $70\text{ }^\circ\text{C}$,³⁰ but it was not selected as a comparable adsorbent in this work.

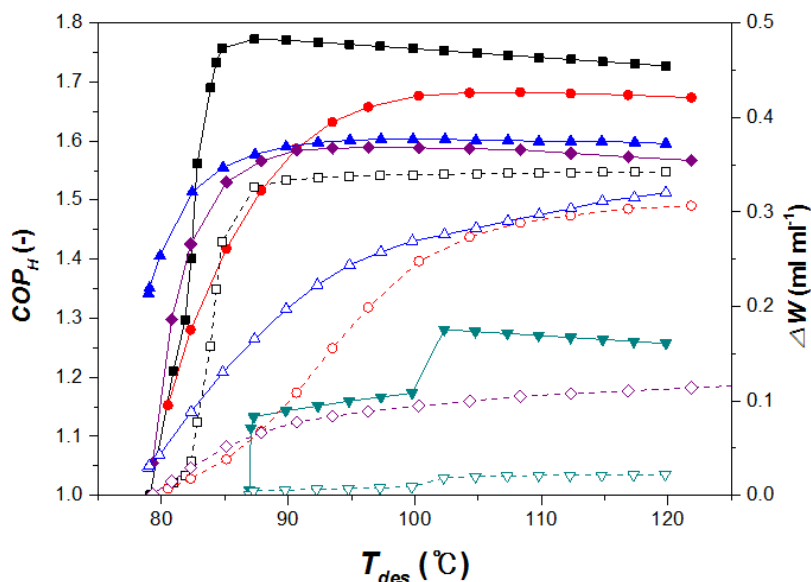


Figure 7. Coefficient of Performance (COP_H) plots for heat pump conditions ($T_{ev} = 15\text{ }^\circ\text{C}$, $T_{ads} = 45\text{ }^\circ\text{C}$) as function of desorption temperature, T_{des} (closed symbols and full lines, left y -axis) and working capacity as volume of liquid water per volume of dry adsorbent, ΔW , as function of desorption temperature (open symbols, dashed lines, right y -axis) for Co-CUK-1 (■), MIL-160 (●),⁹ SAPO-34 (▲),^{8,9} CAU-10-H (▼),⁹ MIP-200 (◆).³⁰

2.5. Effect of the nature of the framework metal ions (M^{2+}) on the water sorption properties

Changing the metal ion in CUK-1 from Co to Ni or Mg was interestingly found to impact the water adsorption properties of M-CUK-1. As shown in Figure 4a, the adsorption isotherms for Co-CUK-1 and Ni-CUK-1 are similar, exhibiting a step-like shape with a pore filling at $P/P_0 = 0.12$; this is perhaps expected since both Co(II) and Ni(II) have very similar ionic radii and electronegativity.

However, the scenario differs more significantly for the 3s-metal-containing Mg-CUK-1, which shows a step in the experimental water adsorption isotherm at higher pressure ($P/P_0 = 0.25$) and a higher gravimetric uptake, due to the lower mass of Mg compared to Co or Ni. Meanwhile,

the total number of water molecules adsorbed at saturation for all materials remains nearly the same *ca.* 30 molecules per unit cell), indicating a similar volumetric capacity, and this is to be expected since the unit cell volumes are similar in all three materials. The higher hydrophobicity of Mg-CUK-1 compared to the two other analogues, was also evidenced by GCMC calculations with the presence of the steep adsorption step at higher $P/P_0 \sim 0.2$ (**Figure 4**). One can see from **Figure 5b** that the RDF (O_w-O_{OH}) peak is of significantly lower intensity for Mg-CUK-1 compared to the two other analogues. This is in-line with a lower probability to find the water molecules interacting with the hydroxyl groups. This behaviour can be explained by the analysis of the RDF between H_2O and the N atoms of the M-CUK-1 framework present in the organic node: Figure 5b clearly emphasizes that the water molecules tend to be located in the vicinity of these N atoms in the case of Mg-CUK-1, as shown by the presence of a well-defined peak at about 3.2 Å. This behaviour is likely due to the significantly higher negative charge on the N atoms in Mg-CUK-1 *versus* those of the two 3d-metal analogues (see Table S2) which renders the organic node more attractive for the adsorbed water. This peculiarity of the Mg analogue is illustrated in **Figure 8c**, which clearly shows a significant distribution of water in the region of the organic linker. Such a dual interaction between H_2O and the Mg-CUK-1 framework leads to a decrease of the overall affinity between the Mg-CUK-1 framework and water. This is confirmed by a lower water adsorption enthalpy calculated at very low coverage for this solid as compared to the two other analogues as can be seen in Figure S7. This trend holds true over the whole range of P/P_0 . Interestingly, the water adsorption isotherm for Mg-CUK-1 at 40 °C clearly displays the two-step uptake (Figure S18), most probably assigned to the first coordination of water with the N atoms followed by a further pore filling with water.

The thermogravimetric weight-loss profiles of the three M-CUK-1 measured with a low ramping rate of heating ($2\text{ }^{\circ}\text{C min}^{-1}$) reflects their energy-efficient character for water sorption (Figure S13). The weight loss profiles exhibit a single step of water removal below $70\text{ }^{\circ}\text{C}$, particularly $60\text{ }^{\circ}\text{C}$ for Mg-CUK-1. In addition to this, water sorption cycling experiments were performed for Ni-CUK-1 and Mg-CUK-1 over 10 cycles (adsorption at $30\text{ }^{\circ}\text{C}$ and 35% RH in N_2 gas; desorption at $55\text{ }^{\circ}\text{C}$ and 10% RH in N_2 gas) (see Supplementary Figure S14 and S15). These test showed negligible difference in weight loss ($0.25 \pm 0.01\text{ g g}^{-1}$ for Ni-CUK-1 and $0.29 \pm 0.01\text{ g g}^{-1}$ for Mg-CUK-1) between cycles. It should be highlighted that these M-CUK-1 materials can be easily dehydrated at $55\text{ }^{\circ}\text{C}$.

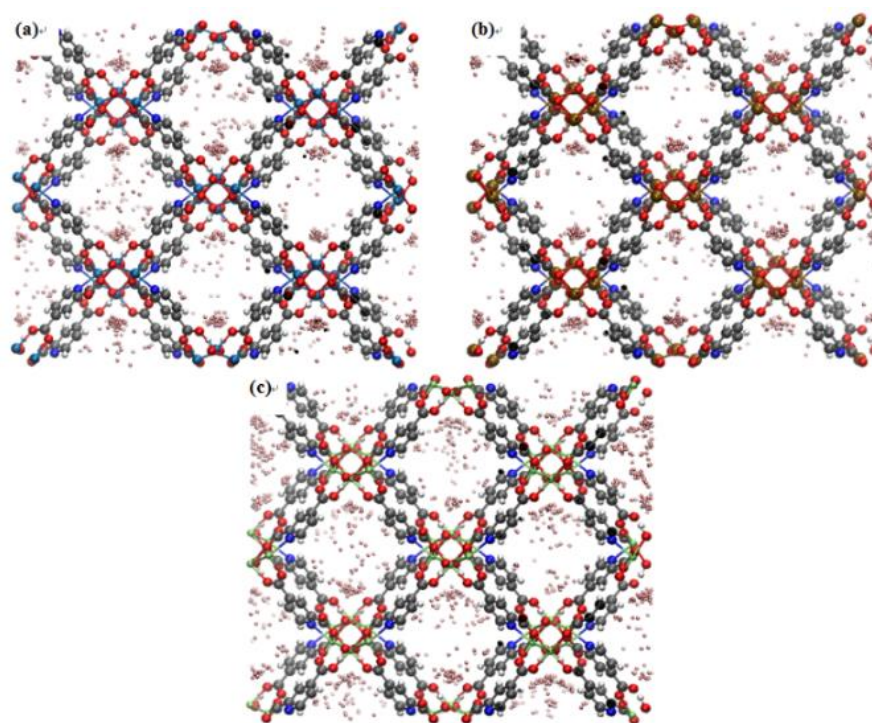


Figure 8. Center of mass distribution of water at low loading (1 water molecule per simulation box) in the Ni-CUK-1 (a), Co-CUK-1 (b) and Mg-CUK-1 (c) averaged over the MC snapshots generated at 30°C . Representation along the a -axis.

To compare the relative water adsorption rates on the three M-CUK-1 analogues with SAPO-34, we collected their weight-gain profiles at the adsorption stage (30 °C and 35% RH) on the second cycle after water adsorption at 30 °C and 35% RH, followed by a regeneration at 63 °C and 10% RH in a nitrogen flow (100 mL min⁻¹). As shown in Figure S16, the relative adsorption rates of three M-CUK-1 could be competitive with that of the commercially water adsorbent SAPO-34. However, precise kinetic analysis on water adsorption with M-CUK-1 is necessary for comparison. Table S1 compares the thermodynamic calculation results for the working capacities of water sorption, heat transferred from evaporator and energy storage capacities for the three M-CUK-1 and SAPO-34. In terms of cooling performances and energy storage capacities, all three M-CUK-1 materials clearly outperform SAPO-34. The performances for Co-CUK-1 and Ni-CUK-1 are very similar, while Mg-CUK-1 has a moderately lower working capacities compared to the two other analogues, but conversely, this material has unique water sorption properties that result in a lower regeneration temperature (55 °C) due to its more hydrophobic character.

However, this MOF requires improving its hydrothermal stability because it showed 6.3 wt% loss of the initial working capacity during 30 cycles. In terms of COP_C, and COP_H, the performances for Co-CUK-1 and Ni-CUK-1 are similar (**Figure 9 and Figure 10**). In particular, Co-CUK-1 (1.77) and Ni-CUK-1 (1.84) have the highest COP values for heating among the MOFs reported so far. For Mg-CUK-1, there is a distinct advantage of incorporating Mg(II) ions into an adsorbent used at scale, since Mg(II) is a cheaper metal source than the transition metal ions Co or Ni, and Mg is also both non-toxic and biocompatible, which is preferential for many water sorption applications.

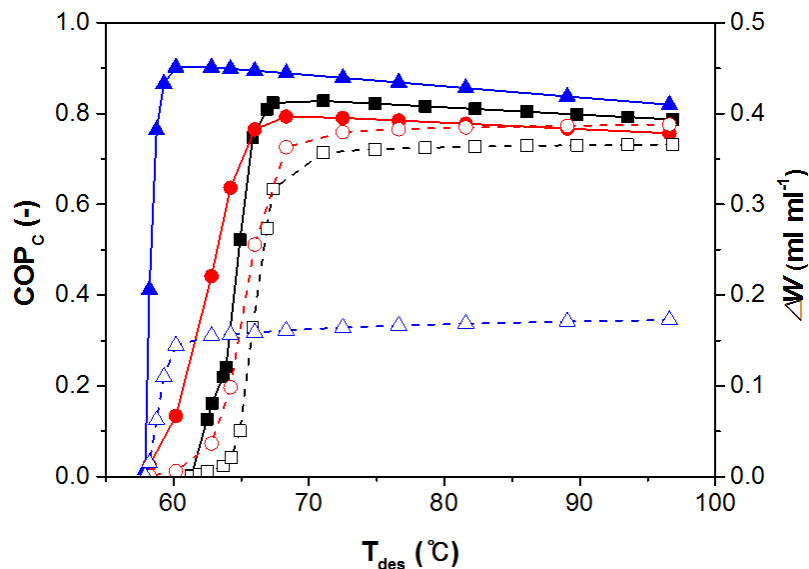


Figure 9. Coefficient of Performance (COP_c) plots for chiller conditions ($T_{ev} = 5\text{ }^\circ\text{C}$, $T_{ads} = 30\text{ }^\circ\text{C}$) as function of desorption temperature, T_{des} (closed symbols and full lines, left y-axis) and working capacity as volume of liquid water per volume of dry adsorbent, ΔW , as function of desorption temperature (open symbols, dashed lines, right y-axis) for Co-CUK-1 (■), Ni-CUK-1 (●), Mg-CUK-1 (▲).

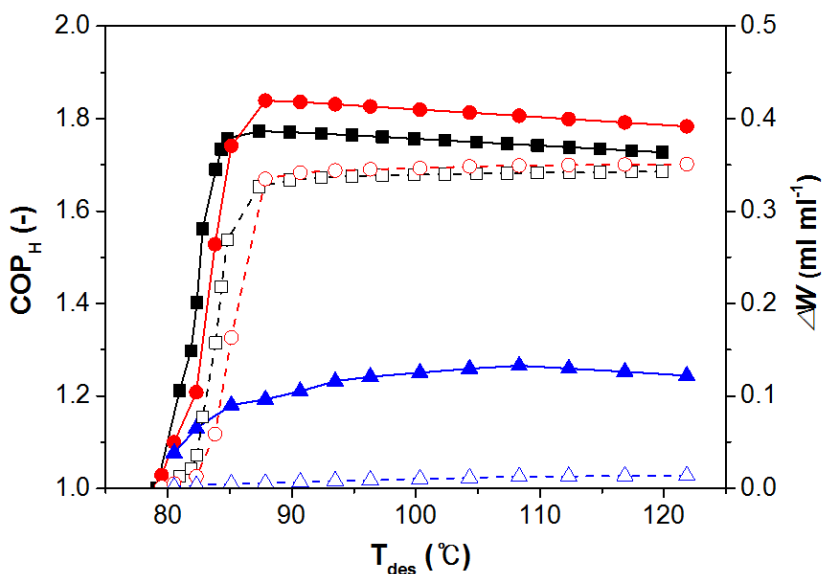


Figure 10. Coefficient of Performance (COP_H) plots for heat pump conditions ($T_{ev} = 15\text{ }^\circ\text{C}$, $T_{ads} = 45\text{ }^\circ\text{C}$) as function of desorption temperature, T_{des} (closed symbols and full lines, left y-axis) and working capacity as volume of liquid water per volume of dry adsorbent, ΔW , as function of desorption temperature (open symbols, dashed lines, right y-axis) for Co-CUK-1 (■), Ni-CUK-1 (●), Mg-CUK-1 (▲).

As shown in **Figure 11** and **Table S1**, we estimated the gravimetric and volumetric heat values for the evaporative and heat storage capacities for the M-CUK-1 materials, as well as for some benchmark adsorbents under specific working conditions. Under a single cooling cycle (where $T_{ev} = 5\text{ }^\circ\text{C}$ (or $10\text{ }^\circ\text{C}$), $T_{con} = 30\text{ }^\circ\text{C}$, and $T_{des} = 70\text{ }^\circ\text{C}$), Ni- and Co-CUK-1 showed high volumetric heat values of evaporation and higher heat storage capacities compared with that for SAPO-34 and other MOFs, although the gravimetric heat capacities were slightly lower than the value previously reported for CAU-10. Mg-CUK-1 exhibited higher volumetric heat and heat storage capacity than those for SAPO-34 at evaporator temperatures of $10\text{-}20\text{ }^\circ\text{C}$. These results indicate that Mg-CUK-1 is advantageous at higher evaporator temperatures for adsorption cooling performance while other CUK-1 materials are effective for low temperature cooling below $10\text{ }^\circ\text{C}$. In contrast, MIP-200 was reported to be effective for adsorption cooling upon low-temperature regeneration (desorption, below $65\text{ }^\circ\text{C}$),³⁰ but the performance was reduced at higher regeneration temperatures ($70\text{ }^\circ\text{C}$).

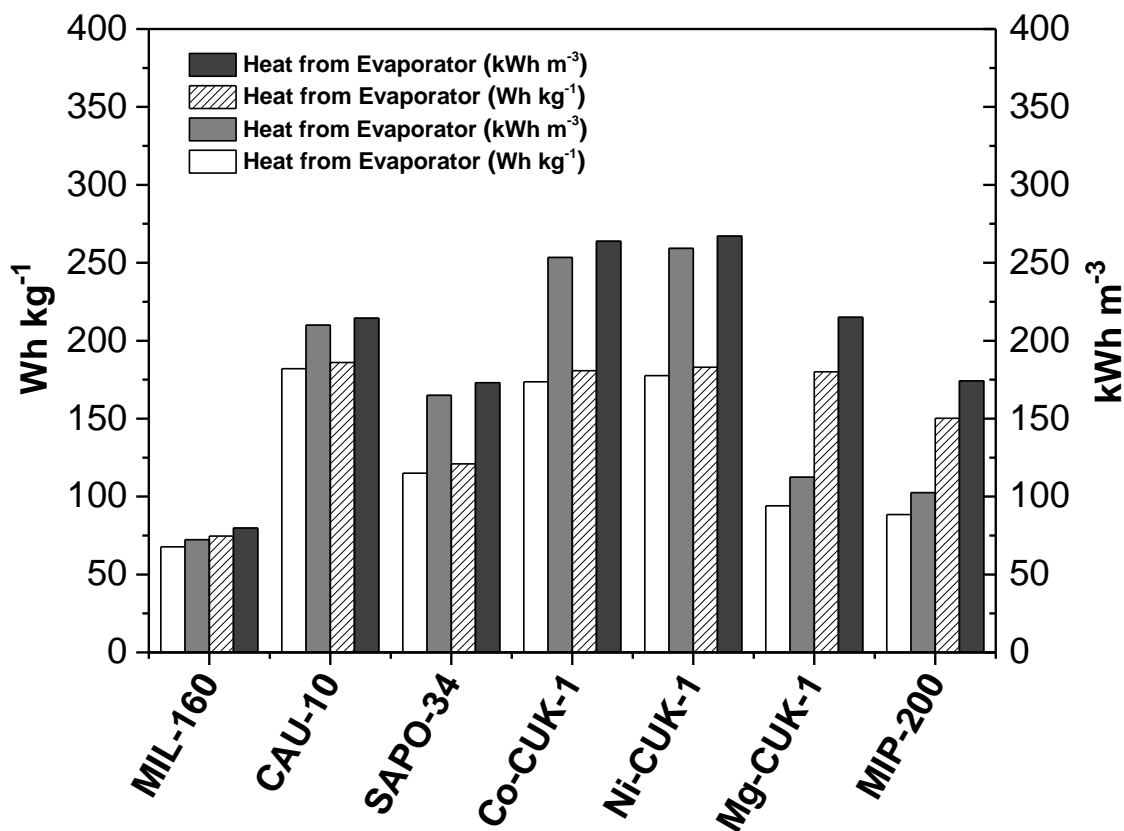


Figure 11. Gravimetric and volumetric heats from evaporator calculated for M-CUK-1 and benchmark adsorbents. Boundary conditions: heats transferred from the evaporator in one cooling cycle at $T_{ev} = 5\text{ }^{\circ}\text{C}$, $T_{con} = 30\text{ }^{\circ}\text{C}$, and $T_{des} = 70\text{ }^{\circ}\text{C}$ (white and grey bars) and $T_{ev} = 10\text{ }^{\circ}\text{C}$, $T_{con} = 30\text{ }^{\circ}\text{C}$, and $T_{des} = 70\text{ }^{\circ}\text{C}$ (shaded and dark grey bars). White and shaded bars denote the gravimetric heats (Wh kg^{-1}), while grey and dark grey bars indicate the volumetric heats (kWh m^{-3}).

Considering the five requirements stated as key qualities for MOFs to act as efficient adsorbents, all three CUK-1 materials achieve high volumetric and gravimetric water sorption capacities; they display ideal step-type water adsorption-desorption isotherms with a high volumetric uptake of water between $P/P_0 = 0.10\text{-}0.25$; they enable facile regeneration at low driving temperatures ($70\text{ }^{\circ}\text{C}$ or lower); they display high thermal energy cooling efficiencies (for Ni- and Co-CUK-1) and heating (for Mg-CUK-1) and, they were shown to be highly cyclable due

to suitable levels of chemical and mechanical robustness. Therefore, it is evident that the water sorption properties of the CUK-1 materials outperform commercial water adsorbents including silica gel and SAPO-34, as well as several benchmark MOF adsorbents. While MOFs can achieve unparalleled levels of water sorption performance their synthesis costs and scalability in comparison to naturally-occurring zeolitic sorbents continue to be a limiting step towards their implementation in large-scale platforms. Arguably, the CUK-1 materials lead the field in this regard because they are synthesized using simple reagents and water as the only solvent, and they can be prepared at scale using continuous microwave-assisted heating.

3. CONCLUSIONS

In comparison with other commercial benchmarks and existing MOFs that have been proposed for the chiller and/or heat pump applications, the three M-CUK-1 analogues described in this work displayed remarkable water sorption properties in terms of the five criteria required for advanced water adsorbents. In this study, thermodynamic calculations revealed that Co-CUK-1 and Ni-CUK-1 exhibit high efficiency for both chiller and heat pump applications considering low driving temperatures. In particular, Co-CUK-1 and Ni-CUK-1 had an excellent COP_H . Although Mg-CUK-1 presented a lower cooling performance compared to the two other analogues, this material displays excellent water sorption properties that permit easy regeneration at low temperature (55 °C), together with the use of environmentally-benign, cheaper and lighter Mg(II) ions in the framework. Mg-CUK-1 shows the best COP_C and a low desorption temperature although its working capacity is half that of the other CUK-1 materials. This work demonstrated that a joint experimental-computational approach combined with thermodynamic calculations is a powerful

means to investigate the most important features of promising water adsorbents such as the M-CUK-1 materials. In particular, molecular simulations confirmed that this Mg-version showed a more pronounced hydrophobic character that makes this series of M-CUK-1 materials tunable depending on the targeted applications and working conditions required.

4. EXPERIMENTAL SECTION

4.1. Typical synthesis of CUK-1. *Synthesis of Co-CUK-1.* The hydrothermal synthesis of Co-CUK-1 from the reaction of the dianion of 2,4-pdcH₂ with hydrated CoCl₂ in basic aqueous solution was performed at 200 °C for 15 h using a recipe already reported elsewhere.³¹ After cooling, the crystalline solid was purified by brief (3 x 20 s) cycles of sonication in fresh H₂O (100 mL), followed by decanting of the cloudy supernatant. The solid was further treated with DMF or ethanol under stirring at 70 °C for 5 h. Then, large pink prismatic crystals were isolated (product yield: 67%).

Synthesis of Ni-CUK-1. A solution of pyridine-2,4-dicarboxylic acid (185 mg, 1.0 mmol) and KOH (1.0 M, 4.5 mL) was added to a stirred aqueous solution (3 mL) of nickel(II) chloride hexahydrate (357 mg, 1.5 mmol) to give a 3:2:9 ratio of Ni:L:OH.³² The resulting solution was loaded in a 100 mL Teflon autoclave, which was heated to 200 °C for 15 h, and then cooled to room temperature. The bright green crystalline solid was purified by short cycles (3 x 60 s) of ultrasonic treatment in H₂O, and decanting off the cloudy supernatant. The solid was finally dried overnight at 100 °C (product yield: 65%).

Synthesis of Mg-CUK-1. 2,4-pdcH₂ (170 mg, 1.0 mmol) and KOH (2.0 M, 2.0 mL) in H₂O (2.0 cm³) were added to a stirred solution of Mg(NO₃)₂-hydrate (380 mg, 1.5 mmol) in H₂O (3.0 mL) to give a viscous, opaque slurry, which was then transferred to a 100 mL Teflon-lined autoclave, heated at 210 °C for 15 h and cooled for 6 h.³³ After cooling, the crystalline solid was purified by brief cycles of sonication in fresh H₂O (20 mL), followed by decantation of the cloudy supernatant to yield large, colourless prismatic crystals (product yield: 70%).

4.2. Characterization of CUK-1. Powder X-ray diffraction patterns of CUK-1 were obtained using a Rigaku D/MAX IIIB diffractometer (operating at 2kW) using Ni-filtered CuK_α-radiation (40 kV, 30 mA, λ=1.5406 Å) and a graphite crystal monochromator. The particle morphology and crystal size were analyzed by scanning electron microscopy (SEM, Pilips, XL30S FEG). BET surface area measurements were performed using CO₂ adsorption-desorption isotherms at dry ice temperature (-78.5 °C) after dehydration under vacuum at 300 °C for 12 h using a Micromeritics Tristar 3020. Surface areas were evaluated using the Brunauer-Emmett-Teller (BET) method, and pore volume was taken by a single point method at $P/P_0 = 0.99$. Thermogravimetric analysis (TGA) was carried out in a thermogravimetric analyzer (DT Q600, TA Instruments, Universal V4.5A). Analysis was performed in a dry air flow of 100 mL min⁻¹. The temperature was increased from 25 to 700 °C with a heating rate of 2 °C min⁻¹ or 5 °C min⁻¹. Before each TGA measurement, samples were hydrated in a chamber with 70% relative humidity at 30 °C for 2 days.

4.3. Water sorption measurements. Water sorption isotherms and test for adsorptive chiller have been measured by an intelligent gravimetric analyzer (IGA, Hiden Analytical Ltd.). The IGA was automatically operated to precisely control the water vapor pressure (1-95% RH) and temperature (20-100 °C). Prior to adsorption experiments, samples were dehydrated at 100 °C for 1 h under high vacuum (<10⁻⁶ Torr). Multiple cycles of water adsorption-desorption were

performed using a thermogravimetric analyzer (TGA, DT Q600, TA Instruments, Universal V4.5A) connected with a humidity generator. The humidity was controlled by using two mass flow controllers and a humidified nitrogen gas flow was passed through a thermogravimetric balance. The adsorption profiles were measured at 30 °C in humid nitrogen with RH = 35%, while desorption data were collected between 55-70 °C in dry nitrogen (6-10% RH) with a cycle time of 3 h.

4.4. Molecular simulations. GCMC simulations were carried out at 30 °C to predict the adsorption behaviour of water in the different M-CUK-1 analogues using the Complex Adsorption and Diffusion Simulation Suite (CADSS) code. The simulation box was made of 12 conventional unit cells (3×2×2) maintaining the atoms fixed in their initial positions. A mixed set of universal force field (UFF)⁴⁴ and DREIDING⁴⁵ force field parameters were adopted to describe the Lennard-Jones (LJ) parameters for the atoms in the inorganic and organic part of the MOF framework while the partial charges carried by these atoms were derived at the Density Functional Theory level (see Supporting Information). Water molecules were described by the TIP4P/2005 potential model.³⁶ The LJ contributions from the H-atoms of hydroxyl groups in the inorganic nodes were ignored in accordance with the strategy we validated in a previous study.⁹ Further description of the derivation of the atomic partial charges and LJ parameters are given in the ESI. The water/M-CUK-1 interactions considered the sum a coulombic term and a van der Waals contribution with the use of 12-6 LJ expression with parameters calculated using the Lorentz Berthelot equation. While the long-range electrostatic interactions were handled using the Ewald summation technique, the van der Waals term was calculated using a cut-off distance of 12 Å. For each point in the adsorption isotherm, 2×10⁸ Monte Carlo steps were used for both equilibration and production runs. The adsorption enthalpy at low coverage (Δh) was calculated through

configurational-bias Monte Carlo simulations performed in the NVT ensemble using the revised Widom's test particle insertion method. In order to gain insight into the configurational distributions of the adsorbed species in the different CUK-1, additional data were calculated at different fixed pressures (fixed number of water molecules) including the hydrogen bond networks and the radial distribution functions (RDF) of intermolecular atom-pairs.

4.5. Thermodynamic calculations. The thermodynamic calculations of adsorption chiller and heat pump cycles are performed by an express method based on the methodology reported by De Lange *et al.*⁸ The coefficient of performance (COP) is adopted to illustrate the energy efficiency of heat pump cycle from a thermodynamic perspective. The energy analysis allows the determination of the COP, which is a ratio of useful heating or cooling energy output provided to work required. To be able to assess the COP of a working pair, knowledge of the enthalpy of adsorption is of prime importance.⁸ As described in more detail in [8], isosteric heats of adsorption were estimated by the Clausius-Clapeyron equation and compensated by the virial equation.⁴⁶ The isosteric enthalpy of adsorption is calculated from isotherms at multiple temperatures by Eq. (1):

$$\Delta_{ads}H_W = R \left(\frac{\partial \ln p}{\partial \left(\frac{1}{T}\right)} \right)_W \quad (1)$$

where $\Delta_{ads}H_W$ is the isosteric enthalpy of adsorption, R is the universal gas constant, p and T represent temperature and pressure respectively and W is the volume of water (liquid) adsorbed per volume of adsorbent (crystalline densities are used for the conversion).⁸

Furthermore, the virial equation was also used to calculate the steric heat of adsorption (Q_{st}) from isotherms measured at different temperatures.⁴⁶

$$\ln p = \ln v + \left(\frac{1}{T}\right) \sum_{i=1}^m a_i v^{i-1} + \sum_{i=1}^n b_i v^{i-1} \quad (2)$$

where v is amount adsorbed and a_i and b_i are empirical parameters.

The virial-type equation was applied comparing with Clausius-Clapeyron equation as shown in Figure S21-S27. A set of temperature independent parameters a_i which lead to direct evaluation of Q_{st} can be derived by fitting equation (2) continuously using adsorption isotherms obtained at different temperatures.

$$Q_{st} = -R \left(\frac{\partial \ln p}{\partial \left(\frac{1}{T}\right)} \right)_v = -R \sum_{i=1}^m a_i v^{i-1} \quad (3)$$

Using the two equations, it was confirmed that the isosteric enthalpies of adsorption for CUK-1 show overall a similar shape.

For calculation procedures, a characteristic curve needs to be constructed to transfer the loading from two dependent variables (p , T) to one, the adsorption potential, A , which is the molar Gibbs free energy of adsorption with opposite sign, defined as:

$$A = RT \ln \left(\frac{p_o(T)}{p} \right) \quad (4)$$

where p_o is the temperature-dependent vapor pressure of the adsorbate of choice. The amount adsorbed should be expressed as volume occupied by the adsorbed phase. As the density of the adsorbed phase is often not known, the liquid phase density is used as approximation:

$$W = \frac{q(p, T)}{\rho_{liq}^{wf}(T)} \quad (5)$$

where q is the mass adsorbed, W is the volume liquid adsorbed and $\rho_{\text{liq}}^{\text{wf}}$ is the liquid density of the same adsorbate. If temperature invariance of W is assumed, all measured adsorption data should collapse onto one single “characteristic curve”. An adsorption driven heat pump cycle can be used for either heating or cooling. As the working pair (sorbent-sorbate) is known, only four distinct temperature levels need be defined to be able to determine the Coefficient of Performance for either application.⁸ Note that the desorption temperature is allowed to vary to investigate the required desorption temperature. The COP is defined as the useful energy output divided by the energy required as input. For heating, this becomes:

$$\text{COP}_{\text{H}} = \frac{-(Q_{\text{con}} + Q_{\text{ads}})}{Q_{\text{regen}}} \quad (6)$$

where Q_{con} is the energy released during condensation, and Q_{ads} is the energy released during adsorption. Both have a negative value as energy is withdrawn from the adsorption cycle. Q_{regen} is the energy required for regeneration of adsorbent. In this case, a positive quantity as energy is added to the system. For cooling, the coefficient of performance COP_{C} becomes:

$$\text{COP}_{\text{C}} = \frac{Q_{\text{ev}}}{Q_{\text{regen}}} \quad (7)$$

where Q_{ev} is the energy withdrawn by the evaporator. Note that the COP_{H} should have a value between 1 and 2 and the COP_{C} is per definition not larger than unity. The specifics on how to exactly calculate these energetic contributions are explained in detail in [8]. Please note, lastly, that the specific heat capacity is assumed to be $1 \text{ J g}^{-1} \text{ K}^{-1}$, which is an average value for a variety of MOF materials. In fact, the actual value of this quantity has a negligible effect on calculated COPs.

Supporting Information ((delete if not applicable))

Supporting Information is available from the Wiley Online Library or from the author.

ACKNOWLEDGMENTS

J. S. Lee, J. W. Yoon and P. G. M. Mileo contributed equally to this work. The Korean authors are grateful to the Global Frontier Center for Hybrid Interface Materials (GFHIM, Grant No. NRF-2013M3A6B1078879) and the Center for Convergent Chemical Process (CCP, Grant No. SKC1810-4) for financial support. Y. K. Hwang and U.-H. Lee (KRICT) are also acknowledged for their helpful discussions of the water sorption experiments. P.G.M. thanks the National Counsel of Technological and Scientific Development CNPQ for the scholarship; G.M. the Institut Universitaire de France for its support; S.M.H. acknowledges the Welch Foundation (F-1738) for financial support.

CONFLICTS OF INTEREST

The authors declare no conflict of interest.

Received: ((will be filled in by the editorial staff))
Revised: ((will be filled in by the editorial staff))
Published online: ((will be filled in by the editorial staff))

REFERENCES

- (1) Anastas, P. T.; Kirchoff, M. M. Origins, Current Status, and Future Challenges of Green Chemistry. *Acc. Chem. Res.* **2002**, *35*, 686-694.
- (2) Sheldon, R. A. Green Solvents for Sustainable Organic Synthesis: State of the Art. *Green Chem.* **2005**, *7*, 267-278.
- (3) Li, Q.; Piechna, J.; Mueller, N. Design of a Novel Axial Impeller as a Part of Counter-rotating axial compressor to compress water vapor as refrigerant. *Appl. Energy* **2011**, *88*, 3156-3168.

- (4) Kilicarslan, A.; Mueller, N. A Comparative Study of Water as a Refrigerant with Some Current Refrigerants. *Int. J. Energy Res.* **2005**, 29, 947-959.
- (5) Isaac, M.; van Vuuren, D. P. Modeling Global Residential Sector Energy Demand for Heating and Air Conditioning in the context of Climate Change. *Energy Policy* **2009**, 37, 507-521.
- (6) Rogelj, J.; den Elzen, M.; Höhne, N.; Fransen, T.; Fekete, H.; Winkler, H.; Schaeffer, R.; Sha, F.; Riahi, K.; Meinshausen, M. Paris Agreement Climate Proposals Need a Boost to Keep Warming Well Below 2°C *Nature* **2016**, 534, 631-639.
- (7) Ghafoor, A.; Munir, A. Worldwide Overview of Solar Thermal Cooling Technologies. *Renew. Sust. Energ. Rev.* **2015**, 43, 763-774.
- (8) De Lange, M. F.; Verouden, K. J.; Vlugt, T. J.; Gascon, J.; Kapteijn, F. Adsorption-Driven Heat Pumps: The Potential of Metal-Organic Frameworks. *Chem. Rev.* **2015**, 115, 12205-12250.
- (9) Cadiau, A.; Lee, J. S.; Borges, D. D.; Fabry, P.; Devic, T.; Wharmby, M. T.; Matrineau, C.; Foucher, D.; Taulelle, F.; Jun, C. -H.; Hwang, Y. K.; Stock, N.; De Lange, M. F.; Kapteijn, F.; Gascon, J.; Maurin, G.; Chang, J. -S.; Serre, C. Design of Hydrophilic Metal Organic Framework Water Adsorbents for Heat Reallocation. *Adv. Mater.* **2015**, 27, 4775-4780.
- (10) Wu, W.; Zhang, X. L.; Li, X. T.; Shi, W. X.; Wang, B. L. Comparisons of Different Working Pairs and Cycles on the Performance of Absorption Heat Pump for Heating and Domestic Hot Water in Cold Regions. *Appl. Therm. Eng.* **2012**, 48, 349-358.
- (11) Henninger, S. K.; Jeremias, F.; Kummer, H.; Schossig, P.; Henning, H. -M. Novel Sorption Materials for Solar Heating and Cooling. *Energy Proc.* **2012**, 30, 279-288.
- (12) Krajnc, A.; Varlec, J.; Mazaj, M.; Ristic, A.; Logar, N. Z.; Mali, G. Superior Performance of Microporous Alumino-phosphate with LTA Topology in Solar-Energy Storage and Heat Reallocation. *Adv. Energy Mater.* **2017**, 7, 1601815.
- (13) Freni, A.; Bonaccorsi, L.; Calabrese, L.; Capri, A.; Frazzica, A.; Sapienza, A. SAPO-34 Coated Adsorbent Heat Exchanger for Adsorption Chillers. *Appl. Therm. Eng.* **2015**, 82, 1-7.
- (14) Burtch, N. C.; Jasuja, H.; Walton, K. S. Water Stability and Adsorption in Metal-Organic Frameworks. *Chem. Rev.* **2014**, 114, 10575-10612.
- (15) Küsgens, P.; Rose, M.; Senkovska, I.; Fröde, H.; Henschel, A.; Siegle, S.; Kaskel, S. Characterization of Metal-Organic Frameworks by Water Adsorption. *Micropor. Mesopor. Mater.* **2009**, 120, 325-330.

- (16) Demir, H.; Mobedi, M.; Ulku, S. A Review on Adsorption Heat Pump : Problems and Solutions. *Renew. Sustain. Energy Rev.*, **2008**, 12, 2381-2403.
- (17) Kakiuchi, H.; Shimooka, S.; Iwade, M.; Oshima, K.; Yamazaki, M.; Terada, S.; Watanabe, H.; Hidaka, H.; Takewaki, T. Novel Water Vapor Adsorbent FAM-ZO1 and Its Applicability to and adsorption Heat Pump. *J. Chem. Eng. Jpn.* **2005**, 31, 361-364.
- (18) Sapienza, A.; Santamaria, S.; Frazzica, A.; Freni, A. Influence of The Management Strategy and Operating Conditions on the Performance of and Adsorption Chiller. *Energy* **2011**, 36, 5532-5538.
- (19) Zhou, H. C.; Long, J. R.; Yaghi, O. M. Introduction to Metal-Organic Frameworks. *Chem. Rev.* **2012**, 112, 673-674.
- (20) Furukawa, S.; Reboul, J.; Diring, S.; Sumida, K.; Kitagawa, S. Structuring of Metal-Organic Frameworks at the Mesoscopic/Microscopic Scale. *Chem. Soc. Rev.* **2014**, 43, 5700-5734.
- (21) Maurin, G.; Serre, C.; Cooper, A.; Férey, G. The New Age of MOFs and of Their Porous-Related Solids. *Chem. Soc. Rev.* **2017**, 46, 3104-3107.
- (22) Chang, J. -S.; Hwang, Y. K.; Jung, S. H.; Hong, D. -Y.; Seo, Y. -K. (KRICT), *US Patent 8168813*, **2012**; *Korea Patent 10-0803964*, **2008**.
- (23) Seo, Y. -K.; Yoon, J. Y.; Lee, J. S.; Hwang, Y. K.; Jun, C. -H.; Chang, J. -S.; Wuttke, S.; Bazin, P.; Vimont, A.; Daturi, M.; Bourrelly, S.; Llewellyn, P. L.; Horcajada, P.; Serre, C.; Férey, G. Energy-Efficient Dehumidification Over Hierachically Porous Metal-Organic Frameworks as Advanced Water Adsorbents. *Adv. Mater.* **2012**, 24, 806-810.
- (24) Henninger, S. K.; Habib, H. A.; Janiak, C. MOFs as Adsorbents for Low Temperature Heating and Cooling Applications. *J. Am. Chem. Soc.* **2009**, 131, 2776-2777.
- (25) Lenzen, D.; Bendix, P.; Reinsch, H.; Fröhlich, D.; Kummer, H.; Möllers, M.; Hügenell, P. P. C.; Gläser, R.; Henninger, S.; Stock, N. Scalable Green Synthesis and Full-Scale Test of the Metal-Organic Framework CAU-10-H for Use in Adsorption-Driven Chillers. *Adv. Mater.* **2018**, 30, 1705869.
- (26) Kim, H.; Yang, S.; Rao, S. R.; Narayanan, S.; Kapustin, E. A.; Furukawa, H.; Umans, A. S.; Yaghi, O. M.; Wang, E. N. Water Harvesting form Air with Metal-Organic Frameworks Powered by Natural Sunlight. *Science* **2017**, 356, 430-434.
- (27) Abtab, S. M. T.; Alezi, D.; Bhatt, P. M.; Shkurenko, A.; Belmabkhout, Y.; Aggarwal, H.; Weselinski, L. J.; Alsadun, N.; Samin, U.; Hedhili, M. N.; Eddaoudi, M. Reticular Chemistry in

Action: A Hydrolytically Stable MOF Capturing Twice Its Weight in Adsorbed Water. *Chem* **2018**, 4, 94.

(28) Rieth, A. J.; Yang, S.; Wang, E. N.; Dinca, M. Record Atmospheric Fresh Water Capture and Heat Transfer with a Material Operating at the Water Uptake Reversibility Limit. *ACS Cent. Sci.* **2017**, 3, 668-672.

(29) Kummer, H.; Jeremias, F.; Warlo, A.; Fueledner, G.; Froehlich, D.; Janiak, C.; Glaeser, R.; Henninger, S. K. A Functional Full-Scale Heat Exchanger Coated with Aluminum Fumarate Metal-Organic Framework for Adsorption Heat Transformation. *Ind. Eng. Chem. Res.* **2017**, 56, 8393-8398.

(30) Wang, S.; Lee, J. S.; Wahiduzzaman, M.; Park, J.; Muschi, M.; Martineau-Corcus, C.; Tissot, A.; Cho, K. H.; Marrot, J.; Shepard, W.; Maurin, G.; Chang, J. -S.; Serre, C. A Robust Large-Pore Zirconium Carboxylate Metal-Organic Framework for Energy-Efficient Water-Sorption-Driven Refrigeration. *Nat. Energy* **2018**, 3, 985-993.

(31) Humphrey, S. M.; Chang, J. -S.; Jhung, S. H.; Yoon, J. W.; Wood, P. T. Porous Cobalt(II)-Organic Frameworks with Corrugated Walls: Structurally Robust Gas-Sorption Materials. *Angew. Chem. Int. Ed.* **2007**, 46, 272-275.

(32) Humphrey, S. M.; Weldon, G. F.; Wood, P. T. Pyridine-2,4-Dicarboxylate: A Versatile Building Block for the Preparation of Functional Coordination Polymers. *J. Nanosci. Nanotechnol.* **2010**, 10, 34-48.

(33) Saccoccia, B.; Bohnsack, A. M.; Waggoner, N. W.; Cho, K. H.; Lee, J. S.; Hong, D. Y.; Lynch, V. M.; Chang, J. -S.; Humphrey, S. M. Separation of p-Divinyl benzene by Selective Room-Temperature Adsorption Inside Mg-CUK-1 Prepared by Aqueous Microwave Synthesis. *Angew. Chem. Int. Ed.* **2015**, 54, 5394-5398.

(34) Humphrey, S. M.; Mole, R. A.; McPartlin, M.; McInnes, E. J. L.; Wood, P. T. Isolated Magnetic Clusters of Co(II) and Ni(II) within 3-Dimensional organic Frameworks of 6-Mercaptonicotinic Acid: Unique Structural Topologies Based on Selectivity for Hard and Soft Coordination. *Inorg. Chem.* **2005**, 44, 5981-5983.

(35) Lin, R.-B; Li, L.; Zhou, H.-L.; Wu, H.; He, C.; Li, S.; Krishna, R.; Li, J.; Zhou, W.; Chen, B. Molecular sieving of ethylene from ethane using a rigid metal-organic framework. *Nat. Mater.* **2018**, 17, 1128-1133.

- (36) Yoon, J. W.; Jung, S. H.; Hwang, Y. K.; Humphrey, S. M.; Wood, P. T.; Chang, J. –S. Gas-Sorption Selectivity of CUK-1: A Porous Coordination Solid Made of Cobalt(II) and Pyridine-2,4-Dicarboxylic Acid. *Adv. Mater.* **2007**, 19, 1830-1834.
- (37) Yoon, J. W.; Lee, J. S.; Piburn, G. W.; Cho, K. H.; Jeon, J.; Lim, H. –K.; Kim, H.; Jun, C. –H.; Humphrey, S. M.; Krishna, R.; Chang, J. –S. Highly Selective Adsorption of p-Xylene over other C8 Aromatic Hydrocarbons by Co-CUK-1: A Combined Experimental and Theoretical Assessment. *Dalton Trans.* **2017**, 46, 16096-16101.
- (38) Fletcher, A. J.; Cussen, E. J.; Bradshaw, D.; Rosseinsky, M. J.; Thomas, K. M. Adsorption of Gases and Vapors on Nanoporous Ni₂(4,4'-Bipyridine)₃(NO₃)₄ Metal-Organic Framework Materials Templated with Methanol and Ethanol: Structural Effects in Adsorption Kinetics. *J. Am. Chem. Soc.* **2004**, 126, 9750-9759.
- (39) Kalmutzki, J. J.; Diercks, C. S.; Yaghi, O. M. Metal-Organic Frameworks for Water Harvesting from Air. *Adv. Mater.* **2018**, 30, 1704304.
- (40) Freni, A.; Maggio, G.; Sapienza, A.; Frazzica, A.; Restuccia, G.; Vasta, S. Comparative Analysis of Promising Adsorbent/Adsorbate Pairs for Adsorptive Heat Pumping, Air Conditioning and Refrigeration. *Appl. Therm. Eng.* **2016**, 104, 85-95.
- (41) Czepirski, L.; Jagiello, J. Virial-Type Thermal Equation of Gas-Solid Adsorption. *J. Chem. Eng. Sci.* **1989**, 44, 797-801.
- (42) Enteria, N.; Yoshino, H.; Mochida, A. Review of the Advances in Open-Cycle Adsorption Air-conditioning Systems. *Renew Sust Energ Rev.* **2013**, 28, 265-289.
- (43) Krajnc, A.; Varlec, J.; Mazaj, M.; Ristic, A.; Logar, N. Z.; Mali, G. Superior Performance of Microporous Aluminophosphate with LTA Topology in Solar-Energy Storage and Heat Reallocation. *Adv. Energy Mater.* **2017**, 7, 1601815.
- (44) Rappé, A. K. K.; Casewit, C. J. J.; Colwell, K. S. S.; Goddard, I.; Skiff, W. M. U. UFF. A Full Periodic Table Force Field for Molecular Mechanics and Molecular Dynamics Simulations. *J. Am. Chem. Soc.* **1992**, 114, 10024-10035.
- (45) Mayo, S. L.; Olafson, B. D.; Williams, A.; Goddard, I. DREIDING: A Generic Force Field for Molecular Simulations. *J. Phys. Chem.* **1990**, 101, 8897-8909.
- (46) Bandosz, T. J.; Jagiełło, J.; Schwarz, J. A. Adsorption of Sulfur Hexafluoride and Propane at Temperatures near Ambient on Pillared Clays. *J. Chem. Eng. Data.* **1996**, 41, 880-884.