

Roadmap on metamaterial theory, modelling and design

Davies, Bryn; Szyniszewski, Stefan; Dias, Marcelo A.; Kisil, Anastasia; Cooper, Shane; Touboul, Marie; Horsley, Simon A.R.; Conduit, Gareth J.; Duncan, Oliver; Kaczmarczyk, Łukasz

DOI

[10.1088/1361-6463/adc271](https://doi.org/10.1088/1361-6463/adc271)

Publication date

2025

Document Version

Final published version

Published in

Journal of Physics D: Applied Physics

Citation (APA)

Davies, B., Szyniszewski, S., Dias, M. A., Kisil, A., Cooper, S., Touboul, M., Horsley, S. A. R., Conduit, G. J., Duncan, O., Kaczmarczyk, Ł., Scarpa, F., Torrent, D., Cherkaev, E., Wellander, N., Alù, A., Madine, K. H., Sheng, P., Bennetts, L. G., Krushynska, A. O., ... More Authors (2025). Roadmap on metamaterial theory, modelling and design. *Journal of Physics D: Applied Physics*, 58(20), Article 203002. <https://doi.org/10.1088/1361-6463/adc271>

Important note

To cite this publication, please use the final published version (if applicable). Please check the document version above.

Copyright

Other than for strictly personal use, it is not permitted to download, forward or distribute the text or part of it, without the consent of the author(s) and/or copyright holder(s), unless the work is under an open content license such as Creative Commons.

Takedown policy

Please contact us and provide details if you believe this document breaches copyrights. We will remove access to the work immediately and investigate your claim.

ROADMAP • OPEN ACCESS

Roadmap on metamaterial theory, modelling and design

To cite this article: Bryn Davies *et al* 2025 *J. Phys. D: Appl. Phys.* **58** 203002

View the [article online](#) for updates and enhancements.

You may also like

- [PFAS degradation using a hyperbolic vortex plasma reactor](#)
Roman Klymenko, Manuel Disch, Elmar C Fuchs *et al.*
- [Influence of plasma activated water on the growth and vitality of radish \(*Raphanus sativus* L.\)](#)
Tomáš Vozár, Kristína Trebulová, Zdenka Kozáková *et al.*
- [Boron and phosphorus doped diamond: change in the electronic structure post exposure to low pressure deuterium plasma and its effect on the production of negative ions](#)
Ryan Magee, Marie-Amandine Pinault-Thaury, Jocelyn Achard *et al.*



The Electrochemical Society
Advancing solid state & electrochemical science & technology

ECS UNITED

247th ECS Meeting
Montréal, Canada
May 18-22, 2025
Palais des Congrès de Montréal

Register to save \$\$ before May 17

Unite with the ECS Community

Roadmap

Roadmap on metamaterial theory, modelling and design

Bryn Davies^{1,2,29,*} , **Stefan Szyniszewski**^{3,29} , **Marcelo A Dias**⁴ , **Leo de Waal**⁴ , **Anastasia Kisil**⁵ , **Valery P Smyshlyaev**⁶ , **Shane Cooper**⁶ , **Iliia V Kamotski**⁶ , **Marie Touboul**^{2,7,8} , **Richard V Craster**^{2,7,9} , **James R Capers**^{10,12} , **Simon A R Horsley**¹⁰ , **Robert W Hewson**¹¹ , **Matthew Santer**¹¹ , **Ryan Murphy**¹¹ , **Dilaksan Thillaithevan**¹¹ , **Simon J Berry**¹² , **Gareth J Conduit**^{13,14} , **Jacob Earnshaw**³ , **Nicholas Syrotiuk**³ , **Oliver Duncan**¹⁵ , **Łukasz Kaczmarczyk**¹⁶ , **Fabrizio Scarpa**¹⁷ , **John B Pendry**¹⁸ , **Marc Martí-Sabaté**² , **Sébastien Guenneau**^{7,18} , **Daniel Torrent**¹⁹ , **Elena Cherkaev**²⁰ , **Niklas Wellander**²¹ , **Andrea Alù**^{22,23} , **Katie H Madine**²⁴ , **Daniel J Colquitt**²⁴ , **Ping Sheng**²⁵ , **Luke G Bennetts**²⁶ , **Anastasiia O Krushynska**²⁷ , **Zhaohang Zhang**²⁷ , **Mohammad J Mirzaali**²⁸  and **Amir Zadpoor**²⁸ 

¹ Mathematics Institute, University of Warwick, Coventry CV4 7AL, United Kingdom

² Department of Mathematics, Imperial College London, London SW7 2AZ, United Kingdom

³ Department of Engineering, University of Durham, Durham, United Kingdom

⁴ Institute for Infrastructure and Environment, School of Engineering, The University of Edinburgh, Edinburgh EH9 3FG, United Kingdom

⁵ Department of Mathematics, The University of Manchester, Manchester M13 9PL, United Kingdom

⁶ Department of Mathematics, University College London, Gower Street, London WC1E 6BT, United Kingdom

⁷ UMI 2004 Abraham de Moivre-CNRS, Imperial College London, London SW7 2AZ, United Kingdom

⁸ POEMS, CNRS, ENSTA, Inria, Institut Polytechnique de Paris, Palaiseau, France

⁹ Department of Mechanical Engineering, Imperial College London, London SW7 2AZ, United Kingdom

¹⁰ Centre for Metamaterial Research and Innovation, University of Exeter, Exeter EX4 4QL, United Kingdom

¹¹ Department of Aeronautics, Imperial College London, London SW7 2AZ, United Kingdom

¹² QinetiQ Ltd, Cody Technology Park, Farnborough GU14 0LX, United Kingdom

¹³ Theory of Condensed Matter, Cavendish Laboratory, Cambridge CB3 0HE, United Kingdom

¹⁴ Intellegens Ltd, The Studio, Chesterton Mill, Cambridge CB4 3NP, United Kingdom

¹⁵ Department of Manchester Metropolitan University, Manchester M15 6BH, United Kingdom

¹⁶ Glasgow Computational Engineering Centre, James Watt School of Engineering, University of Glasgow, Glasgow G12 8QQ, United Kingdom

¹⁷ Aerospace Engineering, Bristol Composites Institute, School of Civil, Aerospace and Mechanical Engineering, University of Bristol, Bristol, United Kingdom

¹⁸ The Blackett Laboratory, Department of Physics, Imperial College London, London SW7 2AZ, United Kingdom

¹⁹ Institut de Noves Tecnologies de la Imatge (INIT), Universitat Jaume I, 12071, Castelló de la Plana, Spain

²⁰ Department of Mathematics, University of Utah, 155 South 1400 East, JWB 233 Salt-Lake City, United States of America

²⁹ Guest editors of the Roadmap.

* Author to whom any correspondence should be addressed.



²¹ Department of Engineering Sciences and Mathematics, Luleå University of Technology, SE-97 187 Luleå, Sweden

²² Photonics Initiative, Advanced Science Research Center, City University of New York, New York, NY 10031, United States of America

²³ Physics Department, CUNY Graduate Center, City University of New York, New York, NY 10016, United States of America

²⁴ Department of Applied Mathematics, University of Liverpool, Liverpool, Merseyside L69 7ZL, United Kingdom

²⁵ Institute for Advanced Study, Hong Kong University of Science and Technology, Clear Water Bay, Kowloon, Hong Kong Special Administrative Region of China, People's Republic of China

²⁶ School of Mathematics and Statistics, University of Melbourne, Parkville VIC 3010, Australia

²⁷ Engineering and Technology Institute Groningen (ENTEG), Faculty of Science and Engineering, University of Groningen, 9747 AG Groningen, The Netherlands

²⁸ Department of Biomechanical Engineering, Faculty of Mechanical Engineering, Delft University of Technology (TU Delft), Mekelweg 2, 2628 CD Delft, The Netherlands

E-mail: bryn.davies@warwick.ac.uk

Received 15 May 2024, revised 24 February 2025

Accepted for publication 19 March 2025

Published 25 April 2025



Abstract

This Roadmap surveys the diversity of different approaches for characterising, modelling and designing metamaterials. It contains articles covering the wide range of physical settings in which metamaterials have been realised, from acoustics and electromagnetics to water waves and mechanical systems. In doing so, we highlight synergies between the many different physical domains and identify commonality between the main challenges. The articles also survey a variety of different strategies and philosophies, from analytic methods such as classical homogenisation to numerical optimisation and data-driven approaches. We highlight how the challenging and many-degree-of-freedom nature of metamaterial design problems call for techniques to be used in partnership, such that physical modelling and intuition can be combined with the computational might of modern optimisation and machine learning to facilitate future breakthroughs in the field.

Keywords: mechanical, electromagnetic, modelling, artificial intelligence, homogenisation, optimisation, acoustic

Contents

Introduction	4
1. Modelling in mechanical metamaterials	5
2. Analytical methods in metamaterial design	7
3. Two-scale homogenisation of high-contrast subwavelength resonances	9
4. High-frequency homogenization for periodic media	11
5. Adjoint based methods for the design of large-scale non-periodic electromagnetic materials	13
6. Design optimisation of hierarchical structural metamaterials	15
7. Artificial intelligence for electromagnetic metamaterial design	17
8. Strategies to overcome difficult data	19
9. Metamaterials genome: towards synergy between mathematical modelling and AI analysis	21
10. Electromagnetics of time-modulated metamaterials	23
11. Irrational metamaterials and their development	25
12. Polaritonics and metamaterials	28
13. Active chirality in mechanical metamaterials using gyroscopes	30
14. The challenges of underwater acoustics	32
15. Metamaterials for ocean wave control, manipulation and harvesting	34
16. Designing mechanical metamaterials for biomedical engineering and (soft) robotics	36
Data availability statement	40
References	40

Introduction

Bryn Davies¹ and Stefan Szyniszewski²

¹ Mathematics Institute, University of Warwick, Coventry CV4 7AL, United Kingdom

² Department of Engineering, University of Durham, Durham, United Kingdom

The growth of metamaterial science has brought to the fore the power of micro-structuring materials to achieve previously unattainable properties. Metamaterial-based breakthroughs have had wide-ranging technological implications, including realising materials with effectively negative material parameters [1, 2], allowing for design freedoms such as the ability to finely tune highly anisotropic properties [3] or practical considerations such as being able to greatly reduce mass. However, the often complex and many-degree-of-freedom nature of the small-scale geometries that have facilitated these breakthroughs come with associated challenges. Traditional direct numerical simulations can incur significant computational costs (due to the need to use very fine meshes). This, combined with the high-dimensional associated parameter spaces, can render design problems computationally intractable. As a result, researchers have developed a variety of strategies to characterise metamaterials' properties, seeking approaches that greatly simplify problems while still capturing the material's key features.

The pre-eminent approach to succinctly characterising metamaterials is to use asymptotic homogenisation to capture their 'effective' properties. These techniques have a long history in mathematics [4, 5] and are based on the principle that very small-scale periodic structures (which are, for example, at least an order of magnitude smaller than the operating wavelength) can be averaged out. As a result, it is possible to derive a homogeneous material (possibly with some strongly anisotropic or dispersive properties) that displays the same properties as the metamaterial in question (up to some quantifiable errors). It was within this framework that the possibility to create materials with effectively negative permeability and permittivity were created, paving the way for negative refraction [6].

Homogenisation is still at the heart of many of the most important breakthroughs in metamaterial science. In this Roadmap, we will explore how homogenisation strategies have been developed to meet the various needs of the broad and scientifically diverse field of metamaterials. This has included materials with local resonances and strong local dispersion as well as strategies for describing effective properties at non-zero frequencies. Similarly, the contributors will highlight some of the remaining challenges in this domain.

Given the many degrees of freedom available when designing a metamaterial, such design problems are ideal candidates for treatment through numerical optimisation. This Roadmap will explore strategies for topology optimisation as well as recent applications of artificial intelligence (AI). Consistent with the rapid growth in the usability and accessibility of machine learning for problems across the physical sciences, the use of data-driven approaches for designing metamaterials has grown rapidly in recent years. This Roadmap will cover

some of the highlights of these breakthroughs and focus on some of the key challenges, particularly related to assembling the quality and quantity of data needed to facilitate data-driven design.

Several of the main challenges and opportunities in the field of metamaterial modelling and design are related to resolving the differences in scientific approach and philosophy between physics-based modelling and data-driven methods. These two schools of thought can occasionally seem to be at odds with one another, but they have the potential to unlock and accelerate breakthroughs when combined effectively. For example, physics-based models (based on techniques such as homogenisation) have an important role to play in offering concise frameworks for numerical optimisation and machine learning. Conversely, the complexity and high dimensionality of metamaterial design problems mean they stand to benefit significantly from the unparalleled insight possible through modern computation and machine learning. Combining these two sometimes disconnected communities is a major opportunity for the field. The applied metamaterials and engineering communities are ideally placed to manage the synergy between generative AI and rigorous, physics-based techniques, offering intuition and efficiency while also ensuring adherence to the laws and safety regulations. In this way, the development of AI techniques is envisioned to support and augment human creativity, where AI-generated ideas can be fine-tuned, experimentally validated and assessed considering complex regulatory and ethical frameworks.

This Roadmap contains contributions from leading experts in the field which outline the cutting edge and highlight some possible avenues to overcoming the most important challenges. The 16 sections cover a diversity of physical regimes, including electromagnetism, acoustics, mechanical metamaterials and water waves. The contributions are grouped into four main sections. First, analytic approaches (such as homogenisation and other analytic methods) are covered, reflective of the field's roots in asymptotic homogenisation. Following this, numerical methods are considered, ranging from numerical topology optimisation strategies to data-driven machine learning approaches. In the third part, the contributors will cover some of the most exciting frontiers in metamaterials science and explore the new modelling and design challenges that have arisen as a result. This will include time-modulated metamaterials, quasicrystalline metamaterials, polaritonic metamaterials and active metamaterials. Finally, the Roadmap will end with two contributions exploring the theoretical challenges posed by designing metamaterials for industrial applications, such as for biomedical engineering, soft robotics and ocean wave energy harvesting.

The broad and multi-disciplinary nature of metamaterial science means that its grand challenges require breakthroughs in many different areas of science. In this article, we have focused on theoretical, modelling and design challenges. Other notable challenges are, for example, the need to develop scalable manufacturing techniques and to develop metamaterials for use in extreme environments (such as the extreme temperatures experienced in space).

1. Modelling in mechanical metamaterials

Marcelo A Dias and Leo de Waal

Institute for Infrastructure and Environment, School of Engineering, The University of Edinburgh, EH9 3FG Edinburgh, United Kingdom

Status

Progress in mechanical metamaterials research has attracted significant attention in the past decade, resulting in a plethora of designs with distinct complex geometries and mechanical characteristics [7]. Exploration into multifunctional metamaterials is also growing, with a focus on seamlessly integrating constitutive properties with additional functionalities such as thermal conductivity, acoustic insulation, and electromagnetic (EM) response. This has also led to an increasing shift towards nonlinear and tuneable metamaterials [8], emphasising the quest for dynamic control and adaptability in response to varying conditions. The interplay between the structural components of metamaterials and their responses to stimuli is evolving into a focal point of study, drawing inspiration from other complex systems such as active matter that exhibit emergent behaviours and dynamic transformations [9].

These increasing complexities and multiphysics requirements demand the development of sophisticated mathematical and computational tools to allow the accurate representation and analysis of these systems. Of these, Finite Element Analysis and Topology Optimisation are central, allowing precise customisation of mechanical properties by strategically distributing matter within structures. Principle to these modelling approaches is the underlying structural system of smaller constituents, the meta-atom (figure 1), from which large-scale properties emerge. However, often the microscopic representation of these structures is not efficient when applying these modelling tools due to the large number of degrees of freedom that need to be resolved, resulting in a computationally expensive design process. Modelling methods that reduce the computational cost, whilst capturing the relevant phenomenology, are therefore in high demand. Developing these tools will enable the efficient characterisation of highly complex metamaterials with multiphysics interactions, enabling the realisation of their purported industry application potential from within the research community.

Current and future challenges and opportunities

Homogenisation techniques, where at the long wavelength limit the micro-structured material behaves like a homogeneous material [14], remain indispensable for predicting macroscopic properties. Recent advancements have highlighted their computational efficiency, particularly when dealing with the complexities of large-scale metamaterial systems [15]. Key to the successful application of these methods is correctly capturing the quasi-static phenomenology of meta-atoms—even though generalisations to a dynamic scenario are also relevant [9, 10].

To characterise the phenomenology of meta-atoms, there exist useful mathematical tools in the following fields: rigidity theory; topological mechanics; nonlinear mechanics and stability theory. These tools can capture the emergent behaviour from meta-atoms and are applied to design metamaterials. For instance, rigidity theory allows for the design of Origami inspired metamaterials, where the crease pattern of these structures prescribe their kinematics and can be designed so that the underpinning mechanism has a single degree of freedom, i.e. the Miura-ori crease pattern (figure 1(a)). Moreover, rigidity theory is applied to determine the behaviour that dominates the bulk properties: e.g. nodal connectivity of the octet truss (figure 1(b)) results in stretching dominated behaviour. Alternative meta-atoms may be dominated by bending or membrane forces (e.g. beams, plate or minimal surface-based topologies [7]), enabling the effective design of structures with a diverse set of properties.

In parallel, within topological mechanics, there is a pronounced focus on manipulating robust properties, such as soft edge modes, offering an additional layer of tuneability. This can be leveraged to control failure modes, such as the buckling location of a polarised kagome lattice [12] (figure 1(c)).

Additionally, non-linear mechanics stands out for its potential in deliberately engineering instabilities as a means of functionalization, thus enabling controlled responses like energy absorption or precisely orchestrated deformation under specified conditions [8]. Meta-atoms that exhibit snap-through instability are one such example (figure 1(d)).

While traditional homogenisation techniques are commonly applied to attempt to model these phenomena, such theories are often limiting us to systems that assume infinite repetition of meta-atoms and typically they do not manage to capture large deformations, complex loading paths, and evolving microstructures. These challenges manifest as the microstructural length scale approaches the size of the macrocomponent or the length scale associated with macroscopic spatial variability [16]. In such instances, the introduction of higher-order gradients or non-local continua becomes necessary to capture size effects and derive a higher-order constitutive response without requiring assumptions at the macroscopic level.

Advances in methods and techniques to meet challenges

Currently, one way in which these challenges are navigated is through a computational homogenisation approach, involving the utilisation of two interrelated boundary value problems for both macroscopic and microscopic evolving geometries [15, 17]. However, placing more emphasis on an analytical understanding of higher-order homogenisation techniques could be immensely beneficial in providing fundamental insights into challenging questions. These include forward homogenisation, focused on extracting effective material properties from a known microstructural architecture, and inverse homogenisation, which seeks to identify microstructures that exhibit a specified combination of target properties. Furthermore, an

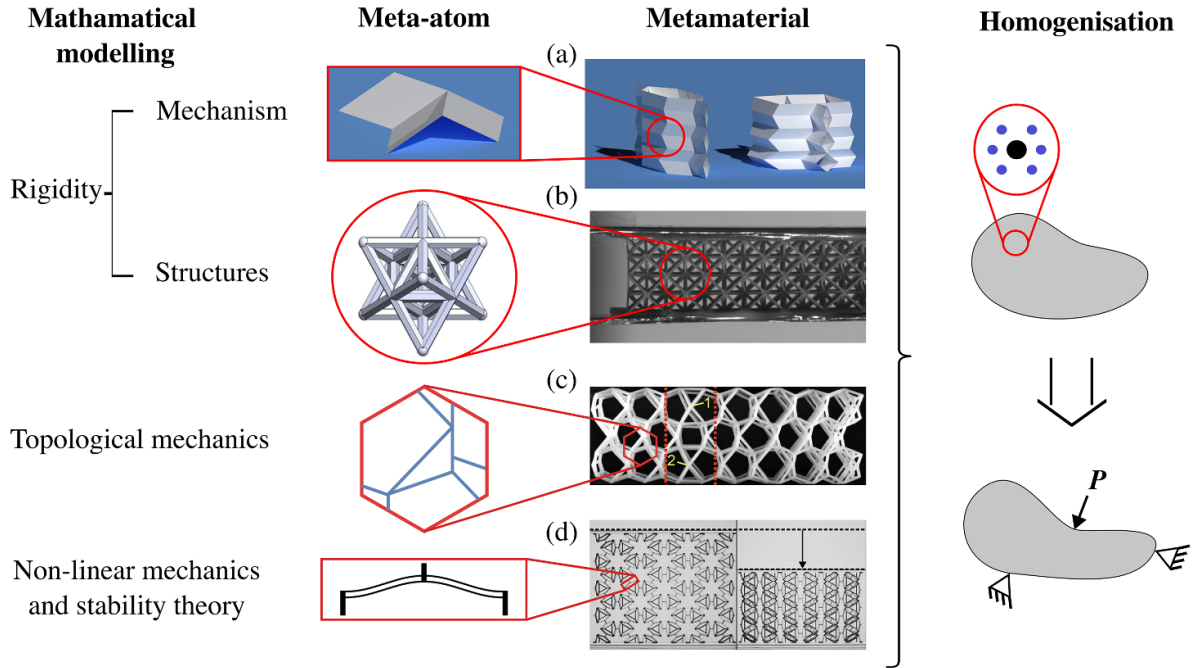


Figure 1. (a) Miura-ori pattern. Reprinted from [10], Copyright (2021), with permission from Elsevier. (b) Octet truss. Reproduced from [11]. CC BY 4.0. (c) Topological metamaterial. Reproduced with permission from [12]. (d) Phase transforming cellular material. Reproduced from [13]. CC BY 4.0.

analytical focus would yield additional advantages, such as eliminating the need for constitutive assumptions regarding overall material behaviour, accommodating large deformations and rotations at both scales, and being applicable to arbitrary material behaviours, including nonlinearities and time-dependency.

Yet, another challenge lies in current trends in nonlinear and tuneable metamaterials [8]. Homogenisation techniques that can capture nonlinear behaviour in metamaterials present a significant mathematical challenge, as bifurcations occurring at the meta-atom scale are closely linked to the loss of rank-one convexity observed at the macroscopic scale [18, 19]. Such energy functionals may, for instance, explain global properties driven by instabilities, phase transformation such as the formation of shear bands, and softening behaviour.

The predominant focus in the modelling of mechanical metamaterials has centred on the constitutive behaviour of meta-atoms. However, the multidisciplinary nature and broad applications of these structures necessitate a more comprehensive understanding of meta-atoms' interaction with other multiphysics phenomena such as thermal conductivity, acoustic damping and electromagnetism. The coupling and resolution of the multiphysics inherently increases the complexity of the models and requires theories that are thermodynamically consistent at the scale of the meta-atom. Addressing this need introduces a set of challenges in the homogenisation modelling of mechanical metamaterials. Firstly, achieving a seamless integration of physical phenomena into a unified model poses a significant hurdle. This requires accounting for couplings of these multiphysics interactions. Secondly, the variability in material properties at smaller scales, alongside the nonlinear behaviours exhibited by mechanical metamaterials,

complicates the modelling process. Thirdly, the scale discrepancy across multiple length scales demands computationally intensive multiscale modelling techniques.

Concluding remarks

A mechanical metamaterial, a complex system of smaller constituent materials or meta-atoms, showcases transformative potential where collective characteristics surpass those of individual components. By leveraging this potential, many innovative metamaterials are being developed to improve the performance of structures in our built environment. These structures often have complex geometries and increasingly require the coupling of their mechanical properties with other multiphysics properties, resulting in significant computational cost when attempting to characterise their behaviour. Homogenisation methods show great potential in addressing this issue, by reducing the complexity and therefore computational cost. However, significant steps are needed to augment these methods to capture large deformations, complex loading paths, evolving microstructures and coupling with other multiphysics phenomena accurately.

Providing an accurate homogenised description of metamaterial simplifies their design process, opening up new possibilities for the creation of metamaterials that not only passively respond to external factors but actively adapt their mechanical properties, presenting a paradigm shift towards materials that can autonomously navigate and adjust in a dynamic and unpredictable environment. Discovering more advanced modelling techniques and principles will signal a new era in metamaterials, crafted not only for strength, but also for dynamic, responsive, and adaptive functionalities.

2. Analytical methods in metamaterial design

Anastasia Kisil

University of Manchester

Status

In 1967 Victor Veselago proved that negative-index materials and superlenses are possible by employing analytical methods. Thirty-three years later, when these material were obtained experimentally, this opened up a new subdiscipline of physics and engineering: metamaterials [20]. Likewise, many analytical methods which are now used to study and design metamaterials pre-date the field of metamaterials, for example, methods to analyse periodic materials. Metamaterials possess unusual properties due to the internal structuring of the material. In particular, if the parameters of the internal structure change, then the properties change. This means that in order to design metamaterials we should be able to tailor the parameters to achieve desired effects. The advantage of using analytical methods is that in an ideal situation the material properties are expressed in terms of the parameters. This offers a huge advantage over methods that simply provided properties for given parameters and then require numerous trial and error in order to find the right parameter sets.

In most realistic situations it is currently not possible to obtain desired properties of a material expressed in terms of the structural parameters. Nevertheless, analytical methods are useful in designing metamaterials when used in conjunction with other methods

1. Employing partially analytical methods can dramatically speed up computation. Some hybrid methods are frequency independent or allow to reuse part of the computed solution for large parameters spaces [21].
2. Analytical methods can help increase accuracy especially since many interesting behaviours can occur at ‘singularity’ or resonances [22].

In this section we will concentrate on analytical methods other than homogenisation, which has been covered in other sections.

Current and future challenges and opportunities

There is a huge variety of different metamaterial, in this section we will concentrate on phononics/photonic crystals which have been extensively studied using analytical methods [23]. In the simplest setting they are 2D and doubly periodic materials with a repeated unit cell. When the unit cell is simple there are exact analytical solutions. The challenge is to be able to extend these analytical results to more realistic settings by:

1. Changing the unit cell from the simplest point scatterer to consider much more complicated unit cells [23];

2. Extending to 3D were some of the analytical methods need significant modifications;
3. To allow for edges and corners in the periodic material [24];
4. To model variation in parameters from cell to cell (which can be a change in size or spacing), they are referred as graded metamaterial or rainbow metamaterials;
5. To consider some local/non-local perturbations to the periodic structure which can lead to interesting effects such as localisation [25].

When addressing the challenges outlined above it might be possible to design hybrid analytical/ numerical methods that allow to capture the key behaviour analytically and use this within a numerical scheme to make it versatile and easy to use.

Advances in methods and techniques to meet challenges

A good example of the advantage of understanding the nature of the phenomena comes from the study of black-hole waves [22]. By studying the associated eigenvalue problem, it is shown that the local behaviour at the corner is analogous to the behaviour at infinity. This allows to pick the correct mesh at the corner for the finite element computation to capture the black-hole waves well. In fact, it is shown that there is a transformation which maps the corner behaviour to a region at infinity. The idea of picking a correct transformation is key in other areas of metamaterial design, for example cloaking [26]. Other applications which have been extensively studied mathematically are filtering and polarisation [23] as well as localisation [25].

One interesting feature of periodic structures is the possibility of resonance effects [23]. In the context of array scattering, it is frequently referred to as Wood’s anomaly. Typically, around the resonant state, interesting phenomena can be observed such as, for example, abnormal transmission or reflection [27]. Also, some frequently used models for example Foldy’s approximation can give non-unique solution at these frequencies [24]. This is different to the existence of Rayleigh–Bloch waves (modes that propagate along the grating and decay exponentially in orthogonal directions) which can also lead to non-uniqueness in certain circumstances [28].

The key in obtaining correct solution fast is to capture the correct behaviour. Matched asymptotic expansion is a popular analytical method which allows to capture the key singular behaviour in different regions and then match the solution together [29]. Also, there are a number of methods that allow to pose an ansatz made up of functions capturing the singular behaviour and then use numerical methods to find the coefficients of the ansatz numerically [21]. Sometimes the singular behaviour can be eliminated by looking at the integral in the complex plane and deforming the contour, this is for example used in the Wiener–Hopf technique or Cauchy’s theorem to deal with removable singularity [24].

Concluding remarks

Modelling wave propagation through metamaterials frequently results in difficult to solve integral equations. Analytical methods played a central role in solving them prior to computers making numerical methods readily available. Now analytical methods are a valuable tool in designing

hybrid numerical schemes which can offer the advantage of accuracy and speed over conventional numerical methods. Further developments are required to make the hybrid methods more flexible, versatile and user-friendly to increase their use in designing metamaterials. In the meantime, the analytical understanding of metastructures might be used to perform computations and solve equations instead of a computer [20].

3. Two-scale homogenisation of high-contrast subwavelength resonances

Valery P Smyshlyaev, Shane Cooper and Ilia V Kamotski
Department of Mathematics, University College London,
Gower Street, London WC1E 6BT, United Kingdom

Status

For a periodic array of high-contrast ‘soft’ inclusions within a ‘stiff’ matrix of comparable density (figure 2), waves of the same frequencies produce much shorter wavelengths in the inclusion material compared to the matrix. If the inclusion’s wavelength is comparable with their size, the frequencies are comparable with the inclusions’ natural frequencies while we are in a long wavelength regime relative to the matrix. This is reflected in a two-scale asymptotics of Bloch waves, which displays a frequency bandgap opening near the subwavelength inclusion resonances. This was probably first formally observed in [30] and then made mathematically rigorous in [31, 32]. Auriault and Bonnet [30] also provided interpretations in terms of frequency-dependent as well as sign-changing effective density and related time-nonlocality. In the context of electromagnetism, similar effects were rigorously interpreted in [33] in terms of artificial magnetism. Analogous effects are observed for highly anisotropic periodic fibres, see [34] where for a scalar static model the macroscopic equations are shown to be spatially non-local. This was advanced in [35], where more general ‘inter-connected’ partially degenerating elastic inclusions serve as generalised micro-resonances. Resulting two-scale formal asymptotics suggests behaviours with a Willis-type coupling in the macroscopic constitutive relations and related coupled directional and frequency gaps. Two-scale homogenisation and spectral convergence for another model with a partial degeneracy is studied in [36], for stiff in compression but soft in shear elastic inclusions. A general convergence theory for two-scale homogenization of partially degenerating systems with periodic coefficients was developed in [37]. The emergence of localised modes due to defects was established for high-contrast periodic media (accompanied by error bounds) in [38], and recently for some high-contrast stochastic media in [39]. In [40], bandgap opening in high-contrast periodic elastic beam lattices was shown. An exciting recent development is on constructing two-scale type operator approximations with error bounds, see [41] and numerous references therein. Such approximations were first constructed in [42] for a basic scalar high-contrast model, and then developed further in e.g. [43] which has also uncovered certain macroscopic dispersive properties at high contrasts. In [41], a general approach was developed constructing such approximations for a broad class of multi-scale problems in terms of associated two-scale limit problems and a ‘connecting operator’ J_ϵ . The latter provides a key link between the original oscillatory and the two-scale limit problems, and appears to be a composition of certain ‘translation’ operators and a ‘two-scale interpolation operator’ I_ϵ (as well their more abstract analogues). Operator

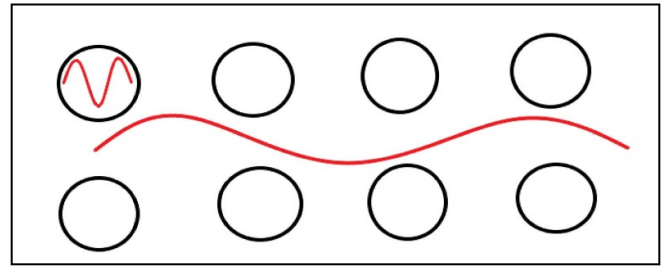


Figure 2. A basic configuration: inclusions of ‘soft’ material periodically distributed within a matrix occupied by a ‘stiff’ material. As a result, the wavelength in the inclusion material is much shorter than in the matrix material (both wavelengths are visualised in red). If the former is comparable to the inclusion size, one is in a micro-resonant regime. With the macroscale comparable with the matrix wavelength, the inclusions serve as subwavelength resonators.

I_ϵ was introduced, in an equivalent form, in [44] under the name of ‘periodic two-scale transform’, and appears to be a two-scale version of a classical Whittaker–Shannon interpolation from signal processing.

Current and future challenges and opportunities

The field of high-contrast homogenization, developed over the last 40+ years, is receiving a renewed interest from the point of view of metamaterial modelling thanks to the importance of locally resonant materials for realising metamaterials [3, 45–47]. Indeed, for the underlying mathematical models with a strong interaction between micro and macro-scales, related two-scale type approximations are often capable of displaying certain non-standard and unusual effects in an asymptotically explicit way. This often clarifies the nature and the microscopic mechanism of the observable macroscopic effects (such as the role of the micro-resonances in bandgap opening, frequency and directional dispersion and localisation, etc). A key general challenge here is to construct tractable but accurate approximations of two-scale type, with controllably small error. The mathematical approach is often capable of achieving this in a systematic and rigorous way, leading to tractable approximate models with tight error bounds. Works like [41] provide certain new mathematical tools for achieving this, both in part of constructing improved approximations and controlling the errors, for a broad class of multiscale scenarios. This is so far restricted however to although broad but still quite specific class of models, which generalises those infinitely periodic and obeying certain ‘spectral gap’ condition (the latter rules out, for example, models with highly anisotropic fibres and their further extensions like in [34, 35] with associated additional interesting effects). A challenge is therefore to tackle such models, as well as physically more realistic problems in bounded domains, higher-order, time-dependent, and non-periodic problems. The latter may range from locally-periodic models to fully random ones. Indeed, if one allows for certain randomness of the micro-resonances, the inclusions’ eigenvalues vary and each inclusion tends to capture

the energy at frequencies close to its natural frequencies. As a wide range of such eigenfrequencies is represented, the inclusions may collectively try to prevent the wave from propagation. This may lead to some interesting phenomena like localisation due to the collective effect of random micro-resonances. A very challenging open problem is to analyse this rigorously, i.e. to control the macroscopic effect of all the interactions of the high-contrast micro-resonances with the macroscopic field and each other.

Advances in methods and techniques to meet challenges

To address the above as well as various other challenges, one may need to advance some recently developed methods in new and exciting ways. The approach developed in [41] is based on very few basic principles and looks promising for its further advance in diverse directions. Indeed, it allows to identify very few generic features of multiscale problems for which two-scale type approximations with error estimates can be constructed. In particular it allows to naturally arrive at such versatile tools as the above mentioned two-scale connecting operators, which bear all the desirable properties and can in principle be used on their own, i.e. even when the Floquet–Bloch transform (from which it was derived in the first place) may be not anymore directly applicable. This opens-up avenues for the approach’s potential applicability to locally periodic problems, problems with boundaries, etc. For tackling the problems with locally periodic (two-scale) coefficients, an emerging exciting prospect is to develop a natural two-scale analogue of semiclassical pseudodifferential calculus. Moreover, the approach of [41] is based on analysis of a general family of asymptotically degenerating variational problems, i.e. not necessarily coming from the Floquet–Bloch transform, with one example of such other families—for ‘concentrated perturbations’—already treated in [41]. This also makes the underlying ideas potentially applicable to other non-periodic problems, which could include quasi-periodic

problems as well as some random ergodic ones. That may require advancing the approach of [41] e.g. in the direction of relaxing the spectral gap condition, or combining it with some other recently advanced techniques see e.g. [48], which could also allow tackling some of the other open problems mentioned above. Another possible exciting direction is towards development of new asymptotic-numerical hybrid approaches for multiscale problems, cf. precedents in asymptotic-numerical hybrid methods in high-frequency scattering [49] as well as in numerical analysis of some wave problems in high contrast heterogeneous media [50, 51]. Indeed, the approach of [41] approximates (with a controllable error) the highly oscillatory solutions of the original problem by non-oscillatory solutions of (higher-dimensional) two-scale limit problems, with the two linked by a two-scale connecting operator. The latter involves data sampling and interpolation, and it may be an exciting challenge to combine the asymptotic approaches with numerical ones for achieving controllably accurate computable approximations for a wide range of scale separation parameters.

Concluding remarks

High-contrast two-scale homogenization is a field with several decades of history. In the context of wave propagation, the critical scaling between the two small parameters of the spatial scale separation and contrast appears to be a micro-resonant scaling. Renewed interest to this area in the context of metamaterial modelling is due to the two-scale asymptotic models’ ability to display often unusual macroscopic physical effects in an asymptotically explicit way, clarifying the nature and the microscopic mechanism of the observable effects due to the subwavelength resonances. Recent advances make substantial progress on constructing improved approximations of a two-scale type with a controllable error for a broad and growing set of models of physical interest. Most recent developments provide exciting opportunities for addressing current and future challenges in metamaterial modelling.

4. High-frequency homogenization for periodic media

Marie Touboul^{1,2} and Richard V Craster³

¹ UMI 2004 Abraham de Moivre & Department of Mathematics, Imperial College, London SW7 2AZ, United Kingdom

² POEMS, CNRS, ENSTA, Inria, Institut Polytechnique de Paris, Palaiseau, France

³ Department of Mathematics & UMI 2004 Abraham de Moivre & Department of Mechanical Engineering, Imperial College, London SW7 2AZ, United Kingdom

Status

Metamaterials are known for their unique properties arising from their internal structure. When this structure exhibits periodicity, effective properties describing these materials can be derived using asymptotic methods [14]. These methods offer numerous advantages:

- The effective properties mimic those of a homogeneous medium, providing analytical insights into wave behaviour more readily than within the microstructure itself.
- Eliminating the need to mesh the fine scale of the microstructure results in significant computational efficiencies.
- These models can serve as a solid foundation for topological optimization or inverse design strategies.

A classical setting for these methods is the low-frequency regime where the typical wavelength is much larger than the periodicity of the material. This results in an effective macroscopic equation for the fields and an approximation that is valid near the origin of the dispersion diagram, i.e. in the quasi-static regime.

However, intriguing phenomena specific to metamaterials emerge at higher frequencies, such as Bragg band gaps where propagation is inhibited, or Dirac points that form the basis for topological considerations. High-frequency homogenization techniques, introduced in [52], enable the extraction of effective properties for the media when the wavelength is comparable to the periodicity, facilitating a deeper understanding of these materials at different frequency ranges.

High-frequency homogenization relies on identifying a specific point on the dispersion diagram and its associated eigenfunction, see figure 3. The eigenfunction represents the rapid-scale variations, which are predominant phenomena at high frequencies, such as standing waves at the corners of the Brillouin zone. Through high-frequency homogenization, an effective equation for the long-scale function that modulates the eigenfunction around the identified point on the dispersion diagram is derived, along with an approximation of the dispersion relation. This process encapsulates all relevant information about the physics and geometry in the effective parameter (or tensor) present in the effective equation for long-scale modulation function.

The methodology has been applied successfully across a wide range of configurations, including discrete lattices, frame

structures, optics, elastic plates, full vector wave systems, elastic composites, reticulated structures, imperfect interfaces, dispersive media. Furthermore, progress has also been achieved in considering source terms, closely located branches of the dispersion diagram [53], and time domain derivations.

Current and future challenges and opportunities

While significant progress has been made in adapting high-frequency homogenization to various scenarios, there are still several challenges that need to be addressed in dealing with more realistic or unconventional settings.

An intriguing scenario involves metasurfaces, where the periodic structure is confined to a single surface rather than the entire space. These metamaterial categories are compelling for size reduction and wavefront manipulation but necessitate specific asymptotic methods to model the boundary effects occurring at the transition between the structured surface and the homogeneous embedding medium.

Moreover, while many metamaterials are based on periodic structures, quasiperiodic materials showcase intriguing wave scattering and transmission properties, offering the potential to greatly broaden the design possibilities for metamaterials. However, transferring the well-established characteristics of wave phenomena from periodic media to quasiperiodic media presents a substantial challenge. Effective properties have been studied at low-frequency [54] and recent mathematical research has concentrated on extending Floquet–Bloch theory [55] and characterising super band gaps [56]. Developing a high-frequency effective model could bolster these efforts and address the scarcity of mathematical techniques, which has prevented the widespread utilization of quasiperiodic media thus far.

Another topical issue is the case of time-modulated media, where properties vary both in time and space. This emerging class of materials has garnered considerable attention due to its potential for wave manipulation, such as enabling non-reciprocal behaviour. Despite some efforts at low frequencies to propose effective models capturing this effect [57–59], addressing this issue remains an open question at higher frequencies. A deeper understanding of the unique dispersion diagrams that exhibit asymmetric band gaps in frequency or unusual gaps in wavenumber could be of significant interest and importance.

Advances in methods and techniques to meet challenges

At low-frequency, effective models are built for metasurfaces thanks to matched asymptotic expansions [60]. They allow to end up with effective jump conditions encapsulating the geometry and the physics of the microstructured surface. These effective jump conditions are able to take into account the boundary effect mentioned above and to provide valuable insights into scattering coefficients. There is a desire to expand these methodologies to address higher frequency scenarios. This could then be a basis for topological optimization

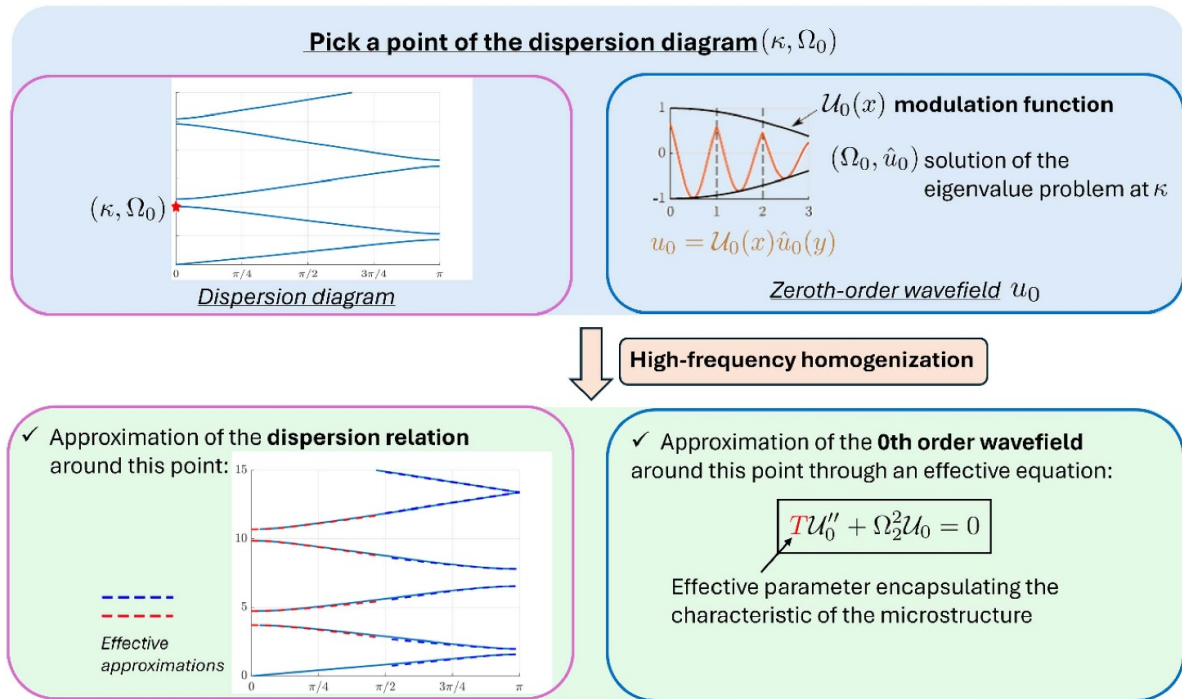


Figure 3. Schematic representation of high-frequency homogenization process in 1D.

techniques [61] of the microstructure in order to optimize the characteristics of the bandgaps or the dispersion.

Getting effective properties at low frequency for quasicrystals [54], or the extension of Floquet–Bloch theory to quasi-periodic structures [55], involves lifting the problem onto a higher-dimensional problem with periodic coefficients. In the higher-dimensional space, the equation obtained is degenerate and more intricate to solve. However, once this problem is addressed, information about the physical quasi-periodic system can be obtained by projecting back the solutions into the real space. However, the adaptation of high-frequency homogenization to this scenario remains a complex challenge. While applying high-frequency homogenization to the periodic higher-dimensional space appears feasible, establishing a connection to an effective equation for the real space is not a straightforward step. Another strategy could be to consider periodic approximants of the material [56], with however similar questions regarding the connection with an effective equation for the physical quasi-periodic problem.

Regarding time-domain media, recent theoretical works have been conducted for a laminate whose properties are modulated in a wave-like fashion. This unique setup enables the consideration of a moving frame where properties are

dependent on a single variable, facilitating the application of standard techniques like the Floquet–Bloch theorem. This framework could serve as a foundation for the advancement of high-frequency methods. However, one should be careful regarding the model precision equivalence in both frames. Additionally, addressing gaps in wavenumber is expected to require a special care beyond current high-frequency homogenization treatments. Extending this analysis to other space-time modulations remains an ongoing area of exploration.

Concluding remarks

High-frequency homogenization has proved to be numerically efficient, enabling a deeper understanding of wave behaviour across a wide range of frequencies. This technique has been successfully applied to various metamaterial configurations. Expanding the application of this method to new areas will require addressing open questions but could play a crucial role in the modelling of the next generation of metamaterials. For example, metasurfaces, time-varying materials or quasi-periodic media, which are fast-developing research areas, would benefit from the development of high-frequency asymptotic techniques.

5. Adjoint based methods for the design of large-scale non-periodic electromagnetic materials

James R Capers^{1,2} and Simon A R Horsley¹

¹ Centre for Metamaterial Research and Innovation, University of Exeter, EX4 4QL, United Kingdom

² QinetiQ Ltd, Cody Technology Park, Farnborough GU14 0LX, United Kingdom

Status

Electromagnetic scattering problems are typically cast in terms of a known material distribution and an incident, or source field. A variety of numerical and analytical methods can then be applied to solve Maxwell's equations for the full electromagnetic field. By contrast, *inverse design problems* are characterised by having the full solution, often only part of it, specified from the outset. One must then devise a way to find the material distribution that yields this field for a specific input wave. Solutions to such inverse problems are crucial for designing metamaterial-based devices that can address key challenges in energy, healthcare and defence.

Topology optimization via the adjoint method has recently emerged as a route to solve inverse design problems in electromagnetics [62]. The adjoint method simplifies the problem of finding the gradient of a figure of merit into two field calculations a 'forwards' field and an 'adjoint' field. As only two field evaluations are required to find how to change the structure at every single point in space, this technique is extremely numerically efficient and can be applied to a huge range of problems. For example, it has enabled the design of mode sorters [63], beam steering devices [64, 65], and even structures that can solve integral equations [66]. Nevertheless, while extremely powerful, in certain contexts the adjoint method can produce graded structures that are challenging to fabricate.

One way to alleviate both the problem of simulating aperiodic metamaterials, and the complex fabrication requirements of adjoint based designs is to concentrate on designs that use an aperiodic distribution of known resonators. Treating such an array as a collection of dipole (or higher order multipole) scatterers greatly simplifies the computational complexity (as depicted in figure 4). Recently, methods have been developed that begin from a particular distribution of scatterers and iteratively move them in order to increase some figure of merit, thus solving the inverse design problem [64, 67]. Treating all scatterers as dipoles enables the calculation of the gradients of figures of merit analytically, making this technique both much more numerically efficient than full wave simulations, and leads to designs that are straightforward to fabricate.

Current and future challenges and opportunities

Despite great progress over the last few decades in solving the inverse design problems, many open challenges remain. For several applications, such as next-generation communications, there is a desire for devices to operate over a wide frequency

band, something which is often neglected in inverse problems. Typically, performance over a large band is achieved by stacking resonances [68], however this requires many independent designs. Instead, one might define a figure of merit in terms of the bandwidth of a system and seek to optimise this algorithmically. This would allow for precise control over the frequency response, allowing for peaks or nulls to be placed arbitrarily, while retaining the convenience of existing fabrication techniques.

There has also been a great deal of recent activity in designing materials that vary in time as well as space: here the inverse design problem is largely unexplored. This new class of material shows great promise for the manipulation of the frequency content of a wave, however the question of how to modulate a material to achieve a desired spectrum remains open. A formulation of the adjoint method in the time domain was recently proposed [69], although has yet to be fully exploited.

Finally, the ability perform inverse design in real time might benefit the application of reconfigurable intelligent surfaces (RISs) to communications challenges. The real-time reconfigurability of these surfaces is often electronic and it is desirable to adapt the EM environment as quickly as possible. If one had reliable physical model that could be quickly evaluated [70], or access to a feedback loop, one could update the structure to manipulate the EM field in real-time. This would allow, for example, a beam to track a moving target. While at lower frequencies, the elements of a RIS can reasonably assumed to be strongly subwavelength thereby scattering as dipoles, at higher frequencies they resonators may be larger with respect to the wavelength causing the dipole approximation to break down (something that could be mitigated through including higher order multipoles, although this comes at the expense of greater numerical demands).

Advances in methods and techniques to meet challenges

To address the challenges presented above, several potential advances to the adjoint method and dipole-based design techniques will be required. Manipulation of the bandwidth of materials using the adjoint method might require a way to algorithmically distribute different materials with different dispersion properties in space, to achieve the desired effect. Alternatively, a range of resonances could be employed for example mixtures of dipole, quadrupole, octupole etc. resonators could be distributed in space. While the theory of collections of interacting multipolar resonators is well developed, the application of this to design scattering systems has yet to be explored.

Applying the usual inverse design techniques to time-varying systems presents a more fundamental challenge. A key feature of the adjoint method is that reciprocity is exploited to convert a gradient evaluation into two field calculations. For time-varying materials, which are not reciprocal, how to formulate the adjoint field remains an open question, although some progress has been made in the context of non-reciprocal materials [71]. There will then be many challenges related

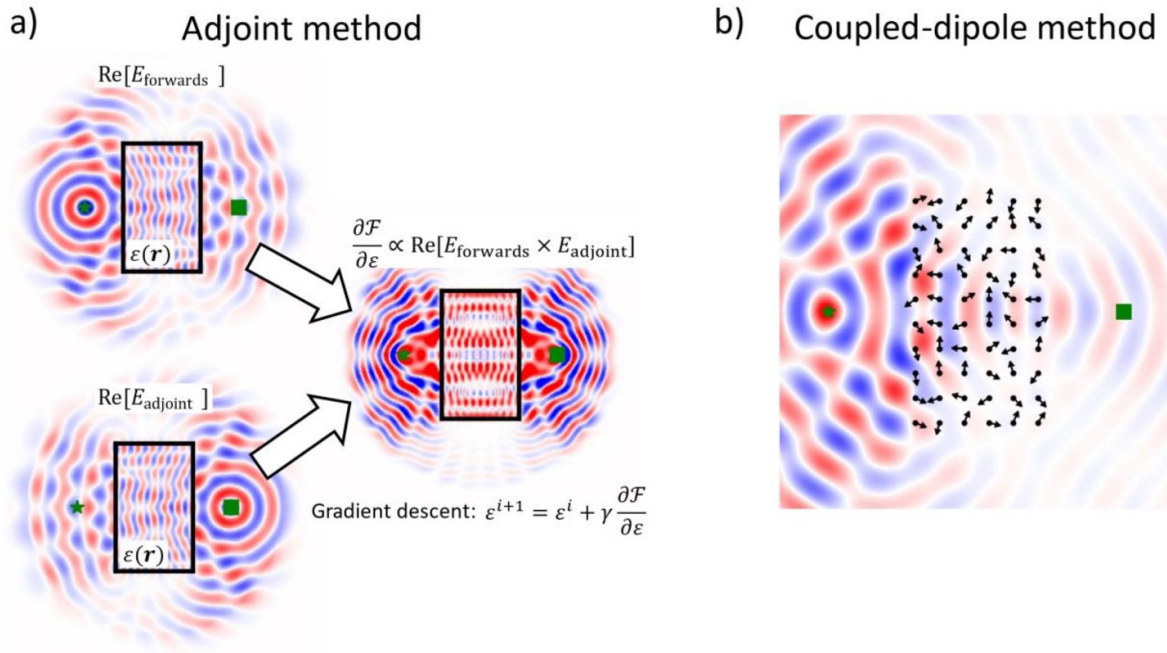


Figure 4. Schematic representations of using (a) the adjoint method and (b) the coupled dipole method to design a lens. We seek to design a structure that focuses radiation from a source at the location indicated by the green star to the location given by the green square. The design region is indicated by the black rectangle. For the adjoint method, only two field calculations a ‘forwards’ and an ‘adjoint’ are required to form the gradient of the figure of merit (field amplitude at the green square) with respect to the whole structure. This allows one to iteratively update the structure according to gradient descent to increase a figure of merit \mathcal{F} . Using the coupled dipole framework, the gradient of the figure of merit with respect to the scatterer locations can be found analytically, providing a map of how to move the scatterers.

to imposing fabrication constraints, as realising time-varying materials experimentally remains challenging.

Concluding remarks

Numerically efficient and conceptually simple, adjoint discrete dipole based inverse design techniques have already shown great promise for designing novel wave-shaping

devices that can be a periodic and many wavelengths in size. Bringing these techniques to new areas of application, such as time-varying materials or real-time reconfiguration, will require many open questions to be addressed. The realisation of an ‘adjoint’ method in the time domain might enable the design of bespoke frequency shifters or amplifiers and real time inverse design might be important in the next generation of communication technologies.

6. Design optimisation of hierarchical structural metamaterials

Robert W Hewson, Matthew Santer, Ryan Murphy and Dilaksan Thillaithevan

Department of Aeronautics, Imperial College London, London SW7 2AZ, United Kingdom

Status

The field of structural metamaterials has gained significant interest in recent years due to the increasingly widespread adoption of additive manufacturing (AM). AM has permitted the manufacture of complex structures including those which span a range of scales and hierarchies. This allows an architected internal structure to be designed and manufactured, with characteristics significantly different from the bulk material. This can lead to complex or even counter-intuitive structural responses from the designed component, for example auxetic behaviour [72], programmed nonlinear behaviour [73], including negative stiffness. The design of complex hierarchical structures now means that in addition to the design of the component's external boundary, the internal structural arrangement can be designed, providing additional exploitable properties. One of the major challenges presented by the new capability is how to design components with architected interiors and where the grading of an internal structure might lead to enhanced structural characteristics, but where the design itself is hard to visualise and therefore design without formal optimisation methods. This presents significant challenges, especially if emerging properties of graded structures are to be exploited rather than utilising a single repeated unit geometry to give uniform structural characteristics. To achieve these, computational methods are required which go far beyond CAD and visualisation tools.

Three approaches are often used to describe the small-scale, (i) the geometric parameters [74] or orientation and thickness of lattice members [75], (ii) the resulting properties of the small-scale geometry (essentially a subset of the elasticity terms in a multiscale problem) [76] and (iii) the small-scale geometry is spatially optimised using inverse homogenisation-based techniques [77]. In (i), sub-optimal small-scale geometries are often employed and (ii) has the equally significant problem that the mapping from graded material properties to small-scale geometries does not guarantee slowly varying geometries. This leads to a breakdown of the underlying assumption on which the heterogeneous multiscale method is based and which is often used as a basis for multiscale structural analysis. Some significant progress has been made to address these deficiencies using the computationally expensive (iii) approach, but there is still work to be done in this area. There has been some excellent work going beyond classical homogenisation methods for multiscale approaches [78] and the potential for this to be extended to nonlinear complex problems is significant.

Current and future challenges and opportunities

The additional design flexibility afforded by the ability to tailor both the internal and external structure extends well beyond the linear elastic regime. Large deformations, nonlinear viscoelastic tailoring of materials, abrupt material changes resulting from internal contact or failure, and tailored multifunctionality could all be areas which could be better realised with the application of hierarchical structures [79]. Coupling these structural metamaterial-based opportunities arising from those of other disciplines such as electromagnetics adds further opportunities to the class of new materials. A further open challenge is how to optimise multiscale structures in a way which allows design flexibility across the scales. Approaches which rely on de-homogenisation of a large scale FGM structure via analytical means require a small-scale approximation to be known [80] or approximated using simulation [81]. The former is typically only available for simple, and usually 2D, geometries in the linear elastic regime and the latter is challenging in highly complex, nonlinear settings.

Some of the major challenges to the development and wider adoption of structural metamaterials are presented below, these do not include challenges which go beyond the computational design of the metamaterial structures, and therefore only touches on the geometric representation of the geometry using CAD, and manufacturing challenges related to computational design rather than the broader challenges. The development of implicit geometry [82] definition is an active area of research which overcomes some of the challenges associated with conventional geometry surface representations. It also focuses on the design optimisation or inverse design of structures, rather than more ad-hoc design methods based on trial-and-error or a human designer's intuition.

One area of significant potential is the development of hierarchical structures which are optimised for nonlinear responses. This includes the development of optimal structures which account for, (i) large displacements, (ii) internal contact, (iii) failure and post failure characteristics. Optimising metamaterials for these requirements pose significant challenges. Multi-level approaches, where small-scale characteristics are stored in a database and an optimisation algorithm relies on design sensitivities, frequently arrived at using a finite element and adjoint method, pose considerable computational processing and storage challenges. This is due to the high level of multidimensionality of the characteristic space (both the material properties in terms of the local displacement field and geometric definition). The underlying assumptions permitting homogenisation theory may also start to breakdown, for example small scale buckling of members potentially no longer being consistent with the assumption of a slowly changing and periodic displacement field. Developing model order reduction approaches which go beyond classical homogenisation approaches could provide a means of accessing complex, nonlinear material properties, allowing assembly of small-scale geometry to form components optimised across scales.

Loaded structures exhibiting contact, negative stiffness and failure all have the potential to dramatically change how we consider metamaterials if they become accessible to formal design optimisation methodologies. An example of this is that if we are able to optimise the progressive failure of a metamaterial. By considering internal contact and fracture, safer, impact resistant structures for a wide range of applications could be designed. The potential to go far beyond ad-hoc design and testing of structures will no doubt deliver not only improved performance, but also the ability to direct impact, as well as gain an understanding of the overall compromise between the impact resistance of a structure and its other functionality, such as stiffness.

Multifunctionality of structures, where components go beyond purely structural response, for example to include actuation, sensing or energy storage, require a multifunctional analysis of the problem and an understanding of the combined objective of the system. The optimisation of such systems is frequently made more complex by the significantly different approaches to parameterisation required for the different discipline [79]. The optimisation of the metamaterial will then not only provide an optimal design, but of equally importance also tell the designer something about the compromises required and how the discipline specific requirements interact.

Advances in methods and techniques to meet challenges

There are a number of exciting model order reduction methods being developed, as previously described, to analyse structural metamaterials efficiently. This leads to the potential to go beyond analysis and to optimise the system. The complexity of structural metamaterials means that a model order reduction technique is commonly required to make the analysis and optimisation of the problem accessible. Much of the

model order reduction has thus far centred on the application of homogenisation or small-scale analytical approaches. However, homogenisation relies on the underlying assumption of a slowly spatially varying geometry, property field and solution field. There exist a range of approaches which do not rely on homogenisation methods which could potentially be exploited to design and optimise metamaterial structures rather than for analysis. Examples include hyper-reduction approaches [83] and the use of subspace methods [84]. The latter potentially facilitated by the use of machine learning as an efficient model order reduction tool to enable the design of metamaterials and going beyond the more well-established approaches of using machine learning for the efficient interpolation of databases of already designed structures. Developing such methods with efficient optimisation approaches, typically gradient-based methods, with similarities to classical SIMP-based topology optimisation, could deliver optimisation of complex hierarchical structures without requiring a separation of scales and all the associated challenges. Contact, failure or problem scales which are non-separable reduce the relevance of the approach and require other methods to be considered.

Concluding remarks

Much work on structural metamaterial design often focuses on the efficient graphical and geometric representation of a design. The authors believe that unlocking the potential of complex nonlinear, multifunctional metamaterials lies in the application of formal optimisation methods which go beyond CAD and instead consider the functional grading of a structure. The renewed interest in machine learning approached and other model order reduction approaches hold significant promise in dealing with the efficient coupling between scales required.

7. Artificial intelligence for electromagnetic metamaterial design

Simon J Berry

QinetiQ Ltd, Cody Technology Park, Farnborough GU14 0LX, United Kingdom

Status

Artificial intelligence (AI) has gained widespread recognition in the mainstream consciousness in the last twelve months due to the emergence of significant large language models such as ChatGPT. However, AI has been developed for the design of electromagnetic (EM) structures for over 20 years [85]. Due to the recent increase in interest in this area there is a significant increase in the amount of hype in this area alongside excellent technical progress. Sorting the hype from the truly novel work will take time as the research community implements these developments.

Deep learning and neural networks have been used to predict the response of metamaterials with a wide variety of structures, examples include split ring resonators [86] and coded metasurfaces [87]. A summary of deep learning techniques for EM metamaterials is given by Khatib *et al* [88]. An alternative technique, sometimes making use of deep learning techniques, involves replacing the computationally expensive steps with a simpler model by fitting to known data points, known as a surrogate model. This has been done in an adjacent field using finite element method modelling in determining the stress within a sample subject to a controlled increase in temperature [89]. This surrogate modelling technique has the potential to supplement full computational electromagnetic modelling (CEM) in producing training data for deep learning models.

AI has the potential to provide a benefit to the design of EM metamaterials due to the difficulty inherent in the inverse design problem for metamaterials. The inverse design problem for metamaterials is challenging as metamaterials are often a high dimensional optimisation problem which is solved using CEM techniques. These techniques, involving solving Maxwell's equations across the metamaterial structure, are time consuming for each individual iteration of the structure and determine the maximum number of simulations that are practical and therefore the number of iterations available to the optimiser. Were AI able to reduce the time for each iteration in the traditional optimisation process or improve the approximation of the design space, for example through surrogate modelling, this would provide a significant benefit to metamaterial optimisation.

Current and future challenges and opportunities

The biggest issue facing using AI for EM metamaterial design is actually a wider issue; the inverse design problem [90]. Inverse problems involve attempting to calculate cause from effect, see figure 5, which leads to a variety of challenges. Inverse problems, in particular the inverse EM metamaterial design problem, are almost always 'ill-posed problems'.

Ill-posed problems violate at least one of the following principles of 'well-posed problems':

Criteria 1: Existence (a solution exists)

Criteria 2: Uniqueness (there is only one solution)

Criteria 3: Stability (the solution depends continuously on initial conditions)

In inverse EM metamaterial design we can reasonably expect to design problems that are; not physically realisable e.g. violate the laws of physics (violates Criteria 1), is physically realisable but the solution is not within the bounds of the design space (violates Criteria 1) or is physically realisable but with multiple solutions within the design space (violates Criteria 2).

Another major issue with using AI for EM metamaterial design is a wider issue in AI development which is the requirement for significant quantities of data required to train the model, in our case this data is often generated using time-consuming CEM. For instance, the training data required for a neural network is often between 1000 and 10 000 data points across the design space [88]. This requirement means that the main driver of the time taken for these models is the CEM time to generate the training and test dataset. If a single optimisation is required then it is often quicker to simply perform a traditional optimisation, where multiple solutions can be drawn from the same design space an AI method is significantly more beneficial.

The major open problem, related to a large range of AI problems, is mitigating the dependency of AI models on large amounts of training data. Reducing the training data burden for future models would enable an expansion of the use of AI models to design and optimise EM metamaterials.

Advances in methods and techniques to meet challenges

Given the difficulty of the inverse design problem the primary focus of future techniques will likely be on reducing the requirement for substantial amounts of training data. This has the advantage of being useful across a wide range of AI applications, not just EM metamaterials. Two promising avenues are active learning and transfer learning; active learning involves allowing the neural network to influence, or choose, the training data that it uses to build and model, whilst transfer learning involves leveraging trained models from adjacent problems to help reduce the training time.

Active learning has been studied extensively across the machine learning community and can be particularly helpful where an optimisation goal is known [91]. Another widely-used technique is to use 'uncertainty sampling' where the model adds further training data at points where the model solution has the greatest uncertainty. This is a very useful technique for EM metamaterial development since obtaining the training data involves time-consuming CEM simulations for a given point within the design space and therefore 'uncertainty sampling' can improve the AI model accuracy for the

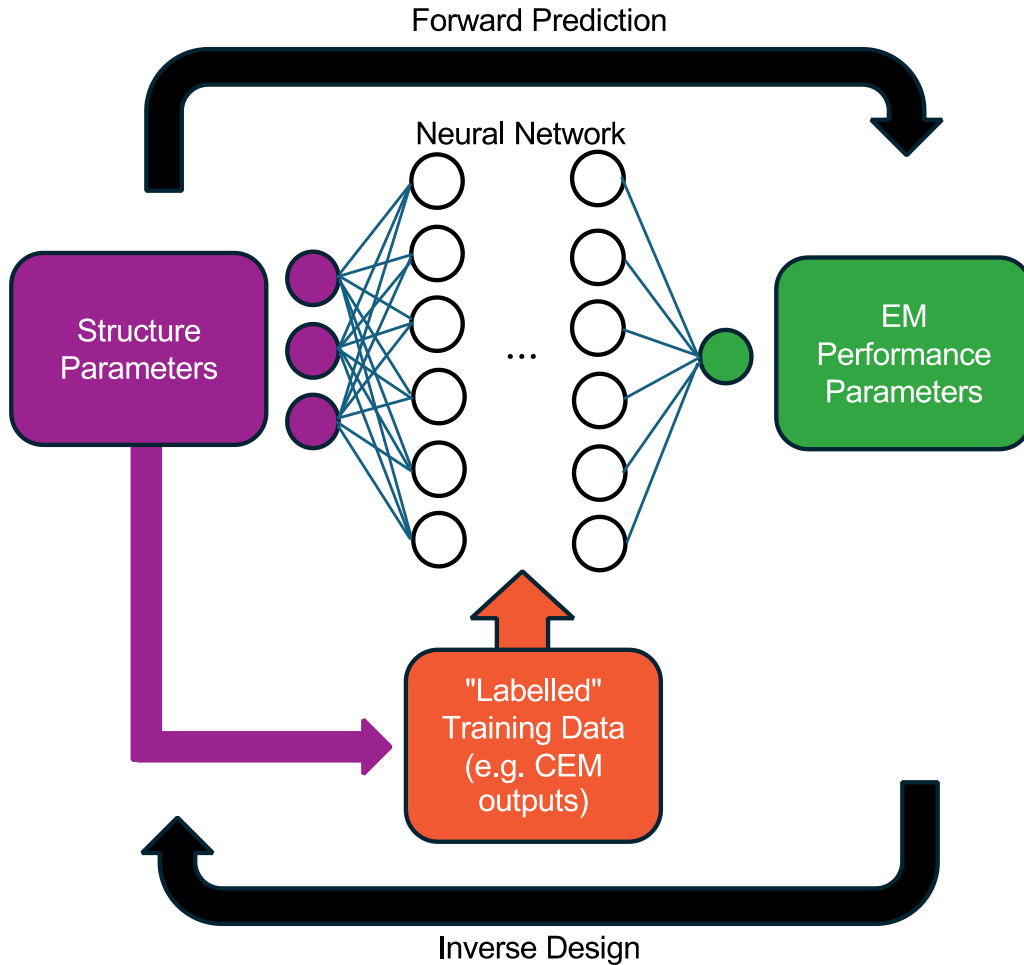


Figure 5. Schematic illustration of the use of a neural network to take the place of time consuming computational electromagnetic modelling. This also shows the difference between forward prediction and inverse design.

same amount of training data. Alternatively, Transfer learning, involves using training data from an adjacent problem to supplement the training data of the problem being studied. This can be done by pre-training a neural network on the adjacent problem before refining it on the training data for the real problem or by training the network on both problems simultaneously. Given that all EM metamaterial design tasks involve solving Maxwells equations transfer learning could provide a significant benefit in this area.

Another area that is currently being explored is physics informed neural networks (PINNs). PINNs introduce limitations on the neural network to enforce some of the underlying physics on the network result. Previous work has [92–94] enforced the neural network solution obeys partial differential equations and included the problem boundary conditions to limit the available solutions within the neural network. The combination of PINNs and transfer learning, for problems with the same or similar boundary conditions (e.g. infinite planar

metasurfaces), could provide a step change in training neural networks.

Concluding remarks

AI has the potential to revolutionise the optimisation of EM metamaterials. However significant challenges remain, some of which are associated with the wider issue of the inverse design problem. In this context AI tools will be best deployed in a ‘train once, use many’ application where future iterations of a metamaterial can be rapidly generated once the AI tool has been trained sufficiently. If further progress can be made on reducing the training data required to develop the AI models, through some of the methods discussed above, then these AI tools have the potential to provide a route to efficient optimisation of EM metamaterials for industrial applications.

8. Strategies to overcome difficult data

Gareth J Conduit

University of Cambridge & Intellegens

Status

Historians chronicle human civilizations development through the stone, bronze, and iron ages, underlining how materials discovery enables new technology. In each instance, right up to the present day, materials were discovered by a time-consuming and expensive process of experiment-driven trial-and-improvement. However, recently AI has emerged as a tool for materials discovery, offering significant time and cost savings. The first application of AI to materials was in 2003 to design a new steel [95]. Since then, there has been rapid development of AI for materials and chemicals design with a range of industrially proven examples [96], and early commercial adoption.

Artificial intelligence learns from historic data, and so the amount and quality of this historic data is key to success. We discuss two approaches to improve this fundamental underpinning of AI:

1. **Additional data:** sections 1–3 and 6 of this roadmap offer complementary analytical methods that offer additional information about a system. Therefore, we propose the development of AI that can exploit all possible knowledge about a system, combining the strengths of experimental data, first principles computer simulations, and physical rules of thumb.
2. **Explainability and reliability of data:** section 7 discusses physics and chemistry aware AI. Therefore, we propose improvements to the explainability of AI, which will not only provide critical insights to scientists and engineers, but moreover assess reliability of data to fulfil a common regulatory requirement for evidence of the underlying mechanisms.

Current and future challenges and opportunities

Artificial intelligence is a powerful tool that has found applications across materials and chemical systems, spanning both research and also industrial settings. In the face of inevitably challenging training data, researchers are pursuing approaches that exploit additional information to accelerate further applications in materials and chemicals:

There are several open problems in AI, pertaining to handling difficult data, that if solved, would open significant opportunities in the application of machine learning to metamaterials. We highlight just two opportunities below:

Exploit all available information: Data is often sparse, for example values are not all measured or individual companies curate private data silos but guard them jealously even when it may be mutually beneficial to share. Furthermore, there is much untapped knowledge beyond traditional experimental

data, including first principles computer simulations and physical rules of thumb. The development of AI methods that can juxtapose these sources of knowledge would lead to a predictive tool more powerful than the sum of its parts.

Explainability and reliability of data: Experimental data often carries uncertainty. However, scientists and engineers often require more than accurate predictions and designs, they need to understand that a design will be reliable and why the design works. This not only provides the insights that drive future development, but moreover is often demanded by regulators for safety critical products. The development of an AI tool that can open the box, explore robustness, and explain the physical insights behind its predictions would be a gamechanger for the practical applications.

Sometimes the supplied training data could simply be insufficient to train a reliable model. There are then two possible ways forward that we discuss below:

Design of experiments: Sometimes there is not enough data available to build an AI model, or even for a human scientist to infer the underlying mechanisms. The solution is often to gather more data, which can often be gathered in a judicious pattern to efficiently cover design space. Standard methods do this without any knowledge of the behaviour of the end-goal properties, but methods under development in AI can take advantage of existing knowledge and the end goal to more efficiently explore space, saving experimental time and cost.

Design of formulations: An even more powerful use of AI is to propose new formulations that fulfil a target specification. However, models can be uncertain owing to either lack or noise in data. Another area of active research, this requires not only the algorithmic development to enable more accurate predictions, but also a measure of their confidence, so that only the most robust proposals are taken forward.

Advances in methods and techniques to meet challenge of difficult data

In the materials and chemicals sectors experiments remain the key tool to understand the properties of materials, including metamaterials. However, experiments are expensive and time consuming, and moreover are not always performed to completion. Therefore, AI that can extract value from highly sparse and noisy data has emerged as a key opportunity in the materials and chemicals sectors. Three approaches have emerged to overcome sparse data:

Modelling technique ignores sparsity: Perhaps the clearest approach is to adopt a modelling technique that ignores the missing values. The straightforward approach is to simply discard entries where any single component is missing, however this can leave no data remaining. Alternatively, missing values can be simply ignored, or replaced by an average value, for example k -means clustering skips around missing input values by simply sampling those inputs present [97].

Multi-output neural network: The model is set up so the two linked properties share many hidden nodes, with the two properties distinguished only by the final hidden layer [98]. Therefore, the bulk of the physics is captured by the common hidden nodes, and so can be learnt from both properties, extracting more information from sparse data.

Self-consistent imputation: A third approach is to make guess at the missing values, thereby generating a complete dataset [96]. From this a standard AI algorithm can be applied to make predictions for all values, including those that were missing. These improved estimates for the missing values can be used as inputs in successive training and prediction cycles until the predictions reach self-consistency.

Experimental data is often noisy, stemming from inevitable experimental uncertainty. Artificial intelligence methods

can not only average over this noise (rather than overfit), they can also estimate the uncertainty in their prediction owing to this noise. Additional contributions to the uncertainty arise when extrapolating beyond the range of the training data. By understanding this uncertainty, AI can focus on the most robust predictions that are most likely to fulfil the target specification [96].

Concluding remarks

We have demonstrated that there are many opportunities to ensure quality and availability of data to apply AI to metamaterials. The holistic exploitation of all sources of information and explainability to ensure reliability in face of difficult data are two especially important themes for further development.

9. Metamaterials genome: towards synergy between mathematical modelling and AI analysis

Stefan Szyniszewski¹, Jacob Earnshaw¹, Nicholas Syrotiuk¹, Oliver Duncan², Łukasz Kaczmarczyk³ and Fabrizio Scarpa⁴

¹ Department of Engineering, University of Durham, Durham, United Kingdom

² Department of Manchester Metropolitan University, Manchester M15 6BH, United Kingdom

³ Glasgow Computational Engineering Centre, James Watt School of Engineering, University of Glasgow, Glasgow G12 8QQ, United Kingdom

⁴ Aerospace Engineering, Bristol Composites Institute, School of Civil, Aerospace and Mechanical Engineering, University of Bristol, Bristol, United Kingdom

Status

What is the best use of machine learning techniques in the context of computational mechanics and relatively scarce experimental data sets? One could attempt to gain a general understanding of the design possibilities by aggregating results from a large number of targeted engineering projects, i.e. tapping into the so-called ‘data exhaust’ of the broader research and engineering community. Understanding the limits of the design space is a key aspect in optimising complex hierarchical structures and is vital for exploring and designing novel Metamaterials.

The development of machine learning and AI technologies has been accelerated by abundant data (mostly text, images, geographical coordinates) aggregated by multinational corporations. Although increasingly conceptually advanced, the origins of machine learning can be traced back to traditional statistical methods and data-centric analysis. These techniques have been used in fields where establishing relationships and using differential equations or closed-form descriptions have been challenging due to the systems’ complexity. However, well-established, and validated physics-based modelling tools offer direct solutions for various physical domains relevant to metamaterials.

Fundamentally, numerous research groups and companies repeatedly carry out physics-based calculations, all employing the same fundamental equations such as Maxwell, wave, or dynamic equations of motion. Therefore, one can recognise the potential for a large collection of results, which are currently scattered across various research groups and frequently guarded in private data silos. In many instances, the results are discarded at the completion of specific projects or placed in disparate archives for a limited time. As recognised by several US federal agencies [99–101], creating an open research commons and appropriate standards and infrastructure for sharing, reusing and recycling existing data (including computational tools) can accelerate the development of novel materials, reduce effort duplication, and facilitate creative, fast-paced knowledge generation.

Current and future challenges and opportunities

To create an open research commons that can integrate multiple physical domains like mechanical, optical, EM, etc it is necessary to establish common data standards [102]. This requires input and agreement from both academic and industrial groups. Moreover, these standards may change over time. Therefore, it is important to establish methods for migrating and adapting data.

Shared repositories of knowledge require the trust of all stakeholders [103], sustainable funding, and a transparent governance structure. To achieve satisfactory cyber security resilience, such a repository might require distributed storage across academic and industrial stakeholders and specialist cybersecurity support. Low barriers for adaptation and usage are also required to facilitate broader benefits and adaptation by the widest possible group of stakeholders.

Optimising the process of organising and utilising data that already exists can save time and resources for all stakeholders. Additionally, establishing a shared open research commons can lead to improved collaboration and knowledge mapping by linking research groups based on similarity and proximity metrics of the structures they produce. By enabling search engines for specific required properties, manufacturers and industrial stakeholders can quickly identify the key research groups and technology suppliers in the design space.

Shared data from ‘adjacent’ problems can be used to inform and suggest solutions for the problem being studied (also in different physical domains). Since Metamaterial problems solve a limited number of physical laws, transfer learning provides significant benefits in this area and suggests good starting points for developing Metamaterials with specific properties. This can be achieved by leveraging prior iterations and the experience of other academic groups and stakeholders. Transverse learning can be facilitated using approximate surrogate models trained on prior data. Such fast-running surrogate models are also vital for optimisation and can underpin AI generative design, which could suggest promising areas for novel material discoveries. However, performing final design checks can be reliable and accurately achieved using computational physics and mechanics, guaranteeing accurate results, ensuring adherence to known laws of physics and offering explainable results.

Another interesting application is the use of large language models to suggest suitable physical models, regulatory requirements, design equations, and modelling code snippets. In such instances, AI tools are focused on enhancing human productivity and easing access to knowledge. However, the validation and reliability of such co-generative tools remain an issue.

An example of an unsolved problem in the field is the development of a compact topology parameterisation compatible with machine learning tools. Such encoding should be able to generate any suitable Metamaterial topologies

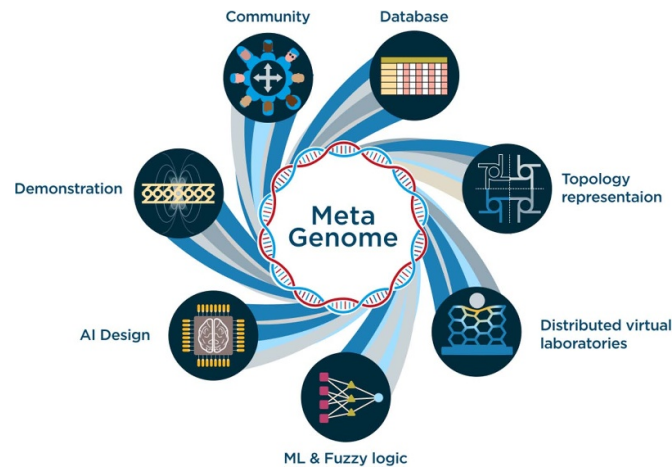


Figure 6. Synergy between physics-based modelling tools, the scientific community, AI toolboxes, manufacturers, and end-users is essential for a successful development ecosystem.

without being restricted to a specific subclass of structures. Another challenge is incorporating manufacturability, cost, and sustainability aspects into the optimisation process, as well as the generative capabilities of the shared open research commons. What is the best pathway to standardise such data to enable interoperability and facilitate data sharing?

Advances in methods and techniques to meet challenges

The National Institute of Standards and Technologies (NIST) has developed an open-source platform called the configurable data curation system (CDCS) [104] that can curate complex data structures. This platform is designed with cybersecurity in mind and is continuously updated and supported by NIST. We have used this platform to create a prototype of a shared database of metamaterials, which is accessible online [105] and outlined in figure 6. The database can handle complex hierarchical XML data structures, including topology information in discrete voxel formats and more parametric, vector-like descriptions such as step formats. The open-source code can also be cloned, and independent repositories can be created while leveraging shared data standards and programmatic developments in toolkits for working and processing large datasets. This database is particularly relevant in the context of recent developments in the

computer science community, where tools like VQGAN [106] are being used to describe topologies. These tools hold promise in establishing critical links between physical information in the Metamaterials community and rapidly developing AI toolboxes with generative capabilities demonstrated for other material domains [107]. Recent developments of AI-generated mechanical metamaterials [108–110] further underscore the benefits of shared data repositories for the overall progress of the discipline.

Concluding remarks

Through the establishment of a shared open research commons, collaboration and knowledge mapping can be improved by utilising property-based norms and metrics. This will enable the community to quickly identify key research groups, manufacturers, and industrial stakeholders in the design space by searching for specific required properties. Secondly, it will enable researchers to focus on the most interesting and high-value activities, minimising duplication of effort and leveraging prior material discoveries. Thirdly, a standardised shared data platform lays the foundation for experimentation with and developing generative AI toolkits to augment and guide future meta-material discoveries. Establishing a thriving ecosystem where all skill bases are complementary is fundamental for ensuring benefits for all stakeholders.

10. Electromagnetics of time-modulated metamaterials

John B Pendry

The Blackett Laboratory, Department of Physics, Imperial College London, London SW7 2AZ, United Kingdom

Status

The interaction of light with structured media is now commonplace: photonic crystals are widely deployed to control light, and metamaterials appear in many. Structure should be on the same scale as, or less than the wavelength of radiation. Initially this was technically demanding but technology has advanced to the point where photonic crystals and metamaterials are commonplace. The obvious extension is to structuring in time, and once more the length scale for effectiveness is dictated by the radiation concerned: it should be on the same scale or shorter than the radiation's temporal period. The time challenge is a much more demanding experimentally than the spatial one and has held up development of the field until recently when technology has opened new horizons for us.

Just as the static Bragg grating is the starting point for diffraction theory, so a grating in space and time,

$$\varepsilon(x, t) = \varepsilon_1 [1 + 2\alpha \cos(gx - \Omega t)]$$

has been the workhorse of theory for time modulated materials [111]. In almost all studies it is assumed that the material itself does not move but is locally modulated, rather as a water wave spreads over the ocean without carrying the water with it. This ensures that the velocity of the structure, $c_g = \Omega/g$, is not limited by the speed of light. It also avoids complications that arise from performance of mechanical work when materials physically move.

Early theoretical work showed that the model is PT symmetric and gives rise to real dispersion relations, $\omega(k)$. The exception is the so called trans-luminal regime defined by the grating travelling at a speed comparable to the velocity of light such that there is a point in the grating where light travels at the same speed as the grating [112]. This is a trapping point where radiation is compressed and amplified: the PT symmetric model breaks down and $\omega(k)$ can no longer be defined. Figure 7 shows the dramatic consequences. A recent review gives more [113].

Current and future challenges and opportunities

The most obvious opportunity is the breaking of time reversal symmetry [114]. This means systems can dispense with the need for magnetic fields to produce isolators and replace them with more compact devices. As space-time structure becomes more elaborate, systems show true topological protection of the flow of light, rather than relying on spin conservation. For example, helical structures have been studied where polarizability rotates in time giving a spin dependence to its response. The surface states of these structures have rich potential for topological properties.

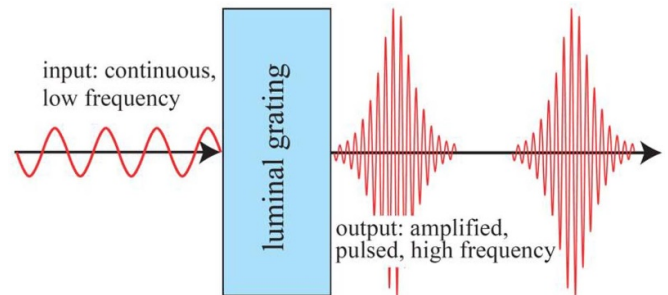


Figure 7. Schematic transmission through a luminal grating. Incident radiation grows exponentially in intensity undergoing compression into a series of pulses separated by the time period of the grating.

Most fascinating is the transluminal regime. Theory has identified the mechanism by which light is amplified and compressed in this regime: lines of force are conserved and energy added by compressing them as in compression of a magnet's quasistatic field as it approaches a superconductor [115]. In quantum terms amplification takes place by photons climbing a ladder of frequencies in units of Ω .

The quantum nature of light is very much emphasised by time dependent structures [116]. A simple periodic modulation in time of frequency Ω will give rise to a band gap at $\omega = \Omega/2$ by hybridising states at $\pm\Omega/2$, i.e. by mixing positive and negative frequencies giving rise to parametric amplification with amplitude growing exponentially in time. In quantum terms this amounts to creation of qubits—highly correlated pairs of photons. This process is well known but there is another mechanism for pair creation which has only recently been identified. In the transluminal regime light is amplified irrespective of the frequency, trapped at the accumulation points referred to in the previous section. For upward movement of frequency photons are conserved. In contrast downward movement of frequency meets an impasse when attempting to cross from positive to negative frequencies and can only do so by creating a qubit with one of the components having a negative frequency. This mechanism is analogous to Hawking radiation which although in a totally different context also involves a singularity in the propagation of light at the Schwarzschild radius and the creation of negative frequency photons.

The quantum domain is ripe for future studies with many questions waiting to be answered.

Advances in methods and techniques to meet challenges

For theory to be taken seriously it must connect to experiment. There are now several experiments showing extremely fast modulation of materials properties. An early example is the so called 'push broom' effect [117]: a sufficiently intense pump pulse of light travels in an optical fibre changing the refractive index at the leading edge. A probe pulse travels at a different frequency at a lower velocity and is overtaken by the pump which then captures the probe into the transluminal region created by the pump and compresses

it, even though the modulations in refractive index may be tiny.

More substantial modulation has been achieved in recent experiments. The Sapienza group exploited the ‘epsilon near zero’ property of indium tin oxide (ITO) combined with plasmonic enhancement of an incident pump pulse to turn the ITO into a reflecting surface [118]. Modulation of the reflectivity of 230 GHz radiation in this experiment was substantial—of the order of 50%. The problem they faced was that the onset of reflectivity was so sudden that neither the pump nor the probe could resolve it, both being of the order of 800fs wide. This issue was resolved by creating two windows of reflectivity to make a time domain analogy of a Young’s slits experiment. In the original experiment slits separated in real space disperse radiation over a range of angles and fringes arise from interference. The decay of fringe intensity with angle is dictated by how narrow the slits are. In the Sapienza experiment the ‘slits’ now appear in the time domain, and the interference fringes in the frequency shift of the probe. The decay of fringe visibility with frequency shift is a measure of how narrow the time-slits are remarkably the experiment

revealed that the rise time of the reflectivity was at least as rapid as the 5fs period of the radiation. Work is underway to combine this very rapid time variation with spatial modulation.

Experiments at Technion-Israel Institute of Technology, and Purdue University had a different approach [119]. They were able to compress the pump pulse to 6fs and under the assumption that the material responds more or less instantaneously, produced a very sharp rise time of refractive index which was measured by observing the colour shift of a probe as the refractive index is modulated.

Concluding remarks

Time modulated metamaterials are a rapidly expanding field with encouraging experimental progress. In my opinion the chief challenges lie in the further development of experiments. Theory makes a vital contribution and is well prepared for their interpretation and will press on to exploit opportunities in the quantum domain.

11. Irrational metamaterials and their development

Marc Martí-Sabaté¹, Sebastien Guenneau², Daniel Torrent³, Elena Cherkasova⁴ and Niklas Wellander⁵

¹ Department of Mathematics, Imperial College, London SW7 2AZ, United Kingdom

² The Blackett Laboratory & UMI 2004 Abraham de Moivre, Imperial College, London SW7 2AZ, United Kingdom

³ GROC, UJI, Institut de Noves Tecnologies de la Imatge (INIT), Universitat Jaume I, 12071 Castelló de la Plana, Spain

⁴ Department of Mathematics, University of Utah, 155 South 1400 East, JWB 233 Salt-Lake City, United States of America

⁵ Department of Engineering Sciences and Mathematics, Luleå University of Technology, SE-97 187 Luleå, Sweden

Status

Quasicrystals, which were experimentally observed 40 years ago by the team of the Nobel Prize winner Dan Shechtman [120], are arrangements of particles or elements in such a fashion that they do not present translational symmetries, but they show long-range order. They can be modelled from a cut and projection of a periodic structure in a higher dimensional space onto a hyperplane as in [121–123]. Other kinds of structures [124–126], incommensurately modulated crystals, also present non-periodic features. They derive from Harper's equation, which can be understood by Bellissard's K-theory of C^* -algebras [127], linking their properties to the bulk-boundary theorem and topology. Alternatively, they can be engineered with diffraction orders disallowed by the crystallographic restriction theorem [128].

Effective properties of quasicrystals can be rigorously derived from elliptically degenerate differential operators depending upon some irrational coefficients [54]. There are oddities in their effective properties in the infinite conducting case [127]. When rational approximants are considered, periodic structures with increasingly large unit cells are generated [121] whose effective properties approximate those of corresponding quasiperiodic structures. In [121], the nearly isotropic effective speed of sound is approached in chiral crystalline mechanical metamaterials (see figure 8, panels (a)–(c)).

In the Bragg regime, some phenomena akin to stop bands occur [55, 122, 129]. Applications are for instance, transmission problems between periodic half-spaces with incommensurate periods along the interface. Such systems are analogous to edge waves in quasiperiodic arrays of scatterers studied in [124, 126]. Figure 8 panels (d) and (e) taken from [123] show that when the slope of the hyperplane is spatially graded, some fractal rainbow effect revealing features of the Cantor spectrum of quasicrystals can be observed.

The spectrum of quasiperiodic crystals can be explored in the phase space in conjunction with the Hofstadter butterfly, which reveals the existence of topological edge states like those in periodic structures [124, 125]. The quantum Hall effect can then be generalized to quasiperiodic structures such as Moiré lattices [130]. Localization is related to topology

[126, 131], and the edge states in quasiperiodic structures possess unique properties, making them suitable for wave-control devices. In figure 9, two examples of edge states are shown, in mechanics and optics, in both one and two dimensions, proving the versatility of these structures.

Current and future challenges and opportunities

The transposition of the well-known features of wave phenomena in periodic media (effective properties, stop bands, topological effects, etc) to quasiperiodic media is challenging, as we have discussed. Exploration of irrational acoustic, EM, and mechanical metamaterials requires some mathematical background (with some knowledge of functional analysis, spectral theory, number theory), computational skills (numerical exploration of their properties guides the theoretical conjectures before they can eventually be proven), and physical interpretation (one should be careful to not jump at a conclusion based on what is known for periodic structures).

Several challenges are still open in the field of quasiperiodic structures; understanding the propagation of waves in quasicrystals might bridge the gap between ordered media (studied with the Floquet–Bloch theory) and disordered media (commonly analysed in Anderson's localization framework). An alternative classification for long-range ordered systems is hyperuniformity [132]. Hyperuniform materials include perfect crystals, perfect quasicrystals, and some amorphous states of matter. In this sense, quasicrystal properties might also be formulated under the hyperuniform framework.

Moreover, not only propagation is relevant, but as we have stated before, localization of waves is essential for novel modern wave devices. Certain quasicrystal structures present Cantor spectra, which allows us to theoretically define band stops in every frequency range, even at extremely low frequencies [121, 126], and this makes possible to create structures exhibiting forbidden bands, i.e. perfect reflection at extremely large wavelengths, in complete contradiction with periodic structures [133]. This property makes them appealing for the realization of deep-subwavelength wave devices, but it remains a challenge to implement them effectively. Not only the lower part of the spectrum presents its challenges, but also at higher frequencies the spectrum becomes complex and difficult to decipher.

Advances in science and technology to meet challenges

From the theoretical point of view, although massive efforts were devoted to understanding quasicrystals and their properties during the '90s, ongoing research lines still produced compelling advances in the last years. In [55], Floquet–Bloch theory is generalized to quasiperiodic structures by treating two wave propagation problems first in the periodic high dimensional space and then projecting the solutions into the real space by adequately solving the elliptically degenerate differential operators. In [56], a theorem is established for the

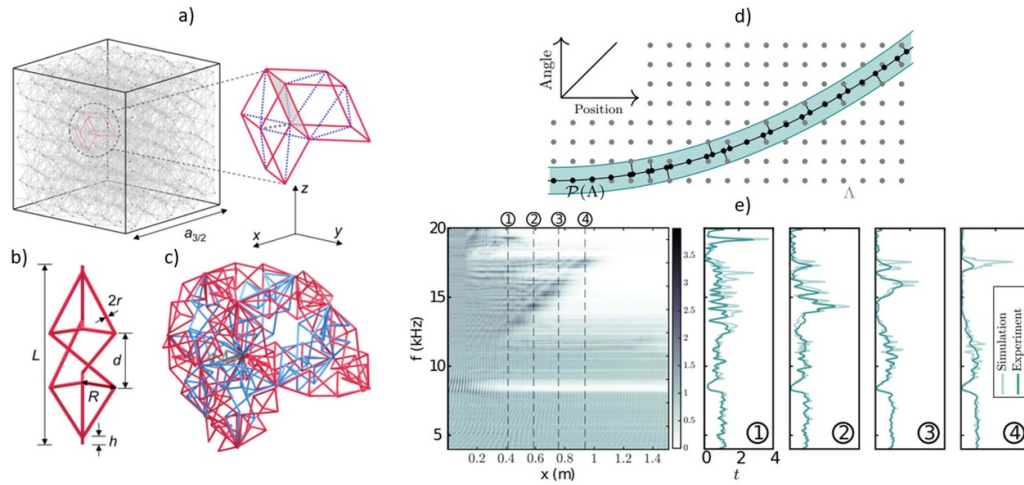


Figure 8. Two examples of quasicrystalline structures generated with the cut-and-project method. The first example, reproduced from [121], is generated from a high dimensional space of order 6 to a 3D icosahedral quasicrystalline metamaterial (a). After replacing each rod with either an achiral homogeneous cylindrical rod or with a homogeneous uniaxial chiral rod, an achiral or a chiral 3D structure is approached. (b) The homogeneous uniaxial chiral rod is approximated by the metarod depicted in (b), resulting in the structure shown in (c). (a)–(c) Reprinted (figure) with permission from [121], Copyright (2020) by the American Physical Society. The second example, reproduced from [123], shows a quasicrystalline structure obtained by grading the slope of the cut-and-project technique from dimension 2 into dimension 1 (d). (e) Demonstration of the fractal rainbow effect by smoothly grading the slope of the hyperplane. The frequency spectra are shown as a function of position. The numbered lines show the measurement positions and simulation shown in the numbered plots. (d), (e) Reproduced from [123]. CC BY 4.0.

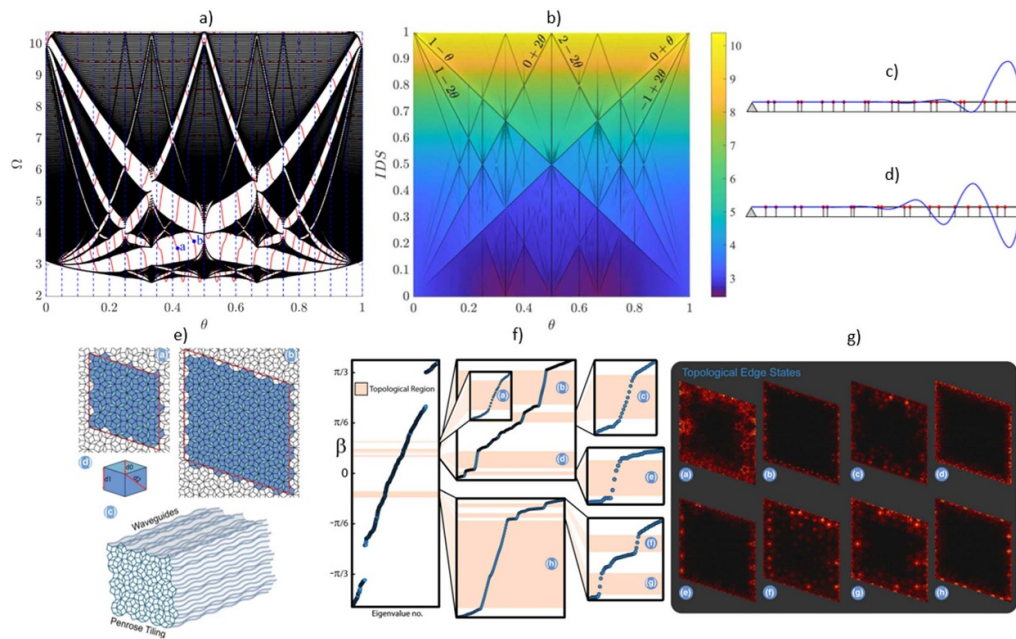


Figure 9. Two examples of topological edge states in quasicrystals. The first one, reproduced from [126], is a one-dimensional finite mechanical beam with mass-spring resonators attached at some positions along the beam. (a) The spectrum of a finite system with $S_f = 20$ scatterers attached to it (red) superimposed by the bulk spectrum (black) as a function of θ (the modulation parameter). Red curves spanning the bulk gaps are topological edge modes localized at the right boundary of the finite beam. (b) The integrated density of states (IDS) with θ exhibiting sharp jumps at the bandgaps. The colormap indicates frequency Ω . (c), (d) mode shapes corresponding to the eigenfrequencies marked by blue dots with labels (a) and (b), respectively, in panel (a). (a)–(d) Reproduced from [126]. © IOP Publishing Ltd. CC BY 3.0. The second example, reproduced from [131], is photonic fibre modulated as a Penrose quasicrystal. (e) Periodic Penrose approximants of Penrose quasicrystals and a sketch of the photonic Floquet quasicrystal. (f) Topological features at different levels of the energy spectrum. (g) Topological edge states associated with the fractal spectrum of a finite topological quasicrystal. (e)–(g) Reproduced from [131]. CC BY 3.0.

apparition of super band gaps in periodic approximants of generalized Fibonacci sequence, which might be especially useful for practically implementing quasicrystals in photonic and phononic systems.

The advances in AI can help design quasiperiodic structures with complex features, as in figure 8. It is difficult to visualize periodic structures in dimension higher than 3 for a human being, but computers can explore periodic structures in high dimensions provided they have been trained in cases that can be visualized by human beings. Furthermore, optimization algorithms and neural networks might help solve inverse problems when design quasiperiodic structures for a given purpose. Generally, these problems are ill-posed and require an iterative process that is computationally expensive and time consuming.

Advances in nanomanufacturing allow for the creation of nanostructures that can perform the most sophisticated and efficient tasks on the smallest scale. The exhaustive control in the manufacturing process has reduced tolerances and errors, which paves the way for implementing structures that are not so robust against disorder. This technology has opened the field of nanomaterials and beyond, and the reachable wavelengths and frequencies have led to the control of wave packets at their lowest level. Noticing that quasiperiodic arrangements of layered media allow for a larger

photonic state density than that of their periodic counterparts makes possible polarization insensitive broadband optical absorbers [134].

Concluding remarks

Irrational metamaterials is a fast-developing research area. Quasicrystals have proved to be suitable for a wide range of wave applications, from tailoring effective properties of the material to trapping energy efficiently in space. Advancements in computational techniques and nanomanufacturing allow us to envisage solving inverse problems to design 3D quasicrystal metamaterials with optimized properties and at useful wavelengths for desired applications. Some questions remain unsolved for the lower part of the spectrum, which is the one that gives access to their effective properties, such as the appearance of stop bands at extremely low frequencies [121, 126]. Furthermore, moving to higher frequencies, the spectrum becomes so complex that its mathematical properties are still elusive, even in the one-dimensional case [55, 124, 132]. There is much that remains to be done with one-dimensional quasicrystals in terms of localization and topological states, but it seems timely to start exploring their two-dimensional and three-dimensional counterparts.

12. Polaritonics and metamaterials

Andrea Alù

City University of New York, New York, NY, United States of America

Status

The field of metamaterials has been evolving over time, encompassing a wide range of wave phenomena, frequencies and functionalities. An important role in this progress has been played by the material platforms used to build these engineered materials. *Plasmonics* [135] has been at the basis of the first generation of metamaterials, due to the strong field confinement and enhanced light-matter interactions emerging at the interface between metals and dielectrics, driven by the coupling of light with electrons that supports *plasmon polaritons*. However, the challenges posed by these materials, mostly in the context of losses and poor compatibility with integrated and silicon-based platforms, has driven a quest to explore low-loss plasmonic alternatives and heterostructures [136].

In the last few years an interest in a broader range of material phenomena supporting strong light-matter interactions has emerged, in the context of *polaritonics* [137, 138]. Polaritons are quasi-particles, half-light half-matter, emerging when light is so tightly coupled with the material response that the optical and material response cannot be separated. While plasmons are arguably the most widely explored form of polaritons, new opportunities have emerged in the context of alternative polariton species, based on light coupled to phonons, excitons, magnons, or other material excitations. In turn, these responses have been opening a wide range of opportunities for metamaterials, with new functionalities and new frequency regimes. Of particular interest is the recent surge of interest around phonon polaritons, which enable low-loss and highly directional excitations in the mid-infrared frequency range [139]. This platform can naturally support hyperbolic bulk waves and surface waves, with broadband highly-confined and low-loss light-phonon transport. Coupling phononic materials with meta-structures, as in figure 10(a) for the case of boron nitride, enables to transfer exotic optical features to polaritons [140], which may be directly observed in the far-field response. Other materials, such as molybdenum trioxide (figure 10(b)) or calcite (figure 10(c)), naturally offer even more exotic polaritonic modes at their interfaces with air, which may be further controlled using metamaterial principles by rotations and twists [141, 142]. Other exciting opportunities for metamaterials have emerged leveraging exciton polaritons, supported by 2D materials and transition-metal dichalcogenides [143], or magnon polaritons in chromium sulfide bromide [144].

Current and future challenges and opportunities

These recently emerged classes of polaritonic materials offer unique opportunities for wave control when combined with metamaterial concepts. Yet, they also pose unique challenges in the context of modelling and simulations. First, these

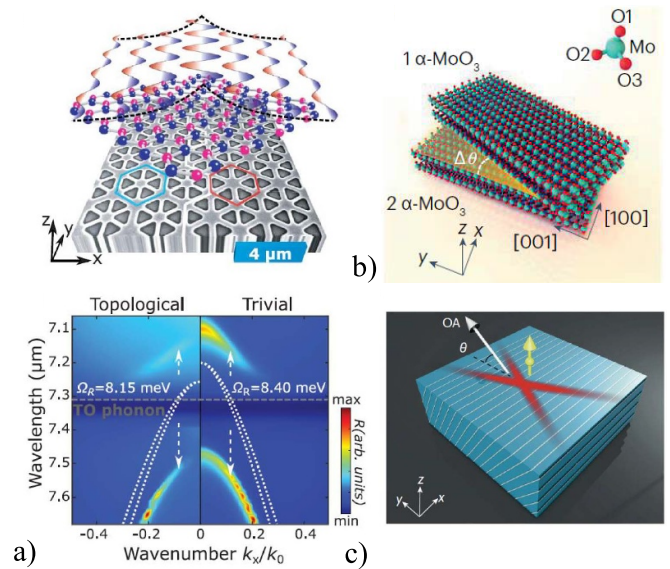


Figure 10. Polaritonic metamaterials: (a) A topological metasurface strongly coupled to a thin layer of boron nitride enables exotic topological phase transfer from light to phonon polaritons [140]. From [140]. Reprinted with permission from AAAS; (b) twisted bilayers of molybdenum trioxide can drastically modify the nature of the supported surface modes as a function of the twist angle [141]. Reproduced from [141], with permission from Springer Nature; (c) the angle between the calcite crystal axis and its interface with air drastically controls the confinement and directionality of surface polariton modes [142]. Reproduced from [142], with permission from Springer Nature.

exotic wave-matter interactions are inherently dispersive, both in time—leading to strong resonances and large variations with frequency—and in space—leading to nonlocality phenomena that impact light localization and transport. Special efforts must be made to properly capture these features in analytical and numerical models, and suitably characterize the underlying material constituents. In this framework, density functional theory and other *ab-initio* techniques to model the underlying materials and polaritonic phenomena become necessary to properly model the EM problem. In this context, it is also crucial to make sure that causality relations are considered in modelling the frequency and momentum dispersion of the underlying materials and polaritonic metamaterials.

Dispersion is also associated with material losses, which poses a challenge not only in terms of the functionality of the resulting devices, but also in the modelling aspects. Carefully capturing the associated retardation phenomena and dissipation is crucial to model polaritonic metamaterials. Similarly, active materials, nonlinearities and lasing phenomena naturally emerge in polaritonic systems, leading to even more complex modelling requirements that need to carefully analyse stability and causality.

Polaritons are commonly associated with extreme light confinement, with wavelengths shortened by up to two orders of magnitude compared to free space. This leads to challenging multi-scale modelling problems, in which largely different spatial scales need to be considered in the modelling and simulations. Similarly, the recent interest in

exploring time modulation and Floquet phenomena in polaritonic metamaterials implies analogous challenges in the temporal domain, in which the scale of modulation is largely different from the relevant polariton dynamics. A related challenge is associated with the inherent multi-physics nature of polaritons: the fact that light is so tightly coupled with material responses implies that optical modelling alone is not sufficient to capture the phenomena at stake. Multi-physics modelling, both analytical and numerical, and co-simulations emerge as important in this context, with finite-element and semi-analytical methods playing a prominent role in this context.

Clearly, the described challenges are closely tied to exciting opportunities that emerge in polaritonic metamaterials. These new needs for modelling and simulations are tightly linked to the new physics emerging in these structures and the strong opportunities associated with them, both from the fundamental standpoint and in the context of emerging technologies.

Advances in methods and techniques to meet challenges

The challenges and opportunities mentioned in the previous section open interesting directions for the future of modelling techniques aimed at the analysis and design of polaritonic metamaterials. Analytical methods offer a powerful way to capture the fundamental aspects of the problem. Coupled-mode theories, properly augmented to consider the multi-physics aspects at play, offer an elegant platform to describe in compact ways the polaritonic response. Efforts to expand the multi-physics nature of these theories is important, as well as to capture in efficient ways the nonlocalities, both in space and time, stemming from polaritonic responses.

Sophisticated numerical tools that involve multi-scale meshing, both in space and time are necessary tools to efficiently study polaritonic metamaterials. In this context, new numerical approaches and new expansion basis functions need to be devised, keeping in mind also the trade-offs between general purpose models and ad-hoc complexity. For time-varying structures, finite-difference time-domain techniques appear to be the only general modelling solution, but given the widely different time scales involved it also implies excruciatingly

long and intense simulations. In the case of periodic modulations, augmented frequency-domain techniques or mixed time-domain/frequency-domain approaches can offer large speed-ups. These approaches can be also extended to spatial modulations to study space-time gratings made of polaritonic materials.

Opportunities to link these efforts to other fields of theoretical physics also emerge. For instance, the field of Floquet matter has been making progress in modelling driven systems composed of resonant particles, very relevant to polaritonic metamaterials. Also the excitement around chiral phonons has relevance in the context of phonon-polariton metamaterials, in which chiroptical responses can be transferred to phonon polaritons. More generally, the field of polaritonic metamaterials inherently leads to a highly inter-disciplinary effort, bringing together different communities that can feed and guide the modelling efforts discussed in this section. Close work with experimentalists and with *ab-initio* theorists is likely to lead to new breakthroughs on the modelling side, paving the way to exciting prospects to capture the polaritonic metamaterial response, and apply them in larger systems for new technologies, from quantum to classical waves.

Concluding remarks

The field of polaritonic metamaterials has been blossoming in recent years, pushing forward a new paradigm of material responses for light, matter and wave control. The opportunities that stem from coupling structured light in metamaterials with phonons, excitons, magnons and electronic responses in materials open exciting directions for science and technology. Yet, they need to be properly supported by new modelling tools—analytical and numerical—that allow to capture the underlying multi-physics phenomena, and enable analysis, design and optimization of the resulting devices. In turn, these efforts are likely to expand and enrich the theoretical physics and engineering communities, with new mathematical tools and numerical techniques uniquely suited to address these challenging problems. A bright future for polaritonic metamaterials is ahead, both from the modelling and from the experimental perspective.

13. Active chirality in mechanical metamaterials using gyroscopes

Katie H Madine and Daniel J Colquitt

Department of Applied Mathematics, University of Liverpool

Status

Since the inception of metamaterials as a field of study, there have been several challenges in the physical realisation of their designs. For example, metamaterials must be manufactured on length scales comparable to the wavelengths of the fields with which they should interact, which can be a significant issue for optical metamaterials [145]. However, recent developments in manufacturing techniques have allowed for the implementation of many designs that were previously impossible [146]. In contrast to photonic metamaterials, the science of elastic metamaterials has attracted less attention, but represents a rapidly expanding area of study due to the growing interest in the applications to solid mechanics and mechanical systems [147]. For example, elastic lattices of beams—combined with various supports, such as pillars and Winkler foundations—have been used to model real-world systems, such as bridges, with particular emphasis on improving their resilience against earthquakes [148]. Despite the requisite length scales being typically larger for mechanical metamaterials compared with optical metamaterials, the physical realisation of many elastic metamaterials now faces similar challenges to those that have long affected the manufacturing of photonic metamaterials.

Although there is significant scope for the translation of ideas between elasticity and electromagnetism, it must be emphasised that the underlying frameworks are very different for the two classes of metamaterials—indeed, even the physical laws governing individual classes of mechanical metamaterials (elastic, flexural, gyroscopic, etc) have significant differences. Achieving negative refraction was pivotal to the development of EM metamaterials, and while the mechanism is very different, concepts have been proposed for inducing the negative refraction of elastic waves on lattices of beams at rotational inertia interfaces [149]. However, currently, there is no formal analogue of a negative index of refraction in photonic media for elastic media. Furthermore, elastic ‘invisibility cloaks’ have been proposed, with experimental results showing significant success at cloaking voids in plates [147].

Another parallel between elastic and photonic metamaterials arises in relation to the growing interest in chiral lattices. Photonic metamaterials are usually associated with passive chirality, that is, molecules that are chiral because of their geometry [150]. However, recently methods have been devised to induce chirality on elastic arrays through the incorporation of gyroscopic resonators. Gyroscopes are described as ‘actively’ chiral, which differs from passive (geometric) chirality in that two identical gyroscopes become chiral only when they are spinning in different directions, in which case they are mirror images, but cannot be super-imposed [151], as demonstrated in figure 11.

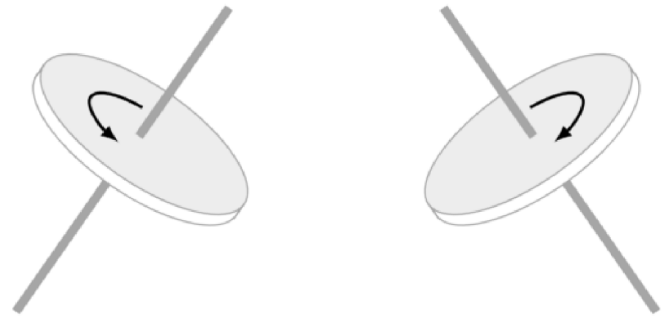


Figure 11. Two geometrically identical tilted gyroscopes that are spinning in opposite directions, demonstrating their active chirality.

Current and future challenges and opportunities

Several studies have demonstrated remarkable effects with systems of gyroscopes and flexural elements. In the papers [152, 153] strongly localised uni-directional waves were produced at chiral interfaces by setting gyroscopes on either side of the interface spinning in different directions. This was achieved in [152] for flexural plates with arrays of upright beams topped by gyroscopes; whereas [153] used a 2D triangular lattice of beams that was supported by a network of tilted gyroscopes at the beam junctions. In [152, 153] the localisation was so strong that waves were successfully bent around corners with minimal backscattering. The acronym Dynamic Amplification by Spinners in Elastic Reticulated systems was coined in [153] to describe the phenomena of interfacial waves travelling in closed loops, amplifying the original signal.

While the results of [152, 153] are indeed impressive, such structures requiring hundreds (if not thousands) of gyroscopes that are all perfectly synchronised would be exceedingly difficult to build and control. Although there are many physical systems that have inherent gyroscopic motion—wind turbines, boat propellers, and motorcycles to name a few—gyroscopes are often considered difficult to model analytically. Even simulating gyroscopes numerically is a computationally challenging multi-body dynamics problem. Moreover, there are several accepted conventions which are often employed for analytically modelling flexural systems that would need to be considered when building physical models. For example, it is commonplace to neglect the effects of gravity on systems, and the coupling of flexural and torsional rotations between elastic elements. Although there are some works that have studied these effects in elastic systems [149, 154] wherein it was demonstrated that the effects of gravity and the coupling of rotations can be significant.

Advances in methods and techniques to meet challenges

In the papers [151, 155] ‘chiral boundary conditions’ were developed, which provide a set of forces and moments that account for the presence of a gyroscope without needing to

solve the full equations of motion for the spinner. While deriving analytical solutions for any system would rarely be described as simple, using these boundary conditions provides significant simplifications when considering the equations of motion of chiral systems. Additionally, the chiral boundary conditions can be employed in finite element simulations, eliminating the need to model the full gyroscopic system, which in turn greatly reduces the computation time. The chiral boundary conditions contain a quantity called the *gyricity* which is defined as the sum of the rate of spin and rate of precession of the spinner (although, it is noted that the term ‘gyricity’ has had different definitions in other works, such as in [156]). With this, the ability to change the direction of spin of the gyroscope resides solely in changing the sign of the gyricity constant. The papers [152, 154] both employed these chiral boundary conditions to produce large scale models of chiral resonators.

There has also been progress in forming parallels between gyroscopic spinners and existing experiments. For example, the work reported in [154] has not only included the effects of gravity in studying gyropendulums (hanging rods with gyroscopes at the tips) but also showed the same ray tracing as Foucault’s pendulum—whereby a swinging pendulum precesses due to the rotation of the earth. Furthermore, there have been studies that have drawn parallels between systems of beams and gyroscopes and gyrobeams—that is, beams with continuously distributed rotational inertia. In [155], a chain of beams with gyrohinges at the junctions was shown to be a

good discrete approximation of a gyrobeam. Gyrobeams have been proposed in the designs of earthquake protection systems [157] and even for use in the propulsion of spacecraft [156]. Similar to [155], in [154] a chain of gyropendulums was shown to be a discrete approximation of a chiral rope.

Concluding remarks

The field of metamaterials is still considered a young area of research, with technology often significantly lagging the theoretical developments. The first concept of negative refractive indices [1] put forward by Veselago in the 1960’s was in danger of fading into obscurity. It took another 30 years for the significance of the results to be recognised and another decade for optical metamaterials to be implemented [145]. In the same way that recent advances in manufacturing have made the realisation of photonic metamaterials for optical wavelengths possible, advances in manufacturing technology could well make many of the designs discussed in this review achievable in the near future.

Studies of periodic arrays of gyroscopic resonators could provide insights into the behaviour of large-scale systems of spinning rotors, such as wind farms formed of arrays of spinning turbines. With the hopes that, this research could determine method for reducing the vibrations of offshore wind farms, which are known to affect marine ecosystems [158].

14. The challenges of underwater acoustics

Ping Sheng

Emeritus, HKUST, Hong Kong, and Associate of Clare Hall, Cambridge University

Status

In the broad field of acoustics, ultrasound undoubtedly occupies the top position in terms of maturity, broad applications, and R&D outputs. Air-borne sound has received a rejuvenation through the advent of acoustic metamaterials. Underwater acoustics, covering the frequency range of few hundred to few thousand Hertz, is however up to now firmly in the third position both in terms of published research outputs as well as commercialized applications. This is due to the longer wavelength involved, as well as the much smaller contrast in its impedance with solids, as compared to that of air. These differences can translate into larger required sizes for wave manipulating devices, thereby hindering their applications and relevant experiments. It is a valid question on whether acoustic metamaterials can alter this situation for underwater acoustics. Some works have already been done along this direction, but still far short of the range and depth attained in the airborne acoustics (see, e.g. the review article [159]).

Current and future challenges and opportunities

In terms of underwater acoustic wave attenuation, one can have either absorption or blocking (reflection). Whereas the former is limited by the causality constraint in terms of the sample thickness necessary to attain the target absorption performance, the latter is governed by the mass density law. These constraints are especially stringent for low frequency applications.

We propose to re-examine the use frequency gap for low frequency acoustic blocking. The well-known phononic crystal bandgaps would imply very large lattice constants for low frequency bandgaps, as the phononic crystals' bandgaps are based on the Bragg scattering mechanism. So, in this context a frequency gap that starts at just above zero frequency and has an upper gap frequency ω_0 , denoted here as the zero frequency gap, would be impractical for phononic crystals owing to the periodicity required. The question here is: Are there other avenue (s) to realize a zero-frequency gap? In this regard an earlier publication [160] has pointed out that for a solid plate with periodically perforated holes, a zero-frequency gap can be realized provided the zero-displacement condition is applied to the edges of the holes. The zero-displacement condition implies that practical realization requires the whole plate to be fixed to the ground, or some infinite mass; i.e. without the rigid overall translation degrees of freedom. Can the zero-frequency gap be realized with only the centre of mass be fixed, so that there is no rigid translational motion of the whole sample, i.e. immobilize the $k = 0$ mode in the frequency ω versus wave vector k dispersion relation for a solid plate? Below we will use the term 'zero frequency gap' to denote

a frequency gap that excludes the rigid translational motion of the whole sample.

Advances in methods and techniques to meet challenges

Offshore structures usually require underwater support that extends to the seabed. Such structures can often generate very significant underwater low frequency noise. Shielding such noise would be beneficial to marine creatures and the relevant ecology. Here we propose the use of geometric design that is inherent to the central theme of acoustic metamaterials, to enhance the magnitude of the bending modulus for a structured solid plate, in order to realize something that is second best to the zero-frequency gap, i.e. a zero-frequency gap beyond a minimum wavevector k . In a sense this is exactly the finite size effect: The fact that a finite-sized plate (which has a natural minimum cutoff k corresponding roughly to the size of the plate $1/k$) would have a gap in its frequency of excitations. If the centre of mass of the plate is fixed, e.g. by fixing its edges, then the minimum excitation frequency ω_0 would be related to its size and to its bending modulus. However, what we hope to do is not to have a small square sample which would be of little practical use, but something that is meter (s) off in size so that it can exhibit a significant difference with a uniform plate of similar size, thickness, and mass density.

The consideration of solid plate does not mean to exclude other potentially possible avenues for attaining the same goal of shielding low frequency noise, e.g. absorption by bubbles. However, in this article we focus only on solid plates owing to their ease of application if realized, and lack of any pressure effects that can be a serious consideration in underwater acoustics.

The fact that a zero-frequency gap is directly linked to the bending modulus can be easily seen from the eigenfunctions expansion of the Green's function (1), here defined as the local displacement ξ of the solid plate in response to the pressure modulation p :

$$G(x, x' = x, \omega) = \frac{\xi}{p} = \sum_{n=1}^N \frac{\phi_n^*(x) \phi_n(x' = x)}{m_n (\omega_n^2 - \omega^2 - i\beta\omega)} = \sum_{n=1}^N \frac{|\phi_n(x)|^2}{m_n (\omega_n^2 - \omega^2 - i\beta\omega)}, \quad (1)$$

where x is the lateral coordinate of the plate, ϕ_n is the n th eigenfunction in unit of displacement, $\omega_n = 2\pi f_n$ is the associated eigenfrequency of the solid, $\omega = 2\pi f$ is the frequency of the acoustic wave, β is the solid's dissipation coefficient, and m_n is the averaged mass of the sample weighted locally by the eigenfunction magnitude. Hence, the displacement at x can be expressed as equation (2) below:

$$\xi(x) = p \sum_{n=1}^N \frac{|\phi_n(x)|^2}{m_n (\omega_n^2 - \omega^2 - i\beta\omega)}. \quad (2)$$

For fixed p , the magnitude of displacement ξ is inversely related to the response modulus. Smaller displacement implies

a larger modulus. In the case of a zero-frequency gap, with no excitations below the frequency $\omega_0 \gg \omega$, then in the low-frequency range above the zero frequency, we have an approximate expression (3):

$$\xi(x) \cong \frac{|\phi_0(x)|^2}{m_0 \omega_0^2} p. \quad (3)$$

That displacement can be very small, implying a very large effective modulus.

The above discussion can also be made plausible through the simple qualitative description. Consider the dispersion of the two plate modes, S_0 and A_0 , the symmetric and antisymmetric modes, in the limit where the relevant wavelength is much larger than the plate thickness. Whereas the dispersion relation of S_0 is linear, that of A_0 is quadratic. They are both governed by the biharmonic equation of motion with the bending modulus as the only physical parameter. If the bending modulus is large, then both the slope of the linear dispersion and the curvature of the quadratic dispersion will increase accordingly. If we have a fixed ω_0 on the vertical frequency axis, then we can imagine that both dispersion relations will intersect the horizontal line, located at the height of ω_0 , in two values of k . The larger value of the two can be denoted the minimum wavevector beyond which there is a zero-frequency gap. Larger the bending modulus, smaller would be the minimum wavevector. That in turn implies the realization of the

zero-frequency bandgap can be realized in a large, though finite, sample.

There are existing structures that are light and have a high bending modulus, e.g. the honeycomb lattice made of aluminium sheets is one such example. To be used for acoustic attenuation, two skin layers need to be attached to the honeycomb lattice to form a sandwich structure. These have already been commercialized for acoustic applications [161]. However, it is not always easy to attach the skin layers to the honeycomb lattice, and the bending modulus does depend on the height of the honeycomb structure. Larger the height, larger the bending modulus. However, that would mean a thick structure if the target bending modulus is large. The acoustic result as reported (in the website) shows that it does not display the ideal zero frequency gap behaviour for acoustic attenuation. Hence the search for such a metamaterial structure remains an open topic.

Concluding remarks

There can be multiple applications to underwater acoustics for a metamaterial with a zero-frequency gap, provided a suitable structure can be found. A material/structure that can display static rigidity significantly beyond that of water can effectively attenuate the underwater acoustic wave transmission, beyond the limitation imposed by the mass density law at low frequencies. Work in this direction is presently underway.

15. Metamaterials for ocean wave control, manipulation and harvesting

Luke G Bennetts

The University of Melbourne

Status

Strong winds over the open ocean generate surface gravity water waves, in the form of vertical fluctuations at the air–water interface that travel along the ocean surface. The wave fields are random and dispersive, consisting of a spectrum of frequencies and directions, with characteristic periods on the order of seconds to tens of seconds and amplitudes order metres. They carry huge stores of energy over great distances across the ocean—with power comparable to the capacity of a power plant—before breaking at the coastline.

Ocean waves are a potentially fatal hazard for offshore and coastal structures and dictate their design. This is an area of topical interest as humans increasingly encroach into the ocean, to extract natural resources (e.g. seabed mining), to capture renewable energy (e.g. using offshore wind farms), and to utilise the space offered on the ocean surface (e.g. using very large floating structures). Moreover, ocean waves play an important role in coastal morphology, which is also a subject of topical interest as climate change enhances coastal erosion.

Metamaterial-inspired ideas to control ocean waves are gaining traction in three broad application areas. Methods are being explored to *cloak objects* from ocean waves, based on the transformation media and metamaterials approach developed in optics, and in the context of reducing or eliminating hydrodynamic loads on the cloaked objects. There have only been a few experimental realisations of water-wave cloaking theories, using an array of vertical cylinders [162] and corrugations in the bathymetry [163]. Further, a water-wave cloak in a channel has been realised using bathymetric variations, with potential applications for controlling wave impacts in ports and wharfs [164]. There is also a so-called direct method for water-wave cloaking, in which the geometry (i.e. the bathymetry) or a structure surrounding the cloaked object is optimised to minimise wave scattering and, hence, the drift force on the cloaked object [165].

Metamaterial concepts have revitalised concepts for *harvesting ocean wave energy* for human use. There has been major progress over recent decades to the point of small-scale deployments. Most of the devices used to capture ocean wave energy (so-called wave energy converters; WECs) are designed to resonate at a chosen frequency, but, in general, they are narrow-banded and display poor performance in real (random) seastates, as the prevailing wave field at the WEC array may not carry significant energy at the resonant frequency. Metamaterial-esque structures have been proposed to focus wave energy into a target region, where it can be efficiently harvested by a WEC or WECs (an idea that dates back to the late 1970s). Designs have also been proposed

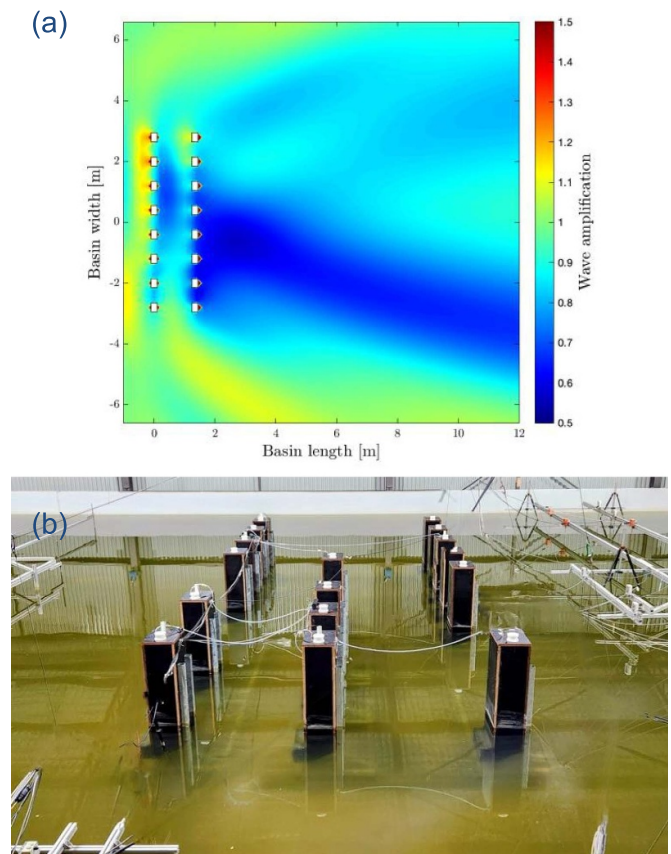


Figure 12. Potential combined wave energy harvesting and coastal protection by refraction created by a graded array of oscillating water column-type WECs. (a) Numerical prediction of wave amplification by a 8×2 array of WECs (graded in increasing natural period from 1.4 s on top row to 1.7 s on bottom row), for a regular incident wave of period 1.6 s that propagates from left to right. (b) Experimental set-up of a similar array, with an optimised configuration proposed by [166].

in which the WECs themselves are the unit elements of the array, analogous to locally resonant metamaterials in optics and acoustics. These WEC-arrays aim to focus energy within the array, such that the WECs forming the array can absorb the energy. Arrays of offshore structures have an alternative application for *coastal protection* [166]. In contrast to standard breakwaters that block all water flow, offshore structures have been designed with band-structures that reflect [167–169] or redirect [170] wave energy over the damaging frequency bands (e.g. causing coastal erosion), whilst allowing transmission of bands associated to beneficial coastal processes (see figure 12).

There are other examples of metamaterial-type structures for controlling water waves that do not fit into the three main application areas of cloaking, energy harvesting or coastal protection. These include negative refraction, reflectionless bends in channels, interface states, hydroelastic scattering cancellation, and spoof surface water wave polaritons along structured breakwaters.

Current and future challenges and opportunities

Cloaking offshore structures: Transformation media and metamaterial approaches to designing water wave cloaks have only been applied for simplified models, such as shallow water, for which the governing equations are equivalent to those of acoustics and optics. Extending the approach to the full linear water wave equations is an open challenge. The direct method allows greater freedom, such as finite water depths, and has been applied to finite depth water with cloaks formed from the bathymetry [165, 171] or an annular thin floating elastic plate [172]. However, the direct method has only been used to cloak at isolated frequencies, leaving the design of broadband cloaks an open challenge. Moreover, the direct method includes wave scattering by the cloaked objects, and, hence, the relationships to transformation media and metamaterials are unclear.

Wave energy converters: WEC-arrays require broadband absorption from an economical design to become a competitive renewable energy source. Over the past five years, there has been a move towards graded structures [173], inspired by rainbow trapping in optics and its translation into seismology and acoustics. The structures are broadband, with water wave energy amplified at locations chosen according to frequency, using standard vertical cylinders [174, 175], resonant C-shaped cylinders [176] and submerged cylinders [177], and where the grading is in terms of the cylinder spacing or the cylinder dimensions. Theories have been developed in 2D (one horizontal dimension plus depth) in which WECs are embedded in a graded structure to form quasi-perfect broadband wave energy capture [178]. The effect has also been achieved for structures formed from the WECs [179]. The design of 3D versions of the graded WEC-array for absorption over a broad range of frequencies and directions is an open challenge.

Coastal protection: To date, proposed designs are based on periodic arrays with wide, low-frequency bandgaps to block selected frequency ranges. The bandgaps are generated by local resonances of C-shaped cylinders [167] and fast wave speeds in stationary disk arrays at the water surface [168, 170]. Questions remain about how to control and optimise the bandgap properties. However, the most pressing challenge is to design practical and (relatively) cost-efficient arrays. The arrays should occupy as little surface area and/or contain as few unit elements as possible. Ideally, the unit elements themselves would be easy to deploy, not requiring bottom mounting or a separate structure to hold the elements in place.

Advances in methods and techniques to meet challenges

The challenges outlined above should be considered in the context of the high cost of installing and maintaining structures and devices in the ocean. This overarching challenge is a defining feature of metamaterials for ocean waves. It will direct modelling and design towards dual use structures to increase their cost effectiveness. WEC-arrays for combined energy harvesting and coastal protection have already been proposed, although, thus far, without fully utilising existing metamaterial concepts. Similarly, WECs have been proposed to stabilise larger offshore structures, such as floating wind turbines. This appears to be an area that will benefit from metamaterial techniques for energy harvesting and cloaking.

It is advantageous for costs and other practical considerations that metamaterials for ocean waves consist of relatively few units. Thus, there is a need to move beyond the band-structure paradigm for metamaterial design and develop analysis techniques for metamaterials of finite dimensions. Further, modelling and design tools must be suitable for lossy metamaterials, as energy absorbing WECs are likely to be their standard units.

Current modelling and design of metamaterials for ocean waves is almost exclusively based on linear water wave theory (or its degenerate shallow water variant), which assumes the water is incompressible, inviscid and irrotational, in addition to small wave amplitudes. Software that can be used to test metamaterial designs when operational considerations in the ocean, such as nonlinear energy transfers, wave breaking, currents, realistic bathymetries and coastlines, and more, will accelerate progress of the research field.

Concluding remarks

There have been significant advances in the modelling and design of water-wave metamaterials in recent years, backed by small-scale experiments. Although key research challenges remain, large scale testing of the metamaterial concepts is the next major frontier in the move towards ocean applications. The tests will help to refine the modelling and design challenges, among other benefits. Closer interactions between the metamaterials research community and those with expertise in ocean structures will drive the next major steps for the field.

16. Designing mechanical metamaterials for biomedical engineering and (soft) robotics

Anastasiia O Krushynska^{1,*}, Zhaohang Zhang¹,
 Mohammad J Mirzaali² and Amir Zadpoor²

¹ Engineering and Technology Institute Groningen (ENTEG), Faculty of Science and Engineering, University of Groningen, 9747 AG Groningen, The Netherlands

² Department of Biomechanical Engineering, Faculty of Mechanical Engineering, Delft University of Technology (TU Delft), Mekelweg 2, 2628 CD Delft, The Netherlands

*E-mail: a.o.krushynska@rug.nl

Status

The research into mechanical metamaterials started with the rational design of micro-architected materials with unusual mechanical properties. These include negative stiffness or negative thermal expansion coefficients, extreme anisotropy, and ultra-high stiffness coupled with ultra-light weight, etc [3]. Over the last decade, the focus has gradually shifted from unusual properties to functionalities that are otherwise challenging or impossible to realize, such as shape morphing, adaptive mechanical behaviour, mechanical logic, and (re-)programmable actuators [180].

Recent advancement in mechanical metamaterials have transcended their exceptional mechanics into the realm of multifunctional and application-oriented designs [181, 182]. Multifunctional metamaterials demonstrate a range of advanced mechanical properties simultaneously, such as shape morphing, targeted elasticity, along with tunable or extreme or double-negative elastic moduli [3]. Alternatively, multifunctionality can be attained by integrating unique mechanical features with unusual dynamic, acoustic, thermal, biomedical, and other properties. Notable examples include high-static combined with zero-dynamic stiffness, shape morphing with adaptable mechanical properties for regulating biomechanical behaviour [183], and metamaterials combining targeted mechanical responses with sound- or energy-absorbing functionalities.

Two rapidly developing application areas for metamaterials are biomedical engineering and (soft) robotics. In biomedical engineering, engineered materials with unique combination of mechanical, biophysical and biological properties are defined as meta-biomaterials [184]. These two examples of mechanical metamaterials require the integration of three pillars: design, fabrication, and functionality (figure 13). For instance, the design space of meta-biomaterials can be tuned to combine auxetic (i.e. negative Poisson's ratio) and non-auxetic behaviour, creating hybrid meta-implants designed to improve implant longevity through enhanced primary and secondary fixations. This is achieved by rationally integrating both types of metamaterial unit cells to enhance bone-implant contact [184]. In the field of robotics, metamaterials significantly expand the range of geometric parameters and deformation degrees of freedom, thereby offering exciting prospect to equip

robots with sensing, actuating, and interactive functionalities that are otherwise inaccessible [185].

As far as manufacturing is concerned, 3D printing techniques have already been widely used in biomedical engineering and robotics. Depending on the application, meta-biomaterials cover a wider range of materials from metals to polymers, while in robotics, the focus is on polymers and particularly smart polymers (e.g. shape memory polymers). The primary concern from the material viewpoint for biomedical applications is their biocompatibility and adaptability within the human body.

Current and future challenges and opportunities

Periodic architectures, which are common in all metamaterials, often limit the functionalities of mechanical metamaterials. Therefore, a key design challenge is to identify non-periodic combinations of architectural elements that cannot only deliver the desired mechanical properties but also can ensure structural integrity and manufacturability (figure 14). Non-periodic architectures are particularly crucial for applications such as shape morphing, deployability, and programmability. These can be obtained by various design strategies, which are currently limited to relatively simple deformations and randomness [3, 180, 183, 184].

Another challenge is achieving multifunctionality, specifically in terms of integrating electrical, magnetic, optical, or thermal properties with mechanical characteristics within a single construct. This integration is not straightforward, or sometimes even impossible, for microarchitectures composed of linear-elastic elements. Additionally, the use of functional materials possessing nonlinear, time-varying, or evolving material properties is still in the early stages of development. This area represents a significant research gap that requires further exploration and has the potential to unlock novel features in mechanical metamaterials, including strain-rate dependent functionalities [181].

The challenges associated with meta-biomaterials are closely linked to patient-specific designs, which, despite their benefits, remain labour-intensive and costly. Additionally, there are often contradictory requirements regarding their mechanical behaviour. This is illustrated by the need to enhance the strength of porous meta-biomaterials, which, intuitively, could be addressed by increasing their density. This approach, however, leads to reduced porosity and lower permeability, which are undesirable for biological functionalities. Other challenges include ensuring compatibility of the developed meta-biomaterials with existing manufacturing techniques and the stringent requirements of clinical applications. This complexity complicates the realization of design objectives, such as bone-mimicking mechanical properties or osteogenic behaviour, in clinically approved materials. It also affects the ability to achieve a desired pores size or customized surface (nano)pattern [184].

In robotics, the large number of design parameters becomes burdensome for many optimization methods, complicating the analysis of non-trivial deformations. The design complexity is

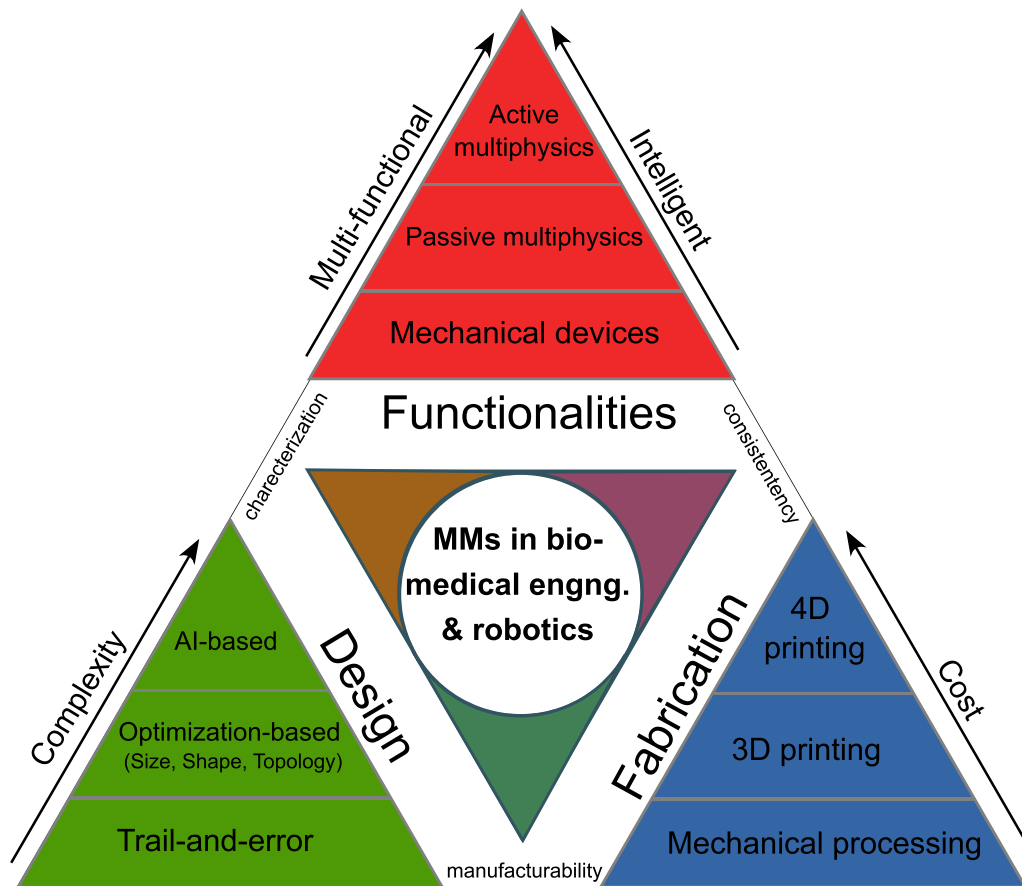


Figure 13. Three pillars for biomedical and robotic mechanical metamaterials.

further increased in compliant metamaterials due to the nonlinear behaviour of their hyperelastic or viscoelastic constituents [180]. Implementation challenges arise from the limitations of cost-efficient additive-manufacturing techniques, which hinder the resolution of a microarchitecture and the minimization of residual stresses and post-processing effects. Robotic applications demand excellent motion controllability, reversibility, stability, and robustness, which are difficult to simultaneously integrate into a design approach that also considers fabrication constraints.

Advances in methods and techniques to meet challenges

Multifunctional metamaterials hold significant potential in thermal control, energy storage, condition monitoring, power absorption, and energy harvesting. Their responsiveness to electric, magnetic, light, or thermal stimuli can be harnessed to enable adaptivity, shape-locking, or tunability activated by external stimuli or environmental conditions. The design of such metamaterials can be advanced by data-driven and AI-based techniques surpassing the limitations of gradient-based, topology, and evolutionary optimization. These tools have demonstrated potential in exploring design possibilities, optimizing performance control, addressing computational complexity, and overcoming technical challenges to guarantee

fabrication feasibility and accurate response prediction [181]. They appear to be the most suitable approaches for utilizing randomness as a design tool, thereby expanding the design space of mechanical metamaterials to achieve even more exotic properties [180]. Accelerated inverse design of metamaterials based on AI shows great promise in tackling challenges from meta-implants to soft robotics [109]. For instance, video diffusion generative models can predict and tune nonlinear deformations and stresses in large-strain regimes, including buckling and contact, and can be extended to estimate deformation paths and full-field internal stress distribution.

Practical implementation of such solutions requires materials with non-trivial constitutive behaviour, including, e.g. flexible, nonlinear, photo- or magneto-sensitive materials. The careful selection of constituent materials is especially crucial for meta-biomaterials, as the right material can add another level of functionality, such as high corrosion or fatigue resistance, improved biocompatibility, or superelasticity. For instance, ceramic-reinforced metals form meta-biomaterials that combine the mechanical properties of metal with the biological functionalities of ceramic [184].

The emergence of multi-material and advanced additive manufacturing is promising for producing high-quality final meta-structures. Significant progress has been made by 3D grey-tone two-photon lithography in manufacturing thermoelastic metamaterials [189]. Inkjet and extrusion-based

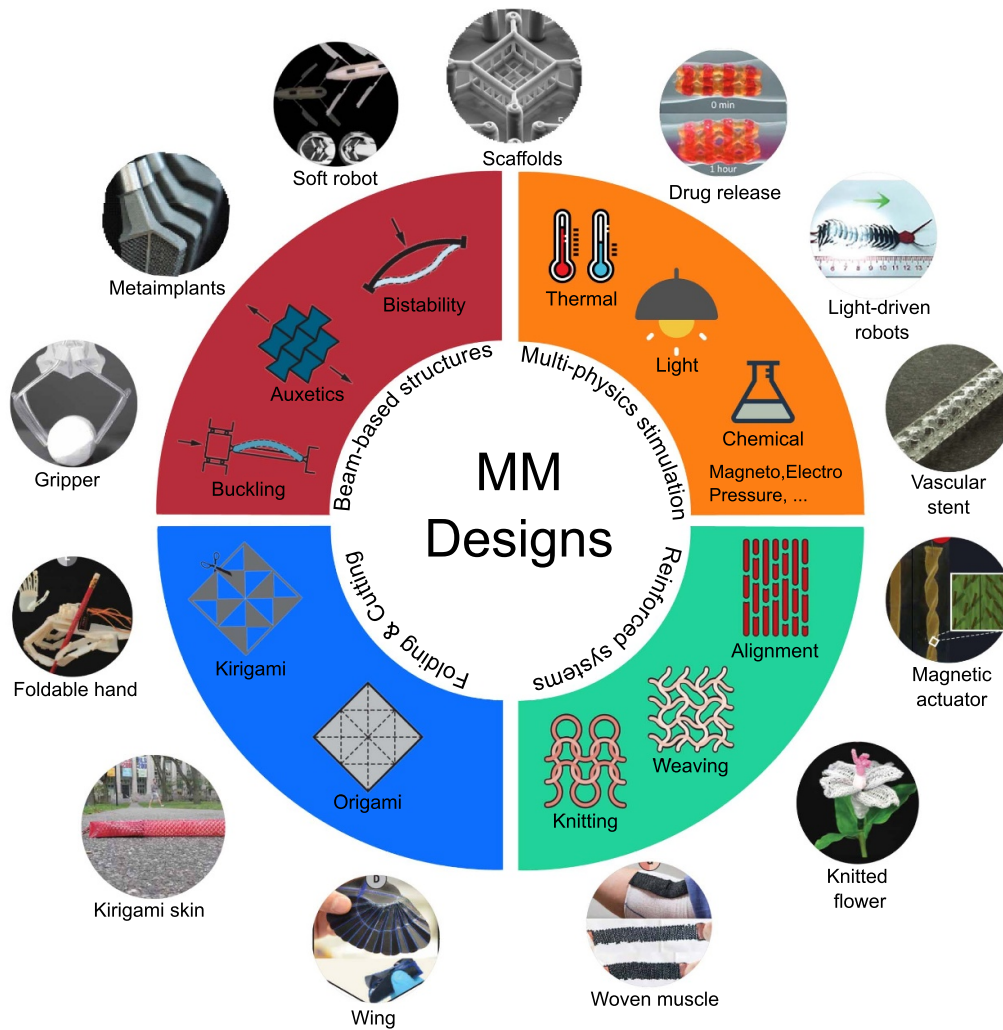


Figure 14. Mechanical metamaterial designs and examples of applications. Reproduced icons: beam-based structures, folding & cutting, reinforced systems, soft robot, gripper, foldable hand, kirigami skin, wing, woven muscle, knitted flower, magnetic actuator: from [185]. Reprinted with permission from AAAS. Multi-physics stimulation, drug release, light-driven robots, vascular stent: Reproduced from Qi *et al* [186]. CC BY 4.0. Metaimplants: Reproduced with permission from Kolken *et al* [187]. CC BY-NC 3.0. Scaffolds: Greiner *et al* [188] John Wiley & Sons. [Copyright © 2012 WILEY-VCH Verlag GmbH & Co. KGaA, Weinheim].

printing have been used to expand the range of materials, e.g. to metals with biodegradable properties [184]. Optimizing ink formulations for printability and adjusting bio-ceramic powder particles can facilitate the creation of multifunctional meta-biomaterials with modulated scaffold biodegradation rates. An emerging area is the application of 4D printing techniques to produce shape-morphing meta-implants [184]. The consistency between an initial design and the fabricated structure can be improved by topology optimization considering fabrication uncertainty or robustness theories at the design stage.

Robotic metamaterials with integrated soft logic modules can potentially simplify control systems while maintaining unrestricted mobility [109]. This approach, combined with scalable manufacturing, could facilitate the development of autonomous robotic systems that can perform complex motions.

Concluding remarks

Mechanical metamaterials, when combined with advanced manufacturing techniques, not only expand the range of realizable mechanical and multi-physical properties and functionalities but also demonstrate strong potential for a paradigm shift in mechanics and several other disciplines. In biomedical engineering, meta-biomaterials may enable treatment of skeletal diseases by encapsulating improved physical and biological performance, stability, longer service life, and shape customization within unique metamaterial (micro)architectures. This opens a new perspective for truly personalized medical treatments, moving beyond the current ‘one-size-fits-all’ approach [184]. In robotics, metamaterials have transformed design approaches and perceptions by proposing adaptable systems that can undergo complex motion and perform different tasks, thanks to

their programmable architecture [184]. Nevertheless, most metamaterials have only been developed up to proof-of-concept stage. This highlights the need for further research into fatigue, long-term local buckling, damage, and future design optimization, which are highly relevant for practical applications [190].

Acknowledgements

1. Modelling in mechanical metamaterials

Marcelo A Dias and Leo de Waal

The authors thank UKRI for support under the EPSRC Open Fellowship scheme (Project No. EP/W019450/1).

2. Analytical methods in metamaterial design

Anastasia Kisil

A V K is supported by a Royal Society Dorothy Hodgkin Research Fellowship and a Dame Kathleen Ollerenshaw Fellowship. The authors would like to thank the Isaac Newton Institute for Mathematical Sciences for support and hospitality during the programme ‘Mathematical theory and applications of multiple wave scattering’ which helped in writing this article. This programme was supported by EPSRC Grant EP/R014604/1.

3. Two-scale homogenisation of high-contrast sub-wavelength resonances

Valery P Smyshlyaev, Shane Cooper and Ilia V Kamotski

V P S would like to thank the Isaac Newton Institute for Mathematical Sciences for support and hospitality during the programme on ‘Mathematical Theory and Applications of Multiple Wave Scattering’, which stimulated various developments on the topic of this article.

4. High-frequency homogenization for periodic media

Marie Touboul^{1, 2} and Richard V Craster³

R V C thanks UKRI and EPSRC for support through grant number EP/Y015673/1.

5. Adjoint based methods for the design of large-scale non-periodic EM materials

James R Capers^{1, 2} and Simon A R Horsley¹

J R C wishes to acknowledge financial support from Defence Science Technology Laboratory (DSTL). S.A.R.H acknowledges financial support from the Royal Society (URF\R\211033).

6. Design optimisation of hierarchical structural metamaterials

Robert W Hewson, Matthew Santer, Ryan Murphy and Dilaksan Thillaithevan

This work was supported by the EPSRC OncoEng programme (Grant No.: EP/W007096/1).

7. Artificial intelligence for EM metamaterial design

Simon J Berry

The author would like to acknowledge the Royal Society Industrial Fellowship and QinetiQ Ltd funding that has enabled this work.

8. Strategies to overcome difficult data

Gareth J Conduit

The author acknowledges funding from the Royal Society and Intellegens Ltd.

9. MetaMaterials genome: towards synergy between mathematical modelling and AI analysis

Stefan Szyniszewski¹, Jacob Earnshaw¹, Nicholas Syrotiuk¹, Oliver Duncan², Lukasz Kaczmarczyk³ and Fabrizio Scarpa⁴

We would like to acknowledge financial support from the Royce Institute for the Mechanical MetaMaterials Database (MCAP068) pilot project, funded under the Materials Challenge Accelerator Programme (MCAP).

10. Electromagnetics of time-modulated metamaterials

John B Pendry

I acknowledge funding from the Gordon and Betty Moore Foundation.

11. Irrational metamaterials and their development

Marc Martí-Sabaté¹, Sebastien Guenneau², Daniel Torrent³, Elena Cherkav⁴ and Niklas Wellander⁵

This document was supported by the DYNAMO Project (101046489), funded by the European Union, but the views and opinions expressed are, however, those of the authors only and do not necessarily reflect those of the European Union or the European Innovation Council. Neither the European Union nor the granting authority can be held responsible for them. This publication is part of Project No. PID2021-124814NB-C22, funded by MCIN/AEI/10.13039/501100011033, ‘FEDER, A way of making Europe.’

12. Polaritonics and metamaterials

Andrea Alù

Our work on polaritonics and metamaterials has been supported by the Department of Defense, the National Science Foundation and the Simons Foundation.

13. Active chirality in mechanical metamaterials using gyroscopes

Katie H Madine and Daniel J Colquitt

K H M and D J C gratefully acknowledge funding from The Leverhulme Trust through Research Project Grant RPG-2022-26. DJC would also like to thank the Isaac Newton Institute for Mathematical Sciences for support and hospitality during the programme on Mathematical theory and applications of multiple wave scattering, which stimulated many discussions on the topic of this article. This programme was supported by EP/R014604/1.

14. The challenges of underwater acoustics

Ping Sheng

Work on the delineated ideas is being explored in collaboration with Nan Gao (UPV, Valencia), Jean-Philippe Groby (LAUM, Le Mans), and Vicente Romero de Garcia (UPV, Valencia). The author wishes to thank Isaac Newton Institute for Mathematical Sciences for support and hospitality during the programme ‘The Theory and Applications of Multiple Wave Scattering’ when the initial idea of this piece took shape (this programme was supported by EPSRC Grant EP/R014604/1).

15. Metamaterials for ocean wave control, manipulation and harvesting

Luke G Bennetts

LGB is supported by the Australian Research Council (FT190100404). The images in figures 12(a) and (b) were provided by Natalia Sergienko and Nadav Cohen, respectively.

16. Designing mechanical metamaterials for biomedical engineering and (soft) robotics

Anastasiia O Krushynska^{1,*}, Zhaohang Zhang¹,
Mohammad J Mirzaali² and Amir Zadpoor²

Z Z appreciates the support from the China Scholarship Council.

Data availability statement

No new data were created or analysed in this study.

ORCID iDs

Bryn Davies  <https://orcid.org/0000-0001-8108-2316>

Stefan Szyniszewski  <https://orcid.org/0000-0002-7862-8506>


Marcelo A Dias  <https://orcid.org/0000-0002-1668-0501>

Leo de Waal  <https://orcid.org/0000-0003-0487-3848>

Valery P Smyshlyaev  <https://orcid.org/0000-0002-5209-2272>

Marie Touboul  <https://orcid.org/0000-0003-4052-0994>

Richard V Craster  <https://orcid.org/0000-0001-9799-9639>

Oliver Duncan  <https://orcid.org/0000-0001-9503-1464>

Fabrizio Scarpa  <https://orcid.org/0000-0002-5470-4834>

Marc Martí-Sabaté  <https://orcid.org/0000-0001-7646-0546>

Andrea Alù  <https://orcid.org/0000-0002-4297-5274>

Katie H Madine  <https://orcid.org/0000-0001-6135-5495>

Daniel J Colquitt  <https://orcid.org/0000-0001-5637-1626>

Luke G Bennetts  <https://orcid.org/0000-0001-9386-7882>

Anastasiia O Krushynska  <https://orcid.org/0000-0003-3259-2592>

Zhaohang Zhang  <https://orcid.org/0000-0003-4215-6604>

References

- [1] Veselago V G 1968 The electrodynamics of substances with simultaneously negative values of ϵ and μ *Sov. Phys.—Usp.* **10** 509–14
- [2] Pendry J B 2000 Negative refraction makes a perfect lens *Phys. Rev. Lett.* **85** 3966–9
- [3] Kadic M, Milton G W, van Hecke M and Wegener M 2019 3D metamaterials *Nat. Rev. Phys.* **1** 198–210
- [4] Papanicolaou G, Bensoussan A and Lions J-L 1978 *Asymptotic Analysis for Periodic Structures* (Elsevier)
- [5] Pavliotis G and Stuart A 2008 *Multiscale Methods: Averaging and Homogenization* (Springer Science & Business Media)
- [6] Pendry J B, Holden A J, Stewart W J and Youngs I 1996 Extremely low frequency plasmons in metallic mesostructures *Phys. Rev. Lett.* **76** 4773
- [7] Xianglong Y *et al* 2018 Mechanical metamaterials associated with stiffness, rigidity and compressibility: a brief review *Pro. Mater. Sci.* **94** 114–73
- [8] Bertoldi K *et al* 2017 Flexible mechanical metamaterials *Nat. Rev. Mater.* **2** 1–11
- [9] Shankar S *et al* 2022 Topological active matter *Nat. Rev. Phys.* **4** 380–98
- [10] de Waal L *et al* 2021 Dynamic behaviour of graded origami honeycomb *Int. J. Impact Eng.* **157** 103976
- [11] Athanasiadis A E, Dias M A and Michal K B 2021 Can confined mechanical metamaterials replace adhesives? *Extreme Mech. Lett.* **48** 101411
- [12] Paulose J, Meeussen A S and Vitelli V 2015 Selective buckling via states of self-stress in topological metamaterials *Proc. Natl Acad. Sci.* **112** 7639–44
- [13] Zhang Y, Restrepo D, Velay-Lizancos M, Mankame N D and Zavattieri P D 2019 Energy dissipation in functionally two-dimensional phase transforming cellular materials *Sci. Rep.* **9** 12581
- [14] Bensoussan A, Lions J-L and Papanicolaou G 2011 *Asymptotic Analysis for Periodic Structures* vol 374 (American Mathematical Soc.)
- [15] Glaesener R N *et al* 2020 Continuum representation of nonlinear three-dimensional periodic truss networks by on-the-fly homogenization *Int. J. Solids Struct.* **206** 101–13
- [16] Athanasiadis A E F, Budzik M K, Fernando D and Dias M A 2024 On micropolar elastic foundations *Eur. J. Mech. A* **105** 105277
- [17] Herrnböck L and Steinmann P 2022 Homogenization of fully nonlinear rod lattice structures: on the size of the RVE and micro structural instabilities *Comput. Mech.* **69** 947–64
- [18] Müller S, Triantafyllidis N and Geymonat G 1993 Homogenization of nonlinearly elastic materials, microscopic bifurcation and macroscopic loss of rank-one convexity *Arch. Ration. Mech. Anal.* **122** 231–90
- [19] Bhattacharya K, Kohn R V and Kozlov S 1999 Some examples of nonlinear homogenization involving nearly degenerate energies *Proc. R. Soc. A* **455** 567–83
- [20] Mohammadi Estakhri N, Edwards B and Engheta N 2019 Inverse-designed metastructures that solve equations *Science* **363** 1333–8
- [21] Hewett D P, Langdon S and Chandler-Wilde S N 2014 A frequency-independent boundary element method for scattering by two-dimensional screens and apertures *IMA J. Numer. Anal.* **35** 1698–728
- [22] Bonnet-Ben Dhia A-S, Hazard C and Monteghetti F 2021 Complex-scaling method for the complex plasmonic

- resonances of planar subwavelength particles with corners *J. Comput. Phys.* **440** 110433
- [23] Movchan A B, Movchan N V, Jones I S and Colquitt D J 2018 *Mathematical Modelling of Waves in Multi-Scale Structured Media* (Chapman & Hall/CRC) (<https://doi.org/10.1201/9781315155388>)
- [24] Nethercote M, Kisol A V, Thompson I and Assier R C 2022 Array scattering resonance in the context of Foldy's approximation *Proc. R. Soc. A* **478** 20220604
- [25] Bennetts L G, Peter M A and Montiel F 2017 Localisation of Rayleigh–Bloch waves and damping of resonant loads on arrays of vertical cylinders *J. Fluid Mech.* **813** 508–27
- [26] Milton G W, Briane M and Willis J R 2006 On cloaking for elasticity and physical equations with a transformation invariant form *New J. Phys.* **8** 248
- [27] Korolkov A I, Nazarov S A and Shanin A V 2016 Stabilizing solutions at thresholds of the continuous spectrum and anomalous transmission of waves *ZAMM—J. Appl. Math. Mech./Z. Angew. Math. Mech.* **96** 1245–60
- [28] Antonakakis T, Craster R V, Guenneau S and Skelton E A 2014 An asymptotic theory for waves guided by diffraction gratings or along microstructured surfaces *Proc. Math. Phys. Eng. Sci.* **470** 20130467
- [29] Smith M J A and Abrahams I D 2022 Tailored acoustic metamaterials. Part I. Thin- and thick-walled Helmholtz resonator arrays *Proc. R. Soc. A* **478** 20220124
- [30] Auriault J-L and Bonnet G 1985 Dynamique des composites elastiques periodiques *Arch. Mech.* **37** 269–84
- [31] Hempel R and Lienau K 2000 Spectral properties of periodic media in the large coupling limit properties of periodic media *Commun. PDE* **25** 1445–70
- [32] Zhikov V V 2005 On gaps in the spectrum of some divergence elliptic operators with periodic coefficients *St. Petersburg Math. J.* **16** 773–19
- [33] Bouchitté G and Felbacq D 2004 Homogenization near resonances and artificial magnetism from dielectrics *C.R. Acad. Sci. Paris, Ser. I* **339** 377–82
- [34] Cherednichenko K D, Smyshlyaev V P and Zhikov V V 2006 Non-local homogenised limits for composite media with highly anisotropic periodic fibres *Proc. R. Soc. Edinburgh A* **136** 87–114
- [35] Smyshlyaev V P 2009 Propagation and localization of elastic waves in highly anisotropic periodic composites via two-scale homogenization *Mech. Mater.* **41** 434–47
- [36] Cooper S 2013 Homogenisation and spectral convergence of a periodic elastic composite with weakly compressible inclusions *Appl. Anal.* **93** 1401–30
- [37] Kamotski I V and Smyshlyaev V P 2019 Two-scale homogenization for a general class of high contrast PDE systems with periodic coefficients *Appl. Anal.* **98** 64–90
- [38] Kamotski I V and Smyshlyaev V P 2019 Localized modes due to defects in high contrast periodic media via two-scale homogenization *J. Math. Sci.* **232** 349–37
- [39] Cherdantsev M, Capoferri M and Velčić I 2023 Eigenfunctions localised on a defect in high-contrast random media *SIAM J. Math. Anal.* **55** 7449–89
- [40] Kamotski I V and Smyshlyaev V P 2019 Bandgaps in two-dimensional high-contrast periodic elastic beam lattice materials *J. Mech. Phys. Solids* **123** 292–304
- [41] Cooper S, Kamotski I V and Smyshlyaev V P 2023 Quantitative multiscale operator-type approximations for asymptotically degenerating spectral problems (arXiv:2307.13151)
- [42] Cherednichenko K D and Cooper S 2016 Resolvent estimates for high-contrast elliptic problems with periodic coefficients *Arch. Ration. Mech. Anal.* **219** 1061–86
- [43] Cherednichenko K D, Ershova Y Y and Kiselev A V 2020 Effective behaviour of critical-contrast PDEs: micro-resonances, frequency conversion, and time dispersive properties. I *Commun. Math. Phys.* **375** 1833–84
- [44] Wellander N 2009 The two-scale Fourier transform approach to homogenization; periodic homogenization in Fourier space *Asymptotic Anal.* **62** 1–40
- [45] Zhengyou L, Zhang X, Mao Y, Zhu Y Y, Yang Z, Chan C T and Sheng P 2000 Locally resonant sonic materials *Science* **289** 1734–6
- [46] Ammari H, Davies B, Hiltunen E O, Lee H and Yu S 2022 Wave interaction with subwavelength resonators *Applied Mathematical Problems in Geophysics* (Springer International Publishing) pp 23–83
- [47] Kaina N, Lemoult F, Fink M and Lerosey G 2015 Negative refractive index and acoustic superlens from multiple scattering in single negative metamaterials *Nature* **525** 77–81
- [48] Lipton R and Perera R 2022 Bloch spectra for high contrast elastic media *J. Differ. Equ.* **332** 1–49
- [49] Dominguez V, Graham I G and Smyshlyaev V P 2007 A hybrid numerical-asymptotic boundary integral method for high-frequency acoustic scattering *Numer. Math.* **106** 471–510
- [50] Ohlberger M and Verfürth B 2018 A new heterogeneous multiscale method for the Helmholtz equation with high contrast *Multiscale Model. Simul.* **16** 385–411
- [51] Peterseim D and Verfürth B 2020 Computational high frequency scattering from high-contrast heterogeneous media *Math. Comput.* **89** 2649–74
- [52] Craster R V, Kaplunov J and Pichugin A V 2010 High-frequency homogenization for periodic media *Proc. R. Soc. A* **466** 2341–62
- [53] Guzina B, Meng S and Oudghiri-Idrissi O 2019 A rational framework for dynamic homogenization at finite wavelengths and frequencies *Proc. R. Soc. A* **475** 20180547
- [54] Wellander N, Guenneau S and Cherkaev E 2018 Two-scale cut-and-projection convergence; homogenization of quasiperiodic structures *Math. Meth. Appl. Sci.* **41** 1101–6
- [55] Amenoagbadji P, Fliess S and Joly P 2023 Wave propagation in one-dimensional quasiperiodic media (arXiv:2301.01159)
- [56] Davies B and Morini L 2024 Super band gaps and periodic approximants of generalised Fibonacci tilings *Proc. R. Soc. A* **480** 20230663
- [57] Nassar H, Xu X C, Norris A N and Huang G L 2017 Modulated phononic crystals: non-reciprocal wave propagation and Willis materials *J. Mech. Phys. Solids* **101** 10–29
- [58] Huidobro P A, Silveirinha M G, Galiffi E and Pendry J B 2021 Homogenization theory of space-time metamaterials *Phys. Rev. Appl.* **16** 014044
- [59] Touboul M, Lombard B, Assier R C, Guenneau S and Craster R V 2023 High-order homogenisation of the time-modulated wave equation: non-reciprocity for a single varying parameter (arXiv:2311.10096)
- [60] Marigo J-J, Maurel A, Pham K and Sbitti A 2017 Effective dynamic properties of a row of elastic inclusions: the case of scalar shear waves *J. Elast.* **128** 265–89
- [61] Noguchi Y, Yamada T, Izui K and Nishiwaki S 2018 Topology optimization for hyperbolic acoustic metamaterials using a high-frequency homogenization method *Comput. Methods Appl. Mech. Eng.* **335** 419–71
- [62] Lalau-Keraly C M, Bhargava S, Miller O D and Yablonovitch E 2013 Adjoint shape optimization applied to electromagnetic design *Opt. Express* **21** 21693–701
- [63] Frellsen L F, Ding Y, Sigmund O and Frandsen L H 2016 Topology optimized mode multiplexing in silicon-on-insulator photonic wire waveguides *Opt. Express* **24** 16866–73

- [64] Capers J R, Boyes S J, Hibbins A P and Horsley S A R 2022 Designing disordered multi-functional metamaterials using the discrete dipole approximation *New J. Phys.* **24** 113035
- [65] Capers J R, Stanfield L D, Sambles J R, Boyes S J, Powell A W, Hibbins A P and Horsley S A R 2024 Multiscale design of large and irregular metamaterials *Phys. Rev. Appl.* **21** 014005
- [66] Cordaro A, Edwards B, Nikkhah V, Alù A, Engheta N and Polman A 2023 Solving integral equations in free space with inverse-designed ultrathin optical metagratings *Nat. Nanotechnol.* **18** 365–72
- [67] Capers J R, Boyes S J, Hibbins A P and Horsley S A R 2021 Designing the collective non-local resonances of metasurfaces *Commun. Phys.* **4** 209
- [68] Huang H, Overvig A C, Xu Y, Malek S C, Tsai C-C, Alù A and Yu N 2023 Leaky-wave metasurfaces for integrated photonics *Nat. Nanotechnol.* **18** 580–8
- [69] Baxter J and Ramunno L 2023 Inverse design of optical pulse shapes for time-varying photonics *Opt. Express* **31** 22671–84
- [70] Faqiri R, Saigre-Tardif C, Alexandropoulos G C, Shlezinger N, Imani M F and Del Hougne P 2023 PhysFad: physics-based end-to-end channel modeling of RIS-parametrized environments with adjustable fading *IEEE Trans. Wirel. Commun.* **22** 580–95
- [71] Cisowski C M, Waller M C and Bennett R 2023 Towards nanophotonic optical isolation via inverse design of energy transfer in non-reciprocal media (arXiv:2310.13485)
- [72] Duncan O, Shepherd T, Moroney C, Foster L, Venkatraman P D, Winwood K, Allen T and Alderson A 2018 Review of auxetic materials for sports applications: expanding options in comfort and protection *Appl. Sci.* **8** 941
- [73] Thillaithevan D, Murphy R, Hewson R and Santer M 2024 Inverse design of periodic microstructures with targeted nonlinear mechanical behaviour *Struct. Multidiscip. Optim.* **67** 1–16
- [74] Imediegwu C, Murphy R, Hewson R and Santer M 2019 Multiscale structural optimization towards three-dimensional printable structures *Struct. Multidiscip. Optim.* **60** 513–25
- [75] Wu J, Wang W and Gao X 2021 Design and optimization of conforming lattice structures *IEEE Trans. Vis. Comput. Graph.* **27** 43–56
- [76] Schumacher C, Bickel B, Rys J, Marschner S, Daraio C and Gross M 2015 Microstructures to control elasticity in 3D printing *ACM Trans. Graph.* **34** 1–13
- [77] Sivapuram R, Dunning P D and Kim H A 2016 Simultaneous material and structural optimization by multiscale topology optimization *Struct. Multidiscip. Optim.* **54** 1267–81
- [78] White D A, Kudo J, Swartz K, Tortorelli D A and Watts S 2023 A reduced order model approach for finite element analysis of cellular structures *Finite Elem. Anal. Des.* **214** 103855
- [79] Panesar A, Ashcroft I, Brackett D, Wildman R and Hague R 2017 Design framework for multifunctional additive manufacturing: coupled optimization strategy for structures with embedded functional systems *Addit. Manuf.* **16** 98–106
- [80] Woldseth R V, Bærentzen J A and Sigmund O 2024 Phasor noise for dehomogenisation in 2D multiscale topology optimisation *Comput. Methods Appl. Mech. Eng.* **418** 116551
- [81] Murphy R, Thillaithevan D, Hewson R and Santer M 2024 Multiscale structural optimization for prescribed deformations in the nonlinear elastic regime *Struct. Multidiscip. Optim.* **67** 1–18
- [82] Frisken S F and Perry R N 2005 Designing with distance fields *Proc.—Int. Conf. on Shape Modeling and Applications, SMI'05* vol 2005 pp 58–59
- [83] Czech C, Lesjak M, Back C and Duddeck F 2022 Data-driven models for crashworthiness optimisation: intrusive and non-intrusive model order reduction techniques *Struct. Multidiscip. Optim.* **65**
- [84] Huang M, Cui T, Liu C, Du Z, Zhang J, He C and Guo X 2023 A problem-independent machine learning (PIML) enhanced substructure-based approach for large-scale structural analysis and topology optimization of linear elastic structures *Extreme Mech. Lett.* **63**
- [85] Watson P and Gupta K 1996 EM-ANN models for microstrip vias and interconnects in dataset circuits *IEEE Trans. Microw. Theory Tech.* **44** 2495–503
- [86] Hou Z *et al* 2020 Prediction network of metamaterial with split ring resonator based on deep learning *Nanoscale Res. Lett.* **15** 83
- [87] Zhang Q, Liu C, Wan X, Zhang L, Liu S, Yang Y and Cui T J 2019 Machine-learning designs of anisotropic digital coding metasurfaces *Adv. Theory Simul.* **2** 1800132
- [88] Khatib O, Ren S, Malof J and Padilla W J 2021 Deep learning the electromagnetic properties of metamaterials—A comprehensive review *Adv. Funct. Mater.* **31** 2101748
- [89] Bagheri S, Reinicke U, Anders D and Konen W 2021 Surrogate-assisted optimization for augmentation of finite element techniques *J. Comput. Sci.* **54** 101427
- [90] Mueller J 2012 *Linear and Nonlinear Inverse Problems with Practical Applications* (Society for Industrial and Applied Mathematics)
- [91] Pestourie R, Mroueh Y, Nguyen T V, Das P and Johnson S G 2020 Active learning of deep surrogates for PDEs: application to metasurface design *npj Comput. Mater.* **6**
- [92] Chen Y, Lu L, Karniadakis G E and Dal Negro L 2020 Physics-informed neural networks for inverse problems in nano-optics and metamaterials *Opt. Express* **28** 11618
- [93] Fang Z and Zhan J 2019 Deep physical informed neural networks for metamaterial design *IEEE Access* **8** 24506
- [94] Raissi M, Perdikaris P and Karniadakis G E 2019 Physics-informed neural networks: a deep learning framework for solving forward and inverse problems involving nonlinear partial differential equations *J. Comput. Phys.* **378** 686–707
- [95] Tancret F, Bhadeshia H K D H and MacKay D J C 2003 Design of a creep resistant nickel base superalloy for power plant applications: part 1—mechanical properties modelling *Mater. Sci. Technol.* **19** 283–90
- [96] Conduit B D, Jones N G, Stone H J and Conduit G J 2017 Design of a nickel-base superalloy using a neural network *Mater. Des.* **131** 358
- [97] Shraddha S and Naganna S 2014 A review ON K-means DATA clustering approach *Int. J. Inf. Comput. Technol.* **4** 1847
- [98] Xu D, Shi Y, Tsang I W, Ong Y-S, Gong C and Shen X 2020 Survey on multi-output learning *IEEE Trans. Neural Netw. Learn. Syst.* **31** 2409–29
- [99] Bourne P E *et al* 2022 Playing catch-up in building an open research commons *Science* **377** 256–8
- [100] Dima A *et al* 2016 Informatics infrastructure for the materials genome initiative *JOM* **68** 2053–64
- [101] National Science and Technology Council and Committee on Technology Subcommittee on the Materials Genome 2021 Initiative Materials genome initiative strategic plan (Department of Defence, National Science Foundation, Office of Science and Technology Policy and National Institute of Standards and Technology (USA)) (available at: www.mgi.gov/sites/default/files/documents/MGI-2021-Strategic-Plan.pdf)

- [102] Henry Royce Institute 2021 Materials 4.0: a role for standards (available at: www.royce.ac.uk/content/uploads/2021/06/Materials-4.0-A-Role-for-Standards.pdf) (Accessed 24 August 2022)
- [103] Henry Royce Institute 2021 Enabling trust in data exchange for materials 4.0 (available at: www.royce.ac.uk/content/uploads/2021/06/Materials-4.0-Enabling-Trust-in-Data-Exchange-Materials.pdf) (Accessed 24 August 2022)
- [104] NIST Configurable data curation system (CDCS) (available at: www.nist.gov/programs-projects/configurable-data-curation-system-cdcs) (Accessed 6 March 2024)
- [105] Earnshaw J, Byers J, Duncan O, Kaczmarczyk L, Scarpa F and Szyniszewski S 2023 (available at: <https://github.com/Meta-Genome-Org/>)
- [106] Yu J *et al* 2022 Vector-quantized image modeling with improved VQGAN (arXiv:2110.04627)
- [107] Koscher B A *et al* 2023 Autonomous, multiproperty-driven molecular discovery: from predictions to measurements and back *Science* **382** eadi1407
- [108] Lew A J and Buehler M J 2023 Single-shot forward and inverse hierarchical architected materials design for nonlinear mechanical properties using an Attention-Diffusion model *Mater. Today* **64** 10–20
- [109] Bastek J-H and Kochmann D M 2023 Inverse-design of nonlinear mechanical metamaterials via video denoising diffusion models (arXiv:2305.19836)
- [110] Cerniauskas G, Sadia H and Alam P 2024 Machine intelligence in metamaterials design: a review *Oxford Open Mater. Sci.* **4** itae001
- [111] Oliner A A and Hessel A 1961 Wave propagation in a medium with a progressive sinusoidal disturbance *IRE Trans. Microw. Theory Tech.* **9** 337–43
- [112] Cassedy E S 1967 Dispersion relations in time-space periodic media part II—Unstable interactions *Proc. IEEE* **55** 1154–68
- [113] Galiffi E, Tirole R, Yin S, Li H, Vezzoli S, Huidobro P A, Silveirinha M G, Sapienza R, Alù A and Pendry J B 2022 Photonics of time-varying media *Adv. Photon.* **4** 014002–1–014002–32
- [114] Sounas D L and Alù A 2017 Non-reciprocal photonics based on time modulation *Nat. Photon.* **11** 774–83
- [115] Pendry J B, Galiffi E and Huidobro P A 2022 Photon conservation in trans-luminal metamaterials *Optica* **9** 724–30
- [116] Horsley S A R and Pendry J B 2023 Quantum electrodynamics of time-varying gratings *Proc. Natl Acad. Sci.* **120** e2302652120
- [117] de Sterke C M 1992 Optical push broom *Opt. Lett.* **17** 914–6
- [118] Tirole R, Vezzoli S, Galiffi E, Robertson I, Maurice D, Tilmann B, Maier S A, Pendry J B and Sapienza R 2023 Double-slit time diffraction at optical frequencies *Nat. Phys.* **19** 999–1002
- [119] Lustig E *et al* 2023 Time-refraction optics with single cycle modulation *Nanophotonics* **12** 2221–30
- [120] Shechtman D, Blech I, Gratias D and Cahn J W 1984 Metallic phase with long-range orientational order and no translational symmetry *Phys. Rev. Lett.* **53** 1951–3
- [121] Chen Y, Kadic M, Guenneau S and Wegener M 2020 Isotropic chiral acoustic phonons in 3D quasicrystalline metamaterials *Phys. Rev. Lett.* **124** 235502
- [122] Della Villa A, Enoch S, Tayeb G, Pierrro V, Galdi V and Capolino F 2005 Band gap formation and multiple scattering in photonic quasicrystals with a Penrose-type lattice *Phys. Rev. Lett.* **94** 183903
- [123] Davies B, Chaplain G J, Starkey T A and Craster R V 2023 Graded quasiperiodic metamaterials perform fractal rainbow trapping *Phys. Rev. Lett.* **131** 177001
- [124] Martí-Sabaté M and Torrent D 2021 Edge modes for flexural waves in quasi-periodic linear arrays of scatterers *APL Mater.* **9** 081107
- [125] Ni X, Chen K, Weiner M, Apigo D J, Prodan C, Alu A, Prodan E and Khanikaev A B 2019 Observation of Hofstadter butterfly and topological edge states in reconfigurable quasi-periodic acoustic crystals *Commun. Phys.* **2** 55
- [126] Pal R K, Rosa M I N and Ruzzene M 2019 Topological bands and localized vibration modes in quasiperiodic beams *New J. Phys.* **21** 093017
- [127] Golden K, Goldstein S and Lebowitz J L 1989 Discontinuous behavior of effective transport coefficients in quasiperiodic media *J. Stat. Phys.* **58** 669
- [128] Cherkaev E, Vasquez F G, Mauck C, Prisbrey M and Raeymaekers B 2021 Wave-driven assembly of quasiperiodic patterns of particles *Phys. Rev. Lett.* **126** 145501
- [129] Rodriguez A W, McCauley A P, Avniel Y and Johnson S G 2008 Computation and visualization of photonic quasicrystal spectra via Bloch's theorem *Phys. Rev. B* **77** 104201
- [130] Dean C R *et al* 2013 Hofstadter's butterfly and the fractal quantum Hall effect in Moiré superlattices *Nature* **497** 598–602
- [131] Bandres M A, Rechtsman M C and Segev M 2016 Topological photonic quasicrystals: fractal topological spectrum and protected transport *Phys. Rev. X* **6** 011016
- [132] Torquato S and Stillinger F H 2003 Local density fluctuations, hyperuniform systems, and order metrics *Phys. Rev. E* **68** 041113
- [133] Zolla F, Felbacq D and Guizal B 1998 A remarkable diffractive property of photonic quasi-crystals *Opt. Commun.* **148** 6–10
- [134] Dong C, Shen K-S, Zheng Y, Liu H-C, Zhang J, Xia S-Q, Wu F, Lu H, Zhang X-Z and Liu Y-F 2021 Quasiperiodic metamaterials empowered non-metallic broadband optical absorbers *Opt. Express* **29** 13576–89
- [135] Maier S A, Brongersma M L, Kik P G, Meltzer S, Requicha A A G and Atwater H A 2001 Plasmonics—A route to nanoscale optical devices *Adv. Mater.* **13** 1501
- [136] Boltasseva A and Atwater H 2011 Low-loss plasmonic metamaterials *Science* **331** 290–1
- [137] Sanvitto D and Kéna-Cohen S 2016 The road towards polaritonic devices *Nat. Mater.* **15** 1061–73
- [138] Grosso G, Pietka B, Antón-Solanas C, Ballarini D and Fainstein A 2024 Polaritonics: introduction to feature issue *Opt. Mater. Express* **14** 155–6
- [139] Galiffi E *et al* 2024 Extreme light confinement and control in low-symmetry phonon-polaritonic crystals *Nat. Rev. Mater.* **9** 9–28
- [140] Guddala S, Komissarenko F, Kiriushechikina S, Vakulenko A, Li M, Menon V M, Alù A and Khanikaev A B 2021 Topological phonon-polariton funneling in midinfrared metasurfaces *Science* **374** 225–7
- [141] Hu G *et al* 2020 Topological polaritons and photonic magic angles in twisted α -MoO₃ bilayers *Nature* **582** 209–13
- [142] Ma W *et al* 2021 Ghost hyperbolic surface polaritons in bulk anisotropic crystals *Nature* **596** 362–6
- [143] Huang L, Krasnok A, Alù A, Yu Y, Neshev D and Miroshnichenko A E 2022 Enhanced light-matter interaction in two-dimensional transition metal dichalcogenides *Rev. Prog. Phys.* **85** 046401
- [144] Dirnberger F *et al* 2023 Magneto-optics in a Van der Waals magnet tuned by self-hybridized polaritons *Nature* **620** 533–7
- [145] Shelby R A, Smith D R and Schultz S 2001 Experimental verification of a negative index of refraction *Science* **292** 77–80

- [146] Ergin T, Fischer J and Wegener M 2011 Optical phase cloaking of 700nm light waves in the far field by a three-dimensional carpet cloak *Phys. Rev. Lett.* **107** 173901
- [147] Misseroni D, Movchan A B and Bigoni D 2019 Omnidirectional flexural invisibility of multiple interacting voids in vibrating elastic plates *Proc. R. Soc. A* **475** 20190283
- [148] Carta G, Giaccu G F and Brun M 2017 A phononic band gap model for long bridges. The ‘Brabau’ bridge case *Eng. Struct.* **140** 66–76
- [149] Madine K H and Colquitt D J 2022 Negative refraction and mode trapping of flexural–torsional waves in elastic lattices *Phil. Trans. R. Soc. A* **380** 20210379
- [150] Wang Z, Cheng F, Winsor T and Liu Y 2016 Optical chiral metamaterials: a review of the fundamentals, fabrication methods and applications *Nanotechnology* **27** 412001
- [151] Nieves M J, Carta G, Jones I S, Movchan A B and Movchan N V 2018 Vibrations and elastic waves in chiral multi-structures *J. Mech. Phys. Solids* **121** 387–408
- [152] Carta G, Colquitt D J, Movchan A B, Movchan N V and Jones I S 2019 One-way interfacial waves in a flexural plate with chiral double resonators *Phil. Trans. R. Soc. A* **378** 20190350
- [153] Carta G, Jones I S, Movchan N V, Movchan A B and Nieves M J 2017 “Deflecting elastic prism” and unidirectional localisation for waves in chiral elastic systems *Sci. Rep.* **7**
- [154] Kandiah A, Movchan N V and Movchan A B 2023 Gravity-induced waveforms in chiral non-periodic waveguides *Int. J. Solids Struct.* **285** 112528
- [155] Carta G, Nieves M J, Jones I S, Movchan N V and Movchan A B 2018 Elastic chiral waveguides with gyro-hinges *Q. J. Mech. Appl. Math.* **71** 157–85
- [156] D’Eleuterio G M and Hughes P C 1987 Dynamics of gyroelastic spacecraft *J. Guid. Control Dyn.* **10** 401–5
- [157] Carta G, Jones I S, Movchan N V, Movchan A B and Nieves M J 2017 Gyroelastic beams for the vibration reduction of long flexural systems *Proc. R. Soc. A* **473** 20170136
- [158] He R, Tsouvalas A, Xu X and Dong L 2023 Editorial: noise and vibrations in offshore wind farms and their impact on aquatic species *Front. Mar. Sci.* **10** 1293733
- [159] Dong E, Cao P, Zhang J, Zhang S, Fang N X and Zhang Y 2023 Underwater acoustic metamaterials *Natl Sci. Rev.* **10** nwa246
- [160] Movchan A B, Movchan N V and McPhedran R C 2007 Bloch–Floquet bending waves in perforated thin plates *Proc. R. Soc. A* **463** 2505–18
- [161] Honylite Honeycomb cores & panels (available at: <https://honylite.com/industries/acoustics/>) (Accessed 1 March 2024)
- [162] Farhat M, Enoch S, Guenneau S and Movchan A 2008 Broadband cylindrical acoustic cloak for linear surface waves in a fluid *Phys. Rev. Lett.* **101** 134501
- [163] Chen H, Yang J, Zi J and Chan C T 2009 Transformation media for linear liquid surface waves *Europhys. Lett.* **85** 24004
- [164] Zou S *et al* 2019 Broadband waveguide cloak for water waves *Phys. Rev. Lett.* **123** 074501
- [165] Porter R and Newman J 2014 Cloaking of a vertical cylinder in waves using variable bathymetry *J. Fluid Mech.* **750** 124–43
- [166] Cui L *et al* 2024 Protecting coastlines by offshore wave farms: on optimising array configurations using a corrected far-field approximation *Renew. Energy* **224** 120109
- [167] Dupont G, Remy F, Kimmoun O, Molin B, Guenneau S and Enoch S 2017 Type of dike using C-shaped vertical cylinders *Phys. Rev. B* **96** 180302
- [168] Zeng J, Zhao X, Sun X and Hu X 2023 Achieving complete band gaps of water waves with shallow-draft cylinder arrays *Phys. Rev. Appl.* **19** 044058
- [169] De Vita F, De Lillo F, Bosia F and Onorato M 2021 Attenuating surface gravity waves with mechanical metamaterials *Phys. Fluids* **33** 047113
- [170] Zhao X, Hu X and Zi J 2021 Fast water waves in stationary surface disk arrays *Phys. Rev. Lett.* **127** 254501
- [171] Bobinski T, Maurel A, Petitjeans P and Pagneux V 2018 Backscattering reduction for resonating obstacle in water-wave channel *J. Fluid Mech.* **845** R4
- [172] Iida T, Zareei A and Alam M-R 2023 Water wave cloaking using a floating composite plate *J. Fluid Mech.* **954** A4
- [173] Bennetts L G, Peter M A and Craster R V 2018 Graded resonator arrays for spatial frequency separation and amplification of water waves *J. Fluid Mech.* **854** R4
- [174] Archer A J, Wolgamot H A, Orszaghova J, Bennetts L G, Peter M A and Craster R V 2020 Experimental realization of broadband control of water-wave-energy amplification in chirped arrays *Phys. Rev. Fluids* **5** 062801
- [175] Lu L, Zhou Z, Qin J, Song Z, Xie Z, Lou X and Li Y 2021 Three-dimensional viscous numerical simulations of focused waves on bottom-mounted multiple rigid circular cylinders *Int. J. Offshore Polar Eng.* **31** 61–70
- [176] Bennetts L G, Peter M A and Craster R V 2019 Low-frequency wave-energy amplification in graded two-dimensional resonator arrays *Phil. Trans. R. Soc. A* **377** 20190104
- [177] Xu J, Chen L, Ning D and Zhao M 2023 Resonance of water waves propagating over a uniform and a graded line array of rectified submerged cosinoidal bars *Appl. Ocean Res.* **134** 103531
- [178] Wilks B, Montiel F and Wakes S 2022 Rainbow reflection and broadband energy absorption of water waves by graded arrays of vertical barriers *J. Fluid Mech.* **941** A26
- [179] Westcott A R, Bennetts L G, Sergiienko N Y and Cazzolato B S 2024 Broadband near-perfect capture of water wave energy by an array of heaving buoy wave energy converters *J. Fluid Mech.* **998** A5
- [180] Krushynska A O *et al* 2023 Emerging topics in nanophononics and elastic, acoustic, and mechanical metamaterials: an overview *Nanophotonics* **12** 659–86
- [181] Jiao P, Mueller J, Raney J R, Zheng X and Alavi A H 2023 Mechanical metamaterials and beyond *Nat. Commun.* **14** 6004
- [182] Sorrentino A and Castagnetti D 2023 Novel polyhedral mechanical metamaterial exhibiting negative Poisson’s ratio *Smart Mater. Struct.* **32** 035008
- [183] Zhang Z and Krushynska A O 2023 Shape morphing of tubular structures with tailorable mechanical properties *Adv. Eng. Mater.* **26** 2300383
- [184] Mirzaali M J and Zadpoor A A 2024 Orthopedic meta-implants *APL Bioeng.* **8** 010901
- [185] Rafsanjani A, Bertoldi K and Studart A R 2019 Programming soft robots with flexible mechanical metamaterials *Sci. Robot.* **4** eaav7874
- [186] Qi J, Chen Z, Jiang P, Hu W, Wang Y, Zhao Z and Fang D 2022 Recent progress in active mechanical metamaterials and construction principles *Adv. Sci.* **9** 2102662
- [187] Kolken H M, Janbaz S, Leeflang S M, Lietaert K, Weinans H H and Zadpoor A A 2018 Rationally designed

- meta-implants: a combination of auxetic and conventional meta-biomaterials *Mater. Horiz.* **5** 28–35
- [188] Greiner A M, Richter B and Bastmeyer M 2012 Micro-engineered 3D scaffolds for cell culture studies *Macromol. Biosci.* **12** 1301–14
- [189] Chen Y, Mai Y-W and Ye L 2023 Perspectives for multiphase mechanical metamaterials *Mater. Sci. Eng. R* **153** 100725
- [190] Zadpoor A A, Mirzaali M J, Valdevit L and Hopkins J B 2023 Design, material, function, and fabrication of metamaterials *APL Mater.* **11** 020401