

Categorization of formulas for calculation of crack width and spacing in reinforced concrete elements

van der Esch, Anton; Wolfs, Rob; Fennis, Sonja; Roosen, Marco; Wijte, Simon

DOI

[10.1002/suco.202300535](https://doi.org/10.1002/suco.202300535)

Publication date

2023

Document Version

Final published version

Published in

Structural Concrete

Citation (APA)

van der Esch, A., Wolfs, R., Fennis, S., Roosen, M., & Wijte, S. (2023). Categorization of formulas for calculation of crack width and spacing in reinforced concrete elements. *Structural Concrete*, 25(1), 32-48. <https://doi.org/10.1002/suco.202300535>

Important note

To cite this publication, please use the final published version (if applicable).
Please check the document version above.

Copyright

Other than for strictly personal use, it is not permitted to download, forward or distribute the text or part of it, without the consent of the author(s) and/or copyright holder(s), unless the work is under an open content license such as Creative Commons.

Takedown policy

Please contact us and provide details if you believe this document breaches copyrights.
We will remove access to the work immediately and investigate your claim.

ARTICLE

Categorization of formulas for calculation of crack width and spacing in reinforced concrete elements

Anton van der Esch¹  | Rob Wolfs¹  | Sonja Fennis²  | Marco Roosen^{2,3}  | Simon Wijte¹ 

¹Department of the Built Environment, Eindhoven University of Technology, Eindhoven, The Netherlands

²Rijkswaterstaat Grote Projecten en Onderhoud, Utrecht, The Netherlands

³Faculty of Civil Engineering and Geosciences, Delft University of Technology, Delft, The Netherlands

Correspondence

Anton van der Esch, De Zaale, Building 6, PO box 513, 5600 MB Eindhoven, The Netherlands.

Email: i.a.v.d.esch@tue.nl

Funding information

Rijkswaterstaat

Abstract

Over the last century, over one hundred crack width formulas have been developed to calculate the width and spacing of cracks in reinforced and prestressed concrete elements. It is unclear which formulas are the most accurate. An extensive comparison study is required to determine which formulas accurately describe the crack patterns, consisting of the crack width and spacing. To make such a study possible, this paper proposes categorizing formulas. The categorization of the formulas is based on their applicability, crack pattern representation, and background. The categorization presents an overview of the different assumptions and application areas for describing crack patterns.

KEYWORDS

categorization, crack spacing, crack width, prestressed concrete, reinforced concrete

1 | INTRODUCTION

In the Netherlands, civil engineering structures, such as bridges, tunnels, and underpasses, are frequently constructed out of reinforced or prestressed concrete. Their replacement value is estimated at €28 billion and is growing as new concrete structures are being designed.^{1,2} In these structures, loading due to external forces or restrained imposed strains may lead to cracks.³ Although current studies do not all agree if corrosion increases with increasing crack widths,⁴ the impact of cracking on durability performance is indicated by various studies,^{5–7} and led to the definition of crack width limits for ingress rates. Cracking can jeopardize the service life of these civil engineering structures,⁸ and thus, an accurate description of crack patterns in existing and new concrete structures is essential, considering both the crack width w and spacing between the cracks s_r .

The description of crack patterns due to loads is based on formulas such as described in EN 1992-1-1.⁹ Over one

hundred formulas for crack calculation have been developed in the last century for numerous applications in reinforced and prestressed concrete structures. In 1936, Saliger derived formulas to calculate the crack width and spacing in uniaxial loaded elements using bond stress–slip relationships,¹⁰ and an approach for elements loaded in bending in 1950.¹¹ Empirical formulas were developed in the 60s, such as those developed by Gergely and Lutz.¹² Also, in the 60s, parallel to the introduction of prestressed concrete in civil structures, the first formulas targeted the description of crack width in prestressed structures.¹³ Formulas that consider cracking due to the restraint of imposed strains were introduced in the 70s and 80s and are still being developed today.^{14,15}

Due to the numerous developments and differences between formulas for calculating crack width and spacing in concrete elements, it is unclear which formulas are the most accurate. To assess their accuracy, a comparative study of the performance of the formulas is required.

Comparisons between crack widths or spacings calculated with formulas and measured crack widths or spacings in experiments are presented by Allam et al.,¹⁶ Pérez Caldentey et al.,¹⁷ CROW-CUR,¹⁵ Scholz,¹⁸ Dawood and Marzouk,¹⁹ and Oh and Kang.²⁰ However, these studies generally compare only a limited number of formulas for calculating crack widths and spacings. In 2018, Lapi et al.²¹ presented a study where 30 formulas were thoroughly described and distinguished if it was based on experiments, fracture mechanics, bond stress-slip relationships, or semi-analytical approaches.^{21,22} Lapi et al. used the formulas to compare the outcomes with crack width measurements from experiments described in the literature. It was outside the scope of the cited comparative studies to extensively address the formulas' different assumptions and application areas for describing crack patterns. Hence, categories for formulas calculating the crack width and spacing in reinforced concrete are missing.

This paper categorizes formulas to calculate crack width and spacing in concrete elements loaded in tension and bending. The paper first identifies categories based on the applicability, the representation of crack patterns, and the background used for deriving the formulas for crack width and spacing. Those main categories are then further detailed based on their respective subcategories. Finally, the proposed categories were applied to 130 formulas to describe crack patterns, presented in Appendix A. Conclusions on the application and background of the categories are presented, which provides the basis for recommendations for future research.

2 | IDENTIFICATION OF CATEGORIES OF FORMULAS FOR CALCULATING CRACK WIDTH AND SPACING

Three main categories have been identified and applied to 130 formulas from 94 individual publications for calculating the crack width and spacing in reinforced and prestressed concrete structural elements. The main categories are application (A), representation (R), and background (B). These categories are then subdivided to cover the relevant characteristics of the cracking process in concrete structures, which enables all of the selected formulas to be classified. An overview of the categories is presented in Figure 1.

The (A) of each formula concerns different structural types (ST), the state of loading (SL), and the resulting internal strain distribution (SD).

The (R) indicates how the formulas describe the crack patterns, which is essential since various formulas

generally do not describe crack patterns similarly. This concerns the applicable cracking stage (CS), the position where the cracks are described (P), and a definition of the crack width (W) and spacing (S).

Each formula's (B) can be used to determine the extent of applicability for the structural and loading application or how the crack patterns are represented. It allows for assessing the assumptions behind each formula and identifies application areas not explicitly described in the corresponding literature. The four subcategories were chosen as fully (B1) empirical models, models based on fracture mechanics (B2), models based on bond stress-slip relationships (B3), and semi-analytical models (B4). The choice of the subcategories was partially inspired by Lapi et al. and Borosnyói and Balázs.^{21,22}

3 | APPLICATIONS OF FORMULAS FOR CALCULATING CRACK WIDTH AND SPACING

3.1 | Structural type

Concrete structures typically contain reinforcing steel (ST1), prestressing steel (ST2), or a combination of the two (ST3). The reinforcement in these structures can be non-metallic,²³ for example, fiber-reinforced polymers, but most reinforced structures contain steel reinforcing bars,^{24,25} which are either plain or deformed, often incorporated in the formulas through a bond factor. The formulas for calculating crack widths and spacings usually consider only the longitudinal reinforcement, while, for example, Rizkalla and Hwang,²⁶ also consider transverse reinforcement.

Contrary to structures with reinforcing steel, prestressed structures use pre or posttensioned bonded and unbonded tendons. Formulas for crack width and spacing are applied to bonded tendons in partially prestressed structures or structures with unbonded tendons combined with reinforcing steel since cracks can develop and be controlled in these structures. Examples include EN 1992-1-1⁹ or *fib* Model Code (MC) 2010,²⁷ where a bond factor is used to convert the bond properties of a prestressed structure to an equivalent reinforced structure, allowing for a straightforward calculation in the case of prestressed steel or a combination of reinforcing and prestressing steel.

3.2 | State of loading

The state of loading of a concrete structure is crucial since it mainly determines the crack width.²⁸ In the formulas

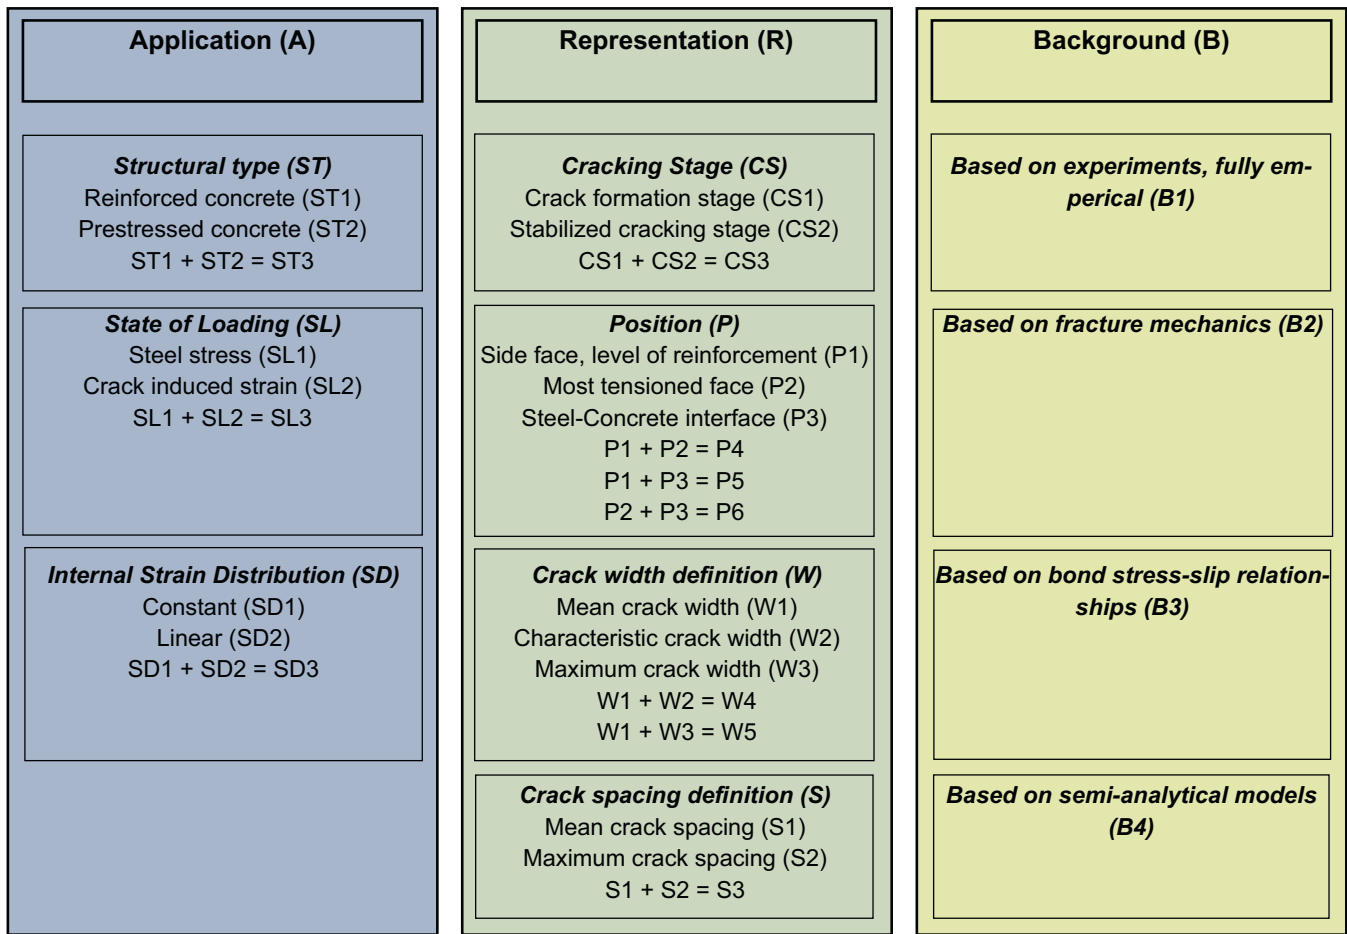


FIGURE 1 Categorization of formulas based on Application (A), Representation (R), Background (B), and their respective subcategories. The abbreviation of the categories is denoted between brackets.

for crack width and spacing, it is represented in various ways.

(SL1) First, a specific steel stress σ_s can be used, depending on the source of the applied load. In case of an external force, the resulting steel stress is implemented in various formulas, like EN 1992-1-1,⁹ *fib* MC 2010,²⁷ and many others. For structures that are restrained at the ends (Figure 2a), the stress in the reinforcement, just after a crack occurred and denoted as σ_{sr} , is frequently used for σ_s . This stress is obtained from the axial force N_{cr} that is required for cracking and depends on the concrete's tensile strength f_{ct} .

(SL2) Second, the load effect can be represented by a crack-inducing strain ϵ_{cr} . The formulas can then be applied to structures subjected to an edge restraint (Figure 2b) or an internal restraint. In EN 1992-3,²⁹ the crack-inducing strain is defined as the restrained component of the free strain ϵ_{free} , resulting from drying or autogenous shrinkage, temperature loading, or creep.³⁰ The crack-inducing strain in a structural element results from an axial imposed strain or an imposed curvature.

Formulas for calculation of the crack width that use a crack-inducing strain are CIRIA C766,³⁰ ICE/0706/012,³¹ or eq. (M.3) of EN 1992-3.²⁹ In addition, some formulas using ϵ_{cr} implement a strain release,³⁰ which is frequently assumed to be equal to half of the ultimate strain capacity of concrete in tension and allows for examining the cracking behavior after the first or subsequent cracks occur.^{31,32}

(SL3) Third, some formulas require an input of both the steel stress and a crack-inducing strain. These formulas are used if crack-inducing strains are combined with external forces, called a load and deformation combination.³² These formulas use a steel stress, calculated by the user of the formula, based on the magnitude of the external forces, and a calculated steel stress, representing the effect of crack-inducing strains. Finally, the stresses are added together, considering the sequence of the different applied loads, and used as input in the specific formula.³² Examples of those formulas are described in NEN 6720³³ and ICE/0706/012.³¹ Other literature^{28,34} indicates how load and deformation combinations might be addressed

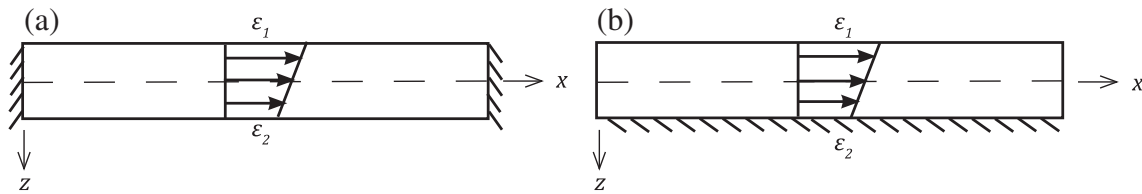


FIGURE 2 Strain conditions in structures subjected to (a) End restraints, (b) Edge restraints. The largest and smallest imposed strains are indicated with ε_1 and ε_2 , respectively.

but does not explicitly present formulas for calculating crack widths and spacings for this case.

3.3 | Internal strain distribution

The described loads (SL) lead to an internal strain distribution in the considered structural element, influencing the crack pattern. Constant strain over the height of the cross-section, that is, an evenly distributed strain in an element (SD1), represents an axial load, while a linear varying strain distribution (SD2) represents a bending moment. In most formulas, the strain distribution is incorporated by a reduction factor for the transfer length, which is based on the reasoning that in the case of bending, a smaller load is needed to generate a new crack with respect to the case of pure tension.¹⁷ Therefore, no reduction is applied in the case of a constant strain. The case of constant strain is discussed by Saliger,¹⁰ Broms and Lutz,³⁵ and Ouyang and Shah.³⁶ Unlike tension, bending leads to a curvature κ of the cross-section. Thus, the strains vary linearly over the cross-section height, and a reduction factor of 0.5 is applied in the case of pure bending. Cracking in structures subjected to pure bending can be calculated by the formulas developed by Base et al.,³⁷ Oh and Kang,²⁰ and Gergely and Lutz.¹² For the combination of axial and bending loads (SD3), the resulting strain distribution is calculated based on the strain at the most tensioned side ε_1 and the least tensioned side ε_2 . The way how those strains need to be combined to calculate the reduction factor is often prescribed in the documentation of the specific formula, like EN 1992-1-1,⁹ *fib* MC 2010,²⁷ and Noakowski.^{14,38}

4 | REPRESENTATION OF FORMULAS FOR CALCULATING CRACK WIDTH AND SPACING

4.1 | Cracking stage

The cracking stages of reinforced and prestressed concrete structures can be divided into the crack formation

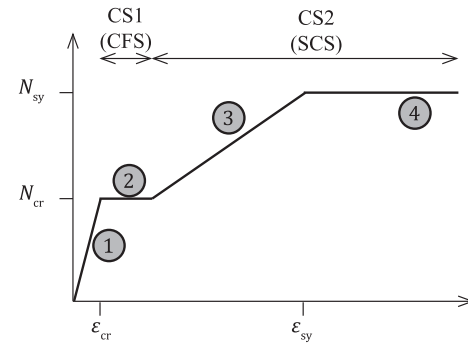


FIGURE 3 N, ε -relation for a concrete tie. Branch (1) indicates the uncracked behavior, (2) the crack formation stage, (3) the stabilized cracking stage before yielding of the reinforcement, and (4) the stabilized cracking stage at yielding. N_{cr} : internal force at cracking. ε_{cr} : strain at cracking. N_{sy} : internal force at yielding. ε_{sy} : strain at yielding.

stage (CS1) and the stabilized cracking stage (CS2),³ see Figure 3. Following the uncracked behavior, indicated by branch (1), the crack formation stage often applies for cracking due to restrained imposed strains and is characterized by a constant branch (2). In contrast, the stabilized cracking stage often represents cracking in the case of external forces and is represented by a linear branch (3) and eventually the horizontal branch at yielding (4).³³

Although most formulas for crack calculation do not explicitly mention for which cracking stage they apply, frequently, their applicability can be derived from the context or the background of the formulas; the latter is further described in Section 5.

Regarding the context, the crack formation stage often occurs when imposed strains are restrained.³² This can be observed in the corresponding formula if σ_{sr} is used as the steel stress directly after a crack occurs, or ε_{cr} as the crack-inducing strain. The related internal force is indicated with N_{cr} . For the stabilized cracking stage, the load effect is considered by a general value of σ_s , which is larger than σ_{sr} . In some cases, two distinct formulas for both the crack formation stage and stabilized cracking stage are provided, such as Van Breugel et al.,³² *Fpr*EN 1992-1-1,²⁸ EN 1992-3,²⁹ and *fib* MC 2020.³⁹ However, frequently, only one formula is given, specified for the

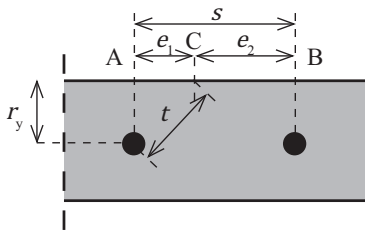


FIGURE 4 Schematic representation of a cross-section to determine the distance t . t is the distance from the reinforcing bar to the considered location on the concrete surface, indicated with C . t can be calculated based on Pythagoras' theorem, $t = \sqrt{e^2 + r_y^2}$, with $e = \frac{e_1 e_2}{s}$, r_y is the vertical distance from the center of the reinforcing bar to the most tensioned face and s is the spacing between the reinforcing bars.

stabilized cracking stage, which can be modified to the crack formation stage by substitution of σ_{sr} into σ_s . This is, amongst others, implemented in *fib* MC 2010²⁷ and NVN-ENV 1997-1-1.⁴⁰

4.2 | Position of the measured crack width

Formulas for calculating crack widths evaluate the crack width at the level of the reinforcement (P1), the most tensioned face (P2), or the steel-concrete interface (P3). Model codes, like *fib* MC 1990,⁴¹ 2010,²⁷ 2020,³⁹ and codes such as EN 1992-1-1⁹ and FprEN 1992-1-1,²⁸ consider the crack width at the most tensioned face since the calculated crack widths are compared to crack width limits, following from the exposure class of the structure.²⁷

In the case of bending, the crack width varies over the height of the crack. *fib* MC 2020³⁹ and FprEN 1992-1-1²⁸ extrapolate the crack widths from the reinforcement level to the most tensioned face, using a curvature factor $k_{1/r}$,^{17,39} based on an analysis of the cracked concrete element. $k_{1/r}$ is defined as⁴²:

$$k_{1/r} = \frac{h - x}{d - x} \quad (1)$$

where h represents the height of the cross-section, x represents the depth of the concrete compression zone, and d represents the effective depth. The curvature factor only affects elements loaded in bending; for elements loaded in pure tension, the factor equals one. The inverse of Equation (1) is sometimes implemented in empirical-based formulas to convert the description of the calculated crack width from the most tensioned face to the side face at the level of the reinforcement.^{22,42}

Broms and Lutz³⁵ and Frosch⁴³ allow calculating the crack width at an arbitrary place on the most tensioned face. They implement the distance t from the center of the reinforcing bar to the location on the tension face where the crack width is calculated (Figure 4).

In addition, BS 8007⁴⁴ and BS 8110⁴⁵ allow for the calculation of crack width at an arbitrary place on the concrete surface, though they define t as the distance between the steel-concrete interface and the most tensioned face.

Finally, crack widths are evaluated at the steel-concrete interface, following the analytical derivation from the bond stress-slip relationship.

4.3 | Crack width definition

Due to the stochastic material properties of concrete,²² crack width and spacing vary in a structural element. Hence, formulas for calculating the crack width and spacing frequently express a representative value of the calculated crack width, which might deviate from actual crack widths observed on a structure.³⁹ Most used are the calculated mean crack width w_m and the calculated characteristic crack width w_k .

The calculated mean crack width (W1) is addressed by the formulas of Saliger,^{10,11} Broms,⁴⁶ Ferry-Borges,⁴⁷ and *fib* MC 2020.³⁹ However, comparing calculated values with values obtained from crack width measurements is not straightforward. For instance, there is no consensus in the literature on the definition of w_m based on measured crack widths in a structure. *fib* MC 2020³⁹ defines w_m as the mean value of the measurements of at least 10 individual points, which can be individual cracks, denoted to the closest 0.05 mm, having the same restraint at randomly selected locations. Other codes do not specifically state which cracks should be taken into account and define the average of all individually measured crack widths.

The calculated characteristic crack width (W2) is regularly defined as the 95% quantile for the statistical variation when assuming a lognormal distribution.⁴⁸ This can be interpreted as the crack width at the 95% fractile of the crack widths, which can be expected in a reinforced or prestressed member.⁴⁹ Beeby defined w_k using an 80% quantile, reasoning that the reduced quantile was appropriate since the 5% probability of exceedance is too small to pose a risk of corrosion or seriously impair appearance.^{21,50} This was later implemented in CP 110 as part of the British Standards.²¹ The calculated design crack width w_d is frequently considered equal to the calculated characteristic crack width.²¹ For formulas allowing to

calculate both the mean and characteristic crack width, a conversion between the two is usually obtained with a factor $\beta_w = w_k/w_m$.^{28,32}

The formulas developed by Gergely and Lutz,¹² Oh and Kang,²⁰ and König and Tue,⁵¹ use the maximum crack width $w_{\max}$ (W3). The maximum calculated crack width is regularly considered to be equal to the calculated characteristic crack width.²¹

4.4 | Crack spacing definition

Formulas describing crack patterns might provide a crack spacing besides the crack width. Crack spacing is often relevant for the stabilized cracking stage only since, in that stage, the number of developed cracks and, thus, the crack spacing is constant. Nonetheless, formulas applicable for end restraints like EN 1992-3,²⁹ CIRIA C766³⁰ and ICE/0706/012³¹ present a crack spacing, even though these formulas frequently describe the crack formation stage.

Crack spacing in formulas is defined as the mean crack spacing $s_{r,m}$ (S1) and the maximum crack spacing $s_{r,\max}$ (S2). The relation between mean and maximum crack spacing is reported in some cases by the factor β_w , however, based on the ratio $s_{r,\max}/s_{r,m}$ instead of w_k/w_m .^{26,39,40} These ratios are not equivalent.⁵²

5 | BACKGROUND OF FORMULAS FOR CALCULATING CRACK WIDTH AND SPACING

5.1 | Based on experiments, fully empirical (B1)

Empirical formulas, fully based on experiments, are derived by fitting formulas with unknown regression constants. The regression constants are obtained by comparing the formulas with the measured crack widths.

One of the first empirical formulas for reinforced concrete structures was developed by Kaar and Mattock in 1963,⁵³ investigating cracking in high-strength reinforcing bars for rectangular and T-beams loaded in bending. Flexural cracking was further investigated in 1965 by Kaar and Hognestad.⁴² Both authors proposed a crack width formula:

$$w = A \sqrt[4]{\frac{A_{c,\text{eff}}}{n}} \sigma_s, \quad (2)$$

where A is a regression constant, n is the number of reinforcement bars, and $A_{c,\text{eff}}/n$ is the effective area of the concrete $A_{c,\text{eff}}$, related to a single reinforcing bar.

In 1968, Gergely and Lutz¹² used a largely similar formula as Equation (2) but used a cube root¹² and incorporated the distance from the tension face to the center of the reinforcing bar r_y , resulting in:

$$w = A \sqrt[3]{\frac{A_{c,\text{eff}}}{n}} r_y \sigma_s. \quad (3)$$

Multiple authors and codes used a similar form for formulas for crack width calculation.^{34,54–57}

Besides reinforced concrete structures, fully experimental-based formulas were also developed for prestressed structures based on the fictitious or nominal tensile stress and the net stress methods.⁵⁸

In 1967, Abeles introduced the fictitious stress method.⁵⁹ In this method, the fictitious stress is calculated based on the uncracked properties of the cross-section. Similar to Equations (2) and (3), the formulas use regression constants and are then fitted with the measured crack widths obtained with laboratory tests. Finally, the crack widths can be calculated based on formulas considering the calculated fictitious tensile stress; this stress should be lower than an allowable fictitious tensile stress. Raju et al.⁶⁰ and Meier and Gergely⁵⁵ further implemented fictitious stress methods.

Contrary to the fictitious stress method, the net stress method calculates the steel stress based on the cracked concrete properties. The steel stress in the formulas for prestressed concrete structures is considered a change in the steel stress in the prestressing element, evaluated from the load level at the onset of decompression at the beam's tensile face to the load level at which the crack width is considered.⁶⁰ Formulas incorporating the net stress method are presented by Bennet and Veerasubramanian,⁶¹ Nawy and Potyondy,⁶² Martino and Nilson,⁶³ and Suri and Dilger.⁵⁴

Finally, recently, empirically derived formulas for formulas to calculate the crack width and spacing might be derived by artificial neural networks (ANNs). The ANNs are used as a regression technique on collected experimental data to derive new formulas for calculating the crack width and spacing.^{64,65}

5.2 | Based on fracture mechanics (B2)

Formulas can also be derived based on fracture mechanics.^{20–22,36,66} Oh and Kang²⁰ derived the formula for crack width and spacing for elements loaded in bending, using fracture mechanics based on the energy and strength criterion. The results of the numerical experiments then determined the regression constants in the formula, making it a semi-empirical approach.

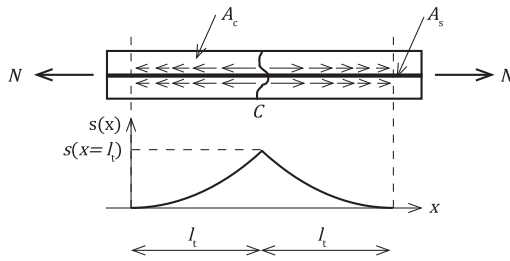


FIGURE 5 Slip distribution along a cracked concrete element. The location of the crack is indicated with point C . The figure is based on Lapi et al.²¹

Ouyang and Shah^{36,66} derived a formula for elements loaded in pure tension. A fracture resistance curve was used to represent the fracture process zone, and the rates of change of the strain energy from unloading, sliding and debonding were calculated. Then, an energy balancing equation was implemented in the models, and the crack width and spacing were predicted with the resulting formulas.

5.3 | Based on bond stress-slip relationships (B3)

Formulas based on bond stress-slip relationships or analytical models are derived using the differential equation for bond slip:

$$\frac{d^2 s_x}{dx^2} - \frac{\tau_b(s_x, x) 4(1 + \alpha_e \rho)}{E_s \emptyset} = 0, \quad (4)$$

where s_x denotes the slip of the reinforcement concerning the concrete, ρ is the reinforcement ratio, $\tau_b(s_x, x)$ is the bond stress as a function of the slip and the position x , measured from the start of the transfer length as indicated in Figure 5. Equation (4) can be solved for the slip from which the crack width can be calculated.⁶⁷ Due to the assumed symmetry of the slip distribution, the crack width is considered as twice the slip distance, evaluated at the transfer length l_t .

This can be presented by the following formula:

$$w = 2s_x(x = l_t). \quad (5)$$

Equation (4) is often solved for the crack formation stage, and the crack width can then be calculated with Equation (5). Besides the crack formation stage, Equation (4) can theoretically assess the stabilized cracking stage too. However, due to inhomogeneous boundary conditions, the solution procedure and the resulting expression are complex for practical implementation when applying a linear or non-linear bond

stress-slip relation.^{68,69} Nonetheless, Noakowski used some simplifications in the derivation of the resulting formula on a non-linear bond-stress slip relation, making it applicable in the stabilized cracking stage.^{14,38} Theoretically, the solution presented in Equation (5) is valid only in the case of pure tension and presents the crack width at the steel-concrete interface. An extension to bending and a combination of bending and tension was incorporated into the formula developed by Noakowski^{14,38} in 1985 and formed the basis of other formulas derived from Equation (4), like.⁶⁷ Another adaptation to Equation (5) is the addition of a factor to calculate the crack width at the most tensioned face instead of the steel-concrete interface.⁷⁰

5.4 | Based on semi-analytical models (B4)

Formulas based on semi-analytical models are partially based on bond stress-slip relations and calibrated with experimental crack width and spacing measurements. In the formulas, a simple relation between the crack width and spacing is presented as:

$$w = s_r(\varepsilon_{sm} - \varepsilon_{cm}), \quad (6)$$

where $\varepsilon_{sm} - \varepsilon_{cm}$ denotes the difference between the average strain in the reinforcement and the concrete within the transfer length and for cracking due to external forces or end-restraint cracking, often described as:

$$\varepsilon_{sm} - \varepsilon_{cm} = \frac{\sigma_s - \beta_{TS} \sigma_{sr}}{E_s}, \quad (7)$$

where β_{TS} is a factor considering the average strain of the steel within the transfer length.²⁷ In the case of edge restraint cracking, Equation (7) is often written as:

$$\varepsilon_{sm} - \varepsilon_{cm} = R_{ax} \varepsilon_{free}, \quad (8)$$

and used to calculate the strain difference and, subsequently, the crack width, using Equation (6). When formulas like Equation (7) are used, the steel stress σ_{sr} is frequently implemented. The development of formulas based on semi-analytical models started in 1936 with Saliger.¹⁰ Saliger proposed an equivalent formula for crack spacing based on mechanical considerations⁵²:

$$s_r \sim l_t = \frac{f_{ct,eff} \emptyset}{4 \rho_{eff} \tau_{bm}}. \quad (9)$$

In Equation (9), where ρ_{eff} is the effective reinforcement ratio, a mean bond stress τ_{bm} is considered,

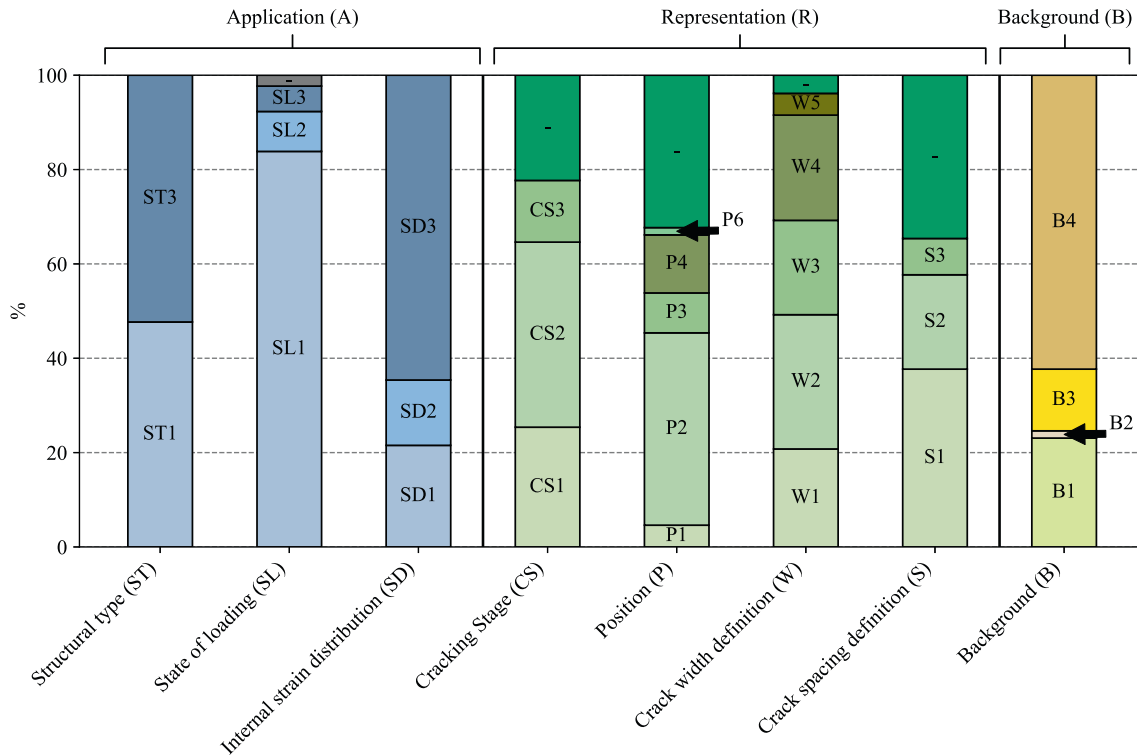


FIGURE 6 Graphical quantification of Appendix A for the three categories. Each color represents a relevant characteristic of each subcategory, and each column indicates a subcategory, according to Figure 1. The denotation “-” indicates that the corresponding information is not provided or stated in the literature.

simplifying the derivation of the transfer length. Thus, it is assumed that the crack spacing is proportional to the transfer length. In the crack formation stage, the crack width is calculated according to the semi-analytical approach according to Equations (6), (7), and (9), coincides with the bond stress-slip approach. The approach of Saliger was further implemented by the German national annex of EN 1992-1-1,⁷¹ *fib* MC 1990⁴¹ and König and Tue.⁵¹

In 1965, Broms introduced the concrete cover or no-slip approach.⁴⁶ Instead of assuming that the transfer length is entirely dependent on the bond slip, it is assumed that bond failure does not occur and that the distributed zone is proportional to the concrete cover. Hence, the crack spacing is presented by:

$$s_r = k_3 c, \quad (10)$$

where k_3 determines the effect of the concrete cover c on the crack spacing. The no-slip approach was further implemented by Broms and Lutz.³⁵ Base et al.³⁷ and Beeby⁵⁰ proposed a formula based on the elastic analysis of the concrete, for example, incorporated in BS 8007⁴⁴ and BS 8110.⁴⁵

In 1966, Ferry-Borges⁴⁷ combined the contributions of the concrete cover and the bond stress-slip approach and developed a new formula equivalent to:

$$s_r = k_3 c + k_1 k_2 k_4 \frac{f_{ct,eff} \sigma}{\rho_{eff} \tau_{bm}}. \quad (11)$$

An equivalent form of Equation (11) is implemented in modern (model) codes, such as EN 1992-1-1,⁹ *fib* MC 2010,²⁷ and MC 2020.³⁹

6 | CATEGORIZATION AND OBSERVATIONS

A categorization of 130 formulas for crack width and crack spacing was performed based on the framework presented in the previous chapters. The results for each formula are presented in Appendix A, and a graphical summary is provided in Figure 6. Based on the complete overview, some observations can be made:

- The formulas do not address ST2. The developed formulas for prestressed concrete structures include the possibility of adding reinforcing steel or were calibrated on experiments on concrete structures having reinforcing and prestressing steel.
- Seven formulas address crack widths in concrete structures subjected to loading and deformation combinations, related to SL3. More literature addresses the importance

of considering these combinations but does not give formulas. Three formulas do not include a loading state.

- The formulas based on empirical models often do not provide a crack spacing but exclusively a crack width. The formulas only allow a steel stress as input and not a crack-inducing strain. Furthermore, little attention is paid to the range of applicability of their input parameters in the literature that describes these empirical formulas.
- Formulas based on fracture mechanics do not address prestressed concrete structures.
- Formulas based on bond stress–slip relationships frequently describe the crack width at the steel–concrete interface. Formulas using fracture mechanics present the crack width at the concrete side face at the reinforcement level, at the steel–concrete interface or the most tensioned face, while formulas based on bond stress–slip relationships frequently use the stress as the state of loading and often describe the crack widths in the crack formation stage at the steel–concrete interface.
- Formulas for calculation of the crack width and spacing only apply to a portion of the suggested categories, thus to a relatively small application area. However, the overview showed that semi-analytical-based formulas do address most categories.

7 | CONCLUSIONS AND FUTURE WORK

This paper presents a categorization framework for formulas to calculate the crack width and spacing in concrete elements. The categorization was based on three main categories: application, representation, and background and was further divided into subcategories. In total, 130 formulas for crack calculation have been categorized. The framework can be applied to include new and other existing formulas. The categorized formulas in this paper might also be extended to other application areas. For example, for various formulas that pay attention to the stabilized cracking stage, the crack formation stage can be addressed by implementing the steel stress at the onset of cracking. Also, the extension from the crack width calculation at the reinforcement level to the most tensioned face can be incorporated. The validity of these additional application areas and the potential of these existing formulas is a topic for further research.

The categorization enables researchers to investigate the most accurate formulas inside a category and compare the accuracy between the presented categories. Finally, this paper can guide engineers and designers in selecting an appropriate formula for their crack width calculation.

LIST OF SYMBOLS

$A_{c,eff}$	Effective concrete area (mm ²)
c	Concrete cover (mm)
d	Effective depth (mm)
E_s	Modulus of elasticity of reinforcing steel (MPa)
E_c	Modulus of elasticity of concrete (MPa)
f_{ct}	Axial tensile strength of concrete (MPa)
$f_{ct,eff}$	Effective axial tensile strength of concrete (MPa)
f_{ctm}	Mean value of axial tensile strength of concrete (MPa)
k	Coefficient (–)
l_t	Transfer length (mm)
n	Number of reinforcing bars in the effective tensile zone (–)
N_{cr}	Axial cracking force (N)
N_y	Axial yielding force of reinforcement (N)
r_y	Cover to the center of the bar in the y-direction (mm)
R_{ax}	Restrained factor (–)
s	Spacing of reinforcing bars (mm)
s_x	Slip (mm)
s_r	Distance between cracks (mm)
$s_{r,m}$	Mean spacing between cracks (mm)
$s_{r,max}$	Maximum spacing between cracks (mm)
x	Depth of concrete compression zone (mm)
w	Crack width (mm)
w_m	Mean crack width (mm)
w_k	Characteristic crack width (mm)
w_{max}	Maximum crack width (mm)
w_{lim}	Nominal limit value of crack width (mm)
α_e	Modular ratio ($= E_s/E_c$) (–)
β	Ratio ($= w_k/w_m$) (–)
β_{TS}	Factor considering ϵ_{sm} within l_t (–)
ϵ_{cm}	Average concrete strain within transfer length (–)
ϵ_{cr}	Crack-inducing strain (–)
ϵ_{free}	Free strain (–)
ϵ_{sm}	Average steel strain within transfer length (–)
ϵ_r	Restraint strain (–)
σ_s	Steel stress (MPa)
σ_{sr}	Steel stress in a crack directly after cracking (MPa)
ρ	Reinforcement ratio (–)
ρ_{eff}	Effective reinforcement ratio (–)
τ_b	Bond stress (MPa)
τ_{bm}	Mean bond stress (MPa)
$\emptyset$	Nominal diameter of a reinforcing bar (mm)

ACKNOWLEDGMENTS

The authors thank Rijkswaterstaat Grote Projecten en Onderhoud (GPO) for their financial support and

valuable feedback in writing this paper. The help of Jenny Govers in digitizing literature is appreciated.

CONFLICT OF INTEREST STATEMENT

Sonja Fennis and Marco Roosen are co-authors of this paper and are affiliated with Rijkswaterstaat GPO, giving financial support to this research. They declare that their affiliations do not affect their input while writing this paper.

DATA AVAILABILITY STATEMENT

Data sharing not applicable to this article as no datasets were generated or analysed during the current study.

ORCID

Anton van der Esch  <https://orcid.org/0000-0002-3229-5267>

Rob Wolfs  <https://orcid.org/0000-0001-7897-433X>

Sonja Fennis  <https://orcid.org/0000-0002-5695-3287>

Marco Roosen  <https://orcid.org/0000-0002-7466-6900>

Simon Wijte  <https://orcid.org/0000-0003-4869-4948>

REFERENCES

- Bleijenberg IAN. Instandhouding civiele infrastructuur Proeve van landelijk prognoserapport vervanging en renovatie. Delft: TNO; 2021.
- Bloksma HR, Westenberg KDF. Civiele kunstwerken in Nederland," iAsset. Harderwijk, The Netherlands: Westenberg B.V.; 2021.
- Jedrzejewska A, Zych M, Kanavaris F, Chen F, Ito S, Torrenti JM, et al. Standardized models for cracking due to restraint of imposed strains—the state of the art. *Struct Concr*. 2023;24(4):5388–5405.
- Chen E, Berrocal CG, Lofgren I, Lundgren K. Correlation between concrete cracks and corrosion characteristics of steel reinforcement in pre-cracked plain and fibre-reinforced concrete beams. *Mater Struct*. 2020;53(2):1–22.
- Otieno MB, Alexander MG, Beushausen H-D. Corrosion in cracked and uncracked concrete - influence of crack width, concrete quality and crack reopening. *Mag Concr Res*. 2010; 62(6):393–404.
- Scott A, Alexander MG. The influence of binder type, cracking and cover on corrosion rates of steel in chloride-contaminated concrete. *Mag Concr Res*. 2007;59(7):494–505.
- Otieno MB, Alexander MG, Beushausen H-D. Resistivity-based chloride-induced corrosion rate prediction models and hypothetical framework for interpretation of resistivity measurements in cracked RC structures. *Mater Struct*. 2016;49(6): 2349–66.
- Koenders EAB. Integral solutions for sustainable construction (IS2C)—a structural health monitoring program in The Netherlands. SMAR-first Middle East conference on smart monitoring. Dubai: Empa; 2011.
- E. C. F. Standardization. Eurocode 2: design of concrete structures—part 1–1: general rules and rules for buildings. Brussels: European Committee for Standardization; 2011.
- Saliger R. High-grade steel in reinforced concrete. Proc., 2nd congress of the Int. association for bridge and structural engineering. Zürich: IABSE; 1936. p. 293–315.
- Saliger R. Die neue theorie des stahlbetons. Vienna: Franz Deuticke; 1950.
- Gergely P, Lutz LA. Maximum crack width in reinforced concrete flexural members. *Spec Publ*. 1968;20(6):87–117.
- Brice LP. Idées Générales sur la fissuration du béton armé et du béton précontraint. *Ann Inst Tech Bâtiment Trav Publics*. 1964;198:686–700.
- Noakowski P. Verbundorientierte, kontinuierliche Theorie zur Ermittlung der Rißbreite. *Beton-und Stahlbetonbau*. 1985; 80(7):185–90.
- CROW-CUR. Scheurwijdtebeheersing van betonconstructies, fase 1: scheurwijdteberekeningen voor gewapende betonconstructies met verhinderde vervormingen. Ede: CROW; 2020.
- Allam SM, Shoukry MS, Rashad GE, Hassan AS. Crack width evaluation for flexural RC members. *Alex Eng J*. 2012;51(3): 211–20.
- Caldentey AP, García R, Gribniak V, Rimkus A. Tension versus flexure: reasons to modify the formulation of MC 2010 for cracking. *Struct Concr*. 2020;21(5):2101–23.
- Scholz H. Simple deflection and cracking rules for partially prestressed members. *Am Concr Inst*. 1991;88(2):199–203.
- Dawood N, Marzouk H. An analytical model for crack spacing of thick reinforced concrete plates. *Eng Struct*. 2010;32(2): 472–82.
- Oh BH, Kang Y-J. New formulas for maximum crack width and crack spacing in reinforced concrete flexural members. *Am Concr Inst*. 1987;84(2):103–12.
- Lapi M, Orlando M, Spinelli P. A review of literature and code formulations for cracking in R/C members. *Struct Concr*. 2018;19(5):1481–503.
- Borosnyói A, Balázs GL. Models for flexural cracking in concrete: the state of the art. *Struct Concr*. 2005;6(2):53–62.
- Taerwe L. Non-metallic (FRP) reinforcement for concrete structures: proceedings of the second international RILEM symposium. Second International RILEM symposium, Quebec. London: CRC Press; 2004.
- Arduini M, Balconi G. Applications of non-metallic concrete reinforcements. Proceedings of Italian concrete days. Lecco: Springer; 2018.
- Melo J, Fernandes C, Varum H, Rodrigues H, Costa A, Arêde A. Numerical modelling of the cyclic behaviour of RC elements built with plain reinforcing bars. *Eng Struct*. 2011;33(2):273–86.
- Rizkalla SH, Hwang LS. Crack prediction for members in uniaxial tension. *Am Concr Inst*. 1984;81(6):572–9.
- International Federation for Structural Concrete. Model Code 2010. Lausanne: International Federation for Structural Concrete; 2013.
- European Committee for standardization. FprEN1992-1-1-D7 working file [Stable_version_51_e_stf]. Brussels: European Committee for standardization; 2023.
- European Committee for Standardization. Eurocode 2: design of concrete structures—part 3: liquid retaining and containment structures. Brussels: European Committee for Standardization; 2006.
- CIRIA. Control of cracking caused by restrained deformation in concrete. London: CIRIA; 2017.

31. Institution of Civil Engineers. The development of a revised unified approach for the Design of Reinforcement to control cracking in concrete resulting from restrained contraction. London: Institution of Civil Engineers; 2010.
32. van Breugel K, Braam CR, Koenders EAB. Concrete structures under imposed thermal and shrinkage deformations. Delft: Delft University of Technology; 2013.
33. Nederlands Normalisatie Instituut. TGB 1990—Voorschriften Beton—Constructieve Eisen en Rekenmethoden (VBC1995). Delft: Nederlands Normalisatie Instituut; 1995.
34. American Concrete Institute. Cracking of concrete members in direct tension. *J Am Concr Inst.* 1986;83(1):3–13.
35. Broms BB, Lutz LRA. Effects of arrangement of reinforcement on crack width and spacing of reinforced concrete members. *J Am Concr Inst.* 1965;62(11):1395–409.
36. Ouyang C, Shah SP. Fracture energy approach for predicting cracking of reinforced concrete tensile members. *Am Concr Inst.* 1994;91(1):69–78.
37. Base GD, Read JB, Beeby AW, Taylor H. An investigation of the crack control characteristics of various types of bar in reinforced concrete beams. *Cem Concr Assoc.* 1966;1:1–44.
38. Noakowski P. Verbundorientierte, kontinuierliche Theorie zur Ermittlung der RiBbreite. *Beton-und Stahlbetonbau.* 1985; 7:215–21.
39. Federation international du beton, model code 2020 [final draft]. Lausanne: Federation International du Beton; 2023.
40. Eurocode 2: design of Concrete Structures - part 1–1: general rules and rules for buildings. Brussels: EN; 1997.
41. Comite Euro-International du Beton. CEB-FIB model code 1990. Lausanne: Comite Euro-International du Beton; 1990.
42. Kaar P, Hognestad E. High strength bars as concrete reinforcement, part 7: control of cracking in t-beam flanges: Portland cement association. *J PCA Res Dev Lab.* 1965;10: 42–53.
43. Frosch RJ. Another look at cracking and crack control in reinforced concrete. *Am Concr Inst.* 1999;96(3):437–42.
44. British Standard Institution. Code of practice for Design of Concrete Structures for retaining aqueous liquids. London: British Standard Institution; 1987.
45. British Standard Institution. Structural use of concrete—part 2: code of practice for special circumstances. London: British Standard Institution; 1997.
46. Broms BB. Crack width and crack spacing in reinforced concrete members. *J Am Concr Inst.* 1965;62(1):1237–56.
47. Borges JF. Cracking and deformability of reinforced concrete beams. Zürich: IABSE; 1966. p. 73–95.
48. Tan R, Hendriks MAN, Kanstad T. Evaluation of current crack width calculation methods according to Eurocode 2 and fib model code 2010. High tech concrete: where technology and engineering meet, Maastricht. Cham, Switzerland: Springer; 2018.
49. Comite Euro-International du Beton. Bulletin d'information No. 158-E. Lausanne: Comite Euro-International du Beton; 1985.
50. Beeby AW. The prediction of crack widths in hardened concrete. *Struct Eng.* 1979;57A(1):9–17.
51. König G, Tue NV. Grundlagen und bemessungshilfen für die RiBbreitenbeschränkung im stahlbeton und spannbeton. Berlin: Beuth Verlag GmbH; 1996.
52. Schlicke D, Dorfmann EM, Fehling E, Tue NV. Calculation of maximum crack width for practical design of reinforced concrete. *Civ Eng Des.* 2021;3(3):45–61.
53. Kaar PH, Mattock AH. High strength bars as concrete reinforcement, part 4: control of cracking. *J PCA Res Dev Lab.* 1963;10:15–38.
54. Suri KM, Dilger WH. Crack width of partially prestressed concrete members. *Am Concr Inst.* 1986;83(5):784–97.
55. Meier SW, Gergely PM. Flexural crack width in prestressed concrete beams. *Am Soc Civil Eng.* 1981;107(2):429–33.
56. American Concrete Institute. Building code requirements for reinforced concrete. Farmington Hills: American Concrete Institute; 1995.
57. American Concrete Institute. Cracking of concrete members in direct tension. Farmington Hills: American Concrete Institute; 1997.
58. Au FTK, Du JS. Partially prestressed concrete. *Prog Struct Eng Mater.* 2004;6(2):127–35.
59. Abeles PW. Design of partially prestressed concrete beams. *Am Concr Inst J.* 1967;64(10):669–77.
60. Raju NK, Basavarajiah BS, Kutty UCA. Flexural behaviour of pretensioned concrete beams with limited prestress. *Build Sci.* 1973;8(2):179–85.
61. Bennett E, Veerasubramanian N. Behavior of nonrectangular beams with limited prestress after flexural cracking. *Am Concr Inst.* 1972;69(9):533–42.
62. Nawy EG, Potyondy JG. Flexural cracking behavior of pretensioned I-and T-beams. *J Proc.* 1971;68(5):355–60.
63. Martino NE, Nilson AH. Crack widths in partially prestressed concrete beams. Ithaca: Cornell University; 1979.
64. Elshafey AA, Dawood N, Marzouk H, Haddara M. Crack width in concrete using artificial neural networks. *Eng Struct.* 2013;52:676–86.
65. Elshafey A, Dawood N, Marzouk H, Haddara M. Predicting of crack spacing for concrete by using neural networks. *Eng Fail Anal.* 2013;31:344–59.
66. Shah SP, Swartz SE, Ouyang C. Fracture mechanics of concrete: applications of fracture mechanics to concrete, rock and other quasi-brittle materials. Hoboken, NJ: John Wiley & Sons; 1995.
67. Balázs GL. Cracking analysis based on slip and bond stresses. *Am Concr Inst.* 1993;90(4):340–8.
68. Russo G, Romano F. Cracking response of RC members subjected to uniaxial tension. *J Struct Eng.* 1992;118(5):1172–90.
69. Tan R, Hendriks MAN, Kanstad T, Mette G. Analytical calculation model for predicting cracking behavior of reinforced concrete ties. *Am Soc Civil Eng.* 2020;146(2):1–17.
70. Yang S, Chen J. Bond slip and crack width calculations of tension members. *Am Concr Inst.* 1988;85(4):414–22.
71. Beuth. DIN EN 1992-2/NA:2013–04. Berlin: Beuth; 2013.
72. American Concrete Institute. Control of cracking in concrete structures. Farmington Hills: American Concrete Institute; 2001.
73. Stichting Commissie Voorschriften Beton. Voorschriften Beton. Delft: Nederlands Normalisatie Insituut; 1974.
74. Nederlands Normalisatie-instituut. Voorschriften Beton VB 1974/1984. Delft: Nederlands Normalisatie-instituut; 1984.
75. Schießl P, Wölfel E. Konstruktionsregeln zur Beschränkung der RiBbreite - Grundlage zur Neufassung DIN 1045, Abschnitt 17.6 (Entwurf 1985). *Beton-und Stahlbetonbau.* 1986;1:8–15.

76. Menn C. Zwang und Mindestbewehrung. Beton-und Stahlbetonbau. 1986;81(4):94–9.
77. Leonhardt F. Crack control in concrete structures. IABASE Surveys. 1977;4:1–26.
78. Sygula S. Vergleichende Untersuchungen über Biege-Bruchformeln für Stahlbeton. Beton-und Stahlbetonbau. 1981;5:114–7.
79. Wicke M. Cracking and deformation in structural concrete. IABSE Reports. 1991;62:49–57.
80. Egyptian Code Standing Committee for Design and Construction of Concrete Structures. Egyptian code for design and construction of concrete structures. Cairo: Egyptian Code Standing Committee for Design and Construction of Concrete Structures; 2007.
81. CIRIA. Early-age thermal crack control in concrete. London: CIRIA; 2007.
82. Empelmann M, Krakowski W. Erweitertes Modell zur Berechnung der Rissbreite. Beton-und Stahlbetonbau. 2015;110: 458–67.
83. Standards Australia Committee. Australian standard—concrete structures. Sydney: SAI Global Limited; 2018.
84. CEB-FIP. Bulletin d'information N. 172/173. Lausanne: CEB-FIP; 1978.
85. Stichting CURNET. CUR 85 - Scheurvorming door krimp en temperatuurwisseling in wanden. Gouda: Stichting CURNET; 1978.
86. Norges Standardiseringsforbund. Design of concrete structures—design and detailing rules. Oslo: Norges Standardiseringsforbund; 2003.
87. Janovic K, Kupfer H. Beschränkung der Rißbreite bei teilweiser Vorspannung. Bauingenieur. 1982;57:109–14.
88. Japan Society of Civil Engineers. Standard specifications for concrete structures—2007. Tokyo: Japan Society of Civil Engineers; 2007.
89. Nawy EG. Flexural cracking behavior of pretensioned and post-tensioned beams: the state of the art. Am Concr Inst. 1985;82(6):890–900.
90. König G, Fehling E. Zur Rißbreitenbeschränkung im Stahlbetonbau. Beton-und Stahlbetonbau. 1988;83(6):161–7.
91. Edwards AD, Picard A. Theory of cracking in concrete members. J Struct Div. 1972;98(12):2687–700.
92. Krips M. Rißbreitenbeschränkung im Stahlbeton und Spannbeton. Berlin: Ernst & Sohn Verlag; 1985.
93. Bernardi S, Mesureur B, Rivillon P. Study of high-strength concretes reinforced with high-strength reinforcement: study of bonding laws and cracking in static system. Am Concr Inst. 1999;96(4):491–9.
94. Braam CR. Control of crack width in deep reinforced concrete beams. Delft: W.D. Meinema b.v; 1990.
95. Mohan Rao SVK, Dilger WH. Control of flexural crack width in cracked prestressed concrete members. Am Concr Inst. 1992;89(2):127–38.
96. Ouzaa K, Benmansour MB. Cracks in continuously reinforced concrete pavement. Arab J Sci Eng. 2014;39(12):8593–608.
97. Venkateswarlu B, Gesund H. Cracking and bond slip in concrete beams. J Struct Div. 1972;98(12):2663–85.
98. Martin H, Schießl P, Schwarzkopf M. Ableitung eines allgemeingültigen Berechnungsverfahrens für Rißbreiten aus Lastbeanspruchung auf der Grundlage von theoretischen Erkenntnissen und Versuchsergebnissen. Forschung Strassenbau Und Strassenverkehrstechnik. 1980;309:29–66.
99. Windisch A. Crack control: an advanced calculation model, part 2: the model. Concr Struct. 2017;40–7.
100. Clark AP. Cracking in reinforced concrete flexural members. J Am Concr Inst. 1956;52(4):851–62.
101. Tan R, Hendriks MA, Geiker M, Kanstad T. Modified cracked membrane model for consistent crack width predictions of reinforced concrete structures subjected to in-plane loading. Eng Struct. 2019;196:1–15.
102. Giordano L, Mancini G. Crack width evaluation of reinforced concrete membrane elements. Struct Eng Int. 2018;19(3): 256–61.
103. Debernardi PG, Taliano M. An improvement to Eurocode 2 and fib model code 2010 methods for calculating crack width in RC structures. Struct Concr. 2016;17(3):365–76.
104. Rehm G, Eligehausen R, Mällée R. Rißverhalten von Stahlbetonkörpern bei Zugbeanspruchung. Stuttgart: IRB Verlag; 1976.
105. Chowdhury S. Crack width predictions of reinforced and partially prestressed concrete beams: a unified formula. Structural Engineering, Mechanics and Computation. Cape Town: Elsevier Science Ltd; 2001.
106. Standards New Zealand. Concrete structures standard 3101 part 1 and part 2. Wellington: Standards New Zealand; 2006.
107. Canadian Standards Association. Design of Concrete Institutes. Mississauga: Canadian Standards Association; 2004.
108. American Concrete Institute. Building code requirements for structural concrete. Farmington Hills: American Concrete Institute; 2019.
109. Wydawnictwa Normalizacyjne. Konstrukcje betonowe, żelbetowe i sprężone. Warsaw: Wydawnictwa Normalizacyjne; 1977.
110. Sokolov I, Gubar V, Sergeeva I. Determination of crack width in reinforced-concrete members of hydraulic structures. Hydrotech Constr. 1975;9(3):220–5.
111. Nawy EG, Huang P. Crack and deflection control of pretensioned prestressed beams. Precast/Prestressed Concr Inst. 1977;22(3):30–47.
112. Nawy EG, Blair KW. Further studies on flexural crack control in structural slab system. Spec Publ. 1971;30:1–42.
113. Chi M, Kirstein AF. Flexural cracks in reinforced concrete beams. J Am Concr Inst. 1958;54(4):865–78.
114. CUR. CUR 37 - Scheurvorming en doorbuiging in gewapend beton bij toepassing van geribd staal. Gouda: CUR; 1968.
115. Holmberg Å, Lindgren S. Crack spacing and crack widths due to normal force or bending moment. Stockholm: National Swedish Council for Building Research; 1970.

AUTHOR BIOGRAPHIES



Anton van der Esch, Department of the Built Environment, Eindhoven University of Technology, Eindhoven, The Netherlands. Email: i.a.v.d.esch@tue.nl.



Rob Wolfs, Department of the Built Environment, Eindhoven University of Technology, Eindhoven, The Netherlands.

Email: r.j.m.wolfs@tue.nl.



Sonja Fennis, Rijkswaterstaat Grote Projecten en Onderhoud, Utrecht, The Netherlands.

Email: sonja.fennis@rws.nl.



Marco Roosen, Rijkswaterstaat Grote Projecten en Onderhoud, Utrecht, The Netherlands.

Email: marco.roosen@rws.nl.



Simon Wijte, Department of the Built Environment, Eindhoven University of Technology, Eindhoven, The Netherlands.

Email: s.n.m.wijte@tue.nl.

How to cite this article: van der Esch A, Wolfs R, Fennis S, Roosen M, Wijte S. Categorization of formulas for calculation of crack width and spacing in reinforced concrete elements. *Structural Concrete*. 2023. <https://doi.org/10.1002/suco.202300535>

APPENDIX A: CATEGORIZATION OF FORMULAS FOR CRACK WIDTH AND SPACING

This appendix presents a categorization of crack width and spacing formulas based on the proposed categories in Figure 1. Please note:

- “-” means that this information is not provided or stated in the corresponding literature or the category cannot be derived or identified.

- If no information on prestressing steel is provided in the literature or the corresponding formula, then it is categorized as only applicable to reinforced concrete structures.
- Prestressed structures will generally lead to a combination of axial and bending loads. Therefore, the internal strain distribution (SD) for formulas describing cracks in prestressed structures is always categorized as “3.”

Info				Categorization							
ID	Publication	Ref.	Year	A			R				B
				ST	SL	SD	CS	P	W	S	
1	NEN-EN 1992-1-1, eqs. (7.8, 7.9)	9	2011	3	1	3	2	2	2	2	4
2	FprEN 1992-1-1, eqs. (9.8, 9.11, 9.15)	28	2023	3	1	3	3	4	4	1	4
	FprEN 1992-1-1, eqs. (9.8, 9.13, 9.15)			3	2	3	1	4	4	1	4
3	NEN-EN 1992-3, eq. (M.1)	29	2006	3	1	3	1	2	2	2	4
	NEN-EN 1992-3, eq. (M.3)			3	2	3	1	2	2	2	4
4	DIN-EN 1992-1-1, eqs. (7.8, 7.9)	71	2013	3	1	3	2	2	2	2	4
5	<i>fib</i> MC 1990, eqs. (7.4-2, 7.4-3)	41	1990	3	1	3	1	2	2	2	4
	<i>fib</i> MC 1990, eqs. (7.4-3, 7.6-3)			3	1	3	2	2	2	2	4
	<i>fib</i> MC 1990, §7.4.3.1.2			3	3	3	3	2	2	2	4
6	<i>fib</i> MC 2010, eqs. (7.6-2, 7.6-3)	27	2013	3	1	3	1	2	2	2	4
	<i>fib</i> MC 2010, eqs. (7.6-5, 7.6-3)			3	1	3	2	2	2	2	4
7	<i>fib</i> MC 2020 (final draft), eqs. (30.5-2, 30.5-3, 30.5-5, 30.5-13)	39	2023	3	1	3	1	4	4	3	4
	<i>fib</i> MC 2020 (final draft), eqs. (30.5-3, 30.5-5, 30.5-12)			3	2	3	3	4	4	3	4
8	ACI 224-01, eq. (4-21)	72	2001	1	1	1	-	2	3	-	1
9	VB 1974, §508.1 + §508.2 (CS1)	73	1974	3	2	3	1	2	3	1	4
	VB 1974, §508.1 + §508.2 (CS2)			3	1	3	2	2	3	1	4
10	NEN 3880, §508.1 + §508.2 (CS1)	74	1984	3	2	3	1	2	3	1	4
	NEN 3880, §508.1 + §508.2 (CS2)			3	1	3	2	2	3	1	4
11	NVN-ENV 1997, eqs. (4.80-4.82)	40	1997	3	1	3	3	2	2	1	4
	NVN-ENV §4.4.2.4(6)			3	3	3	3	2	2	1	4
12	Noakowski, eq. (17)	38	1985	1	1	3	1	-	2	1	3
	Noakowski, eq. (20)			1	1	3	2	-	2	1	3
13	Schießl and Wölfel, eq. (10)	75	1986	1	1	3	1	-	2	1	4
	Schießl and Wölfel, eq. (2)			1	1	3	2	-	2	1	4
	Schießl and Wölfel, §3.4			1	3	1	3	-	2	1	4
14	Broms and Lutz, eqs. (1-5)	35	1965	1	1	1	2	2	4	3	4
15	Broms, eqs. (1-4)	46	1965	1	1	1	2	2	4	3	4
16	Saliger, eqs. (21, 23)	11	1950	1	1	3	2	-	4	1	4
17	BS 8110, eq. (12)	45	1997	3	1	3	2	2	2	-	4
	BS 8110, eq. (14)			1	2	3	1	2	2	-	4

Info				Categorization							
ID	Publication	Ref.	Year	A			R				B
				ST	SL	SD	CS	P	W	S	
18	Van Breugel et al., eq. (4.19)	32	2013	1	1	1	1	-	4	-	3
	Van Breugel et al., eqs. (4.22, 4.23)			1	1	1	2	-	4	1	4
19	Menn, §1	76	1986	1	1	3	3	-	1	1	4
20	Leonhardt, eqs. (3, 6)	77	1977	1	1	3	2	2	4	1	4
21	Sygula, §2	78	1981	1	1	3	-	-	4	-	1
22	Wicke, eqs. (18, 19)	79	1991	3	1	3	3	2	3	2	4
23	König and Tue, eq. (21)	51	1996	3	1	3	1	-	1	-	4
	König and Tue, eq. (26)			3	1	3	2	-	3	2	4
	König and Tue, eq. (59)			3	1	3	1	-	1	-	4
	König and Tue, eq. (62)			3	1	3	2	-	3	2	4
24	ECP 203–2007, eq. (4–66)	80	2007	3	1	3	3	2	4	1	4
25	CROW-CUR, §9	15	2020	3	1	3	1	2	2	2	4
26	Ciria C660, eq. (3.15)	81	2007	3	2	3	1	2	2	2	4
	Ciria C660, eq. (3.16)			3	1	3	1	2	2	2	4
27	Empelmann and Krakowski, eq. (34)	82	2015	1	1	3	1	2	4	3	4
	Empelmann and Krakowski, eq. (35)			1	1	3	2	2	4	3	4
28	Ciria C766, eqs. (3.11, 3.23)	30	2017	3	1	3	1	2	2	2	4
	Ciria C766, eqs. (3.10, 2.23)			3	2	3	1	2	2	2	4
29	AS 3600, eq. (8.6.2.3(1))	83	2018	3	1	3	2	2	2	2	4
30	CEB-fib 1978, eqs. (15.1–15.5)	84	1978	3	1	3	3	2	4	1	4
31	ACI 224.2-R, eq. (3.6)	57	1997	1	1	1	2	2	3	-	1
	ACI 224.2-R, eq. (3.7)			1	1	2	2	4	3	-	1
32	CUR 85, eq. (9.5)	85	1978	1	1	1	1	-	1	1	4
	CUR 85, eq. (9.7)			1	1	1	2	-	1	1	4
33	NS 3473, §A.15.6.2.1	86	2003	3	1	3	2	2	2	3	4
	NS 3473, §A.15.6.2.2			3	1	3	1	2	2	1	4
34	Rizkalla and Hwang, eqs. (9–20)	26	1984	1	1	1	3	-	5	1	4
35	Ferry-Borges, eqs. (1, 4)	47	1966	1	1	2	2	-	5	1	4
36	Janovic and Kupfer, eq. (10)	87	1982	3	1	3	2	-	1	1	4
37	Saliger, §B-b	10	1936	1	1	1	2	-	1	1	4
38	JSCE, eq. (7.4.4)	88	2007	3	1	3	2	2	2	2	4
39	Nawy, eqs. (4, 8)	89	1985	3	1	3	-	4	3	1	1
	Nawy, eqs. (4, 9)			3	1	3	-	4	3	1	1
40	Scholz, eq. (7)	18	1991	3	1	3	-	2	-	1	1
41	Föhling and König, eqs. (9, 9a)	90	1988	1	1	3	1	-	1	-	4
	Föhling and König, eqs. (11, 12)			1	1	3	2	-	4	3	4
	Föhling and König, §2.6.3			1	3	1	3	-	4	3	4
42	Edwards and Picard, eq. (18)	91	1972	3	1	3	1	3	1	-	3
43	Krips, eq. (II.13)	92	1985	3	1	1	1	3	1	-	3
	Krips, eq. (III.9)			3	1	1	1	3	1	-	3
	Krips, eqs. (IV.15, IV16)			3	1	1	2	3	1	-	3
	Krips, eqs. (V.1, V.6)			3	1	2	3	-	1	1	3

(Continues)

Info				Categorization							
ID	Publication	Ref.	Year	A			R				B
				ST	SL	SD	CS	P	W	S	
44	Yang and Chen, eq. (26)	70	1988	1	1	1	1	6	4	-	3
45	Balázs, eq. (20)	67	1993	1	1	3	1	3	1	-	3
46	Bernardi et al., eqs. (12, 13)	93	1999	1	1	1	2	2	-	1	4
47	Oh and Kang, eqs. (5, 9)	20	1987	1	1	2	2	4	3	1	2
48	Ouyang and Shah, eqs. (27, 30)	36	1994	1	1	1	-	3	1	1	2
49	Braam, eqs. (26, 27)	94	1990	1	1	3	3	3	1	1	3
50	Brice, §4 + §5	13	1964	3	1	3	2	-	1	1	4
51	Dawood and Marzouk, eq. (18)	19	2010	1	1	1	1	3	-	2	3
	Dawood and Marzouk, eq. (19)			1	1	1	2	3	-	1	3
52	Kaar and Hognestad, eq. (7)	42	1965	3	1	3	-	4	3	-	1
53	Gergely and Lutz, eqs. (19, 20)	12	1968	1	1	2	-	4	3	-	1
54	ACI 224.2R-86, eq. (3.6)	34	1986	1	1	1	-	-	3	-	1
55	Suri and Dilger, eq. (3)	54	1986	3	1	3	-	-	4	-	1
56	Rao and Dilger, eq. (2)	95	1992	3	1	3	-	-	4	-	1
57	Ouzaa and Benmansour, eq. (18)	96	2014	1	2	1	1	-	1	-	4
	Ouzaa and Benmansour, eq. (24)			1	2	1	2	-	1	1	4
58	Frosch, eqs. (5, 6)	43	1999	1	1	2	-	4	4	3	4
59	Kaar and Mattock, eq. (11)	53	1963	1	1	2	-	1	5	-	1
60	Base et al., §General observations	37	1966	1	1	2	-	1	5	-	4
61	Venkateswarlu and Gesund, eqs. (14, 18, 22)	97	1972	1	1	2	1	6	3	2	3
62	Martin et al., eq. (19)	98	1980	1	1	3	2	1	4	1	4
63	Windisch, eqs. (1, 6)	99	2017	3	1	3	2	2	2	2	4
64	NEN 6720, §8.7	33	1995	3	3	3	3	2	2	-	3
65	Clark, eq. (2)	100	1956	1	1	2	-	2	4	-	1
66	Reignard et al., §CLLM + eq. (77)	101	2019	1	1	1	1	3	1	-	3
	Reignard et al., §CHLM + eq. (77)			1	1	1	2	3	1	1	3
67	Pérez Caldentey et al., eqs. (10–12)	17	2020	3	1	1	2	2	4	2	4
68	ICE/0706/012, eqs. (21, 23, 25)	31	2010	3	3	3	3	2	2	2	4
69	Bennet and Veersubramanian, eq. (4)	61	1972	3	1	3	-	-	3	-	1
70	Meier and Gergely, eqs. (1, 2)	55	1981	3	1	3	-	-	3	-	1
71	Raju et al., §Discussion	60	1973	3	1	3	-	-	3	-	1
72	Martino and Nilson, eq. (5.4)	63	1979	3	1	3	-	-	2	-	1
73	Nawy and Potyondi, eq. (8)	62	1971	3	1	3	2	-	3	-	1
74	Giordano and Mancini, eq. (3, 27)	102	2018	1	1	1	2	2	1	1	4
75	Debernardi and Taliano, eqs. (18, 20)	103	2016	3	1	3	2	2	2	2	4
76	Rehm et al., eq. (7)	104	1976	1	1	3	2	-	4	1	4
77	Chowdhury, eqs. (5–7)	105	2001	3	1	3	2	4	5	1	4
78	NZS 3101, eq. (2.7)	106	2006	1	1	3	2	4	2	-	4
79	CSA A23.3-04, eq. (10–6)	107	2004	1	1	2	2	4	2	-	1
80	CEB Bulletin 158, eqs. (2.6.1, 2.6.3)	49	1985	3	1	3	2	2	4	1	4
	CEB Bulletin 158, eqs. (2.6.1, 2.6.4)			3	1	3	2	2	4	1	4

Info				Categorization							
ID	Publication	Ref.	Year	A			R				B
				ST	SL	SD	CS	P	W	S	
81	ACI 318-95, eq. (10–5)	56	1995	1	1	1	2	2	3	-	1
82	ACI 318-19, §24.3	108	2019	3	1	3	-	-	2	-	1
83	PN-76/B-03264, §Appendix 4	109	1976	1	1	2	2	-	4	1	4
84	Sokolov et al., eqs. (3, 5)	110	1975	1	1	3	-	-	1	1	1
85	Beeby, eq. (6)	50	1979	3	1	3	2	2	2	-	4
86	Nawy and Huang, eqs. (4, 7, 8)	111	1977	3	1	3	2	2	3	1	1
87	Nawy and Blair, §Fracture hypothesis	112	1971	1	1	2	-	4	3	-	1
88	Abeles, §Working load conditions (serviceability)	59	1967	3	1	3	-	2	3	-	1
89	BS 8007, §A.3	44	1987	3	2	3	1	2	2	2	4
90	Chi and Kirstein, eq. (9)	113	1958	1	1	2	-	2	1	-	4
91	CUR 37, eq. (31)	114	1968	1	1	2	-	1	3	-	4
	CUR 37, eq. (20)			1	1	2	-	1	1	-	4
	CUR 37, §5.1			3	1	2	3	1	1	-	4
92	Holmberg and Lindgren, eq. (9)	115	1970	3	1	3	-	4	5	1	1
93	Elshafey et al., eq. (13)	64	2013	1	-	1	-	-	1	-	1
	Elshafey et al., eq. (14)			1	-	2	-	-	1	-	1
94	Elshafey et al., eq. (9)	65	2013	1	-	3	2	-	-	1	1

Note: The colours used are in agreement with Figure 6.

Abbreviations: A, application; B, background; CS, cracking stage; P, position of the measured crack width; R, representation; S, crack spacing definition; SD, internal strain distribution; SL, state of loading; ST, structural type; W, crack width definition.