

## Direct Imaging of Local pH Reveals Bubble-Induced Mixing in a CO<sub>2</sub> Electrolyzer

Baumgartner, Lorenz M.; Kahn, Aron; Hoogland, Maxime; Bleeker, Jorrit; Jager, Wolter F.; Vermaas, David A.

**DOI**

[10.1021/acssuschemeng.3c01773](https://doi.org/10.1021/acssuschemeng.3c01773)

**Publication date**

2023

**Document Version**

Final published version

**Published in**

ACS Sustainable Chemistry and Engineering

**Citation (APA)**

Baumgartner, L. M., Kahn, A., Hoogland, M., Bleeker, J., Jager, W. F., & Vermaas, D. A. (2023). Direct Imaging of Local pH Reveals Bubble-Induced Mixing in a CO<sub>2</sub> Electrolyzer. *ACS Sustainable Chemistry and Engineering*, 11(28), 10430-10440. <https://doi.org/10.1021/acssuschemeng.3c01773>

**Important note**

To cite this publication, please use the final published version (if applicable).  
Please check the document version above.

**Copyright**

Other than for strictly personal use, it is not permitted to download, forward or distribute the text or part of it, without the consent of the author(s) and/or copyright holder(s), unless the work is under an open content license such as Creative Commons.

**Takedown policy**

Please contact us and provide details if you believe this document breaches copyrights.  
We will remove access to the work immediately and investigate your claim.

# Direct Imaging of Local pH Reveals Bubble-Induced Mixing in a CO<sub>2</sub> Electrolyzer

Lorenz M. Baumgartner, Aron Kahn, Maxime Hoogland, Jorrit Bleeker, Wolter F. Jager, and David A. Vermaas\*



Cite This: *ACS Sustainable Chem. Eng.* 2023, 11, 10430–10440



Read Online

ACCESS |



Metrics & More




Article Recommendations



Supporting Information

**ABSTRACT:** Electrochemical CO<sub>2</sub> reduction poses a promising pathway to produce hydrocarbon chemicals and fuels without relying on fossil fuels. Gas diffusion electrodes allow high selectivity for desired carbon products at high current density by ensuring a sufficient CO<sub>2</sub> mass transfer rate to the catalyst layer. In addition to CO<sub>2</sub> mass transfer, the product selectivity also strongly depends on the local pH at the catalyst surface. In this work, we directly visualize for the first time the two-dimensional (2D) pH profile in the catholyte channel of a gas-fed CO<sub>2</sub> electrolyzer equipped with a bipolar membrane. The pH profile is imaged with operando fluorescence lifetime imaging microscopy (FLIM) using a pH-sensitive quinolinium-based dye. We demonstrate that bubble-induced mixing plays an important role in the Faradaic efficiency. Our concentration measurements show that the pH at the catalyst remains lower at  $-100 \text{ mA cm}^{-2}$  than at  $-10 \text{ mA cm}^{-2}$ , implying that bubble-induced advection outweighs the additional OH<sup>-</sup> flux at these current densities. We also prove that the pH buffering effect of CO<sub>2</sub> from the gas feed and dissolved CO<sub>2</sub> in the catholyte prevents the gas diffusion electrode from becoming strongly alkaline. Our findings suggest that gas-fed CO<sub>2</sub> electrolyzers with a bipolar membrane and a flowing catholyte are promising designs for scale-up and high-current-density operation because they are able to avoid extreme pH values in the catalyst layer.

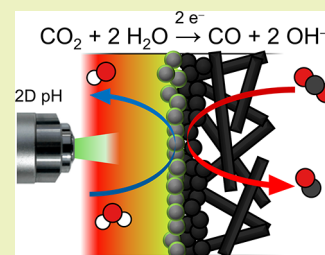

**KEYWORDS:** CO<sub>2</sub> reduction, operando fluorescence imaging, gas diffusion electrode, bipolar membrane, pH imaging

## INTRODUCTION

Electrochemical CO<sub>2</sub> reduction (CO<sub>2</sub>R) could be a promising process to make renewable energies more effective in mitigating climate change<sup>1,2</sup> and to ensure energy security. CO<sub>2</sub>R could utilize electricity from renewable power sources for the sustainable production of hydrocarbon chemicals and fuels.<sup>3</sup> To this end, CO<sub>2</sub> can be captured from point sources,<sup>4</sup> directly from the air,<sup>5</sup> or the ocean,<sup>6</sup> and then reduced electrochemically. Depending on the cathode catalyst, useful chemical intermediates can be formed (e.g., Ag: CO,<sup>7</sup> Sn: HCOOH,<sup>8</sup> or Cu: C<sub>2</sub>H<sub>4</sub>, CH<sub>4</sub>, or ethanol<sup>9</sup>).<sup>10</sup> These could then be further processed into organic chemicals or hydrocarbon fuels using established industrial processes (Fischer–Tropsch or methanol synthesis).<sup>3</sup>

To make electrochemical CO<sub>2</sub> reduction (CO<sub>2</sub>R) economically viable, the process has to be operated at a high current density (e.g.,  $j \geq -200 \text{ mA cm}^{-2}$ ),<sup>11</sup> a high Faradaic efficiency (e.g.,  $FE_{\text{CO}} \geq 95\%$ ),<sup>12</sup> and a low cell potential (e.g.,  $E_{\text{cell}} \leq 3 \text{ V}$ ).<sup>13</sup> The CO<sub>2</sub> mass transfer to the catalyst strongly affects the *FE* for the desired carbon products (e.g., CO). If the mass transfer of CO<sub>2</sub> cannot keep up with the supply of electrons at sufficiently high *j*, the excess current is consumed in the hydrogen evolution reaction (HER), leading to a decrease in  $FE_{\text{CO}}$ . The introduction of gas diffusion electrodes (GDEs) has made it possible to maintain a high *FE* for carbon products at a high *j* by ensuring a sufficient CO<sub>2</sub> mass transfer rate to the catalyst layer (CL).<sup>14</sup>


CO<sub>2</sub> electrolysis with flowing catholyte is typically carried out with pH-neutral electrolytes such as KHCO<sub>3</sub><sup>15,16</sup> or, less commonly, K<sub>2</sub>SO<sub>4</sub>.<sup>17,18</sup> While, for example, the bulk of a 1 M KHCO<sub>3</sub> electrolyte has a CO<sub>2</sub> solubility limit of 0.034 mM and a pH of 7.8, the local concentration of CO<sub>2</sub> and pH at the actual catalyst surface can deviate depending on the process conditions.<sup>19</sup> The local pH at the catalyst surface still affects the *FE* by changing the relative reaction rates of CO<sub>2</sub>R and HER. While neutral pH values are not detrimental to CO<sub>2</sub>R,<sup>15,20</sup> highly alkaline pH values reduce the reaction rate because of the carbonate equilibrium. The local pH increases due to hydroxide formation in the CO<sub>2</sub>R reaction ( $\text{CO}_2 + \text{H}_2\text{O} + 2\text{e}^- \rightarrow \text{CO} + 2\text{OH}^-$ ). At a sufficiently high pH, CO<sub>2</sub> forms bicarbonate ( $\text{CO}_2 + \text{OH}^- \leftrightarrow \text{HCO}_3^-$ ;  $\text{p}K_{\text{a},1} = 6.4$ ) and carbonate ( $\text{HCO}_3^- + \text{OH}^- \leftrightarrow \text{CO}_3^{2-}$ ;  $\text{p}K_{\text{a},2} = 10.3$ ) in homogeneous buffer reactions.<sup>21</sup> Therefore, a high local pH in the CL can diminish the *FE* for CO<sub>2</sub>R.<sup>22</sup>


Also a too low pH can have a negative impact on  $FE_{\text{CO}}$ . Because the exchange current density of proton reduction ( $2\text{H}^+$

**Received:** March 25, 2023

**Revised:** June 7, 2023

**Published:** July 3, 2023



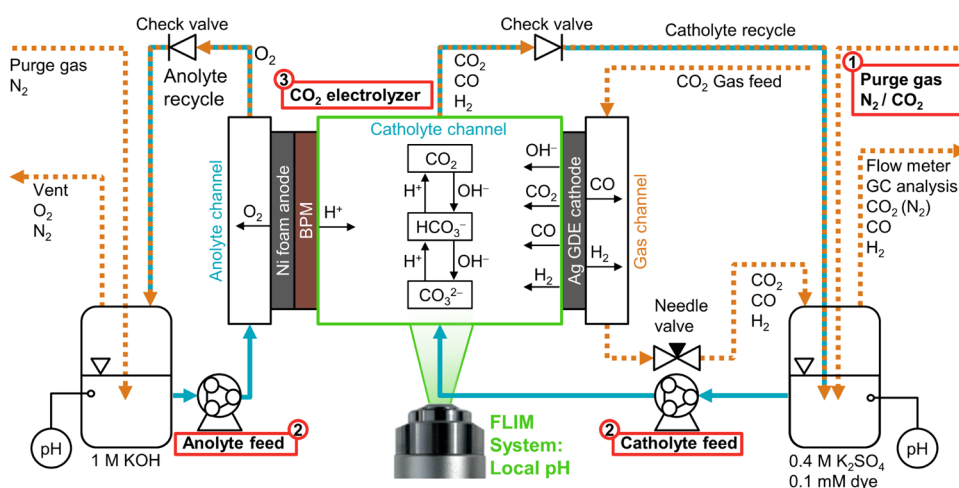

**Figure 1.** Process flow diagram of the CO<sub>2</sub> electrolysis setup with *operando* FLIM of the local catholyte pH. Process parameters: (1) Catholyte purge gas: N<sub>2</sub> purge or saturation with CO<sub>2</sub>; (2) liquid flow rate: 0.9 or 9.0 mL min<sup>-1</sup> ( $\Delta Re = 5$  or  $Re = 50$  in catholyte channel); (3) current density:  $-10$ ,  $-50$ ,  $-100$  mA cm<sup>-2</sup>. The anolyte and the catholyte channel were separated with a bipolar membrane (BPM). The backpressure of both electrolyte streams was set by check valves. Both electrolytes were recirculated to their respective reservoirs, in which the gaseous products were removed with a purge gas. The bulk pH inside the reservoir was measured with a pH meter. The CO<sub>2</sub> gas feed was humidified to 85% relative humidity (r.h.) at 20 °C and passed into the gas channel of the electrolysis cell at a flow rate of 10 mL min<sup>-1</sup>. The gas backpressure was controlled with a manual needle valve. The composition of the cathode product gas was analyzed with gas chromatography (GC). The flow rate was measured with a bubble flow meter. A more detailed process flow diagram is available in the Supporting Information (SI) (Figure S4).

+ 2e<sup>-</sup> → H<sub>2</sub>) is 3 orders of magnitude higher compared to water reduction (H<sub>2</sub>O + 2e<sup>-</sup> → 2OH<sup>-</sup>),<sup>23</sup> the HER is significantly faster in acidic conditions. Therefore,  $FE_{H_2}$  can increase at low pH values, especially if the CO<sub>2</sub>R is limited by CO<sub>2</sub> mass transfer.<sup>20</sup> At high current densities, however, the locally higher pH near the catalyst surface can alleviate the low selectivity for CO<sub>2</sub>R.


In conclusion, we expect high  $FE$  for the desired CO<sub>2</sub>R products as long as there is sufficient CO<sub>2</sub> mass transfer to the catalyst surface and the local pH is not too acidic or too alkaline. It can be challenging, however, to achieve these ideal conditions in practice because they are affected by many interdependent phenomena (e.g., electrochemical reactions, homogeneous reactions, and mass transfer in gas and liquid phases). For this reason, researchers have tried to gain a deeper understanding of the reaction system with numerical simulations in one dimension (1D)<sup>24,25</sup> or two dimensions (2D).<sup>22,26,27</sup> The reaction system is further complicated by the evolution of gas bubbles on the electrodes, which can affect the energy efficiency by introducing overpotentials.<sup>28,29</sup>

Experimental characterization techniques<sup>30,31</sup> can be used to complement these numerical studies. For example, absorption spectroscopy can determine the pH at plate cathode surfaces<sup>32,33</sup> or inside a bipolar membrane (BPM).<sup>34</sup> *Operando* NMR has been used to study aqueous CO<sub>2</sub> electrolysis on silver or copper plate electrodes.<sup>35,36</sup> *Operando* Raman microscopy has allowed us to measure the local (bi)carbonate concentrations and pH values depending on the distance from the cathode in a liquid-fed<sup>37</sup> or gas-fed<sup>38</sup> CO<sub>2</sub> electrolysis flow cell. This technique is limited by the relatively low intensity of the Raman effect,<sup>39</sup> which restricts the imaging speed (typical acquisition time:  $\geq 10$  min).<sup>40,41</sup> Fluorescence microscopy, in contrast, can use the strong fluorescence signal of suitable probe molecules to measure spatially resolved intensity more rapidly,<sup>42</sup> allowing much shorter acquisition times (e.g., 5 s).<sup>43</sup> In another example, Leenheer et al. assessed the activity of water-splitting

electrocatalysts by recording 2D images with a pH-sensitive ratiometric dye.<sup>44</sup>

Fluorescence lifetime imaging microscopy (FLIM) is an imaging technique that uses special fluorescence lifetime probe molecules. Because these dye molecules change their fluorescence lifetime depending on their local environment (e.g., pH or concentration of certain species), FLIM can measure the corresponding spatially resolved local environment of a sample based on the fluorescence lifetime instead of the absolute intensity.<sup>42,45</sup> This makes FLIM especially useful for applications in which inhomogeneous excitation or differences in dye concentration can affect the intensity. While FLIM has been predominantly used to study biological samples,<sup>46,47</sup> it has also enabled the study of ion transport in electrochemical systems, in which the electromigration of charged dye molecules can lead to concentration gradients that would complicate the use of intensity-based imaging. For example, Benneker et al. used FLIM to study the mass transfer of NaCl in a microfluidic desalination cell.<sup>48</sup> In another example, de Valença et al. investigated the mass transfer of Cu<sup>2+</sup> ions in an electrochemical cell.<sup>43,49</sup> So far, only a limited number of studies have applied FLIM to CO<sub>2</sub> electrolysis. For example, Kalde et al. used FLIM to qualitatively determine electrochemically active areas in a microfluidic model of a GDE.<sup>50</sup>

In this work, we study the electrochemical performance and the local pH profile of a CO<sub>2</sub> electrolyzer with a flowing K<sub>2</sub>SO<sub>4</sub> catholyte and a bipolar membrane. The effects of process parameters, i.e., current density, CO<sub>2</sub> saturation, and catholyte flow rate, on the Faradaic efficiency for CO are investigated. For the first time, the 2D pH profile in a CO<sub>2</sub> electrolyzer catholyte channel was visualized experimentally using *operando* FLIM with a pH-sensitive quinolinium dye. This dye was recently developed by us and allows pH measurements between pH 6–9 and 11–13.<sup>51</sup> We demonstrate that bubble-induced mixing plays an important role in the pH profile in the catholyte and the Faradaic efficiency.

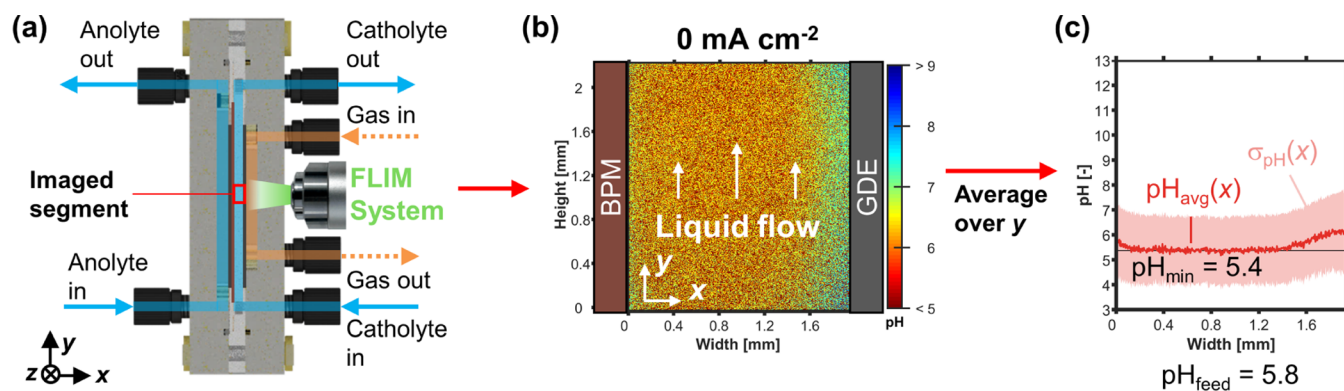

**Figure 2.** Operando FLIM validation. (a) Schematic of the flow cell: Imaging of catholyte flow channel segment in  $x$ – $y$  plane. (b) 2D pH profile over channel height ( $y$ ) and width ( $x$ ). Left: The BPM produces  $H^+$  ions during operation. Right: The GDE is fed  $CO_2$  from the gas channel (not visible). (c) The 1D pH profile,  $pH_{avg}(x)$ , was averaged over the height of the channel segment. The shaded red area indicates the standard deviation of the pH value,  $\sigma_{pH}(x)$ . The minimum value of  $pH_{avg}(x)$  is  $pH_{min}$ . The maximum value of  $pH_{avg}(x)$  is  $pH_{max}$ . The pH value of the catholyte feed,  $pH_{feed}$ , was measured with a pH meter.

## EXPERIMENTAL METHODS

The  $CO_2$  electrolysis with *operando* fluorescence lifetime imaging microscopy (FLIM) was carried out with the setup shown in Figure 1. The 3-compartment electrolysis cell (Figures S1–S3) was equipped with a porous nickel foam as the anode. The cathode GDE was prepared by depositing an Ag catalyst layer ( $1.0 \text{ mg Ag cm}^{-2}$ , 20 wt % Nafion) on an SGL 39BC gas diffusion layer.<sup>52</sup> Its active area had a height of 25 mm and an electrode width of 4 mm ( $1 \text{ cm}^2$ ). The adjacent catholyte channel had a matching depth of 4 mm. The gap width between the GDE and the BPM was 2 mm (Figure S2). The BPM separated the anolyte (1 M KOH) and catholyte (0.4 M  $K_2SO_4$ , 0.1 mM fluorescent dye) ensuring that no significant bulk pH change occurred. Both electrolytes were recirculated during the experiment (Figure 1). The humidified  $CO_2$  feed was supplied to the GDE in flow-by mode. The backpressure of the gas compartment was controlled with a needle valve. A purge gas stream was used to flush the product gases from the catholyte reservoir.

The effects of three process parameters were investigated (Figure 1): The catholyte was continuously purged (1) with  $N_2$  or  $CO_2$  purge gas. The Reynolds number (2) in the catholyte channel,  $Re$ , was set to 5 or 50 by adjusting the liquid flow rate (see Section S2.1 in the SI). After adapting the gas backpressure to achieve a flow-by regime at the GDE, we set a series of current densities (3) in galvanostatic mode ( $-10$ ,  $-50$ , and  $-100 \text{ mA cm}^{-2}$ ). The equilibration time for each process parameter set was 20 min. Then, we performed three measurements of the gas flow rate and three injections with a gas chromatography (GC) system to determine the Faradaic efficiency of the cathode side.

In parallel, we used the FLIM system to record a series of local pH images at three different heights of the flow cell (Figure S5). A more detailed experimental procedure is available in Section 2.2 in the SI. The FLIM system (Figure S6) used a diode laser (405 nm, 20 MHz, 300 mW) as the excitation light source. The modulated laser light passed through a spinning disk confocal unit, which uses disks with microlenses and pinholes to restrict the excitation and emission light paths to a single focal plane.<sup>53</sup> The basis of the system was an inverted microscope with a  $5\times$  objective to record images with a width of 2.4 mm and a height of 2.2 mm. The microscope was focused on the center of the catholyte channel, which corresponds to a depth of 2 mm (Figure S5). The focused laser light excited the fluorescent quinolinium dye in the catholyte (0.1 mM).<sup>51,54</sup> The fluorescent light emitted by the dye was filtered by the spinning disk unit and recorded with the FLIM camera ( $512 \times 470$  pixels). The camera used the frequency-domain technique to record fluorescent lifetime images.<sup>45</sup> The lifetime images are calculated from 6 phase shift images, which each have an exposure time of 75 ms. This results in a total imaging time of 450 ms per frame. We calibrated the FLIM system with an in-line titration setup (Figure S6). The resulting calibration curve was used to convert fluorescent lifetime images to local pH images (Figure S7).

## RESULTS AND DISCUSSION

We carried out a series of galvanostatic  $CO_2$  electrolysis experiments with *operando* FLIM to image the local pH in the catholyte channel. Supplementary calculations, additional results, and the numerical values of plotted data are included in the Supporting Information (SI).

**Fluorescence Lifetime Imaging Microscopy (FLIM) Applied to Operando  $CO_2$  Electrolysis.** For validation, the local pH of a catholyte channel segment with the dimensions of  $2 \times 2 \text{ mm}$  was imaged (Figure 2a), which means one pixel covers about  $5 \mu\text{m} \times 5 \mu\text{m}$ . For a current density of  $0 \text{ mA cm}^{-2}$ , the 2D pH profile in Figure 2b is obtained. The corresponding 1D pH profile is generated by averaging over the  $y$ -coordinate of the segment (Figure 2c). The catholyte bulk pH,  $pH_{min}$ , of  $5.4 \pm 1.4$  is in good agreement with the feed pH,  $pH_{feed}$ , of 5.8, which was obtained from an independent measurement with a pH meter (Figure 2c). The standard deviation of the average pH,  $\sigma_{pH}(x)$ , may seem relatively large, but the 2D image (Figure 2b) shows that the noise is randomly distributed in the  $y$ -direction, which makes the profile of  $pH_{avg}$  statistically reliable. The FLIM images show an increased average pH,  $pH_{avg}(x)$ , close to the walls on both sides of the channel (Figure 2a). This is a systematic error, which most likely originates from the fluorescence of the adjacent poly(ethylene terephthalate) (PET) gaskets (Figure S9), which emit a constant fluorescence lifetime corresponding to about pH 6. Because this signal is convoluted with the fluorescence response of the pH-sensitive dye in the catholyte, our images overestimate the pH at the wall when the actual pH < 6, and probably underestimate the true  $pH_{max}$  when an alkaline boundary layer forms during operation.

The FLIM results in Figure 2 demonstrate that we can map the pH in a 2 mm wide  $CO_2$  electrolyzer flow cell in 2D, accepting noise at the micrometer scale and an offset near the edges. The quinolinium-based dye is most sensitive to pH changes between pH 6 and 9 (Figure S7). This allows us to study the local pH near the GDE when a current is applied to the cell.

**Performance Indicators for BPM-Based  $CO_2$  Electrolyzers.** Our electrolyzer operates with a similar performance as BPM electrolyzers with flowing catholyte reported in the literature (Table 1). The  $E_{cell}$  of our system is higher than that reported by Chen et al. (4.5 vs. 3.5 V) because of the wider catholyte gap,  $d_{cath}$  (2 vs. 1.3 mm), and lower operating temperature,  $T$  (20 vs. 60 °C).<sup>18</sup> De Mot et al. achieved a



**Table 1. Electrochemical Performance of Gas-Fed CO<sub>2</sub> Electrolyzers with BPM and Flowing Catholyte<sup>a</sup>**


parameter	this work	Chen et al. <sup>18</sup>	De Mot et al. <sup>55</sup>
GDE catalyst	1.0 mg Ag cm <sup>-2</sup>	0.5 mg SnO <sub>2</sub> cm <sup>-2</sup>	2.5 mg Ag cm <sup>-2</sup>
<i>j</i>	-100 mA cm <sup>-2</sup>	-100 mA cm <sup>-2</sup>	-100 mA cm <sup>-2</sup>
<i>FE</i>	CO: 70%	HCOOH: 73%	CO: 94%
catholyte	0.4 M K <sub>2</sub> SO <sub>4</sub>	0.4 M K <sub>2</sub> SO <sub>4</sub>	0.5 M KHCO <sub>3</sub>
pH <sub>feed</sub>	5.5	na	7.6
<i>d</i> <sub>cath</sub>	2.0 mm	1.3 mm	1.0 mm
<i>T</i>	20 °C	60 °C	60 °C
<i>E</i> <sub>cell</sub>	4.5 V	3.5 V	4.6 V

<sup>a</sup>The nickel anode was pressed against the BPM in zero-gap configuration and supplied with KOH anolyte. The current density is *j*. The Faradaic efficiency is *FE*. The bulk pH of the catholyte feed is pH<sub>feed</sub>. The thickness of the catholyte gap between BPM and cathode GDE is *d*<sub>cath</sub>. The electrolyzer temperature is *T*. The cell potential is *E*<sub>cell</sub>. This work: The *FE*<sub>CO</sub> of 70% was measured for a Reynolds number, *Re*, of 5, which corresponds to a catholyte flow rate of 0.9 mL min<sup>-1</sup>. The catholyte was purged with N<sub>2</sub> to remove dissolved CO<sub>2</sub>.

significantly higher *FE*<sub>CO</sub> of 94%.<sup>55</sup> This improvement cannot be explained by their higher catalyst loading because the effect of loading on *FE*<sub>CO</sub> levels off after about 1.25 mg Ag cm<sup>-2</sup>.<sup>56</sup> Instead, the higher *FE*<sub>CO</sub> can probably be attributed to the difference in catholyte. We used 0.4 M K<sub>2</sub>SO<sub>4</sub>, a neutral electrolyte without pH buffering capacity. De Mot et al., in contrast, used 0.5 M KHCO<sub>3</sub>,<sup>55</sup> which suppresses the HER from proton reduction and can buffer the pH in the CL.<sup>57</sup>

It is interesting that our electrolyzer exhibits a very poor *FE*<sub>CO</sub> at -10 mA cm<sup>-2</sup> (Figure 3) because CO<sub>2</sub> mass transfer limitation does yet not occur at such a low *j*.<sup>58</sup> Further, we have previously demonstrated that this GDE model can sustain a *FE*<sub>CO</sub> of 89–74% for *j* ranging from -10 to -200 mA cm<sup>-2</sup> with a 1 M KHCO<sub>3</sub> catholyte.<sup>59</sup> Therefore, the poor *FE*<sub>CO</sub> at -10 mA cm<sup>-2</sup> is probably caused by differences in the local pH in the CL when using K<sub>2</sub>SO<sub>4</sub> catholyte.

We expect the K<sub>2</sub>SO<sub>4</sub> catholyte in this experiment to offer minimal pH buffering (Figure 3), especially when the catholyte is purged with N<sub>2</sub>, removing dissolved CO<sub>2</sub> and preventing homogeneous buffering reactions in the bulk of the liquid. Therefore, the catholyte can undergo more extreme pH changes, which could lead to poor conditions for the CO<sub>2</sub>R in the CL. For example, CO<sub>2</sub> from the gas phase might neutralize the OH<sup>-</sup> produced at the catalyst surface by forming HCO<sub>3</sub><sup>-</sup> and CO<sub>3</sub><sup>2-</sup>. Then, the H<sup>+</sup> produced at the BPM could net acidify the catholyte.<sup>18</sup> On the other hand, the OH<sup>-</sup> formation inside the CL might instead lead to a locally high pH if the removal of ionic

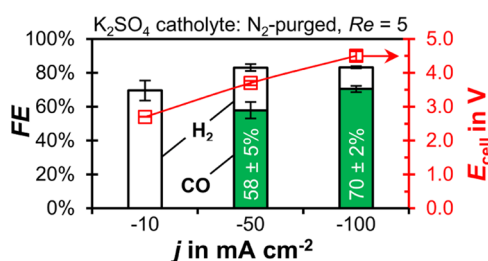

**Figure 3.** CO<sub>2</sub> reduction performance for gas-fed CO<sub>2</sub> electrolyzers with N<sub>2</sub>-purged catholyte at *Re* = 5. The *FE* for CO and H<sub>2</sub> is plotted as a function of current density, *j*, on the left *y*-axis. The error bars represent the estimated standard errors of three GC injections. The cell potential, *E*<sub>cell</sub>, is plotted on the right *y*-axis.

product species (OH<sup>-</sup>, HCO<sub>3</sub><sup>-</sup>, and CO<sub>3</sub><sup>2-</sup>) by the catholyte is too slow.<sup>60</sup> To clarify the effect of low current density on the local pH in the CL, we analyze the catholyte pH profiles through FLIM for different current densities (Figure 4).


**Bubble-Induced Mixing Limits pH Increase and Enhances Mass Transfer.** At -10 mA cm<sup>-2</sup>, the FLIM images show that the flowing catholyte prevents the acidification of the GDE (Figure 4a). Instead, we see the development of an alkaline boundary layer at the GDE, which originates from the OH<sup>-</sup> released by the electrochemical reaction in the CL.<sup>19</sup> Among all of the current densities, -10 mA cm<sup>-2</sup> exhibits the highest local pH close to the CL (Figure 4a: pH<sub>max</sub> = 7.4).

At -50 mA cm<sup>-2</sup>, the boundary layer is significantly thinner and pH<sub>max</sub> is lower despite the 5x increase in OH<sup>-</sup> formation rate (Figure 4b). Further, we observe the evolution of H<sub>2</sub> and/or CO bubbles at the cathode surface (Figure S11). We hypothesize that the growth, break-off, and the wake flow of these bubbles lead to bubble-induced mixing between the boundary layer and the bulk of the catholyte.<sup>61,62</sup> This additional mass transfer mechanism enhances the removal of product ions from the CL, which decreases pH<sub>max</sub> to 6.5 (Figure 4b).

Gas evolution at electrodes influences the overpotentials of the electrolysis cell.<sup>28,63</sup> We use this effect to compare the bubble formation rate for increasing *j* (Figure S12). At -10 mA cm<sup>-2</sup>, we observe an average of 1 bubble being released every 2 min (Figure S12a). Bubbles form at such a low frequency because the formation of dissolved products (cathode: H<sub>2</sub> and CO) is relatively slow compared to the diffusion into the gas channel or into the bulk of the flowing catholyte, which leads to a low degree of oversaturation. At higher *j*, the oversaturation rises due to the more rapid formation of products, which increases the rate of nucleation, growth, and release of bubbles at the cathode.<sup>64,65</sup> For example, at -50 mA cm<sup>-2</sup>, we estimate that around 20 bubbles are released every 2 min (Figure S12b). Therefore, bubble-induced mixing plays a much more important role at *j* = -50 mA cm<sup>-2</sup> and beyond.

We hypothesize that the local pH in the porous CL has to be sufficiently close to the p*K*<sub>a</sub> of the bicarbonate reaction for high *FE*<sub>CO</sub>. This condition is necessary to ensure that CO<sub>2</sub> can be available as a dissolved gas. Due to the limitations of our technique, the pH in the CL cannot be measured directly. However, we can try to use pH<sub>max</sub> as an approximation. At -10 mA cm<sup>-2</sup>, for example, pH<sub>max</sub> reaches a value of 7.4, which might be too high compared to p*K*<sub>a,1</sub> = 6.4. The true pH directly next to the GDE is probably higher than 7.4 because the fluorescence of the PET gasket makes the value appear closer to pH 6. As a result of the high local pH, this experiment yields a poor *FE*<sub>CO</sub> of 0%. At -50 mA cm<sup>-2</sup>, the pH<sub>max</sub> of 6.5 is more favorable and *FE*<sub>CO</sub> rises from 0 to 58% (Figure 3). We note that for unbuffered electrolytes (e.g., K<sub>2</sub>SO<sub>4</sub>), the equilibrium pH of a CO<sub>2</sub>-saturated solution lies close to p*K*<sub>a,1</sub> = 6.4. For buffered electrolytes, the equilibrium pH is higher (e.g., 1 M KHCO<sub>3</sub>: pH = 7.8), which probably influences the local availability of CO<sub>2</sub> in the CL.<sup>19</sup>

At -100 mA cm<sup>-2</sup>, the thickness of the pH boundary layer and pH<sub>max</sub> increase again (Figure 4c). We also observed increased bubble flow in the catholyte, which leads to the inhomogeneity in the 2D pH profile. The OH<sup>-</sup> formation rate in the CL is directly proportional to *j*. In contrast, we assume that the bubble-induced mass transfer is roughly proportional to *j*<sup>0.5</sup>; however, it is challenging to provide an explicit relationship (see next paragraph). Based on this assumption, we suspect that the formation of OH<sup>-</sup> in the CL outpaces the removal through

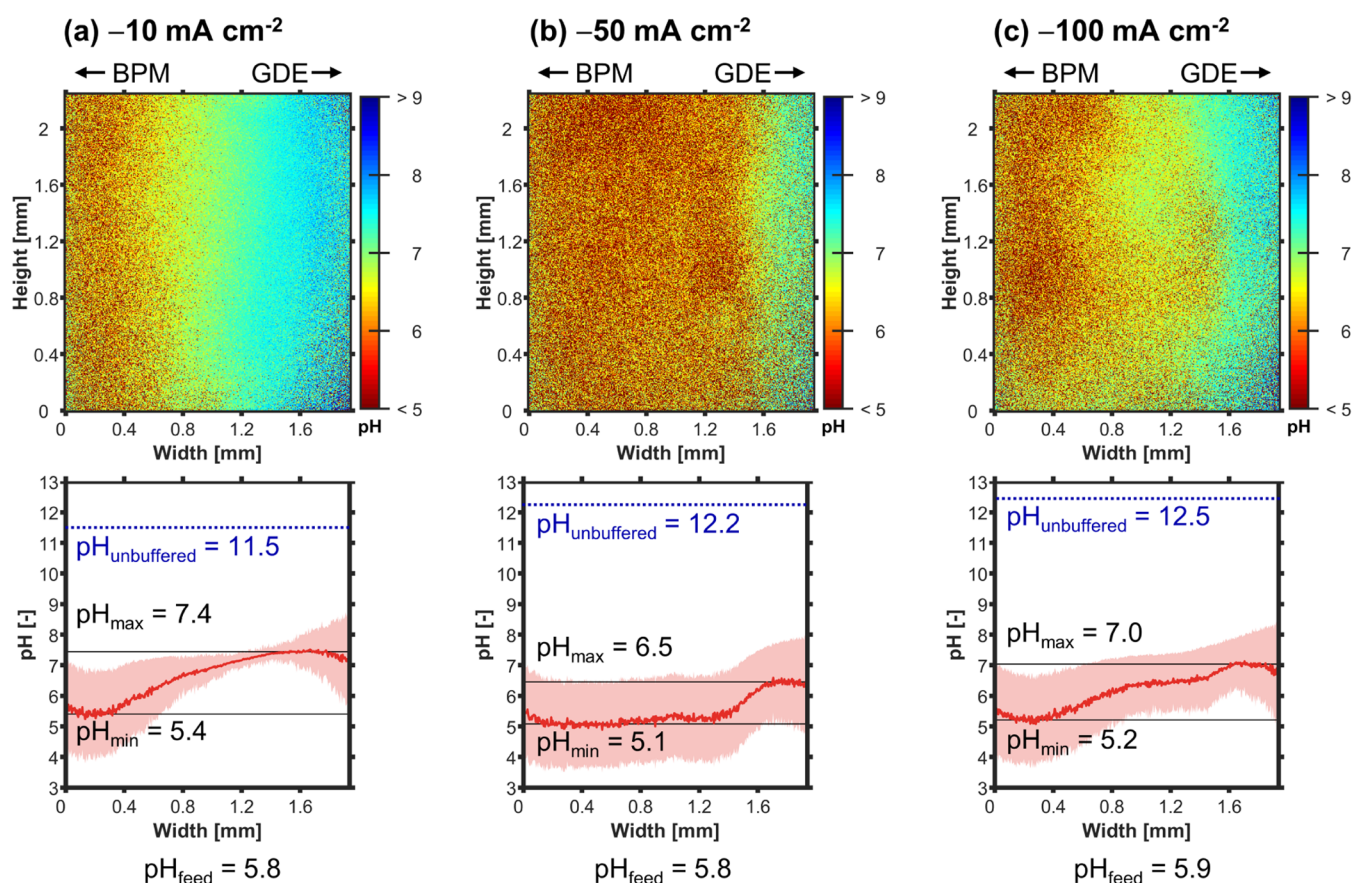

**Figure 4.** FLIM: Catholyte pH profiles at the middle of channel height ( $y = 12.5$  mm) with  $N_2$ -purged catholyte at  $Re = 5$ . Left: The BPM produces  $H^+$  ions during operation. Right: The GDE forms  $OH^-$  and is fed  $CO_2$  from the gas channel (not visible). (a–c) Effect of increasing  $j$ . Top: 2D pH profile over channel height and width. Bottom: The pH profile,  $pH_{avg}$ , was averaged over the height of the channel segment shown in the top panel. The shaded red area indicates the standard deviation of the pH value. The minimum value of  $pH_{avg}$  is  $pH_{min}$ . The maximum value of  $pH_{avg}$  is  $pH_{max}$ . The pH value of the catholyte feed,  $pH_{feed}$ , was measured with a pH meter. The blue dotted line indicates the value of the unbuffered pH limit,  $pH_{unbuffered}$ , which we would expect if no neutralization with  $H^+$  occurred, no homogeneous buffering reactions took place, and  $OH^-$  was evenly mixed across the channel's width (see Section 3.2 in the SI).

bubble-induced mixing at sufficiently high  $j$ . For this reason,  $pH_{max}$  in the catholyte is higher at  $-100$  mA  $cm^{-2}$  than for the  $-50$  mA  $cm^{-2}$  case (Figure 4b vs. c: 6.5 vs. 7.0). It is interesting that the corresponding  $FE_{CO}$  increases from 58 to 70% (Figure 3). Perhaps the higher pH in the CL suppresses the HER by slowing down the proton reduction. At the same time, the local pH might not yet be so high that dissolved  $CO_2$  is fully converted to  $HCO_3^-$  ( $pK_{a,1} = 6.4$ ).


It is difficult to accurately predict the mass transfer coefficient for bubble-induced mass transfer. The different correlations in the literature<sup>61,66,67</sup> assume that the Sherwood number for bubble-induced mass transfer,  $Sh_B$ , is proportional to the square root of the Reynolds number for gas evolution,  $Re_B$  ( $Sh_B \propto Re_B^{0.5}$ ).  $Re_B^{0.5}$  is also assumed to be proportional to  $j^{0.5}$ ; however, the different models<sup>61,67,68</sup> also make assumptions about empirical parameters (e.g., bubble coverage or geometry) that are also a function of  $j$ . Other limitations are that the correlations were often developed for a specific set of mechanisms (e.g., nonsteady diffusion,<sup>66,69</sup> or bubble release<sup>67,68</sup>) or match the experimental data poorly at  $j \leq 200$  mA  $cm^{-2}$ .<sup>61,62</sup>

For all current densities, the  $pH_{max}$  in the catholyte remains far below  $pH_{unbuffered}$  (Figure 4). This is the pH limit we would expect if (1) the released  $OH^-$  was evenly mixed across the channel's width, (2) no neutralization with  $H^+$  occurred, and (3) no homogeneous buffering reactions with  $CO_2$  took place (see

Section 3.2 in the SI). In reality, the  $CO_2$  diffusing to the CL from the gas channel must result in a significant buffering of the pH by forming  $HCO_3^-$  and  $CO_3^{2-}$  species. This is clearly visible at  $j = -10$  mA  $cm^{-2}$  because there is little bubble-induced mixing to facilitate the neutralization with  $H^+$  (Figure 4b). At  $j \geq -50$  mA  $cm^{-2}$ , the  $H^+$  released at the BPM leads to significant acidification of the catholyte, which is visible by the drop of  $pH_{min}$  (Figure 4a vs. b: 5.4 vs. 5.1). Further, the mixing and neutralization of  $H^+$  and  $OH^-$  flattens the pH profile (Figure 4b,c). The release of  $H^+$  is likely to cause an even stronger (local) acidification than  $pH_{min} = 5.1$ , but this cannot be resolved with our FLIM dye, which has a plateau in the calibration curve for  $pH \leq 5$  (Figure S7). We can follow the development of the boundary layers at  $-100$  mA  $cm^{-2}$  by looking at the different positions in the cell (Figure 5).

As the catholyte flows upward and accumulates  $OH^-$ ,  $pH_{max}$  increases along the height of the reactor (Figure 5a vs. c: 6.2 vs. 7.3). Because the increasing boundary thickness slows down the removal of  $OH^-$ , we can expect the local pH in the upper parts of the CL to become less favorable for  $CO_2R$ . To illustrate, the value of  $pH_{max}$  ( $y = 25$  mm) at  $-100$  mA  $cm^{-2}$  is similar to  $pH_{max}$  ( $y = 12.5$  mm) at  $-10$  mA  $cm^{-2}$  (Figure 5a vs. Figure 4b: 7.3 vs. 7.4), which had a  $FE_{CO}$  of 0%. This implies that scaled-up electrodes would have a poor local  $FE_{CO}$  because the top part of the electrode would mostly be producing  $H_2$ .<sup>22,27</sup> However, the



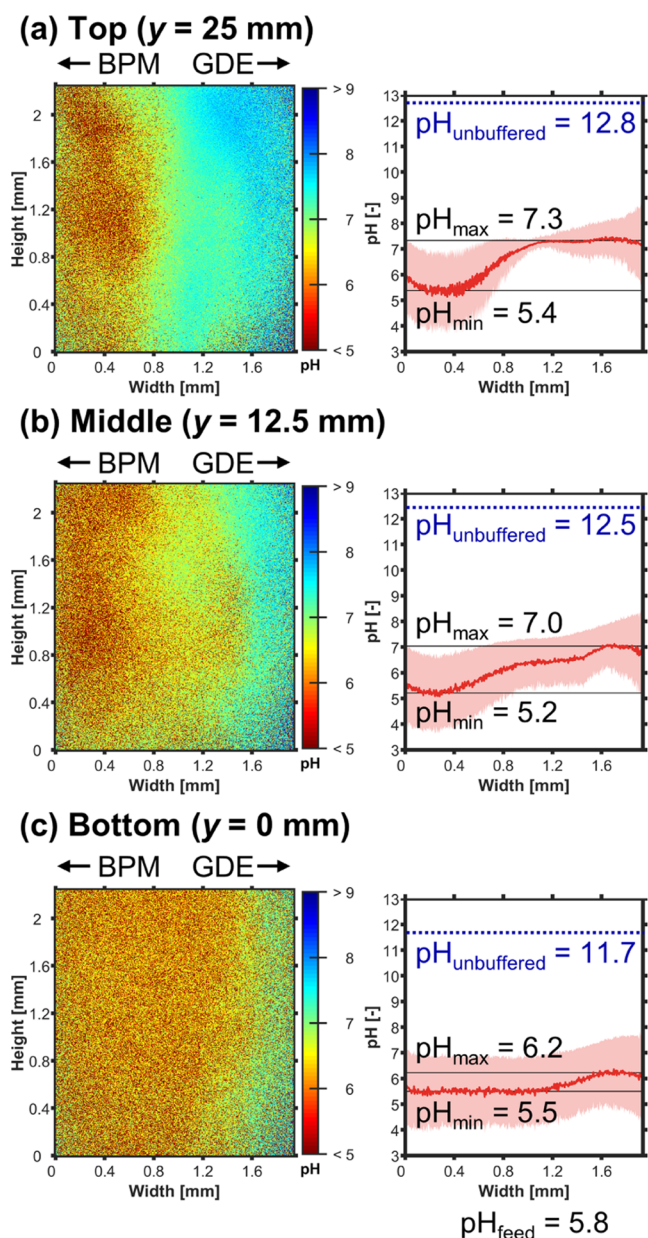


**Figure 5.** FLIM: Catholyte pH profile over the height of the electrolyzer at  $j = -100$  mA cm<sup>-2</sup> with N<sub>2</sub>-purged catholyte at  $Re = 5$ . (a–c) pH profiles at different  $y$ -positions. Left: 2D pH profile over channel height and width. Right: The pH profile,  $pH_{avg}$ , was averaged over the height of the channel segment shown in the left panel. The shaded red area indicates the standard deviation of the pH value. The minimum value of  $pH_{avg}$  is  $pH_{min}$ . The maximum value of  $pH_{avg}$  is  $pH_{max}$ . The pH value of the catholyte feed,  $pH_{feed}$ , was measured with a pH meter. The blue dotted line indicates the value of the unbuffered pH limit,  $pH_{unbuffered}$ , which we would expect if no neutralization with H<sup>+</sup> occurred, no homogeneous buffering reactions took place, and the OH<sup>-</sup> was evenly mixed across the channel's width (see Section 3.2 in the SI).

observed  $pH_{max}$  is still significantly lower than the expected  $pH_{unbuffered}$  along the height of the channel (Figure 5). This raises the question to what extent the supply of CO<sub>2</sub> from the GDE is able to buffer the increase of  $pH_{max}$ . To deconvolute the effect of current density, forced convection, and CO<sub>2</sub> saturation, we studied the cases of saturating the catholyte feed with CO<sub>2</sub> and increasing the flow rate.


**CO<sub>2</sub> Saturation Limits pH Increase and Enhances  $FE_{CO}$ .** Saturating the catholyte feed with CO<sub>2</sub> improves the  $FE_{CO}$  at all investigated current densities (Figure 6). For example, we see an increase from 70 to 77% at  $-100$  mA cm<sup>-2</sup>. This improvement can not be solely explained by the convective mass transfer of CO<sub>2</sub> from the saturated electrolyte bulk, which constitutes an additional partial current density for CO of  $-2$  mA cm<sup>-2</sup> (see Section 3.4 in the SI). In the case of limiting CO<sub>2</sub> mass transfer at  $-100$  mA cm<sup>-2</sup>, this accounts for an increase in  $FE_{CO}$  from 70 to 72%. This suggests that there are other important mechanisms improving  $FE_{CO}$ , such as a difference in local pH changing the relative reaction rates in the CL.

The saturation with CO<sub>2</sub> reduces  $pH_{max}$  at all current densities (Figure 7). For example, at  $-100$  mA cm<sup>-2</sup>,  $pH_{max}$  drops from 7.0 to 5.9 (Figure 7b vs. d). This happens through multiple mechanisms. First, the dissolved CO<sub>2</sub> acidifies the electrolyte by forming carbonic acid, which dissociates further into H<sup>+</sup> and HCO<sub>3</sub><sup>-</sup>. This is illustrated by the decrease in  $pH_{feed}$  from 5.8 to 5.3 (Figure 7a vs. c). Second, the dissolved CO<sub>2</sub> acts as a pH buffer by forming (bi)carbonate ions. This is significant because, e.g., the CO<sub>2</sub> in catholyte bulk could absorb 96% of the OH<sup>-</sup> released at  $-100$  mA cm<sup>-2</sup> (see Section 3.5 in the SI). Third, the CO<sub>2</sub>-saturated catholyte releases CO<sub>2</sub> bubbles at the BPM (Figure S14),<sup>34,70</sup> which likely increases the bubble-induced mixing. Together with bubbles released at the cathode (CO, H<sub>2</sub>), these CO<sub>2</sub> bubbles lead to the inhomogeneities seen in the 2D pH profiles (Figure 7c vs. d). Although we can not measure this effect directly, we assume that the bubble-induced mixing limits the increase of  $pH_{max}$  by enhancing the removal of product ions and also boosts the CO<sub>2</sub> flux from the catholyte bulk to the CL. In summary, saturating the catholyte with CO<sub>2</sub> improves  $FE_{CO}$  by making the local environment in the CL more favorable for CO<sub>2</sub>R.


**Catholyte Reynolds Number Interferes with Bubble-Induced Mixing.** The effect of additionally increasing the catholyte Reynolds number,  $Re$ , on  $FE_{CO}$  is less straightforward. At  $-100$  mA cm<sup>-2</sup>,  $FE_{CO}$  improves from 77 to 85% when  $Re$  is increased from 5 to 50 (Figure 8a). This might be due to additional convective CO<sub>2</sub> flux from the bulk of the catholyte. This flux is enhanced by a factor of 3.2 when  $Re$  is increased by a factor of 10 ( $Sh \propto Re^{0.5}$ ). This increased CO<sub>2</sub> flux can sustain an additional  $j_{CO}$  of  $-4$  mA cm<sup>-2</sup> (see Section 3.4 in the SI), which would correspond to an increase in  $FE_{CO}$  from 77 to 81%  $FE_{CO}$ . There might also be important other mechanisms, such as the change in local pH, possibly explaining the observed increase to 85%  $FE_{CO}$ . However, no significant improvement of  $FE_{CO}$  occurs at  $-50$  mA cm<sup>-2</sup> for the CO<sub>2</sub>-saturated case (Figure 8a). It is plausible that the effect of  $Re$  also depends on  $j$  because both process parameters can influence the local pH and the mass transfer.

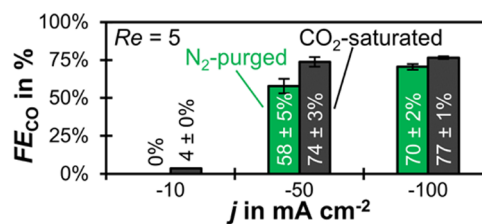

**Figure 6.** Effect of CO<sub>2</sub> saturation:  $FE_{CO}$  as a function of  $j$  for CO<sub>2</sub>-saturated and N<sub>2</sub>-purged catholyte at  $Re = 5$ . The error bars represent the estimated standard errors of three GC injections.

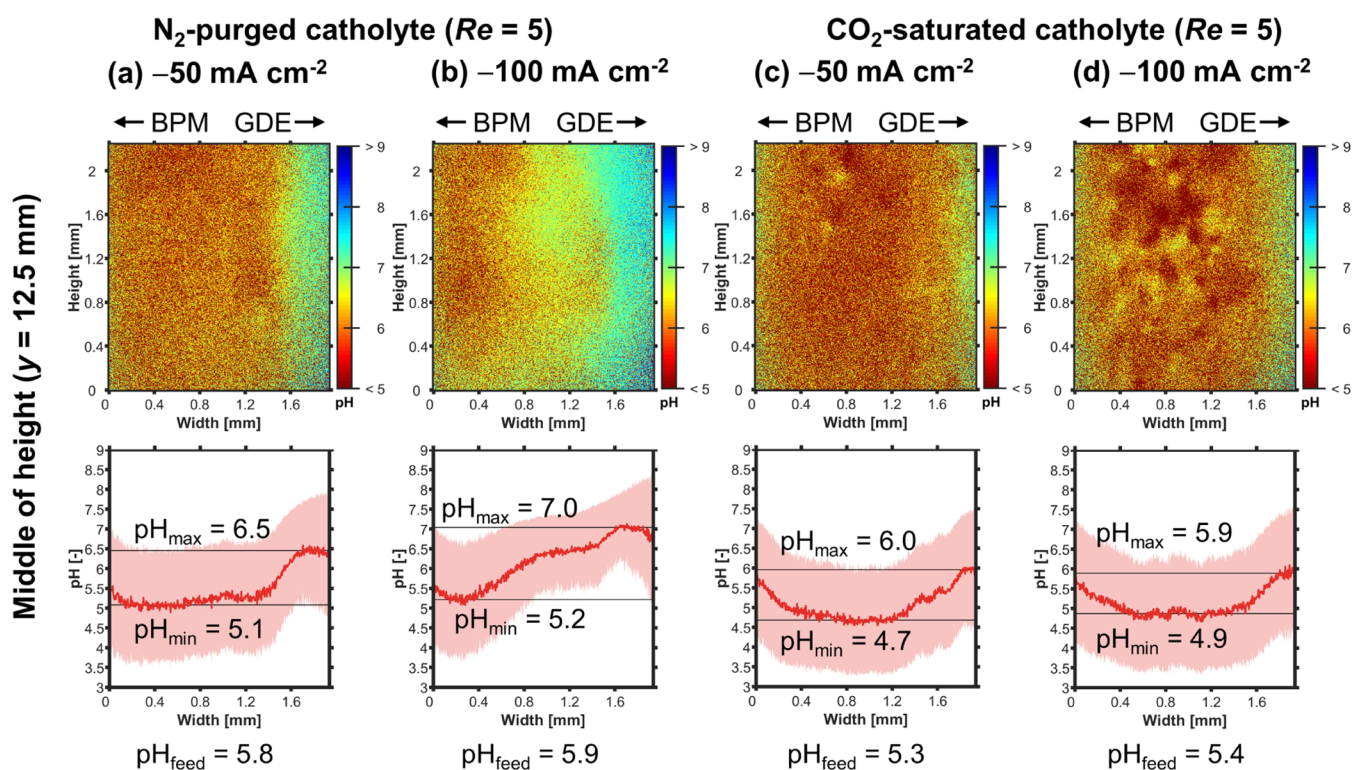

**Figure 7.** FLIM: Effect of  $CO_2$  saturation on catholyte pH profiles at the middle of channel height ( $y = 12.5 \text{ mm}$ ) at  $Re = 5$ . (a, b) Profiles for  $N_2$ -purged catholyte with increasing  $j$ . (c, d) Profiles for  $CO_2$ -saturated catholyte. Top: 2D pH profile over channel height and width. Bottom: The pH profile,  $pH_{\text{avg}}$ , was averaged over the height of the channel segment shown in the top panel. The shaded red area indicates the standard deviation of the pH value. The minimum value of  $pH_{\text{avg}}$  is  $pH_{\text{min}}$ . The maximum value of  $pH_{\text{avg}}$  is  $pH_{\text{max}}$ . The pH value of the catholyte feed,  $pH_{\text{feed}}$ , was measured with a pH meter.

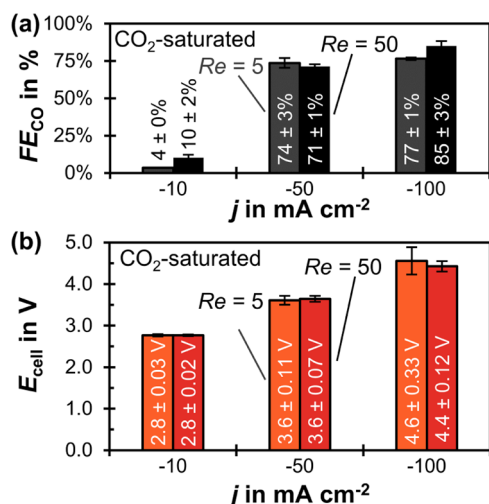

**Figure 8.** Effect of Reynolds number in catholyte channel,  $Re$ , for  $CO_2$ -saturated catholyte. (a)  $FE_{CO}$  as a function of  $j$  and  $Re$ . The error bars represent the estimated standard errors of three GC injections. (b) Average cell potential,  $E_{\text{cell}}$ , as a function of  $j$  and  $Re$ . The error bars represent the sample standard deviation. These potential values are calculated from the last 10 min of each electrolysis step.


Increasing  $Re$  can diminish the overpotentials caused by bubble evolution<sup>28</sup> in the electrolysis cell (Figure 8b). This effect is the strongest at  $-100 \text{ mA cm}^{-2}$ , for which  $E_{\text{cell}}$  drops from 4.6 to 4.4 V when  $Re$  rises from 5 to 50 (Figure 8b). The reduction in overpotentials also leads to lower potential fluctuations for all  $j$  (Figure 8b). This effect occurs because the higher volumetric

flow rate lowers the bubble nucleation rate. Bubbles evolve less frequently because dissolved product gases (e.g.,  $CO$  or  $H_2$ ) are removed more quickly, which reduces their oversaturation level.<sup>71</sup> In addition, the higher shear stress speeds up the release from the electrode surface.<sup>72</sup> As a result, bubbles form at a lower frequency and are released with smaller diameters for a higher  $Re$ .<sup>71</sup> Therefore, a higher liquid flow rate ( $Re$ ) can reduce overpotentials introduced by the evolution of gas bubbles and reduce the energy efficiency of the  $CO_2$  electrolyzer. At the process level, however, this benefit has to be weighed against the additional pumping power required to impose the higher liquid flow rate. The optimization problem is further complicated by the effects of  $Re$  on  $FE_{CO}$  and the mass transfer.<sup>71,72</sup> We can further investigate the mass transfer phenomena in the catholyte gap with snapshots of the local pH profiles (Figure 9).

To our surprise, increasing  $Re$  from 5 to 50 results in a higher local pH at the GDE. At  $-100 \text{ mA cm}^{-2}$ , for example,  $pH_{\text{max}}$  rises from 5.9 to 6.6 (Figure 9b vs. d). This is counter-intuitive because we would expect the increased forced convection to accelerate the removal of  $OH^-$ . We hypothesize that the higher catholyte  $Re$  reduces the contribution of bubble-induced mass transfer. The 10× higher liquid flow rate exerts stronger drag forces on bubbles, which hinders their lateral motion. Therefore, rising bubbles are confined closer to the surface of the electrodes and less bubble mixing perpendicular to the catholyte flow direction occurs.<sup>73</sup> This claim is supported by our 2D pH profiles showing less disturbances through bubbles and a more laminar flow profile when comparing  $Re = 50-5$  (Figure 9d vs. b).

At  $-50 \text{ mA cm}^{-2}$ , increasing  $Re$  from 5 to 50 lowers the disturbance of the liquid flow by gas bubbles, which can be seen



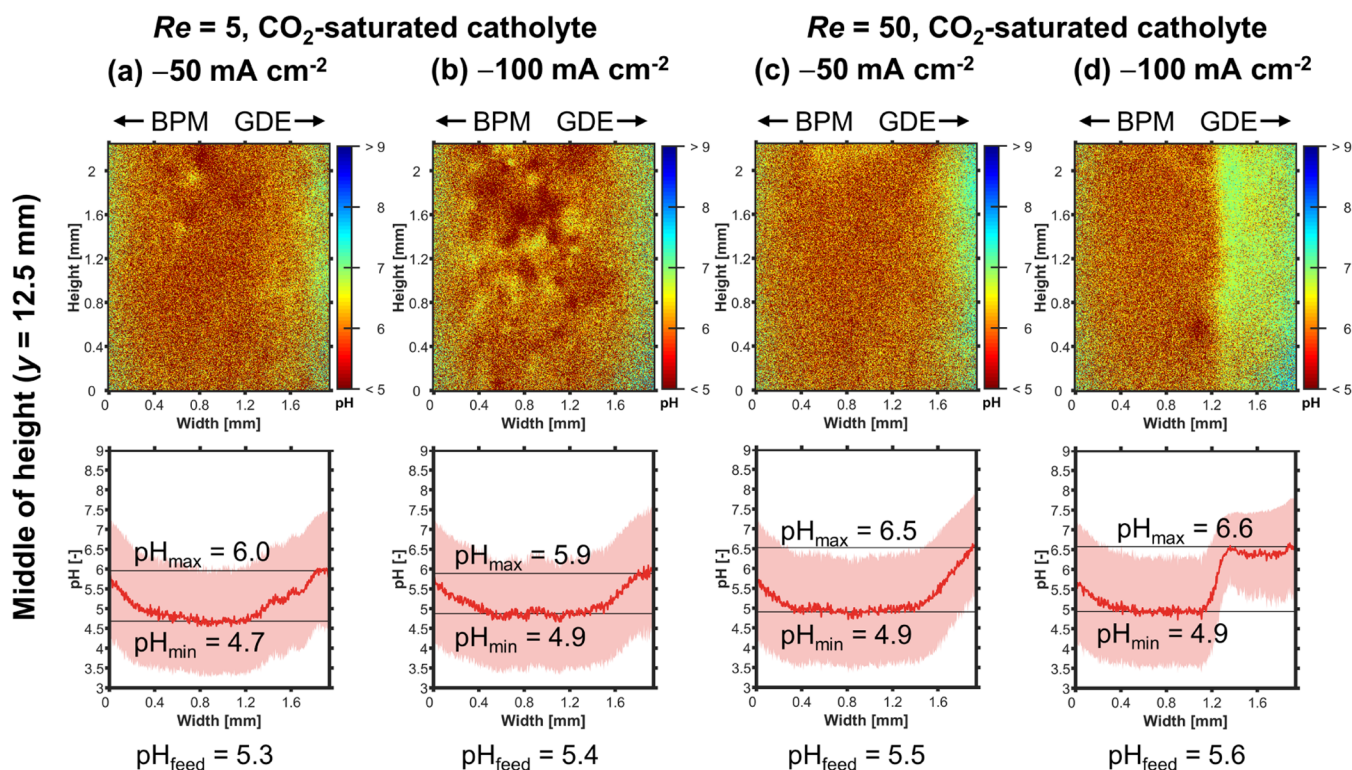


**Figure 9.** FLIM: Effect of Reynolds number,  $Re$ , on pH profiles at the middle of channel height ( $y = 12.5$  mm) with  $\text{CO}_2$ -saturated catholyte. (a, b) Profiles for  $Re = 5$  with increasing  $j$ . (c, d) Profiles for  $Re = 50$ . Top: 2D pH profile over channel height and width. Bottom: The pH profile,  $\text{pH}_{\text{avg}}$ , was averaged over the height of the channel segment shown in the top panel. The shaded red area indicates the standard deviation of the pH value. The minimum value of  $\text{pH}_{\text{avg}}$  is  $\text{pH}_{\text{min}}$ . The maximum value of  $\text{pH}_{\text{avg}}$  is  $\text{pH}_{\text{max}}$ . The pH value of the catholyte  $\text{pH}_{\text{feed}}$  was measured with a pH meter.

by the lower potential fluctuations (Figure 8b:  $\pm 0.11$  vs.  $\pm 0.07$  V). We assume this leads to a reduction in bubble-induced  $\text{CO}_2$  mass transfer from the catholyte, which is not sufficiently compensated by the additional mass transfer of  $\text{CO}_2$  through forced convection. Therefore, the  $\text{CO}_2$  mass transfer stagnates and  $FE_{\text{CO}}$  does not change significantly (Figure 8a:  $74 \pm 3$  to  $71 \pm 1\%$ ). We hypothesize that the  $\text{CO}_2$  mass transfer is more important than the local pH for both cases because their  $\text{pH}_{\text{max}}$  is close to the  $\text{p}K_{\text{a}}$  of the bicarbonate reaction (Figure 9a or c:  $\text{pH}_{\text{max}} = 6.0$  or  $6.5$  vs.  $\text{p}K_{\text{a},1} = 6.4$ ).

Increasing  $j$   $-50$  to  $-100$   $\text{mA cm}^{-2}$  at  $Re = 50$  raises the gas evolution rate in the electrolyzer, which also results in stronger potential fluctuations (Figure 8b:  $\pm 0.07$  vs.  $\pm 0.12$  V). We assume that the higher gas evolution rate enhances the contribution of bubble-induced mixing to mass transfer thereby preventing a significant change to  $\text{pH}_{\text{max}}$  despite the higher  $\text{OH}^-$  formation rate (Figure 9c vs d:  $\text{pH}_{\text{max}}$ :  $6.5$  vs.  $6.6$ ). Although  $\text{pH}_{\text{max}}$  does not change significantly,  $FE_{\text{CO}}$  raises from  $71$  to  $85\%$  (Figure 8a). This result implies that the local pH is not the only condition affecting  $FE_{\text{CO}}$ . We hypothesize that  $FE_{\text{CO}}$  rises because the additional bubble mixing also enhances the  $\text{CO}_2$  mass transfer from the bulk. The importance of the  $\text{CO}_2$  mass transfer from the catholyte bulk is further highlighted by comparing the effect of  $Re$  between the  $\text{CO}_2$ -saturated and the  $\text{N}_2$ -purged cases (Figure 8a vs. Figure S15). If  $j$  is increased from  $-50$  to  $-100$   $\text{mA cm}^{-2}$  at  $Re = 50$  for the  $\text{N}_2$  case, no significant change of  $FE_{\text{CO}}$  occurs (Figure S15:  $70 \pm 2$  to  $73 \pm 1\%$ ).

**Intermediate pH and High Current Density Lead to High Faradaic Efficiency.** The scatter plot in Figure 10 shows  $FE_{\text{CO}}$  as a function of  $\text{pH}_{\text{max}}$  and the process parameters. We

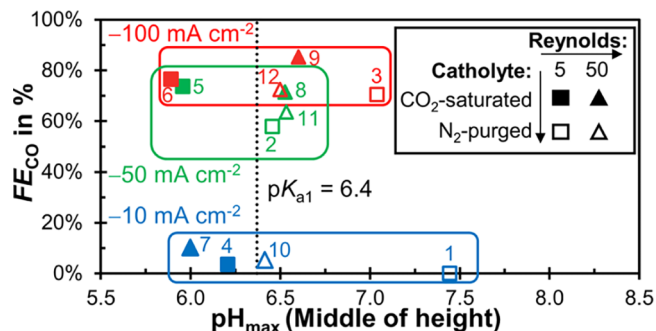

**Figure 10.** Faradaic efficiency for  $\text{CO}_2$ ,  $FE_{\text{CO}}$ , as a function of the maximum pH, at the middle height of the catholyte channel,  $\text{pH}_{\text{max}}$ . The current density,  $j$ , is represented by the color of the data points (blue:  $-10$   $\text{mA cm}^{-2}$ , green:  $-50$   $\text{mA cm}^{-2}$ , red:  $-100$   $\text{mA cm}^{-2}$ ). The Reynolds number of the catholyte,  $Re$ , is indicated by the marker shape (square:  $Re = 5$ , triangle:  $Re = 50$ ). Experiments with  $\text{CO}_2$ -saturated catholyte have filled markers. The dotted line represents the  $\text{p}K_{\text{a}}$  of the bicarbonate reaction ( $\text{CO}_2 + \text{OH}^- \leftrightarrow \text{HCO}_3^-$ ;  $\text{p}K_{\text{a},1} = 6.4$ ).<sup>21</sup> The number next to each marker indicates the ID number (#) of each parameter set.

hypothesize that the following three factors are critical to ensure a high  $FE_{\text{CO}}$ :

- Maximum pH in the electrolyte close to the  $\text{p}K_{\text{a}}$  of the bicarbonate reaction ( $\text{p}K_{\text{a},1} = 6.4$ ): e.g.,  $\text{pH}_{\text{max}} \leq 7.0$ .
- Removal of ions from inside the porous CL to the catholyte ( $\text{OH}^-$ ,  $\text{HCO}_3^-$ , and  $\text{CO}_3^{2-}$ ).
- Dissolved  $\text{CO}_2$  is available in the CL.

The  $\text{CO}_2$  feed in the gas channel, present in all our cases, already limits the  $\text{pH}_{\text{max}}$ . Additionally, we assume that mixing

induced by gas bubbles contributes to both the first (local pH in the electrolyte) and the second (local pH in CL) factor. The process parameter with the strongest effect on  $FE_{CO}$  is  $j$  because it leads to bubble-induced mixing at  $-50 \text{ mA cm}^{-2}$  or higher. We think this mechanism has an important role in keeping  $pH_{\max}$  close enough to  $pK_{a,1}$ . It could further remove product ions from the CL and ensure that  $CO_2$  is available in the CL. For this reason, all experiments with  $j \geq -50 \text{ mA cm}^{-2}$  have a  $FE_{CO} \geq 58\%$  (Figure 10).

Saturating the catholyte with  $CO_2$  also has a positive effect on  $FE_{CO}$ , which is probably due to a combination of additional pH buffering, bubble mixing, and  $CO_2$  mass transfer. For these reasons, the  $FE_{CO}$  highest values occur for experiments with  $CO_2$ -saturated feed and  $j = -100 \text{ mA cm}^{-2}$  (Figure 10: #9 and #6).

The effect of  $Re$  is less clear because the higher liquid flow rate increases the mass transfer through forced convection, but suppresses bubble-induced mixing. However, since a high  $Re$  seems to be beneficial for  $FE_{CO}$  at  $j = -100 \text{ mA cm}^{-2}$  with a  $CO_2$ -saturated catholyte (Figure 10: #9), this is still a relevant parameter for process optimization. It might be interesting, for example, to have a more quantitative study on how  $Re$  influences the dynamics of bubble growth, release, and mixing.

It is remarkable that we obtain a poor  $FE_{CO}$  for experiments with  $j = -10 \text{ mA cm}^{-2}$  although their  $pH_{\max}$  ranges from 6.0 to 7.4 (Figure 10: #1, #4, #7, and #10). This phenomenon might be explained through significantly higher pH values inside the porous CL, which are not accessible through FLIM. It is possible that bubble-induced mixing is necessary to exchange the catholyte inside the porous CL with the catholyte from the channel. Because this mass transfer mechanism is missing at  $j = -10 \text{ mA cm}^{-2}$ , the product ions ( $OH^-$ ,  $HCO_3^-$ , and  $CO_3^{2-}$ ) cannot be removed sufficiently fast leading to an unfavorably high pH in the CL. This hypothesis could be validated with numerical studies in the future.

Close to the GDE of our gas-fed electrolyzer, the catholyte pH remains below 7.0 for all experiments with high  $j$  and high  $FE_{CO}$  (Figure 10: e.g., #9 and #6). In contrast, close to the plate electrode of a liquid-fed electrolyzer, the pH is estimated to be above 10 at only  $-15 \text{ mA cm}^{-2}$ .<sup>19</sup> This raises the question how the pH close to the GDE develops for our system at  $j \geq -200 \text{ mA cm}^{-2}$ . At these conditions, the strong bubble formation leads to a turbulent two-phase flow. This complicates recording the local pH with our FLIM system due to the limited imaging speed (450 ms per image). However, we can speculate that bubble-induced mixing and neutralization with the  $H^+$  from the BPM can maintain a moderate local pH at the GDE for much larger current densities. This might explain why the gas-fed BPM electrolyzer of De Mot et al. can operate at  $-300 \text{ mA cm}^{-2}$  while maintaining a high  $FE_{CO} > 70\%$ .<sup>55</sup>

## CONCLUSIONS

We have studied how process parameters (current density,  $CO_2$  saturation of the electrolyte, and catholyte flow rate) affect the Faradaic efficiency of a gas-fed  $CO_2$  electrolyzer with flowing  $K_2SO_4$  catholyte and bipolar membrane. *Operando* fluorescence lifetime imaging microscopy (FLIM) complemented these measurements by imaging the growth of an alkaline boundary layer along the cathode GDE. Three key factors limit the pH increase at the GDE to  $\leq 7.0$  and enable high  $FE_{CO}$  of 77–85%: (1)  $CO_2$  from the gas phase acts as pH buffer, (2) bubble-induced mixing likely enhances the mass transfer in the catholyte channel and the ion exchange between the catalyst layer and

catholyte, and (3) the  $CO_2$ -saturated catholyte acts as pH buffer and probably leads to additional bubble-induced mixing by releasing  $CO_2$  at the BPM.

We hypothesize the mass transfer contribution of bubble-induced mixing to be more significant than the contribution of forced convection through the flowing catholyte. The bubble-induced mixing is only effective after exceeding a threshold in current density, which makes the maximum pH at  $-10 \text{ mA cm}^{-2}$  higher than at  $-50$  or  $-100 \text{ mA cm}^{-2}$ . High mass transfer rates across the channel are essential to enable a neutralization of  $OH^-$  from the cathode with  $H^+$  from the BPM. This neutralization within the channel might be able to limit the pH increase at the cathode and thereby allow a high  $FE_{CO}$ . Therefore, gas-fed  $CO_2$  electrolyzers with BPM are promising systems for scale-up and operation at high current densities.

## ASSOCIATED CONTENT

### Supporting Information

The Supporting Information is available free of charge at <https://pubs.acs.org/doi/10.1021/acssuschemeng.3c01773>.

Methods;  $CO_2$  electrolysis setup; gas feed; electrolytes; process parameter 1: catholyte purge gas; process parameter 2: Reynolds number/catholyte flow rate; process parameter 3: current density (Figures S1–S23) (PDF)

All data are available in a second SI file (XLSX)

## AUTHOR INFORMATION

### Corresponding Author

David A. Vermaas – Department of Chemical Engineering, Delft University of Technology, 2629 HZ Delft, The Netherlands; [orcid.org/0000-0002-4705-6453](https://orcid.org/0000-0002-4705-6453); Email: [D.A.Vermaas@tudelft.nl](mailto:D.A.Vermaas@tudelft.nl)

### Authors

Lorenz M. Baumgartner – Department of Chemical Engineering, Delft University of Technology, 2629 HZ Delft, The Netherlands

Aron Kahn – Department of Chemical Engineering, Delft University of Technology, 2629 HZ Delft, The Netherlands

Maxime Hoogland – Department of Chemical Engineering, Delft University of Technology, 2629 HZ Delft, The Netherlands

Jorrit Bleeker – Department of Chemical Engineering, Delft University of Technology, 2629 HZ Delft, The Netherlands

Wolter F. Jager – Department of Chemical Engineering, Delft University of Technology, 2629 HZ Delft, The Netherlands; [orcid.org/0000-0001-7664-6949](https://orcid.org/0000-0001-7664-6949)

Complete contact information is available at:

<https://pubs.acs.org/doi/10.1021/acssuschemeng.3c01773>

### Notes

The authors declare no competing financial interest.

## ACKNOWLEDGMENTS

The authors thank Christiaan Schinkel, Stefan ten Hagen, and Duco Bosma for their engineering support. This project has received funding from the European Research Council (ERC) under the European Union's Horizon 2020 research and innovation programme (grant agreement no. 852115).



## REFERENCES

- (1) Blau, J. *The Paris Agreement: Climate Change, Solidarity, and Human Rights*; Springer, 2017.
- (2) Hammond, G.; Newborough, M. Glasgow Climate Pact: A Step on the Way Towards a Lower Carbon Dioxide World. In *Proceedings of the Institution of Civil Engineers-Civil Engineering*; Thomas Telford Ltd., 2022.
- (3) De Luna, P.; Hahn, C.; Higgins, D.; Jaffer, S. A.; Jaramillo, T. F.; Sargent, E. H. What Would It Take for Renewably Powered Electrosynthesis to Displace Petrochemical Processes? *Science* **2019**, *364*, No. eaav3506.
- (4) Roussanaly, S.; Berghout, N.; Fout, T.; Garcia, M.; Gardarsdottir, S.; Nazir, S. M.; Ramirez, A.; Rubin, E. S. Towards Improved Cost Evaluation of Carbon Capture and Storage from Industry. *Int. J. Greenhouse Gas Control* **2021**, *106*, No. 103263.
- (5) Keith, D. W.; Holmes, G.; Angelo, D. S.; Heidel, K. A Process for Capturing CO<sub>2</sub> from the Atmosphere. *Joule* **2018**, *2*, 1573–1594.
- (6) Sharifian, R.; Wagterveld, R. M.; Digdaya, I. A.; Xiang, C.; Vermaas, D. A. Electrochemical Carbon Dioxide Capture to Close the Carbon Cycle. *Energy Environ. Sci.* **2021**, *14*, 781–814.
- (7) Jhong, H. R. M.; Brushett, F. R.; Kenis, P. J. The Effects of Catalyst Layer Deposition Methodology on Electrode Performance. *Adv. Energy Mater.* **2013**, *3*, 589–599.
- (8) Yang, H.; Kaczur, J. J.; Sajjad, S. D.; Masel, R. I. Electrochemical Conversion of CO<sub>2</sub> to Formic Acid Utilizing Sustainion Membranes. *J. CO<sub>2</sub> Util.* **2017**, *20*, 208–217.
- (9) Gabardo, C. M.; O'Brien, C. P.; Edwards, J. P.; McCallum, C.; Xu, Y.; Dinh, C.-T.; Li, J.; Sargent, E. H.; Sinton, D. Continuous Carbon Dioxide Electroreduction to Concentrated Multi-Carbon Products Using a Membrane Electrode Assembly. *Joule* **2019**, *3*, 2777–2791.
- (10) Weekes, D. M.; Salvatore, D. A.; Reyes, A.; Huang, A.; Berlinguette, C. P. Electrolytic CO<sub>2</sub> Reduction in a Flow Cell. *Acc. Chem. Res.* **2018**, *51*, 910–918.
- (11) Verma, S.; Kim, B.; Jhong, H. R. M.; Ma, S.; Kenis, P. J. A Gross-Margin Model for Defining Technoeconomic Benchmarks in the Electroreduction of CO<sub>2</sub>. *ChemSusChem* **2016**, *9*, 1972–1979.
- (12) Masel, R. I.; Liu, Z.; Yang, H.; Kaczur, J. J.; Carrillo, D.; Ren, S.; Salvatore, D.; Berlinguette, C. P. An Industrial Perspective on Catalysts for Low-Temperature CO<sub>2</sub> Electrolysis. *Nat. Nanotechnol.* **2021**, *16*, 118–128.
- (13) Salvatore, D.; Berlinguette, C. P. Voltage Matters When Reducing CO<sub>2</sub> in an Electrochemical Flow Cell. *ACS Energy Lett.* **2020**, *5*, 215–220.
- (14) Higgins, D.; Hahn, C.; Xiang, C.; Jaramillo, T. F.; Weber, A. Z. Gas-Diffusion Electrodes for Carbon Dioxide Reduction: A New Paradigm. *ACS Energy Lett.* **2019**, *4*, 317–324.
- (15) Birdja, Y. Y.; Pérez-Gallent, E.; Figueiredo, M. C.; Göttle, A. J.; Calle-Vallejo, F.; Koper, M. T. M. Advances and Challenges in Understanding the Electrocatalytic Conversion of Carbon Dioxide to Fuels. *Nat. Energy* **2019**, *4*, 732–745.
- (16) Tan, Y. C.; Quek, W. K.; Kim, B.; Sugiarto, S.; Oh, J.; Kai, D. Pitfalls and Protocols: Evaluating Catalysts for CO<sub>2</sub> Reduction in Electrolyzers Based on Gas Diffusion Electrodes. *ACS Energy Lett.* **2022**, *7*, 2012–2023.
- (17) Jeanty, P.; Scherer, C.; Magori, E.; Wiesner-Fleischer, K.; Hinrichsen, O.; Fleischer, M. Upscaling and Continuous Operation of Electrochemical CO<sub>2</sub> to CO Conversion in Aqueous Solutions on Silver Gas Diffusion Electrodes. *J. CO<sub>2</sub> Util.* **2018**, *24*, 454–462.
- (18) Chen, Y.; Vise, A.; Klein, W. E.; Cetinbas, F. C.; Myers, D. J.; Smith, W. A.; Deutsch, T. G.; Neyerlin, K. C. A Robust, Scalable Platform for the Electrochemical Conversion of CO<sub>2</sub> to Formate: Identifying Pathways to Higher Energy Efficiencies. *ACS Energy Lett.* **2020**, *5*, 1825–1833.
- (19) Gupta, N.; Gattrell, M.; MacDougall, B. Calculation for the Cathode Surface Concentrations in the Electrochemical Reduction of CO<sub>2</sub> in KHCO<sub>3</sub> Solutions. *J. Appl. Electrochem.* **2006**, *36*, 161–172.
- (20) Monteiro, M. C. O.; Philips, M. F.; Schouten, K. J. P.; Koper, M. T. M. Efficiency and Selectivity of CO<sub>2</sub> Reduction to CO on Gold Gas Diffusion Electrodes in Acidic Media. *Nat. Commun.* **2021**, *12*, No. 4943.
- (21) Wang, X.-x.; Fu, H.; Du, D.-m.; Zhou, Z.-y.; Zhang, A.-g.; Su, C.-f.; Ma, K.-s. The Comparison of pKa Determination between Carbonic Acid and Formic Acid and Its Application to Prediction of the Hydration Numbers. *Chem. Phys. Lett.* **2008**, *460*, 339–342.
- (22) Kas, R.; Star, A. G.; Yang, K.; Van Cleve, T.; Neyerlin, K. C.; Smith, W. A. Along the Channel Gradients Impact on the Spatioactivity of Gas Diffusion Electrodes at High Conversions During CO<sub>2</sub> Electroreduction. *ACS Sustainable Chem. Eng.* **2021**, *9*, 1286–1296.
- (23) Kas, R.; Yang, K.; Yewale, G. P.; Crow, A.; Burdyny, T.; Smith, W. A. Modeling the Local Environment within Porous Electrode During Electrochemical Reduction of Bicarbonate. *Ind. Eng. Chem. Res.* **2022**, *61*, 10461–10473.
- (24) Weng, L.-C.; Bell, A. T.; Weber, A. Z. Modeling Gas-Diffusion Electrodes for CO<sub>2</sub> Reduction. *Phys. Chem. Chem. Phys.* **2018**, *20*, 16973–16984.
- (25) Weng, L.-C.; Bell, A. T.; Weber, A. Z. Towards Membrane-Electrode Assembly Systems for CO<sub>2</sub> Reduction: A Modeling Study. *Energy Environ. Sci.* **2019**, *12*, 1950–1968.
- (26) Yang, Z.; Li, D.; Xing, L.; Xiang, H.; Xuan, J.; Cheng, S.; Yu, E. H.; Yang, A. Modeling and Upscaling Analysis of Gas Diffusion Electrode-Based Electrochemical Carbon Dioxide Reduction Systems. *ACS Sustainable Chem. Eng.* **2021**, *9*, 351–361.
- (27) Blake, J. W.; Konderla, V.; Baumgartner, L. M.; Vermaas, D. A.; Padding, J. T.; Haverkort, J. W. Inhomogeneities in the Catholyte Channel Limit the Upscaling of CO<sub>2</sub> Flow Electrolyzers. *ACS Sustainable Chem. Eng.* **2023**, *11*, 2840–2852.
- (28) Angulo, A.; van der Linde, P.; Gardeniens, H.; Modestino, M.; Rivas, D. F. Influence of Bubbles on the Energy Conversion Efficiency of Electrochemical Reactors. *Joule* **2020**, *4*, 555–579.
- (29) Krause, K.; Lee, J. K.; Lee, C.; Shafaque, H. W.; Kim, P. J.; Fahy, K. F.; Shrestha, P.; LaManna, J. M.; Baltic, E.; Jacobson, D. L.; Hussey, D. S.; Bazylak, A. Electrolyte Layer Gas Triggers Cathode Potential Instability in CO<sub>2</sub> Electrolyzers. *J. Power Sources* **2022**, *520*, No. 230879.
- (30) Monteiro, M. C. O.; Koper, M. T. M. Measuring Local pH in Electrochemistry. *Curr. Opin. Electrochem.* **2021**, *25*, No. 100649.
- (31) Hursán, D.; Janáky, C. Operando Characterization of Continuous Flow CO<sub>2</sub> Electrolyzers: Current Status and Future Prospects. *Chem. Commun.* **2023**, *59*, 1395–1414.
- (32) Dunwell, M.; Yang, X.; Setzler, B. P.; Anibal, J.; Yan, Y.; Xu, B. Examination of near-Electrode Concentration Gradients and Kinetic Impacts on the Electrochemical Reduction of CO<sub>2</sub> Using Surface-Enhanced Infrared Spectroscopy. *ACS Catal.* **2018**, *8*, 3999–4008.
- (33) Yang, K.; Kas, R.; Smith, W. A. In Situ Infrared Spectroscopy Reveals Persistent Alkalinity near Electrode Surfaces During CO<sub>2</sub> Electroreduction. *J. Am. Chem. Soc.* **2019**, *141*, 15891–15900.
- (34) Yan, Z.; Hitt, J. L.; Zeng, Z.; Hickner, M. A.; Mallouk, T. E. Improving the Efficiency of CO<sub>2</sub> Electrolysis by Using a Bipolar Membrane with a Weak-Acid Cation Exchange Layer. *Nat. Chem.* **2021**, *13*, 33–40.
- (35) Jovanovic, S.; Schleker, P. P. M.; Streun, M.; Merz, S.; Jakes, P.; Schatz, M.; Eichel, R.-A.; Granwehr, J. An Electrochemical Cell for in Operando 13 C Nuclear Magnetic Resonance Investigations of Carbon Dioxide/Carbonate Processes in Aqueous Solution. *Magn. Reson.* **2021**, *2*, 265–280.
- (36) Schatz, M.; Jovanovic, S.; Eichel, R.-A.; Granwehr, J. Quantifying Local pH Changes in Carbonate Electrolyte During Copper-Catalysed CO<sub>2</sub> Electroreduction Using in Operando 13C NMR. *Sci. Rep.* **2022**, *12*, No. 8274.
- (37) Zhang, Z.; Melo, L.; Jansonius, R. P.; Habibzadeh, F.; Grant, E. R.; Berlinguette, C. P. pH Matters When Reducing CO<sub>2</sub> in an Electrochemical Flow Cell. *ACS Energy Lett.* **2020**, *5*, 3101–3107.
- (38) Lu, X.; Zhu, C.; Wu, Z.; Xuan, J.; Francisco, J. S.; Wang, H. In-Situ Observation of the pH Gradient near the Gas Diffusion Electrode of CO<sub>2</sub> Reduction in Alkaline Electrolyte. *J. Am. Chem. Soc.* **2020**, *142*, 15438–15444.

- (39) Heller, E. J.; Sundberg, R.; Tannor, D. Simple Aspects of Raman Scattering. *J. Phys. Chem. A* **1982**, *86*, 1822–1833.
- (40) Gierlinger, N.; Keplinger, T.; Harrington, M. Imaging of Plant Cell Walls by Confocal Raman Microscopy. *Nat. Protoc.* **2012**, *7*, 1694–1708.
- (41) Egawa, M. Raman Microscopy for Skin Evaluation. *Analyst* **2021**, *146*, 1142–1150.
- (42) Lakowicz, J. R. *Principles of Fluorescence Spectroscopy*; Springer Science & Business Media, 2013.
- (43) de Valença, J.; Jögi, M.; Wagterveld, R. M.; Karatay, E.; Wood, J. A.; Lammertink, R. G. H. Confined Electroconvective Vortices at Structured Ion Exchange Membranes. *Langmuir* **2018**, *34*, 2455–2463.
- (44) Leenheer, A. J.; Atwater, H. A. Imaging Water-Splitting Electrocatalysts with pH-Sensing Confocal Fluorescence Microscopy. *J. Electrochem. Soc.* **2012**, *159*, H752–H757.
- (45) van Munster, E. B.; Gadella, T. W. J. Fluorescence Lifetime Imaging Microscopy (Flim). In *Microscopy Techniques*, Rietdorf, J., Ed.; Springer: Berlin, Heidelberg, 2005; pp 143–175.
- (46) Lin, H.-J.; Herman, P.; Lakowicz, J. R. Fluorescence Lifetime-Resolved pH Imaging of Living Cells. *Cytometry, Part A* **2003**, *52*, 77–89.
- (47) Hille, C.; Berg, M.; Bressel, L.; Munzke, D.; Primus, P.; Löhmansröben, H.-G.; Dosche, C. Time-Domain Fluorescence Lifetime Imaging for Intracellular pH Sensing in Living Tissues. *Anal. Bioanal. Chem.* **2008**, *391*, 1871.
- (48) Benneker, A. M.; Gumuscu, B.; Derckx, E. G. H.; Lammertink, R. G. H.; Eijkel, J. C. T.; Wood, J. A. Enhanced Ion Transport Using Geometrically Structured Charge Selective Interfaces. *Lab Chip* **2018**, *18*, 1652–1660.
- (49) de Valença, J. C.; Kurniawan, A.; Wagterveld, R. M.; Wood, J. A.; Lammertink, R. G. H. Influence of Rayleigh-Bénard Convection on Electrokinetic Instability in Overlimiting Current Conditions. *Phys. Rev. Fluids* **2017**, *2*, No. 033701.
- (50) Kalde, A. M.; Grosseheide, M.; Brosch, S.; Pape, S. V.; Keller, R. G.; Linkhorst, J.; Wessling, M. Micromodel of a Gas Diffusion Electrode Tracks in-Operando Pore-Scale Wetting Phenomena. *Small* **2022**, *18*, No. 2204012.
- (51) Bleeker, J.; Kahn, A. P.; Baumgartner, L. M.; Grozema, F. C.; Vermaas, D. A.; Jager, W. F. Quinolinium-Based Fluorescent Probes for Dynamic pH Monitoring in Aqueous Media at High pH Using Fluorescence Lifetime Imaging (Flim). *ACS Sens.* **2023**, *8*, 2050–2059.
- (52) Baumgartner, L. M.; Koopman, C. I.; Forner-Cuenca, A.; Vermaas, D. A. Narrow Pressure Stability Window of Gas Diffusion Electrodes Limits the Scale-up of CO<sub>2</sub> Electrolyzers. *ACS Sustainable Chem. Eng.* **2022**, *10*, 4683–4693.
- (53) Tanaami, T.; Otsuki, S.; Tomosada, N.; Kosugi, Y.; Shimizu, M.; Ishida, H. High-Speed 1-Frame/ms Scanning Confocal Microscope with a Microlens and Nipkow Disks. *Appl. Opt.* **2002**, *41*, 4704–4708.
- (54) Jager, W. F.; Hammink, T. S.; van den Berg, O.; Grozema, F. C. Highly Sensitive Water-Soluble Fluorescent pH Sensors Based on the 7-Amino-1-Methylquinolinium Chromophore. *J. Org. Chem.* **2010**, *75*, 2169–2178.
- (55) De Mot, B.; Hereijgers, J.; Daems, N.; Breugelmans, T. Insight in the Behavior of Bipolar Membrane Equipped Carbon Dioxide Electrolyzers at Low Electrolyte Flowrates. *Chem. Eng. J.* **2021**, No. 131170.
- (56) Duarte, M.; De Mot, B.; Hereijgers, J.; Breugelmans, T. Electrochemical Reduction of CO<sub>2</sub>: Effect of Convective CO<sub>2</sub> Supply in Gas Diffusion Electrodes. *ChemElectroChem* **2019**, *6*, 5596–5602.
- (57) Verma, S.; Lu, X.; Ma, S.; Masel, R. I.; Kenis, P. J. The Effect of Electrolyte Composition on the Electroreduction of CO<sub>2</sub> to CO on Ag Based Gas Diffusion Electrodes. *Phys. Chem. Chem. Phys.* **2016**, *18*, 7075–7084.
- (58) Burdyny, T.; Smith, W. A. CO<sub>2</sub> Reduction on Gas-Diffusion Electrodes and Why Catalytic Performance Must Be Assessed at Commercially-Relevant Conditions. *Energy Environ. Sci.* **2019**, *12*, 1442–1453.
- (59) Baumgartner, L. M.; Koopman, C. I.; Forner-Cuenca, A.; Vermaas, D. A. When Flooding Is Not Catastrophic—Woven Gas Diffusion Electrodes Enable Stable CO<sub>2</sub> Electrolysis. *ACS Appl. Energy Mater.* **2022**, *5*, 15125–15135.
- (60) Blake, J. W.; Padding, J. T.; Haverkort, J. W. Analytical Modelling of CO<sub>2</sub> Reduction in Gas-Diffusion Electrode Catalyst Layers. *Electrochim. Acta* **2021**, *393*, No. 138987.
- (61) Vogt, H.; Stephan, K. Local Microprocesses at Gas-Evolving Electrodes and Their Influence on Mass Transfer. *Electrochim. Acta* **2015**, *155*, 348–356.
- (62) Burdyny, T.; Graham, P. J.; Pang, Y.; Dinh, C.-T.; Liu, M.; Sargent, E. H.; Sinton, D. Nanomorphology-Enhanced Gas-Evolution Intensifies CO<sub>2</sub> Reduction Electrochemistry. *ACS Sustainable Chem. Eng.* **2017**, *5*, 4031–4040.
- (63) Peñas, P.; van der Linde, P.; Vjelselaar, W.; van der Meer, D.; Lohse, D.; Huskens, J.; Gardeniers, H.; Modestino, M. A.; Rivas, D. F. Decoupling Gas Evolution from Water-Splitting Electrodes. *J. Electrochem. Soc.* **2019**, *166*, H769.
- (64) Jones, S. F.; Evans, G. M.; Galvin, K. P. Bubble Nucleation from Gas Cavities—a Review. *Adv. Colloid Interface Sci.* **1999**, *80*, 27–50.
- (65) Van Der Linde, P.; Peñas-López, P.; Soto, Á. M.; Van Der Meer, D.; Lohse, D.; Gardeniers, H.; Rivas, D. F. Gas Bubble Evolution on Microstructured Silicon Substrates. *Energy Environ. Sci.* **2018**, *11*, 3452–3462.
- (66) Venczel, J. Ueber Den Stofftransport an Gasentwickelnden Elektroden. Doctoral Dissertation, ETH Zurich, 1961.
- (67) Roušar, I.; Cezner, V. Transfer of Mass or Heat to an Electrode in the Region of Hydrogen Evolution—I Theory. *Electrochim. Acta* **1975**, *20*, 289–293.
- (68) Roušar, I.; Kačín, J.; Lippert, E.; Šmirous, F.; Cezner, V. Transfer of Mass or Heat to an Electrode in the Region of Hydrogen Evolution—II.: Experimental Verification of Mass and Heat Transfer Equations. *Electrochim. Acta* **1975**, *20*, 295–299.
- (69) Löffelholz, M.; Osiewacz, J.; Lükken, A.; Perrey, K.; Bulan, A.; Turek, T. Modeling Electrochemical CO<sub>2</sub> Reduction at Silver Gas Diffusion Electrodes Using a Tffa Approach. *Chem. Eng. J.* **2022**, *435*, No. 134920.
- (70) Ma, M.; Kim, S.; Chorkendorff, I.; Seger, B. Role of Ion-Selective Membranes in the Carbon Balance for CO<sub>2</sub> Electroreduction Via Gas Diffusion Electrode Reactor Designs. *Chem. Sci.* **2020**, *11*, 8854–8861.
- (71) Angulo, A. E.; Frey, D.; Modestino, M. A. Understanding Bubble-Induced Overpotential Losses in Multiphase Flow Electrochemical Reactors. *Energy Fuels* **2022**, *36*, 7908–7914.
- (72) Nahra, H. K.; Kamotani, Y. Prediction of Bubble Diameter at Detachment from a Wall Orifice in Liquid Cross-Flow under Reduced and Normal Gravity Conditions. *Chem. Eng. Sci.* **2003**, *58*, 55–69.
- (73) Lee, J. W.; Sohn, D. K.; Ko, H. S. Study on Bubble Visualization of Gas-Evolving Electrolysis in Forced Convective Electrolyte. *Exp. Fluids* **2019**, *60*, No. 156.