

## Thermodynamic Measurement of Angular Anisotropy at the Hidden Order Transition of URu<sub>2</sub>Si<sub>2</sub>

Trinh, Jennifer; Brück, Ekkes; Siegrist, Theo; Flint, Rebecca; Chandra, Premala; Coleman, Piers; Ramirez, Arthur P.

**DOI**

[10.1103/PhysRevLett.117.157201](https://doi.org/10.1103/PhysRevLett.117.157201)

**Publication date**

2016

**Document Version**

Final published version

**Published in**

Physical Review Letters

**Citation (APA)**

Trinh, J., Brück, E., Siegrist, T., Flint, R., Chandra, P., Coleman, P., & Ramirez, A. P. (2016). Thermodynamic Measurement of Angular Anisotropy at the Hidden Order Transition of URu<sub>2</sub>Si<sub>2</sub>. *Physical Review Letters*, 117(15), Article 157201. <https://doi.org/10.1103/PhysRevLett.117.157201>

**Important note**

To cite this publication, please use the final published version (if applicable). Please check the document version above.

**Copyright**

Other than for strictly personal use, it is not permitted to download, forward or distribute the text or part of it, without the consent of the author(s) and/or copyright holder(s), unless the work is under an open content license such as Creative Commons.

**Takedown policy**

Please contact us and provide details if you believe this document breaches copyrights. We will remove access to the work immediately and investigate your claim.

## Thermodynamic Measurement of Angular Anisotropy at the Hidden Order Transition of URu<sub>2</sub>Si<sub>2</sub>

Jennifer Trinh,<sup>1</sup> Ekkes Brück,<sup>2</sup> Theo Siegrist,<sup>3,4</sup> Rebecca Flint,<sup>5</sup> Premala Chandra,<sup>6</sup>  
Piers Coleman,<sup>6,7</sup> and Arthur P. Ramirez<sup>1</sup>

<sup>1</sup>Physics Department, University of California Santa Cruz, Santa Cruz, California 95064, USA

<sup>2</sup>Fundamental Aspects of Materials and Energy, Faculty of Applied Sciences, TU Delft Mekelweg,  
15, 2629 JB Delft, Netherlands

<sup>3</sup>National High Magnetic Field Laboratory, Florida State University, Tallahassee, Florida 32310, USA

<sup>4</sup>Department of Chemistry and Biomedical Engineering, Florida State University, Tallahassee, Florida 32310, USA

<sup>5</sup>Department of Physics and Astronomy, Iowa State University, Ames, Iowa 50011, USA

<sup>6</sup>Center for Materials Theory, Rutgers University, Piscataway, New Jersey 08854, USA

<sup>7</sup>Department of Physics, Royal Holloway, University of London, Egham, Surrey TW20 0EX, United Kingdom

(Received 21 April 2016; revised manuscript received 15 July 2016; published 5 October 2016)

The heavy fermion compound URu<sub>2</sub>Si<sub>2</sub> continues to attract great interest due to the unidentified hidden order it develops below 17.5 K. The unique Ising character of the spin fluctuations and low-temperature quasiparticles is well established. We present detailed measurements of the angular anisotropy of the nonlinear magnetization that reveal a cos<sup>4</sup>θ Ising anisotropy both at and above the ordering transition. With Landau theory, we show this implies a strongly Ising character of the itinerant hidden order parameter.

DOI: 10.1103/PhysRevLett.117.157201

Despite intensive theoretical and experimental efforts, the hidden order (HO) that develops below 17.5 K in the heavy fermion superconductor URu<sub>2</sub>Si<sub>2</sub> remains unidentified 30 years after its original discovery [1]. The nature of the quasiparticle excitations and the broken symmetries associated with the HO phase are important questions for understanding not only HO but also the low-temperature exotic superconductivity. While URu<sub>2</sub>Si<sub>2</sub> is tetragonal above the HO, torque magnetometry [2], cyclotron resonance [3], x-ray diffraction [4], and elastoresistivity measurements [5] indicate fourfold symmetry breaking in the basal plane. However, NMR and nuclear quadrupole resonance studies suggest that this nematic signal decreases with increasing sample size and also depends on sample quality, suggesting that the bulk is tetragonal [6,7].

A number of measurements on URu<sub>2</sub>Si<sub>2</sub> indicate Ising anisotropy, suggesting that it is essential to understanding its HO. At the HO transition temperature  $T_c$ , both the linear ( $\chi_1$ ) and nonlinear ( $\chi_3$ ) susceptibilities are anisotropic, with  $\chi_3$  displaying a sharp anomaly,  $\Delta\chi_3 = \chi_3(T_c^-) - \chi_3(T_c^+)$ , that tracks closely with the structure of the specific heat [8,9]. The non-spin-flip ( $\Delta J_z = 0$ ) magnetic excitations seen in both inelastic neutron scattering [10] and in Raman measurements [11,12] also have Ising character, despite the absence of local moments at those temperatures and pressures. Finally, quantum oscillations measured deep within the HO region indicate a quasiparticle  $g$  factor with strong Ising anisotropy,  $g(\theta) \propto \cos\theta$ , where  $\theta$  is the angle away from the  $c$  axis [13,14]. This  $g(\theta)$  is confirmed by upper critical field experiments [15] that indicate that Ising quasiparticles pair to form a Pauli-limited superconductor. In this Letter, we present a bulk thermodynamic measurement of the Ising

nature of the hidden order parameter, which shows that this Ising anisotropy is present not only deep inside the HO but at the transition itself; it is even present in the order parameter fluctuations above  $T_c$ .

As a rank-4 tensor, the nonlinear susceptibility  $\chi_{3abcd}$ ,

$$M^a = \chi_{1ab}H^b + \frac{1}{3!}\chi_{3abcd}H^bH^cH^d, \quad (1)$$

is particularly well suited to probe symmetry-allowed anisotropies in the tetragonal crystal environment (space group  $I4/mmm$ ) of URu<sub>2</sub>Si<sub>2</sub>; here,  $M$  and  $H$  refer to the magnetization and the applied magnetic field, respectively, and we use a summation convention for repeated indices. In this Letter we present an angular survey of the HO transition, reporting an extensive series of nonlinear susceptibility [ $\chi_3(\theta, \phi)$ ] measurements. Our results have important implications for the nature of the quasiparticles in the HO phase, and we also use  $\chi_3(\theta, \phi)$  to probe the angular anisotropy of short-range order parameter fluctuations at temperatures above the HO transition.

The general expression for the field-dependent part of the free energy in a tetragonal crystal at fixed temperature is

$$F = -\chi_1(\theta)\frac{H^2}{2} - \chi_3(\theta, \phi)\frac{H^4}{4!}, \quad (2)$$

with

$$\begin{aligned} \chi_1(\theta) &= \chi_1^a + \chi_1^b \cos^2\theta \quad \text{and} \\ \chi_3(\theta, \phi) &= \chi_3^a + \chi_3^b \cos^2\theta + \chi_3^c \cos^4\theta + \chi_3^d \sin^4\theta \sin^2 2\phi, \end{aligned} \quad (3)$$

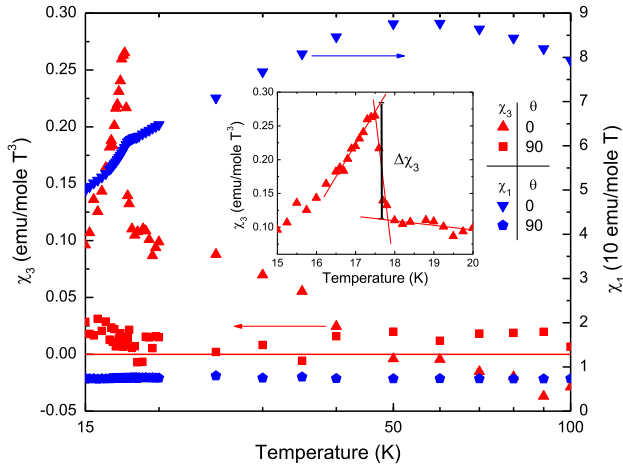


FIG. 1. Linear and nonlinear susceptibility versus temperature for fields along the  $c$  axis ( $\theta = 0^\circ$ ) and in the basal plane ( $\theta = 90^\circ$ ).

where  $\theta$  and  $\phi$  refer to the angles away from the  $c$  axis and in the basal plane, respectively; details of this angular decomposition are in the Supplemental Material [16]. The anomaly in  $\Delta\chi_3$  is a known signature of HO [9]. Because there is no Van Vleck contribution to the anomaly  $\Delta\chi_3$ , it is a direct thermodynamic probe of the  $g$  factor at the HO transition. A key question is whether the anisotropic  $g$  factor found in quantum oscillations persists to higher temperatures in the hidden order phase. Consistency with the low-temperature  $g(\theta) \propto \cos\theta$  results requires a large change in  $\chi_3^c$ ,  $\Delta\chi_3^c$ , and negligible  $\Delta\chi_3^b$  and  $\Delta\chi_3^a$ .

The  $\text{URu}_2\text{Si}_2$  crystal used in this study is of dimension  $4 \times 2.5 \times 2 \text{ mm}^3$  and has been previously described [9,19]. A recent measurement of  $C(T)$  as well as the  $\chi_1$  and  $\chi_3$  measurements reported here show no change in these properties over time [9]. The narrow width of the specific-heat transition,  $\Delta T_{\text{HO}} = 0.35 \text{ K}$ , is consistent with high-quality samples of comparable dimensions [20–22]. Additionally, the single superconducting transition indicates a single phase [19] confirming the high quality of the sample. Measurements of the magnetization  $M$  were performed in a commercial superconducting quantum interference device (SQUID) magnetometer, as a function of temperature ( $T$ ), magnetic field ( $H$ ), and angle ( $\theta$ ) between the sample's  $c$  axis and  $H$ . The variation in angle was achieved with a set of sample mounts machined from Stycast 1266 epoxy. The linear and leading nonlinear ( $\chi_3$ ) susceptibilities were determined as in Ref. [9]. Multiple measurements [ $\sim 1800 M(H)$  scans] were performed with sufficient resolution in  $H$ ,  $T$ , and  $\theta$  to resolve the angular dependence of the  $\chi_3$  discontinuity at  $T_c$ . Values for  $\Delta\chi_3$  were obtained at every  $\theta$  using a straight-line construction assuming a mean-field jump at  $T_c$ .

Figure 1 shows  $\chi_1(T)$  and  $\chi_3(T)$  as a function of temperature at  $\theta = 0^\circ$  and  $90^\circ$ , data that agree well with previous reports [9]. We note that the nonlinear

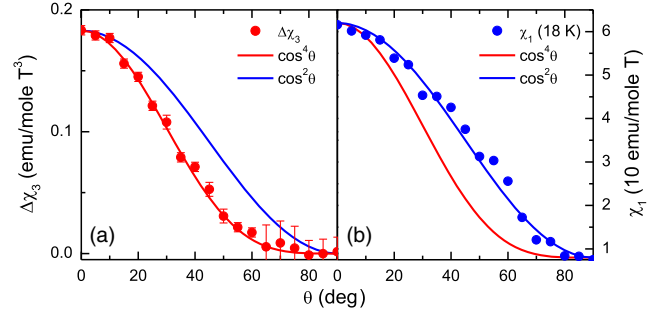


FIG. 2. Angular dependence of (a) the jump  $\Delta\chi_3$  in the nonlinear susceptibility at the hidden order transition and (b) the magnetic susceptibility just above the hidden order transition at 18 K.

susceptibility displays a sharp anomaly at the HO transition, whereas  $\chi_1(T)$  displays a corresponding discontinuity in its gradient  $d\chi_1(T)/dT$ ; both  $\chi$  and  $\chi_3$  are significantly larger for  $\theta = 0^\circ$  ( $c$  axis) than for  $\theta = 90^\circ$  ( $ab$  plane).

In Fig. 2 we show the angular dependence of  $\Delta\chi_3$  and of  $\chi_1$  just above the HO transition. The linear susceptibility displayed in Fig. 2(b) is characterized by the form

$$\chi_1(\theta, T) = \chi_1^{(0)} + \chi_1^{\text{Ising}}(T)\cos^2\theta, \quad (4)$$

where the isotropic component  $\chi_1^{(0)}$  of the susceptibility displays no discernable temperature dependence. The temperature-dependent Ising component  $\chi_1^{\text{Ising}}$  displays a discontinuity  $d\chi_1^{\text{Ising}}/dT$  at the HO transition. Whereas  $\chi_1(\theta)$  varies as  $\cos^2\theta$  at  $T = 18 \text{ K}$ , in Fig. 2(a) the sharp jump in  $\chi_3$  at the transition  $\Delta\chi_3$  has a distinctive  $\cos^4\theta$  dependence,

$$\Delta\chi_3(\theta, \phi) = \Delta\chi_3^{\text{Ising}}\cos^4\theta, \quad (5)$$

without any constant (Van Vleck) terms; this then indicates that  $\Delta\chi_3^c \gg \Delta\chi_3^b, \Delta\chi_3^a$  in Eq. (4), consistent with the low-temperature  $g(\theta)$  measurements. We note that, within experimental resolution, no  $\chi_3^d$  component was observed in the measurements, either above or at the transition.

In Fig. 3 we compare the angular dependences of  $\Delta\chi_3$  with  $\chi_3(18 \text{ K})$ ,  $\chi_3(30 \text{ K})$ , and  $\chi_3(100 \text{ K})$ , just above, moderately above, and well above  $T_c$ . At 18 and 30 K,  $\chi_3$  follows  $\cos^4\theta$ , similar to  $\Delta\chi_3$ . At 100 K, the positive contribution to  $\chi_3$  associated with the HO transition has completely vanished, leaving a negative response presumably associated with single-ion dipolar physics; the signal is too small to resolve the anisotropy. At  $T = 18 \text{ K}$ ,  $\chi_3$  is about 1.6 times smaller than  $\Delta\chi_3$ , (cf. Fig. 1), and is well described by the form

$$\chi_3(\theta, T) = \chi_3^{(0)} + \chi_3^{\text{Ising}}(T)\cos^4\theta, \quad (6)$$

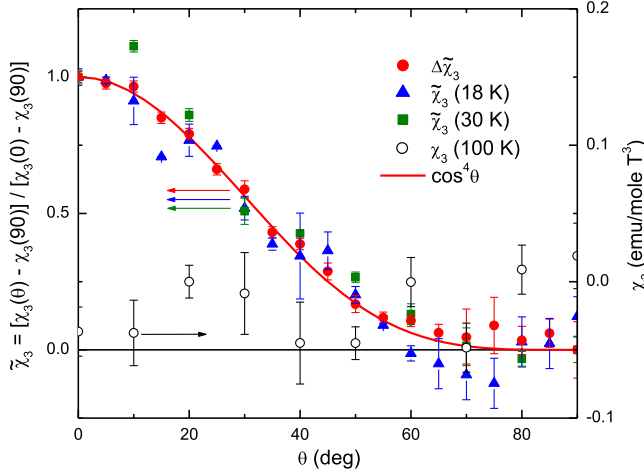


FIG. 3. Angular dependence of  $\Delta\chi_3$  and  $\chi_3$  at three different temperatures, showing the disappearance of the Ising behavior at high temperatures.

where the isotropic component  $\chi_3^{(0)}$  is essentially temperature independent. A  $\cos^4\theta$  dependence in  $\chi_3(T)$  is still observed at 30 K, and by comparing the  $c$ -axis and basal-plane measurements, we estimate that around 60 K,  $\chi_3^{\text{Ising}}(T)$  goes to zero (see Fig. 1). Above 100 K, the  $\cos^4\theta$  dependence is no longer discernable, leading us to infer that the Ising component of the nonlinear susceptibility vanishes around 60 K.

At the HO transition, our results can be analyzed within a minimal Landau free-energy density of the form

$$f(T, \psi) = a[T - T_c(H)]\psi^2 + \frac{b}{2}\psi^4, \quad (7)$$

where we describe a domain of hidden order by a real order parameter  $\psi$  and

$$T_c(H) = T_c - \frac{1}{2}Q_{ab}H_aH_b + O(H^4) \quad (8)$$

defines the leading field-dependent anisotropy in the transition temperature, where  $Q_{ab}$  is a tensor capturing how the order parameter  $\psi$  couples to magnetic field; experimental consequences of Eq. (7) [9] are discussed in the Supplemental Material [16]. The quantity  $\Delta\chi_{ab} = -aQ_{ab}\psi^2$  is the magnetic susceptibility associated with the hidden order. By minimizing the free energy with respect to  $\psi$ , the free energy below  $T_c$  is then  $f(T) = -(a^2/2b)[T_c(H) - T]^2$ . The jump in the linear and nonlinear susceptibilities are then given by

$$\left(\Delta\frac{d\chi_1}{dT}\right)_{ab} = -\frac{a^2}{b}Q_{ab}, \quad (9)$$

$$(\Delta\chi_3)_{abcd} = \frac{a^2}{b}(Q_{ab}Q_{cd} + Q_{ac}Q_{bd} + Q_{ad}Q_{cb}). \quad (10)$$

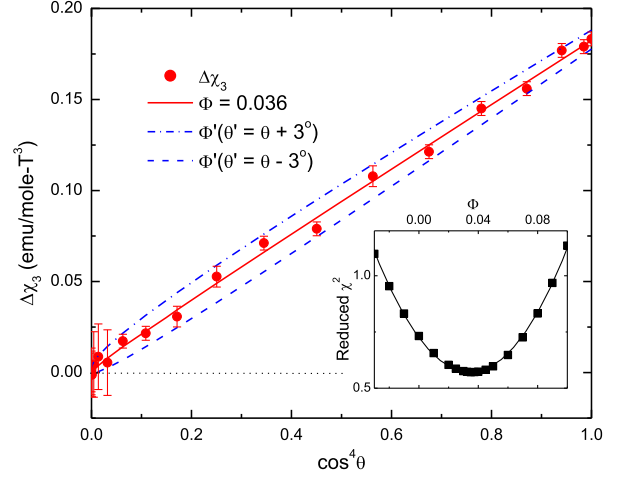


FIG. 4.  $\Delta\chi_3$  as a function of  $\cos^4\theta$ , fit to Eq. (12) for different values of  $\Phi$ . Blue dashed lines indicate  $\Phi$  values assuming an angular offset of  $3^\circ$  ( $\theta' = \theta \pm 3^\circ$ ). Inset shows the effect of  $\Phi$  on the goodness of fit, expressed as the reduced  $\chi^2$  [16].

In order to determine the robustness of the Ising anisotropy, by setting  $Q_{xx} = Q_{yy} = \Phi Q_{zz}$ , we codify our results in terms of an angle-dependent coupling between the hidden order parameter  $\psi$  and the magnetic field of the form

$$\Delta f[\psi, \theta] = -\frac{aQ_{zz}}{2}\psi^2H^2(\cos^2\theta + \Phi\sin^2\theta), \quad (11)$$

where  $\Phi$  quantifies the fidelity of the Ising-like behavior, so that  $\Phi = 0$  and  $\Phi = 1$  correspond to Ising and isotropic behavior, respectively. The corresponding jump in the nonlinear susceptibility at  $T_c$  is

$$\Delta\chi_3(\theta) \propto (\cos^2\theta + \Phi\sin^2\theta)^2. \quad (12)$$

Our measurements indicate a very small  $\Phi = 0.036 \pm 0.021$ , as shown in Fig. 4 (inset), where details of the fitting procedure are given in the Supplemental Materials [16]. Such a small value of  $\Phi$  could be accounted for by an angular offset of only  $1^\circ$ , via Eq. (12). X-ray diffraction orientation measurements indicate an uncertainty in the  $c$  axis of our sample of no more than  $\pm 3^\circ$ . In Fig. 4, one can see that this value provides upper and lower bounds to the  $\cos^4\theta$  dependence of  $\Delta\chi_3$  that bracket the data symmetrically. Thus, a  $\Phi$  value of 0.036 is well below the total uncertainty of the measurement. To reduce the uncertainty in  $\Phi$  even further would require angular accuracy of well below  $1^\circ$ , which is beyond the capability of the present apparatus. Thus, the obtained  $\Phi = 0.036$  is consistent also with  $\Phi = 0$ .

We now discuss the implications of these results. At the very simplest level, our results show that the free energy of  $\text{URu}_2\text{Si}_2$  only depends on the  $z$  component of the magnetic field, i.e.,  $F[\vec{H}] = F[H_z]$ . In particular, (i) the coupling of



the order parameter to the magnetic field involves an Ising coupling  $F[H, \psi] = -\frac{1}{2} Q_{zz} \psi^2 H_z^2$ , and (ii) in the microscopic Hamiltonian, the Zeeman coupling of the magnetic field is strongly Ising, with the field coupling to the  $z$  component of the total angular momentum  $-J_z B_z$ .

The second point follows because derivatives of the free energy with respect to field are equivalent, inside the trace of the partition function, to the magnetization operator,  $-\delta/\delta H_z \equiv \hat{M}_z$ , so that if the free energy only depends on  $H_z$ , the partition function  $Z = \text{Tr} e^{-\beta H}$  and, hence, the Hamiltonian only depends on  $\hat{M}_z = g \hat{J}_z$ .

However, these simple conclusions have implications for the microscopic physics. On the one hand, we can link the Ising anisotropy of the microscopic Hamiltonian to the single-ion properties of the U ions in URu<sub>2</sub>Si<sub>2</sub>, where the Zeeman coupling  $-g_f \mu_B J_z B_z$  is a sign of vanishing matrix elements  $\langle +|J_{\pm}|-\rangle = 0$ . From a single-ion standpoint, an almost perfect Ising anisotropy is a strong indication of an integer spin  $5f^2 U^{4+}$  ground state with  $J = 4$ . High-spin Ising configurations of the alternative  $5f^3 U^{3+}$  ionic configurations are ruled out because the coupling of the local moment to the tetragonal environment mixes configurations by adding angular momenta in units of  $\pm 4\hbar$ , for example,  $J_z = \pm 5/2$  and  $\mp 3/2$ , leading almost inevitably to a nonzero transverse Zeeman coupling when the angular momentum  $J$  is half-integer. Although the precise crystal-field configuration of the U ions is still uncertain [23–25], both dynamical mean-field calculations [26] and high-resolution RIXS measurements [24] confirm the predominantly  $5f^2$  picture.

Yet a single-ion picture is not enough, for the sharpness of the specific-heat anomaly, the sizable entropy, and the gapping of two-thirds of the Fermi surface associated with the hidden order transition [1] all suggest an underlying *itinerant* ordering process. The remarkable feature of our data is that the jump  $\Delta\chi_3$  that reflects the itinerant ordering process exhibits a strong Ising anisotropy. This result links in with the observation of multiple spin zeros in de Haas–van Alphen measurements, which detect the presence of itinerant heavy quasiparticles with an Ising  $g$  factor,  $g(\theta) = g_f \cos \theta$ , at low temperatures. Our new results suggest that these same quasiparticles survive all the way up to the hidden order transition. In the Landau theory, we can identify the Ising-like coupling between HO and the magnetic field in terms of the squared  $g$  factor  $Q_{zz} \psi^2 \cos^2 \theta \propto g(\theta)^2 \psi^2$ .

Reconciling the single-ion and itinerant perspectives, both supported strongly by experiment, poses a fascinating paradox. The simplest possibility is that the Ising anisotropy of the  $f$  electrons is a one-electron effect resulting from a renormalized, spin-orbit-coupled  $f$  band that develops at temperatures well above the hidden order transition. In this purely itinerant view, the hidden order is a multipolar density wave that develops within a preformed

band of Ising quasiparticles [27,28]. Microscopically such quasiparticles are renormalized one-particle  $f$  orbitals formed from high-spin orbitals with half-integer  $|J_z|$ . Provided only one  $|J_z| > 1/2$  is involved, the transverse matrix elements of the angular momentum operator  $\langle \pm |J_{\pm}| \pm \rangle = 0$  identically vanish, leading to a perfect Ising anisotropy. Such Ising quasiparticles have been observed in strong spin-orbit-coupled systems, but only at high-symmetry points in the Brillouin zone [29]. Moreover, in a tetragonal environment, when an electron resonantly scatters off an  $f$  state,  $J_z$  is only conserved mod (4). Thus, a mobile heavy Bloch wave must actively exchange  $\pm 4\hbar$  units of angular momentum as it propagates through the lattice, leading to Bloch states composed of a mixture of  $J_z$  states, such as

$$|\mathbf{k}\pm\rangle = \alpha|\mathbf{k}, \pm 5/2\rangle + \beta|\mathbf{k}, \mp 3/2\rangle. \quad (13)$$

This inevitably gives rise to a finite transverse coupling and a finite  $\Phi$  in the phenomenological Landau theory ( $\Phi \propto |\alpha\beta|^2$ ) that is ruled out by these experiments.

An alternative is that the itinerant  $f$  quasiparticles carry integer angular momentum, inheriting the Ising anisotropy of a localized  $5f^2$  local moment of the U atoms via a phase transition rather than a crossover. In this scenario, even though  $J_z$  is conserved mod(4), Ising anisotropy is preserved since the up-spin and down-spin configurations differ by at least two units of angular momentum. However, this picture requires that the half-integer conduction electrons hybridize with the underlying integer  $f$  states, which can only occur in the presence of a spinorial or “hastatic” order parameter [30–33]. Indeed, the hastatic order scenario predicted the  $\Delta\chi_3 \propto \cos^4 \theta$  observed in this experiment, although theoretical efforts to develop a microscopic theory of hastatic order predicted a small transverse moment that has been shown to be absent in high-precision neutron scattering experiments [34–36]. The vanishing of the anisotropy constant ( $\Phi = 0$ ) in our nonlinear susceptibility measurements combined with the null result reported by neutron scattering represents a fascinating challenge to our future understanding of hidden order.

The continuation of the Ising anisotropy well above  $T_c$  is also remarkable. While single-ion physics can give a negative Ising anisotropic  $\chi_3$ , for an isolated Ising ground-state doublet, or a positive, but more isotropic  $\chi_3$ , if there are several singlets in the temperature range of interest, there is no way to explain the positive Ising anisotropic  $\chi_3$  emerging below 60 K with single-ion physics. Instead, this response indicates Ising anisotropic order parameter fluctuations extending up to more than 3 times  $T_c$ , an extraordinarily large fluctuation regime.

An interesting question raised by our work is whether bulk nonlinear susceptibility measurements can be used to detect microscopic broken tetragonal symmetry that has been reported in torque magnetometry measurements [2].

In principle, were the hidden order to possess domains with broken tetragonal symmetry, interdomain fluctuations in the basal-plane susceptibility would manifest themselves through a finite value of  $\chi_3^d$  below  $T_c$ . The large Ising anisotropy suppresses the precision for in-plane susceptibility measurement: our current work places an upper bound on the microscopic symmetry-breaking susceptibility  $|\Delta\chi_{xy}|$ , such that  $|\Delta\chi_{xy}|/\chi_{xx} \leq 1$ , which is 2 orders of magnitude larger than that measured by torque magnetometry on  $\mu\text{m}$ -size samples [2,16], and thus our negative results are not inconsistent with their positive finding. However, improvement in resolution in future measurements could make it possible to address this issue.

In summary, we have presented a detailed survey of the nonlinear magnetic susceptibility as a function of angle and temperature in the hidden order compound  $\text{URu}_2\text{Si}_2$ . These measurements showcase the unique Ising anisotropy, and imply that it is a key feature of the hidden order parameter. While previous quantum oscillation measurements indicated the presence of Ising quasiparticles, this Ising anisotropy persists not only to the transition temperature, but all the way up to 60 K, putting serious constraints on the theory of hidden order. It would be quite interesting to examine the nonlinear susceptibility anisotropy in and above the antiferromagnetic phase, which could be done in  $\text{URu}_{2-x}\text{Fe}_x\text{Si}_2$  [37].

This work was supported by National Science Foundation Grants No. NSF DGE-1339067 (J. T.), No. NSF DMR-1334428 (P. Chandra), No. NSF DMR-1309929 (P. Coleman), No. NSF DMR-1534741 (A. P. R.), and Ames Laboratory Royalty Funds and Iowa State University startup funds (R. F.). The Ames Laboratory is operated for the U.S. Department of Energy by Iowa State University under Contract No. DE-AC02-07CH11358. P. Chandra, P. Coleman, and R. F. acknowledge the hospitality of the Aspen Center for Physics, supported by NSF PHYS-1066293, where early parts of this work were discussed. T. S. acknowledges funding by the U.S. Department of Energy, Office of Basic Energy Sciences, Materials Sciences and Engineering Division, under Award No. DE-SC0008832. P. Chandra thanks S. Bahramy for a stimulating discussion on Ising quasiparticles in  $\text{MoS}_2$ .

- 
- [1] J. Mydosh and P. M. Oppeneer, Colloquium: Hidden order, superconductivity and magnetism—The unsolved case of  $\text{URu}_2\text{Si}_2$ , *Rev. Mod. Phys.* **83**, 1301 (2011).  
 [2] R. Okazaki, T. Shibauchi, H. J. Shi, Y. Haga, T. D. Matsuda, E. Yamamoto, Y. Onuki, H. Ikeda, and Y. Matsuda, Rotational symmetry breaking in the hidden order phase of  $\text{URu}_2\text{Si}_2$ , *Science* **331**, 439 (2011).  
 [3] S. Tonegawa, K. Hashimoto, K. Ikeda, Y.-H. Lin, H. Shishido, Y. Haga, T. D. Matsuda, E. Yamamoto, Y. Onuki, H. Ikeda, Y. Matsuda, and T. Shibauchi, Cyclotron Resonance in the

- Hidden-Order Phase of  $\text{URu}_2\text{Si}_2$ , *Phys. Rev. Lett.* **109**, 036401 (2012).  
 [4] S. Tonegawa, S. Kasahara, T. Fukuda, K. Sugimoto, N. Yasuda, Y. Tsuruhara, D. Watanabe, Y. Mizukami, Y. Haga, T. D. Matsuda, E. Yamamoto, Y. Onuki, H. Ikeda, Y. Matsuda, and T. Shibauchi, Direct observation of lattice symmetry breaking at the hidden-order transition in  $\text{URu}_2\text{Si}_2$ , *Nat. Commun.* **5**, 4188 (2014).  
 [5] S. C. Riggs, M. C. Shapiro, A. V. Maharaj, S. Raghun, E. D. Bauer, R. E. Baumbach, P. Giraldo-Gallo, M. Wartenbe, and I. R. Fisher, Evidence for a nematic component to the hidden-order parameter in  $\text{URu}_2\text{Si}_2$  from differential elastoresistance measurements, *Nat. Commun.* **6**, 6425 (2015).  
 [6] T. Mito, M. Hattori, G. Motoyama, Y. Sakai, T. Koyama, K. Ueda, T. Kohara, M. Yokoyama, and H. Amitsuka, Investigation of local symmetries in the hidden-order phase of  $\text{URu}_2\text{Si}_2$ , *J. Phys. Soc. Jpn.* **82**, 123704 (2013).  
 [7] S. Kambe, Y. Tokunaga, H. Sakai, and R. E. Walstedt, Distributed twofold ordering in  $\text{URu}_2\text{Si}_2$ , *Phys. Rev. B* **91**, 035111 (2015).  
 [8] Y. Miyako, S. Kawarazaki, H. Amitsuka, C. C. Paulsen, and K. Hasselbach, Magnetic properties of  $\text{U}(\text{Ru}_{1-x}\text{Rh}_x)_2\text{Si}_2$  single crystals ( $0 \leq x \leq 1$ ), *J. Appl. Phys.* **70**, 5791 (1991).  
 [9] A. P. Ramirez, P. Coleman, P. Chandra, E. Brück, A. A. Menovsky, Z. Fisk, and E. Bucher, Nonlinear Susceptibility as a Probe of Tensor Order in  $\text{URu}_2\text{Si}_2$ , *Phys. Rev. Lett.* **68**, 2680 (1992).  
 [10] C. Broholm, H. Lin, P. T. Matthews, T. E. Mason, W. J. L. Buyers, M. F. Collins, A. A. Menovsky, J. A. Mydosh, and J. K. Kjems, Magnetic excitations in the heavy-fermion superconductor  $\text{URu}_2\text{Si}_2$ , *Phys. Rev. B* **43**, 12809 (1991).  
 [11] J. Buhot, M.-A. Measson, Y. Gallais, M. Cazayous, A. Sacuto, G. Lapertot, and D. Aoki, Symmetry of the Excitations in the Hidden Order State in  $\text{URu}_2\text{Si}_2$ , *Phys. Rev. Lett.* **113**, 266405 (2014).  
 [12] H.-H. Kung, R. E. Baumbach, E. Bauer, V. K. Thorsmølle, W. L. Zhang, K. Haule, J. A. Mydosh, and G. Blumberg, Chirality density wave of the hidden order phase in  $\text{URu}_2\text{Si}_2$ , *Science* **347**, 1339 (2015).  
 [13] H. Ohkuni, Y. Inada, Y. Tokiwa, K. Sakurai, R. Settai, T. Honma, Y. Haga, E. Yamamoto, Y. Nuki, and H. Yamagami, Fermi surface properties and de Haas-van Alphen oscillation in both the normal and superconducting mixed states of  $\text{URu}_2\text{Si}_2$ , *Philos. Mag. B* **79**, 1045 (1999).  
 [14] M. M. Altarawneh, N. Harrison, S. E. Sebastian, L. Balicas, P. H. Tobash, J. D. Thompson, F. Ronning, and E. D. Bauer, Sequential Spin Polarization of the Fermi Surface Pockets in  $\text{URu}_2\text{Si}_2$  and Its Implications for Hidden Order, *Phys. Rev. Lett.* **106**, 146403 (2011).  
 [15] M. M. Altarawneh, N. Harrison, G. Li, L. Balicas, P. H. Tobash, F. Ronning, and E. D. Bauer, Superconducting Pairs with Extreme Uniaxial Anisotropy in  $\text{URu}_2\text{Si}_2$ , *Phys. Rev. Lett.* **108**, 066407 (2012).  
 [16] See Supplemental Material at <http://link.aps.org/supplemental/10.1103/PhysRevLett.117.157201>, which includes Refs. [17,18], for details of the angular decomposition of the nonlinear susceptibility in a tetragonal environment, the Landau theory for the minimal free energy, the angular fitting procedure for establishing the Ising

- character of  $\chi_3$ , and an evaluation of the error bounds on the in-plane anisotropy of  $\chi_3$ .
- [17] T. T. M. Palstra, A. A. Menovsky, J. van den Berg, A. J. Dirkmaat, P. H. Kes, G. J. Nieuwenhuys, and J. A. Mydosh, Superconducting and Magnetic Transitions in the Heavy-Fermion System URu<sub>2</sub>Si<sub>2</sub>, *Phys. Rev. Lett.* **55**, 2727 (1985).
- [18] K. H. Kim, N. Harrison, M. Jaime, G. S. Boebinger, and J. A. Mydosh, Magnetic-Field-Induced Quantum Critical Point and Competing Order Parameters in URu<sub>2</sub>Si<sub>2</sub>, *Phys. Rev. Lett.* **91**, 256401 (2003).
- [19] A. P. Ramirez, T. Siegrist, T. T. M. Palstra, J. D. Garrett, E. Bruck, A. A. Menovsky, and J. A. Mydosh, Superconducting phases of URu<sub>2</sub>Si<sub>2</sub>, *Phys. Rev. B* **44**, 5392 (1991).
- [20] T. D. Matsuda, E. Hassinger, D. Aoki, V. Taufour, G. Knebel, T. Naoyuki, Y. Etsuji, Y. Haga, Y. Onuki, Z. Fisk, and J. Flouquet, Details of sample dependence and transport properties of URu<sub>2</sub>Si<sub>2</sub>, *J. Phys. Soc. Jpn.* **80**, 114710 (2011).
- [21] S. Kambe, Y. Tokunaga, H. Sakai, T. D. Matsuda, Y. Haga, Z. Fisk, and R. E. Walstedt, NMR Study of In-Plane Twofold Ordering in URu<sub>2</sub>Si<sub>2</sub>, *Phys. Rev. Lett.* **110**, 246406 (2013).
- [22] P. G. Niklowitz, S. R. Dunsiger, C. Pfleiderer, P. Link, A. Schneidewind, E. Faulhaber, M. Vojta, Y.-K. Huang, and J. A. Mydosh, Role of commensurate and incommensurate low-energy excitations in the paramagnetic to hidden-order transition of URu<sub>2</sub>Si<sub>2</sub>, *Phys. Rev. B* **92**, 115116 (2015).
- [23] J. R. Jeffries, K. T. Moore, N. P. Butch, and M. B. Maple, Degree of 5*f* electron localization in URu<sub>2</sub>Si<sub>2</sub>: Electron energy-loss spectroscopy and spin-orbit sum rule analysis, *Phys. Rev. B* **82**, 033103 (2010).
- [24] L. A. Wray, J. Denlinger, S.-W. Huang, H. He, N. P. Butch, M. B. Maple, Z. Hussain, and Y.-D. Chuang, Spectroscopic Determination of the Atomic *f*-Electron Symmetry Underlying Hidden Order in URu<sub>2</sub>Si<sub>2</sub>, *Phys. Rev. Lett.* **114**, 236401 (2015).
- [25] C. H. Booth, S. A. Medling, J. G. Tobin, R. E. Baumbach, E. D. Bauer, D. Sokaras, D. Nordlund, and T.-C. Weng, Probing 5*f*-state configurations in URu<sub>2</sub>Si<sub>2</sub> with U *L*<sub>III</sub>-edge resonant x-ray emission spectroscopy, *Phys. Rev. B* **94**, 045121 (2016).
- [26] K. Haule and G. Kotliar, Arrested Kondo effect and hidden order in URu<sub>2</sub>Si<sub>2</sub>, *Nat. Phys.* **5**, 796 (2009).
- [27] J. G. Rau and H.-Y. Kee, Hidden and antiferromagnetic order as a rank-5 superspin in URu<sub>2</sub>Si<sub>2</sub>, *Phys. Rev. B* **85**, 245112 (2012).
- [28] H. Ikeda, M.-T. Suzuki, R. Arita, T. Takimoto, T. Shibauchi, and Y. Matsuda, Emergent rank-5 nematic order in URu<sub>2</sub>Si<sub>2</sub>, *Nat. Phys.* **8**, 528 (2012).
- [29] Y. Saito, Y. Nakamura, M. S. Bahramy, Y. Kohama, J. Ye, Y. Kasahara, Y. Nakagawa, M. Onga, M. Tokunaga, T. Nojima, Y. Yanase, and Y. Iwasa, Superconductivity protected by spin-valley locking in ion-gated MoS<sub>2</sub>, *Nat. Phys.* **12**, 144 (2016).
- [30] P. Chandra, P. Coleman, and R. Flint, Hastatic order in the heavy-fermion compound URu<sub>2</sub>Si<sub>2</sub>, *Nature (London)* **493**, 621 (2013).
- [31] R. Flint, P. Chandra, and P. Coleman, Hidden and hastatic orders in URu<sub>2</sub>Si<sub>2</sub>, *J. Phys. Soc. Jpn.* **83**, 061003 (2014).
- [32] P. Chandra, P. Coleman, and R. Flint, Ising quasiparticles and hidden order in URu<sub>2</sub>Si<sub>2</sub>, *Philos. Mag.* **94**, 3803 (2014).
- [33] P. Chandra, P. Coleman, and R. Flint, Hastatic order in URu<sub>2</sub>Si<sub>2</sub>: Hybridization with a twist, *Phys. Rev. B* **91**, 205103 (2015).
- [34] P. Das, R. E. Baumbach, K. Huang, M. B. Maple, Y. Zhao, J. S. Helton, J. W. Lynn, E. D. Bauer, and M. Janoschek, Absence of a static in-plane magnetic moment in the "hidden-order" phase of URu<sub>2</sub>Si<sub>2</sub>, *New J. Phys.* **15**, 053031 (2013).
- [35] N. Metoki, H. Sakai, E. Yamamoto, N. Tateiwa, T. Matsuda, and Y. Haga, Neutron scattering experiments for the study of in-plane ordered moment in URu<sub>2</sub>Si<sub>2</sub>, *J. Phys. Soc. Jpn.* **82**, 055004 (2013).
- [36] K. A. Ross, L. Harriger, Z. Yamani, W. J. L. Buyers, J. D. Garrett, A. A. Menovsky, J. A. Mydosh, and C. L. Broholm, Strict limit on in-plane ordered magnetic dipole moment in URu<sub>2</sub>Si<sub>2</sub>, *Phys. Rev. B* **89**, 155122 (2014).
- [37] N. Kanchanavatee, M. Janoschek, R. E. Baumbach, J. J. Hamlin, D. A. Zocco, K. Huang, and M. B. Maple, Twofold enhancement of the hidden-order/large-moment antiferromagnetic phase boundary in the URu<sub>2-x</sub>Fe<sub>x</sub>Si<sub>2</sub> system, *Phys. Rev. B* **84**, 245122 (2011).